


Nikolas Provatas and Ken Elder

 WILEY-VCH

Phase-Field Methods in Material Science and Engineering

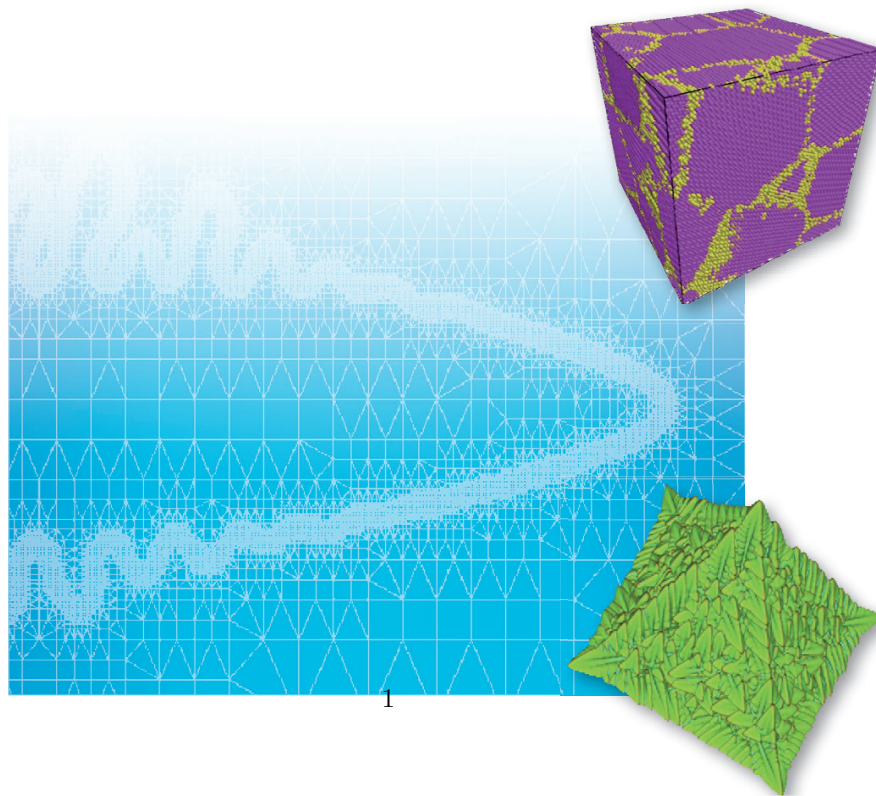

Contents

Preface	i
1 Introduction	1
1.1 The Role of Microstructure Materials Science	1
1.2 Free Boundary Problems and Microstructure Evolution	2
1.3 Continuum Versus Sharp-Interface Descriptions	5
2 Mean Field Theory of Phase Transformations	7
2.1 Simple Lattice Models	8
2.1.1 Phase separation in a binary mixture	8
2.1.2 Ising Model of Magnetism	11
2.2 Introduction to Landau Theory	14
2.2.1 Order parameters and phase transformations	14
2.2.2 The Landau free energy functional	15
2.2.3 Phase transitions with a symmetric phase diagram	17
2.2.4 Phase transitions With a non-symmetric phase diagram	19
2.2.5 First order transition without a critical point	20
3 Spatial Variations and Interfaces	23
3.1 The Ginzburg-Landau Free Energy Functional	23
3.2 Equilibrium Interfaces and Surface Tension	25
4 Non-Equilibrium Dynamics	29
4.1 Driving Forces and Fluxes	30
4.2 The Diffusion Equation	30
4.3 Dynamics of Conserved Order Parameters: <i>Model B</i>	31
4.4 Dynamics of Non-Conserved Order Parameters: <i>Model A</i>	33
4.5 Generic Features of Models A and B	34
4.6 Equilibrium Fluctuations of Order Parameters	35
4.6.1 Non-conserved order parameters	35
4.6.2 Conserved order parameters	36
4.7 Stability and the Formation of Second Phases	37
4.7.1 Non-conserved order parameters	37
4.7.2 Conserved order parameters	38

4.8	Interface Dynamics of Phase Field Models (Optional)	39
4.8.1	Model A	39
4.8.2	Model B	43
4.9	Numerical Methods	43
4.9.1	Fortran 90 codes accompanying this book	43
4.9.2	Model A	44
4.9.3	Model B	47
5	Introduction to Phase Field Modeling: Solidification of Pure Materials	49
5.1	Solid order parameters	49
5.2	Free Energy Functional for Solidification	52
5.3	Single Order Parameter Theory of Solidification	53
5.4	Solidification Dynamics	55
5.4.1	Isothermal solidification: model A dynamics	55
5.4.2	Anisotropy	56
5.4.3	Non-isothermal solidification: model C dynamics	57
5.5	Sharp and Thin Interface Limits of Phase Field Models	58
5.6	Case Study: Thin interface analysis of Equations (5.30)	60
5.6.1	Recasting phase field equations	60
5.6.2	Effective sharp interface model	61
5.7	Numerical Simulations of Model C	63
5.7.1	Discrete equations	63
5.7.2	Boundary conditions	66
5.7.3	Scaling and convergence of model	67
5.8	Properties of Dendritic Solidification in Pure Materials	69
5.8.1	Microscopic solvability theory	69
5.8.2	Phase field predictions of dendrite operating states	72
5.8.3	Further study of dendritic growth	75
6	Phase Field Modeling of Solidification in Binary Alloys	77
6.1	Alloys and Phase Diagrams: A Quick Review	77
6.2	Microstructure Evolution in Alloys	79
6.2.1	Sharp interface model in one dimension	79
6.2.2	Extension of sharp interface model to higher dimensions	81
6.3	Phase Field Model of a Binary Alloy	82
6.3.1	Free Energy Functional	82
6.3.2	General form of $f(\phi, c, T)$	83
6.3.3	$f(\phi, c, T)$ for isomorphous alloys	83
6.3.4	$f(\phi, c, T)$ for eutectic alloys	84
6.3.5	$f(\phi, c, T)$ for dilute binary alloys	85
6.4	Equilibrium Properties of Free Energy Functional	85
6.4.1	Simple example of a “toy” model	86
6.4.2	Calculation of surface tension	88
6.5	Phase Field Dynamics	89
6.6	Thin Interface Limits of Alloy Phase Field Models	90
6.7	Case Study: Analysis of a Dilute Binary Alloy Model	91

6.7.1	Interpolation functions for $f(\phi, c)$	91
6.7.2	Equilibrium Phase Diagram	92
6.7.3	Steady state c_o and ϕ_o profiles	93
6.7.4	Dynamical equations	94
6.7.5	Thin interface properties of dilute alloy model	96
6.7.6	Non-variational version of model (optional)	96
6.7.7	Effective sharp interface parameters of non-variational model (optional)	97
6.8	Numerical Simulations of Dilute Alloy Phase Field Model	100
6.8.1	Discrete equations	100
6.8.2	Convergence properties of model	102
6.9	Other Alloy Phase Field Formulations	104
6.9.1	Introducing fictitious concentrations	104
6.9.2	Formulation of phase field equations	106
6.9.3	Steady state properties of model and surface tension	107
6.9.4	Thin interface limit	108
6.9.5	Numerical determination of C_s and C_L	108
6.10	Properties of Dendritic Solidification in Binary Alloys	109
6.10.1	Geometric models of directional solidification	109
6.10.2	Spacing selection theories of directional solidification	112
6.10.3	Phase field simulations of directional solidification	113
6.10.4	Role of Surface Tension Anisotropy	118
7	Multiple Phase Fields and Order Parameters	123
7.1	Multi-Order Parameter Models	124
7.1.1	Pure materials	124
7.1.2	Alloys	126
7.1.3	Strain effects on precipitation	128
7.1.4	Anisotropy	130
7.2	Multi-Phase Field Models	132
7.2.1	Thermodynamics	132
7.2.2	Dynamics	135
7.3	Orientational Order Parameter for Polycrystalline modeling	135
7.3.1	Pure materials	135
7.3.2	Alloys	139
8	Phase Field Crystal Modeling of Pure Materials	141
8.1	Generic Properties of Periodic Systems	142
8.2	Periodic Free Energies and The Swift-Hohenberg Equation	143
8.2.1	Static Analysis of the SH Equation	145
8.2.2	Dynamical analysis of the SH equation	147
8.3	Phase Field Crystal (PFC) Modeling	151
8.4	Equilibrium Properties in a One Mode Approximation	155
8.4.1	Three dimensions: BCC lattice	155
8.4.2	Two dimensions triangular rods	160
8.4.3	One dimensional planes	161
8.4.4	Elastic Constants of PFC Model	162

8.5	PFC Dynamics	163
8.5.1	Vacancy Diffusion	164
8.6	Multi-scale Modeling: Amplitude Expansions (Optional)	166
8.6.1	One dimensions	168
8.6.2	Two Dimensions	169
8.6.3	Three Dimensions	171
8.6.4	Rotational Invariance	172
8.7	Parameter fitting	173
9	Phase Field Crystal Modeling of Binary Alloys	175
9.1	A Two-Component PFC Model For Alloys	175
9.1.1	Constant density approximation: liquid	176
9.1.2	Constant concentration approximation: solid	177
9.2	Simplification of Binary Model	178
9.2.1	Equilibrium Properties: Two dimensions	179
9.2.2	Equilibrium Properties: Three dimensions (BCC)	181
9.3	PFC Alloy Dynamics	182
9.4	Applications of PFC models	183
A	Thin-Interface Limit of a Binary Alloy Phase Field Model	187
A.1	Phase Field Model	187
A.2	Curvi-linear Coordinate Transformations	188
A.3	Length and Time Scales	190
A.4	Matching Conditions Between Outer and Inner Solutions	191
A.5	Outer Equations Satisfied by Phase Field Model	192
A.6	Inner Expansion of Phase Field Equations	193
A.6.1	Inner Expansion of phase field equation A.37 at different orders	195
A.6.2	Inner expansion of concentration equation A.38 at different orders	195
A.6.3	Inner Chemical potential expansion	196
A.7	Analysis of Inner Equations and Matching to Outer Fields	197
A.7.1	$\mathcal{O}(1)$ phase field equation (A.40)	197
A.7.2	$\mathcal{O}(1)$ diffusion equation (A.43)	198
A.7.3	$\mathcal{O}(\epsilon)$ phase field equation (A.41)	199
A.7.4	$\mathcal{O}(\epsilon)$ diffusion equation (A.44)	200
A.7.5	$\mathcal{O}(\epsilon^2)$ phase field equation (A.42)	203
A.7.6	$\mathcal{O}(\epsilon^2)$ diffusion equation (A.45)	205
A.8	Summary of Results of Appendix Sections (A.2)-(A.7)	208
A.8.1	Effective sharp Interface limit of Eqs. (A.2)	208
A.8.2	Interpretation of thin interface limit correction terms	209
A.9	Elimination of Thin Interface Correction Terms	210
A.9.1	Modifying the phase field equations	211
A.9.2	Changes due to the altered form of bulk chemical potential	211
A.9.3	Changes due to the addition of anti-trapping flux	213
A.9.4	Analysis of modified $\mathcal{O}(\epsilon)$ inner diffusion equation	214
A.9.5	Analysis of modified $\mathcal{O}(\epsilon^2)$ inner phase field equation	214
A.9.6	Analysis of modified $\mathcal{O}(\epsilon^2)$ inner diffusion equation	215

B	Basic Numerical Algorithms for Phase Field Equations	217
B.1	Explicit Finite Difference Method for Model A	217
B.1.1	Spatial derivatives	218
B.1.2	Time marching	219
B.2	Explicit Finite Volume Method for Model B	220
B.2.1	Discrete volume integration	220
B.2.2	Time and space discretization	221
B.3	Stability of Time Marching Schemes	222
B.3.1	Linear stability of explicit methods	222
B.3.2	Non-linear instability criterion for Δt	225
B.3.3	Non-linear instability criterion for Δx	226
B.3.4	Implicit methods	228
B.4	Semi-Implicit Fourier Space Method	228
B.5	Finite Element Method	230
B.5.1	The Diffusion Equation in 1D	230
B.5.2	The 2D Poisson Equation	235
C	Miscellaneous Derivations	239
C.1	Structure Factor: Section (4.6.1)	239
C.2	Transformations from Cartesian to Curvilinear Co-ordinates: Section (A.2)	240
C.3	Newton's Method for Non-Linear Algebraic Equations: Section (6.9.5)	242

Preface

The idea for this book grew out of a series of workshops that took place at McMaster University from 2002-2005 in which a couple of dozen researchers and students (coined the "Canadian Network for Computational Materials Science, CNCMS") were invited to discuss their research and their visions for the future of computational materials science. One serious concern that surfaced through discussions and the meetings' proceedings regarded the gaping hole that existed in the standard pedagogical literature for teaching students –and professors– about computational and theoretical methods in phase field modeling. Indeed, unlike many other fields of applied physics and theoretical materials science, there is a dearth of easy-to-read books on phase field modeling that would allow students to come up to speed with the details of this topic in a short period of time. After sitting on the fence for a while we decided to add our contribution by writing an introductory text about phase field modeling.

The aim of this book is to provide a graduate level introduction of phase field modeling for students in materials science who wish to delve deeper into the underlying physics of the theory. The book begins with the basic principles of condensed matter physics to motivate and develop the phase field method. This methodology is then used to model various classes of non-equilibrium phase transformations that serve as paradigms of microstructure development in materials science phenomena. The workings of the various phase field models studied are presented in sufficient detail for students to be able to follow the reasoning and reproduce all calculations. The book also includes some basic numerical algorithms –accompanied by corresponding Fortran codes on the Wiley website for this book– that students can use as templates with which to practice and develop their own phase field codes. A basic undergraduate level knowledge of statistical thermodynamics and phase transformations is assumed throughout this book. Most long-winded mathematical derivations and numerical details that can serve as references but would otherwise detract from the flow of the main theme of the text are relegated to appendices.

It should be specified at the outset that this book *is not* intended to be an exhaustive survey of all the work conducted throughout the years with phase field modeling. There are plenty of reviews that cover this angle and many of these works are cited herein. Instead, we focus on what we feel is missing from much of the literature: a fast-track to understanding some of the "dirty" details of deriving and analyzing various phase field models, and their numerical implementation. That is precisely what we have observed new students wishing to study phase field modeling are starving for as they get started in their research. As such, this book is intended to be a kind of "phase field modeling for dummies", and so while the number of topics is limited, as many of the details as possible are shown for those topics that are covered.

The broad organization of the material in following chapters is as follows. The first half of the book begins by establishing the basic phase field phenomenology, from its basic origins in mean field theory of phase transformations, to its basic form now in common use as the base of most modern phase field models used in computational materials science and engineering. Phase field theory is applied to several examples,

with a special emphasis placed on the paradigms of solidification and solid state transformations. An appendix is also dedicated to the important issue of mapping the phase field model onto specific sharp interface limits. The Last two chapters of this book deal with the development of more complex class of phase field models coined "phase field crystal" models. These are an extension of the original phase field formalism that makes it possible to incorporate elastic and plastic effects along side the usual kinetics that governing phase transformations. We will see that these models constitute a hybrid between traditional phase field theory and atomistic dynamics. After motivating the derivation of phase field crystal models from classical density functional theory, these models are then applied to various types of phase transformation phenomena that inherently involve elastic and plastic effects. It is noted that some sections of the book are marked as "Optional". These are sections that can be skipped at first reading without losing the main flow of the text and without detracting from the minimum path of topics comprising the basic principles of phase field theory.

Writing this book involved the valued help of many people. We would like to thank all the graduate students in the department of materials science and engineering at McMaster University who took MATLS 791 in the Fall of 2009. Their help and advice in editing and proofing the first edition of the manuscript of this book was greatly appreciated. We also appreciate the cooperation of various authors that allowed us to reference their work in some of the figures of this book (the green dendrite on the cover is from [W.L. George and J.A. Warren, *J. Comput. Phys.* 177, 264-283 (2002)]). I (NP) would like to thank my wife Photini and Sons Spiro and Aristotle for their love and patience during the writing of this book; doing science for a living is fun but their love is what living is actually about. I also suppose thanks are in order to Starbucks Coffee for providing me –at the cost of lots of over-priced bitter coffee– many hours of escape from the mundane administrative environment of a modern university in order that I can work on this book in peace and talk politics with other patrons. I would also like to thank the Technical Research Centre of Finland (VTT) and Helsinki University of Technology for hosting me during my sabbatical leave in 2009 and for flipping the bill for some of my travels to Helsinki where I also worked on this manuscript and other cool stuff. I (KE) would like to thank my wife Nancy, daughter Kate and parents Fay and Stan for the tremendous support they have given me over many years and throughout the writing of this text. In addition I would like to thank Tapio Ala-Nissila and the Helsinki University of Technology (now Aalto University) for providing me the opportunity to give several short courses on phase field and phase field crystal modelling. Some of the material developed for those courses has found its way into the text.

As with anything in print, this book very likely contains typos and oversights. We would be delighted to hear from readers about any such errors or omissions. Please do not hesitate to contact us at provatas@physics.mcgill.ca or elder@oakland.edu.

Chapter 1

Introduction

1.1 The Role of Microstructure Materials Science

The properties of most engineered materials involve a connection to their underlying microstructure. For example, the crystal structure and impurity content of silicon will determine its band structure and its subsequent quality of performance in modern electronics. Most large-scale civil engineering applications demand high strength steels containing a mix of refined crystal grains and a dispersion of hard and soft phases throughout their microstructure. For aerospace and automotive applications, where weight to strength ratios are a paramount issue, lighter alloys are strengthened by precipitating second-phase particles within the original grain structure. The combination of grain boundaries, precipitated particles and the combination of soft and hard regions allow metals to be very hard and still have room for ductile deformation. It is notable that the lengthening of span bridges in the world can be directly linked to the development of perlitic steels. In general, the technological advance of societies has often been linked to their ability to exploit and engineer new materials and their properties.

In most of the above examples, as well as a plethora of untold others, microstructures are developed during the process of solidification, solid state precipitation and thermo-mechanical processing. All these processes are governed by the fundamental physics of free boundary dynamics and non-equilibrium phase transformation kinetics. For example, in solidification and re-crystallization –both of which serve as a paradigms of a first order transformation– nucleation of crystal grains is followed by a competitive growth of these grains under the drive to reduce the overall free energy –bulk and surface– of the system, limited, however, in their kinetics by the diffusion of heat and mass. Thermodynamic driving forces can vary. For example, solidification is driven by bulk free energy minimization, surface energy and anisotropy. On the other hand, strain induced transformation, must also incorporate elastic effects. These can have profound effects on the morphologies and distribution of, for example, second phase precipitates during a heat treatment of an alloy.

The ability to model and predict materials properties and microstructure has greatly benefited from the recent “explosion” of new theoretical and numerical tools. Modern parallel computing now allows several billions atoms to be simulated for times on the scale of nanoseconds. On higher scales, various continuum and sharp interface methods have made it possible to quantitatively model free surface kinetics responsible for microstructure formation. Each of these methodologies, however, comes with its advantages and deficiencies.

1.2 Free Boundary Problems and Microstructure Evolution

Solidification has typically served as a paradigm for many classes of non-equilibrium phase transformations which govern the formation of complex microstructure during materials processing. The most commonly recognized solidification microstructure is the tree-like *dendrite* patterns (which comes from the Greek word for tree, "dendron"). The most popular example of a dendrite is a snowflake, which is a single crystal of ice, which was solidified from water that falls through the sky. Figure (1.1) shows an image of a branch of a snowflake in an organic material known as succinonitrile (SCN) solidifying from its melt. This material is a favorite with researchers because it solidifies at room temperature and is transparent, affording us a good look at the solidification process. It is also often referred to as a "metal analogue" as it solidifies into a cubic crystal structure. Surprisingly the properties learned from this organic material are essentially unchanged qualitatively in metals and their alloys. Patterns like the one in Fig. (1.1)

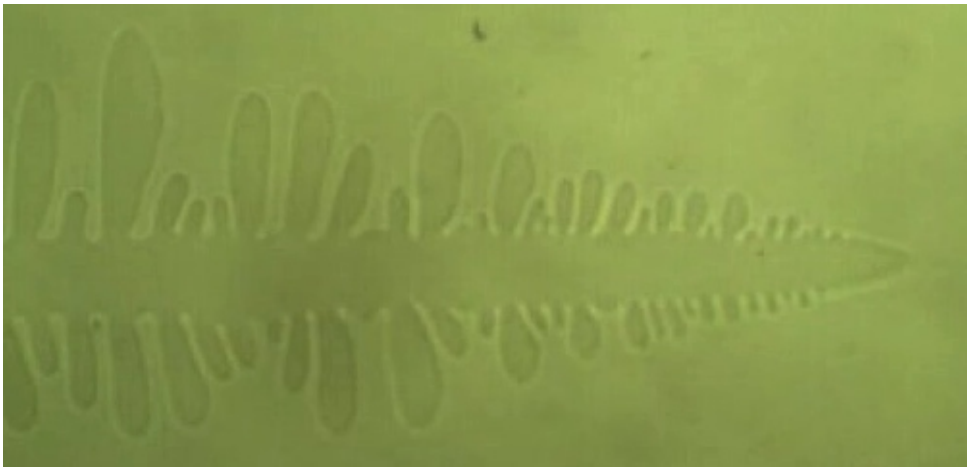


Figure 1.1: A snowflake of succinonitrile (SCN), an organic compound that solidified at room temperature. The image shows the characteristic "dendritic" tree-like pattern of the crystal, typical of crystal formation in nearly all anisotropic solids. It is a ubiquitous shape depends on the physics of reaction-diffusion and the properties of the surface energy between the solid and liquid. (Vincent Proton, McMaster University (2008).)

are not limited to solidification. They also emerge in the solid state transformations. Figure (1.2) shows dendrite patterns that emerge when one solid phase emerges from and grows within another. The business of microstructure modeling involves understanding the physics governing such microstructure formation.

Solidification is at the heart of all metal casting technologies. Figure (1.3) shows a typical layout for casting slabs of steel used in many industries. The basic idea is that a liquid metal alloy enters a region like the one between the rollers in the figure. There the liquid is sprayed with water, which establishes a cooling mechanism that extracts heat from the casting at some rate (\dot{Q}). The liquid solidifies from the outer surface inward. The rate at which heat is extracted –i.e. the cooling rate– is key in establishing the morphology and scale of the solidification microstructure, as seen in the inset of Fig. (1.3). Typical dendrite microstructures in many steel alloys resemble those shown in Fig. (1.4). In this situation the

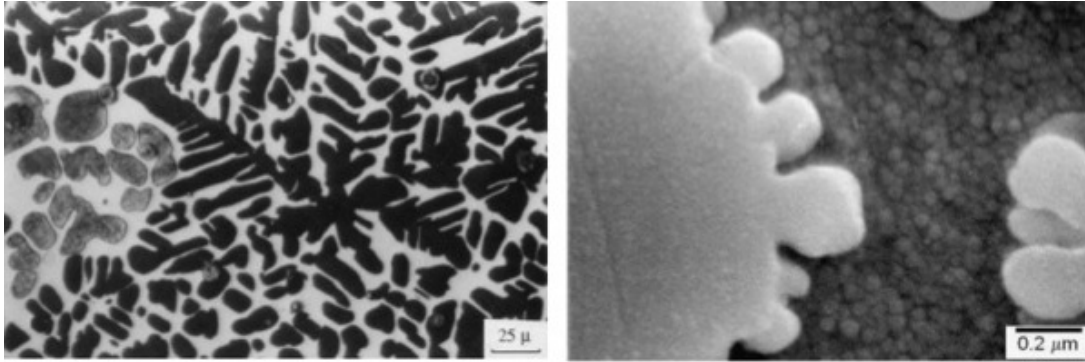


Figure 1.2: Left: solid state dendrites in an alloy of Copper (Cu) and Zinc (Zn). Right: Dendrite in a Nickel-based super-alloy, a material commonly used in aerospace materials due to its very high strength. Reprinted from [220] (left) and [101] (right)

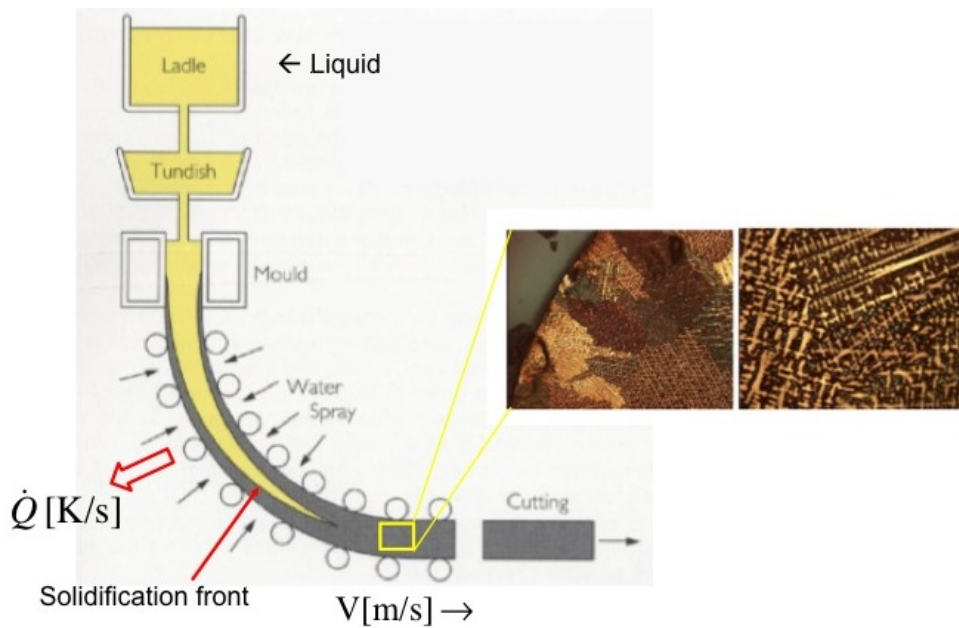


Figure 1.3: Typical industrial layout for thin slab casting. Liquid is enters from top, is cooled by splashing water and is directed –as it solidifis– at some speed (V) to the right. Most steels will then be cut and thermo-mechanically treated to improve their strength properties. In spite of the post solidification treatment that the metal may receive, the so called "as-cast" structure (inset) that is established initially is always, to some extent, present in the final product.

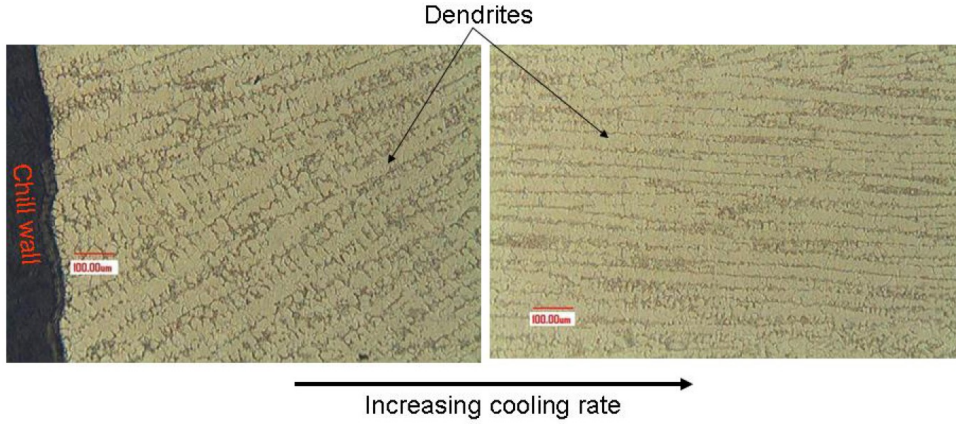


Figure 1.4: Dendrite arrays in a steel alloy. Growth is from bottom left to top right in the left figure and from left to right in the right figure. The figure on the right has been cooled much more rapidly than that of the left. The main striations are known as primary dendrites. The budding branch-like structures coming off of the primary dendrites are known as secondary arms or side-branches.

competitive growth and interaction of a very large number of dendrites means that only partial traces of the traditional snow flake pattern survive. In fact, depending on the direction of heat extraction, cooling rate and geometry of the cast, it is typical that only single "arms" of the characteristic snow flake pattern survive and grow. These form the branch-like striations in the figure.

The kinetics of microstructure formation is traditionally modeled by a set of mathematical relations that describe the release and diffusion of heat, the transport of impurities and the complex boundary conditions that govern the thermodynamics at the interface. These mathematical relations in theory contain the physics that gives rise to the complex structure shown in the above figures. As a concrete example, in the solidification of a pure material the advance of the solidification front is limited by the diffusion of latent heat away from the solid-liquid interface, and the ability of the interface to maintain two specific boundary conditions; flux of heat toward one side of the interface is balanced by an equivalent flux away from the other side and the temperature at the interface undergoes a curvature correction known as the Gibb's Thomson condition. These conditions are expressed mathematically as in the following *sharp-interface model* commonly known as the Stefan Problem:

$$\begin{aligned}
 \frac{\partial T}{\partial t} &= \nabla \cdot \left(\frac{k}{\rho c_p} \nabla T \right) \equiv \nabla \cdot (\alpha \nabla T) \\
 \rho L_f V_n &= k_s \nabla T \cdot \vec{n}|_{\text{int}}^s - k_L \nabla T \cdot \vec{n}|_{\text{int}}^L \\
 T_{\text{int}} &= T_m - \left(\frac{\gamma T_M}{\rho L_f} \right) \kappa - \frac{V_n}{\mu}
 \end{aligned} \tag{1.1}$$

where: $T \equiv T(\vec{x}, t)$ denotes temperature, k thermal conductivity (which assumes values k_s and k_L in the solid and liquid, respectively), ρ the density of the solid and liquid, c_p the specific heat at constant pressure, α the thermal diffusion coefficient, L_f the latent heat of fusion per mass for solidification, γ the solid-liquid surface energy, T_M the melting temperature, κ the local solid-liquid interface curvature, V_n the local normal velocity of the interface, μ the local atomic interface mobility. Finally, the subscript

”int” refers to interface and the superscript ”s” and ”L” refer to evaluation at the interface on the solid or liquid side, respectively.

Like solidification, there are other diffusion limited phase transformations whose interface properties can, on large enough length scales, be described by specific sharp interface kinetics. Most of them can be described by sharp interface equations analogous to those in Eqs. (1.1). Such models –often referred to as sharp interface models– operate on scales much larger than the solid-liquid interface width, itself of atomic dimensions. As a result, they incorporate all information from the atomic scale through effective constants such as the capillary length, which depend on surface energy, the kinetic attachment coefficient and thermal of impurity diffusion coefficient.

1.3 Continuum Versus Sharp-Interface Descriptions

A limitation encountered in modeling free boundary problems is that the appropriate sharp interface model is often not known for many classes of phenomena. For example, the sharp interface model for phase separation or particle coarsening, while easy to formulate nominally, is unknown for the case when mobile dislocations and their effect of domain coarsening is included [154]. A similar situation is encountered in the description of rapid solidification when solute trapping and drag are relevant. There are several different sharp interface descriptions of this phenomenon, each differing in the way they treat the phenomenological drag parameters and trapping coefficients and lateral diffusion along the interface.

Another difficulty associated with sharp interface models is that their numerical simulation of sharp interface models also turns out to be extremely difficult. The most challenging aspect is the complex interactions between topologically complex interfaces that undergo merging and pinch-off during the course of a phase transformation. Such situations are often addressed by applying somewhat arbitrary criteria for describing when interface merging or pinch-off occurs, and manually adjusting the interface topology. It is noteworthy that numerical codes for sharp interface models are very lengthy and complex, particularly in 3D.

A relatively new modeling paradigm on the scene of materials science and engineering is the so-called *phase field method*. The technique has found increasing use by the materials community because of its fundamental origins and because it avoids some of the problems associated with sharp interface models. The phase field method introduces, along side the usual temperature field, an additional continuum field coined the *phase field* or *order parameter*. This field assumes constant values in the bulk of each phase, continuously interpolating between its bulk values across a thin boundary layer, which is used to describe the interface between phases. From the perspective of condensed matter physics, the phase field may be seen as describing the degree of crystallinity or atomic order or disorder in a phase. It can also be viewed as providing a fundamental description of an atomically diffuse interface. As a mathematical tool, the phase field can be seen as a tool that allows the interface to be smeared over a diffuse region for numerical expedience.

Traditional phase field models are connected to thermodynamics by a phenomenological free energy functional ¹ written in terms of the phase field and other fields (temperature, concentration, strain, etc). Through a dissipative minimization of this free energy, the dynamics of one or more order parameter, as well as those of heat or mass transfer are governed by set of no non-linear partial differential equations.

¹A “functional” is a function whose input is an entire function rather than a single number. As a one dimensional example, suppose a quantity f is dependent on a certain function of space $\phi(x)$. The quantify $F = \int f(\phi(x)) dx$ is then dependent on entire function $\phi(x)$ and is said to be a *functional* of $\phi(x)$. The functional dependence of F on $\phi(x)$ will be denoted by $F[\phi(x)]$

Parameters of these dynamical equations of motion are tuned by association of the model –in the limit of a very small interface– with the associated sharp interface equations.

As will be explored in this book, phase field models, besides their fundamental thermodynamic connection are exceedingly simple to program. They often do not require much more than a simple so-called Euler time marching algorithm on a uniform mesh (these will be examined later). For the more advanced users, more sophisticated techniques such as adaptive mesh refinement (AMR) and other rapid simulation schemes are also in abundance for free download and use these days.

The phase field methodology has become ubiquitous as of late and is gaining popularity as a method of choice to model complex microstructures in solidification, precipitation and strain-induced transformations. More recently a new class of phase field models has also emerged, coined *phase field crystal models*, which incorporate atomic scale elasticity alongside the usual phase transformation kinetics of traditional phase field models. Phase field crystal models are appealing as they will be shown to arise as special instances of *classical density functional theory*. This connection of phase field crystal models and classical density functional theory provides insight about the derivation of the effective constants appearing in phase field models from atomistic properties.

Of course there are no free lunches! While phase field models might offer a deeper connection to fundamental thermodynamics than larger-scale engineering or sharp interface models, they come with several severe problems that have traditionally stood in the way of making models amenable to quantitative modeling of experimentally relevant situations. For example, the emergence of a mesoscopic interface renders phase field equations very stiff. This requires multi-scale numerical methods to resolve both the thin interfaces that are inherent in phase field models while at the same time capturing microstructures on millimeter-centimeter scales. Moreover, the numerical time steps inherent in phase field theory –limited by the interface kinetics– makes it impossible to model realistic time scale. As a result new mathematical techniques –thin-interface asymptotic analysis methods– have to be developed that make it possible to accelerate numerical time scales without compromising solution quality. Luckily advances on both these fronts –and others– have recently become possible to overcome some of these challenges in selected problems. Understanding some of these methods and their application to the broader phase field methodology will be one of the main focuses of the chapters that follow.

Chapter 2

Mean Field Theory of Phase Transformations

The origins of the phase field methodology -the focus of this book- have been considerably influenced by mean field theory of first and second order phase transformations. It is thus instructive to begin first with a discussion of some simple phase transformations and their description via mean field theory. Using this as a framework will better allow the concept of an order parameter to be defined and generalized to include spatial variations. This will thus set the stage for the later development of phase field models of solidification and solid state transformation phenomena. Before proceeding, the reader should have a basic background of statistical thermodynamics. For a quick review of, the reader is referred to one of [20], [96], Ref. [43].

Common first order transformations include solidification of liquids and condensation of vapor. They are defined by a release of latent heat and discontinuous first derivative of the free energy. Moreover, just below a first order transformation, nucleation of the meta-stable phase is required to initiate the transformation. Finally, in first order transformations, two phases can typically co-exist over a wide range of temperatures, densities (pure materials) or impurity concentrations (alloys). In contrast, second order transformations occur at well defined temperature, density or concentration. There is no release of latent heat and the transformation begins spontaneously due to thermal fluctuations. A paradigm example is phase separation of a binary mixture or spinodal decomposition in metal alloys. Another is the spontaneous ferromagnetic magnetization of iron below its Currie temperature.

An important concept that is used again and again in the description of phase transformations is that of the *order parameter*. This is a quantity that parameterizes the change of symmetry from the parent (disordered) phase to the daughter (ordered) phase appearing after the transformation. For example, a crystal phase has fewer rotational and translational symmetries compared to a liquid. The order parameter typically takes on a finite value in the ordered state and vanishes in the disordered state. First and second order phase transitions are distinguished by the way the order parameter appears below the transition temperature. In a first order transformation, the order parameter of the ordered state emerges discontinuously from that of the disordered phase, below the transformation temperature. In second order transformation, the disordered state gives way continuously to two ordered phases with non-zero order parameter. Another example of a change of symmetry characterized by changes in the order parameter include the average magnetization. For some phase changes, like vapour \rightarrow vapour + liquid, there is no

change in the structural symmetry groups of the parent and daughter phases. In such case effective order parameters can often be defined in terms of density differences relative to the parent phase.

Mean field theory of phase transformations ignores spatial fluctuations, which always exist due to local molecular motion. The order parameter –treated as an average thermodynamic property of a phase– is used to write the free energy of a system. Its subsequent thermodynamic properties can thus be determined. This approach works reasonably well in first order transformations, where fluctuations influence only regions near nano-scale phase boundaries, even near the transition temperature. In contrast, second order transformations fluctuations influence ordering over increasing length scales, particularly near a critical point. For such problems, spatial fluctuations play a dominant role and mean field Landau free energy functional must be augmented with terms describing spatial fluctuations. These are also written in terms of gradients of the order parameter, which is in this case considered to be varying spatially on scales over which spatial fluctuations occur.

This chapter begins by illustrating two phenomenological microscopic models that help motivate and define the concept of an order parameter and mean field treatments of phase transformations.

2.1 Simple Lattice Models

2.1.1 Phase separation in a binary mixture

Consider a binary mixture of two components A and B. Imagine the domain on which the mixture is broken into many small discrete volume elements labeled with the index i . Each element contains either one A or one B atom. The total number of cells M equals the total number of atoms N , a definition valid for an incompressible fluid mixture. For each cell $1 < i < N$, a state variable n_i is defined, which takes on $n_i = 0$ if a volume elements is occupied by an A atom and $n_i = 1$ when it is occupied by a B atom. The variable n_i thus measures the local concentration of B atoms in each cell. The total number of unique states of the system is given by 2^N , where each configurational state is denoted by the notation $\{n_i\}$. Assuming that each particle interacts with ν of its neighbors, the total interaction energy of a particular configuration of the binary mixture is given by

$$E[\{n_i\}] = - \sum_{i=1}^N \sum_{j=1}^{\nu} \{ \epsilon_{AA}(1 - n_i)(1 - n_j) + \epsilon_{AB}(1 - n_i)n_j + \epsilon_{AB}(1 - n_j)n_i + \epsilon_{BB}n_in_j \} \quad (2.1)$$

This expression can be simplified by interchanging the i and j subscripts and noting that $n_in_j = n_i - n_i(1 - n_j)$, which gives

$$E[\{n_i\}] = \epsilon \sum_{i=1}^N \sum_{j=1}^{\nu} n_i(1 - n_j) + b \sum_i^N n_i - \frac{N\nu\epsilon_{AA}}{2} \quad (2.2)$$

where $\epsilon = \epsilon_{AA} + \epsilon_{BB} - 2\epsilon_{AB}$ and $b = \frac{\nu}{2}(\epsilon_{AA} - \epsilon_{BB})$.

The thermodynamics of this simple system is described by the grand potential [20]

$$\Omega(\mu, N, T) = F(N, \langle N_B \rangle, T) - \mu \langle N_B \rangle \quad (2.3)$$

where μ is the chemical potential of the system and

$$\langle N_B \rangle \equiv \left\langle \sum_{i=1}^N n_i \right\rangle \quad (2.4)$$

is the average concentration of B particles. The free energy per particle can be expressed as

$$f \equiv \frac{F(\phi, N, T)}{N} = \frac{\Omega(\mu, N, T)}{N} + \mu\phi \quad (2.5)$$

where ϕ is the *order parameter*, defined by

$$\phi = \frac{1}{N} \left\langle \sum_{i=1}^N n_i \right\rangle \equiv \langle n_i \rangle \quad (2.6)$$

Equation (2.5) makes explicit the dependencies of the free energy density on the chemical potential and the order parameter of the system, which in this case is the average concentration of B atoms.

From the principles of statistical mechanics, the free energy f in Equation (2.5) can be connected to the interaction energy in Eq. (2.1) via the grand partition function Ξ , which determines the grand potential Ω according to

$$\Omega = -k_B T \ln \Xi \quad (2.7)$$

where k_B is the Boltzmann constant and

$$\Xi = \prod_{i=1}^N \sum_{n_i=0,1} e^{-\beta(E[\{n_i\}] - \mu N_B)} \quad (2.8)$$

where $\beta \equiv 1/k_B T$ and $N_B = \sum_{i=1}^N n_i$. Equation (2.8) represents a configurational sum of the Boltzmann factor over all 2^N configurations of the binary mixture. The order parameter in Eq. (2.6) can be evaluated directly from the grand partition function Eq. (2.8), or from Eq. (2.5), according to

$$\phi = -\frac{1}{N} \left. \frac{\partial \Omega}{\partial \mu} \right|_{N, T} \quad (2.9)$$

The configurational sum in Eq. (2.8) cannot be performed for most complex interacting systems including the simple binary mixture model presented here. Nevertheless, a considerable insight into the thermodynamics of this lattice model can be gleaned from making some simplification on the interaction terms. Namely, we invoke *mean field* approximation, which assumes that the argument of the Boltzmann factor in the configurational sum of Ξ can be replaced by its mean or equilibrium value. The implication of this assumption is that the main contribution to Ξ comes from particle configurations close to those that minimize the argument of the Boltzmann factor in Ξ . Thus, in mean field theory the partition function becomes,

$$\begin{aligned} \Xi &\approx \prod_{i=1}^N \sum_{n_i=0,1} e^{-\beta \langle E[\{n_i\}] \rangle + \mu\beta \langle N_B \rangle} \\ &= \frac{N!}{\langle N_B \rangle! (N - \langle N_B \rangle)!} e^{-\beta \langle E[\{n_i\}] \rangle + \mu\beta \langle N_B \rangle} \end{aligned} \quad (2.10)$$

Accordingly, the grand potential in mean field theory becomes

$$\begin{aligned} \Omega &= -k_B T \ln \Xi \\ &\approx -k_B T \ln \left(\frac{N!}{\langle N_B \rangle! (N - \langle N_B \rangle)!} \right) + \langle E[\{n_i\}] \rangle - \mu \langle N_B \rangle \end{aligned} \quad (2.11)$$

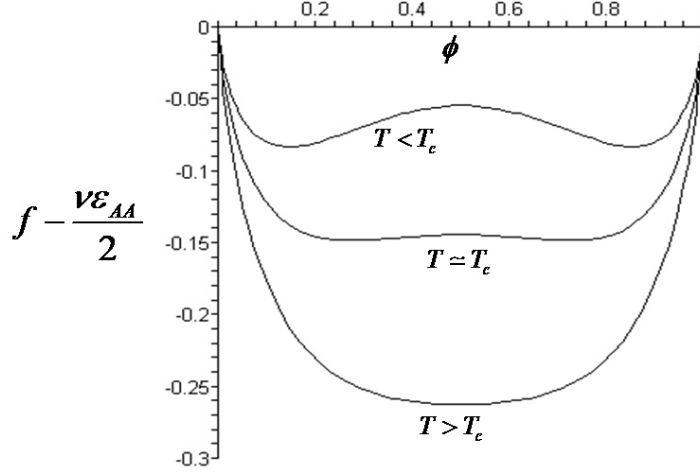


Figure 2.1: Mean field free energy of ideal binary alloy for temperatures ranging from above to below the critical temperature.

where Sterling's approximation was used above. The mean energy $E[\{n_i\}]$ per particle can be written as

$$\begin{aligned} \frac{\langle E[\{n_i\}] \rangle}{N} &= \frac{\epsilon}{N} \sum_{i=1}^N \sum_{j=1}^{\nu} \langle n_i \rangle (1 - \langle n_j \rangle) + \frac{b}{N} \langle \sum_{i=1}^N n_i \rangle - \frac{\nu \epsilon_{AA}}{2} \\ &= \frac{\epsilon \nu}{2} \phi (1 - \phi) + b \phi - \frac{\nu \epsilon_{AA}}{2} \end{aligned} \quad (2.12)$$

This expression makes it possible to finally write the mean field free energy density f in Eq. (2.5) for the binary mixture in terms of the order parameter as

$$f = \frac{\epsilon \nu}{2} \phi (1 - \phi) + b \phi - \frac{\nu \epsilon_{AA}}{2} + k_B T \{ \phi \ln \phi + (1 - \phi) \ln(1 - \phi) \} \quad (2.13)$$

Figure (2.1) shows the free energy in Eq. (2.13) for several temperatures above and below the critical value below which one stable state of concentration continuously gives way to two. It is assumed in this figure that $\epsilon_{AA} = \epsilon_{BB}$ and $\nu = 4$, i.e. the alloy is two dimensional. The free energy well in the figure correspond to free energies of individual phases. Since impurity concentration (i.e. number of B atoms) is conserved, the order parameter in this problem is referred to as *conserved*. It will be seen that this designation has important implications about the type of dynamical equations that can be written for the spatial evolution of ϕ (or other conserved order parameters).

Since the order parameter represents a concentration –a conserved quantity– we can apply the standard Maxwell equal area construction [181, 133] to calculate the stable or equilibrium states of concentration the system can take below the critical temperature (i.e. the phase diagram). This construction leads to the so-called "common tangent construction", in which one graphically connects the free energy wells of any two phases by a common tangent line. The points where this tangent intersects the free energy wells determine the equilibrium concentrations, ϕ_{eq} , of the co-existing alloy phases. The slope of the line corresponds to the equilibrium chemical potential of the system, also expressed as $\mu_{\text{eq}} = \partial f / \partial \phi|_{\phi_{\text{eq}}}$. From the simple form of the free energy curves in Fig. (2.1) the equilibrium chemical potential can be seen to satisfy $\mu_{\text{eq}} = 0$. Thus, the equilibrium concentrations ϕ_{eq} are found by solving

$$\mu_{\text{eq}} = \left. \frac{\partial f}{\partial \phi} \right|_{\phi_{\text{eq}}} = 0 \quad (2.14)$$

Substituting Eq. (2.13) into Eq. (2.14) gives the transcendental equation

$$\phi_{\text{eq}} - \frac{1}{2} = \frac{1}{2} \tanh \left(\frac{\epsilon \nu}{2k_B T} \left(\phi_{\text{eq}} - \frac{1}{2} \right) \right) \quad (2.15)$$

Solutions of Eq. (2.15) exist only for $T < T_c \equiv \epsilon \nu / 4k_B$, which defines the critical temperature for this alloy. This form of the free energy is such that below a critical temperature two states emerge *continuously* from one. This means that at a temperature arbitrarily close to (and below) T_c , the two stable states ϕ_{eq} are arbitrarily close to the value $\phi_{\text{eq}} = 0$ above T_c . This type of behaviour is typical of a *second order* phase transformation.

2.1.2 Ising Model of Magnetism

A second microscopic system that can be described in terms of a well defined order parameter is a collection of magnetic spins in an external magnetic field. Consider a domain of atoms, each of which carries a magnetic spin $s_i = \pm 1$, i.e. the atoms' magnetic moment points up or down. The energy of this system of spins is given by

$$E\{s_i\} = - \sum_{i=1}^N \sum_{j=1}^{\nu} J s_i s_j - B \sum_{i=1}^N s_i \quad (2.16)$$

where ν represents the nearest neighbours of each spin. The first term of Eq. (2.16) sums up the interaction energies of each spin ("i") with all other spins ("j"). The second term adds the energy of interaction of each spin with an externally imposed magnetic field. In this system the order parameter is defined as

$$\phi = \frac{1}{N} \left\langle \sum_{i=1}^N s_i \right\rangle \equiv \langle s_i \rangle \quad (2.17)$$

which represents the average magnetization of the system. Unlike the case of the binary alloy where the average concentration of B atoms relative to the total number of atoms in the system was conserved ¹ the average magnetization is not a conserved quantity.

¹Note that the use in the binary alloy example of the grand canonical ensemble, where particle number varies, was done for convenience. We would have obtained the same results if we used the canonical ensemble where particle number remains fixed.

The statistical thermodynamics of this system can be considered via the canonical partition function for an N -spin system (since the number of spins is assumed not to change), given by

$$Q = \prod_{i=1}^N \sum_{s_i=-1,1} e^{-\beta E(s_1, s_2, s_3, \dots, s_N)} \quad (2.18)$$

One of the primary premises of statistical mechanics is that the partition function can be used to calculate the free energy per spin, according to

$$f = -\frac{k_B T}{N} \ln Q \quad (2.19)$$

From Eqs. (2.18) and (2.19) the order parameter defined by Eq. (2.17) can be evaluated as

$$\begin{aligned} \phi &= \frac{1}{Q} \prod_{i=1}^N \sum_{s_i=-1,1} \left(\frac{1}{N} \sum_{i=1}^N s_i \right) e^{-\beta(-B \sum_{i=1}^N s_i - J \sum_{i=1}^N \sum_{j=1}^{\nu} s_i s_j)} \\ &= \frac{\partial \left[\frac{k_B T}{N} \ln Q \right]}{\partial B} \\ &= -\frac{\partial f}{\partial B} \end{aligned} \quad (2.20)$$

Considering first the order parameter of the system for the simple case where the interaction strength $J = 0$, i.e. where the spins do not interact. This situation describes the case of a *paramagnet*, which occurs at high temperatures. In this case,

$$\begin{aligned} Q &= \prod_{i=1}^N \sum_{s_i=-1,1} e^{-\beta(-B \sum_{i=1}^N s_i)} \\ &= \prod_{i=1}^N \left(2 \frac{e^{\beta B} + e^{-\beta B}}{2} \right) \\ &= [2 \cosh(\beta B)]^N \end{aligned} \quad (2.21)$$

Substituting Eq. (2.21) into Eq. (2.19) gives

$$\begin{aligned} f &= -\frac{k_B T}{N} \ln Q \\ &= -k_B T \left(\ln \left[\cosh \left(\frac{B}{k_B T} \right) \right] + \ln 2 \right) \end{aligned} \quad (2.22)$$

Substituting Eq. (2.22) into the definition of the order parameter Eq. (2.20) gives,

$$\phi = -\frac{\partial f}{\partial B} = \tanh \left(\frac{B}{k_B T} \right) \quad (2.23)$$

The order parameter defined by Eq. (2.23) is shown in Fig. (2.2). Not surprisingly, it follows the sign of the external magnetic field B , since there are no spin-spin interactions.

The more complex case when spins are allowed to interact leads to *ferromagnetism* below a critical temperature T_c . This phenomenon can occur in the absence of an external magnetic field. To study this

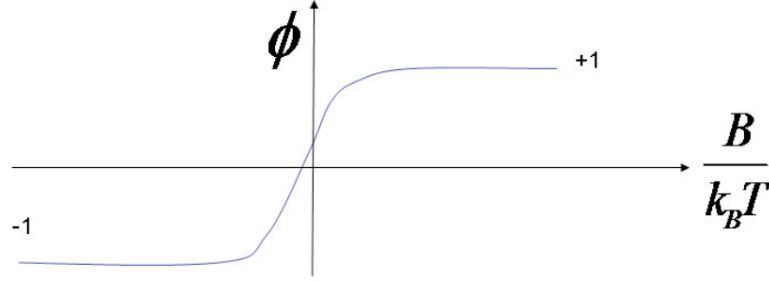


Figure 2.2: The order parameter of a paramagnetic system, in which the spins are assumed to interact with an external magnetic field but not with each other.

phenomenon, it is necessary to consider, once again, a mean field approximation, since evaluating the partition function Eq. (2.18) with $J \neq 0$ is not possible analytically. The mean field approximation in this case requires that we make the following replacement in the interaction energy in Eq. (2.16),

$$\sum_{i=1}^N \sum_{j=1}^N J s_i s_j \rightarrow \sum_{i=1}^N \sum_{j=1}^{\nu} J s_i \langle s_j \rangle = \nu J \phi \sum_{i=1}^N s_i \quad (2.24)$$

This corresponds to replacing the interaction of each spin (i) with all of its neighbours (j) by the interaction of each spin (i) with the mean field magnetization arising from ν neighbours. Doing so allows us to write the partition function as

$$\begin{aligned} Q &= \prod_{i=1}^N \sum_{s_i=-1,1} e^{-\beta(-B \sum_{i=1}^N s_i - J\nu\phi \sum_{i=1}^N s_i)} \\ &= [2 \cosh(\beta\{B + J\nu\phi\})]^N \end{aligned} \quad (2.25)$$

which yields, after application of Eq. (2.20),

$$\phi = \tanh\left(\frac{B + J\nu\phi}{k_B T}\right) \quad (2.26)$$

The transcendental Eq. (2.26) admits solutions even when $B = 0$, which corresponds to the case of spontaneous magnetization. Specifically, $\phi = 0$ for $T > T_c \equiv \nu J/k_B$, since the identity line $y = \phi$ will not intersect the function $y = \tanh(J\nu/k_B T)$ anywhere than $\phi = 0$ (assuming here $B = 0$). Expanding the hyperbolic tangent to third order gives an approximate solution of the order parameter (i.e. the magnetization) at the minima of the mean field free energy,

$$\phi \approx \pm[3(1 - T/T_c)]^{1/2}(T/T_c), \quad T < T_c \quad (2.27)$$

The non-zero equilibrium magnetization states of Eq. (2.27) below T_c go continuously to $\phi = 0$, the temperature state, as the critical temperature is approached, which implies a second order phase transition at T_c when $B = 0$.

It is interesting to substitute Eq. (2.25) into Eq. (2.19) and expand the result to fourth order in ϕ . This yields

$$\frac{f(T)}{k_B T} = -\ln(2) - \frac{1}{2} \left(\frac{J\nu\phi}{k_B T} \right)^2 + \frac{1}{12} \left(\frac{J\nu\phi}{k_B T} \right)^4, \quad (2.28)$$

Equation (2.28) is subtracted from the reference free energy of the disordered state just above the critical temperature,

$$\frac{f(T_c^+)}{k_B T_c} \approx -\ln(2) - \frac{1}{2} \left(\frac{J\nu\phi}{k_B T_c} \right)^2 \quad (2.29)$$

Close to T_c the free energy difference $\Delta f \equiv f(T) - f(T_c^+)$ becomes

$$\frac{\Delta f(T)}{k_B T_c} = \left(1 - \frac{T}{T_c} \right) \ln(2) + \frac{1}{2} \left(\frac{T}{T_c} - 1 \right) \left(\frac{J\nu\phi}{k_B T_c} \right)^2 + \frac{1}{12} \left(\frac{J\nu\phi}{k_B T_c} \right)^4, \quad (2.30)$$

It is straightforward to check that Eq. (2.30) indeed has one minimum state $\phi = 0$ for $T = T_c$ and two (Eq. (2.27)) for $T < T_c$. Such a polynomial expansion of the free energy in terms of the order parameter ϕ is an example of Landau free energy functional, which is the focus of the following section.

2.2 Introduction to Landau Theory

2.2.1 Order parameters and phase transformations

Traditional thermodynamics uses bulk variable such as pressure, volume, average density, internal energy, etc to describe the state of a system during phase transformations. Condensed phases often also display changes in positional and or rotational *order* during a phase transition. In the examples previously considered, for instance, the second order phase changes represented a change in magnetic order or sub-lattice ordering of impurity atoms (i.e. concentration).

Ordered phases are often distinguished from disordered phases by a decreased number of geometric symmetries. For example, a liquid or gas is disordered in the sense that they are symmetric with respect to all rotations and translations in space. A solid however, is only symmetric with respect to a limited number of rotations or translations in space. In a ferro-magnet, the disordered phase are symmetric with respect to all rotations and translations, while the ordered phases are not. The Landau theory of phase transformations treats the order parameter (denoted ϕ in the previous examples of this chapter) as a state variable, used to distinguish between ordered and disordered phases. It is customary to define the disordered state as $\phi = 0$ while the ordered states satisfy $\phi \neq 0$.

Some transformations occur between states that exhibit the same geometric symmetries. An example is a liquid gas transition, or a transition such as the binary alloy considered above, where only the sub-lattice concentrations change in the solid but not the geometrical state of the phases. In such cases it may still be possible to define an order parameter in terms of other thermodynamic variables relevant to the phase transformation. For example, the change of order in a liquid-gas transition can be described using the density difference between the two phases. This definition can, for example, makes it possible to maintain the definition of the "disordered" phase (i.e. that above the critical point) as $\phi = 0$.

When a disordered state gives rise to an ordered state that exhibits less symmetries than the Hamiltonian of the system, this is referred to as a *broken symmetry*. In plain English, what this means loosely speaking is that the Hamiltonian, which exhibits a certain number of symmetries can, mathematically,

give rise to phases (states) that exhibit an equal number of symmetries above some temperature and phases that exhibit fewer symmetries below that temperature.

The order parameter ϕ of a phase can be interpreted as a non-zero average of a local order parameter *field* $\Phi(\vec{r})$, which exhibits spatial variation. The "bulk" order parameter of the form discussed in the above examples can thus be thought of as the spatial average of the local order parameter, i.e. $\phi = \langle \Phi(\vec{r}) \rangle$, averaged over the phase. Throughout a system undergoing a phase transformation, significant spatial variations of $\Phi(\vec{r})$ occur on a length scale often characterized by a so-called *correlation length*, denoted here by ξ . The correlation length sets the scale over which the order changes from one phase to another. In solidification, for example, ξ is the distance comparable to the solid-liquid interface. The correlation length is assumed to be many times larger than the lattice constant of a solid but small enough to be able to describe the spatial variations characterizing a particular pattern of a system during a phase transformation.

The above discussion suggests that it is possible to characterize the state of a system in terms of the configurations of $\Phi(\vec{r})$, since each state of the system corresponds to a state of $\Phi(\vec{r})$. As a result, if it is possible to parameterize a quantity locally in terms of $\Phi(\vec{r})$, its thermodynamic value can be in principle calculated in terms of configurational sums over the states of the order parameter field $\Phi(\vec{r})$. Phase coexistence is then described by a bulk free energy whose minimization gives the possible values of the mean order parameter $\phi = \langle \Phi(\vec{r}) \rangle$ in each phase. This topic will be examined in this chapter.

The order of a phase transformation can be linked to the possible values of the average order parameter ϕ can take. For example, a continuous change from $\phi = 0$ above a certain critical temperature (T_c) to multiple values of $\phi \neq 0$ below a T_c denotes a second order transformation. Other signatures of a second order transformation include a jump in the 2nd derivatives of usual thermodynamic potentials and a spontaneous change of phase not requiring nucleation and not accompanied by a release of latent heat. Also, second order transformations typically preserve the geometrical symmetries between disordered and ordered phases.

A discontinuous change in the possible states of ϕ is the hallmark of a 1st order phase transition. Discontinuous change in ϕ means that $\phi = 0$ above a transition temperature T_m ² gives rise to a discrete jump in ϕ below T_m , the magnitude of which does not go to zero continuously at $T \rightarrow T_m$. Other signatures of a first order transformation include a jump in the first derivatives of thermodynamic potentials. First order transformations that occur between phase of the same symmetry usually terminate at a critical point, where a second order transformation occurs. First order transformations between phases of different geometrical symmetries (the more common cases in most materials) do not terminate at a critical point.

2.2.2 The Landau free energy functional

An elegant approach to illustrate Landau mean field theory, which is followed here to motivate the beginning of this section, is that used in Ref. [20]. This begins by re-grouping the configurational sum in the partition function into realizations of the order parameter that yield a specific spatial average $\langle \Phi(\vec{r}) \rangle \equiv \phi$. Doing so, a generalized partition function is defined by

$$Q(T) = \int_{-\infty}^{\infty} d\phi \Omega(\phi) e^{-\{E(\phi) - BV\phi\}} \quad (2.31)$$

²Note that this is not referred as a "critical" temperature for first order transformations

where $\Omega(\phi)$ in Eq. (2.31) is the density of states (i.e. configurations) of the system corresponding to ϕ (for simplicity only the simple case of a scalar order parameter field will be considered). The order parameter is now assumed to be defined via a volume average, where V is the volume of the system. The variable B plays the role of an ordering field in terms of which the order parameter can be defined from the partition function. It is an external magnetic field in the case of an Ising ferromagnet, while in the case of a binary alloy B is the chemical potential. The probability density of a system having an order parameter ϕ is

$$P(\phi) = \frac{1}{Q(T)} e^{-\{\hat{F}(\phi) - BV\phi\}} \quad (2.32)$$

where $\hat{F}(\phi) = E(\phi) - TS(\phi)$ is called the *Landau free energy*. Here $S(\phi) = k_B T \ln(\Omega(\phi))$ and $E(\phi)$ is the internal energy of the system. For a conserved order parameter, when B corresponds to a chemical potential, the Landau free energy corresponds to the Gibbs free energy. When the order parameter is coupled to an external field via B , the Gibbs free energy is given by $F(\phi) = \hat{F}(\phi) - BV\phi$. As discussed previously, the Gibbs free energy density (or the grand potential density ω) of the system is connected to the generalized partition function by

$$f = -\frac{k_B T}{V} \ln Q(T) \quad (2.33)$$

Equations (2.32) and (2.33) can be used to compute order parameter ϕ according to

$$\bar{\phi} \equiv \langle \phi \rangle = \int_{-\infty}^{\infty} \phi P(\phi) d\phi = \frac{\partial \left[\frac{k_B T}{V} \ln Q(T) \right]}{\partial B} = -\frac{\partial f}{\partial B} \quad (2.34)$$

The premise of Landau theory is to evaluate the partition function in Eq. (2.32) around the extremum of the Boltzmann factor. This leads to the well-known extremum conditions

$$\begin{aligned} \left. \frac{\partial}{\partial \phi} (\hat{F}(\phi) - BV\phi) \right|_{\bar{\phi}} &= 0 \\ \left. \frac{\partial^2}{\partial \phi^2} (\hat{F}(\phi) - BV\phi) \right|_{\bar{\phi}} &> 0 \end{aligned} \quad (2.35)$$

the solutions of which define the mean order parameter $\bar{\phi}$, and in terms of which the generalized equilibrium grand potential is defined as

$$\hat{\omega} \approx \frac{\hat{F}(\bar{\phi})}{V} - B\bar{\phi} \equiv \hat{f}(\bar{\phi}) - B\bar{\phi} \quad (2.36)$$

where $\hat{f}(\bar{\phi})$ is the Landau free energy density. It is emphasized that for the case of a conserved order parameter, B is a chemical potential (μ), $\hat{\omega}$ is actually the grand potential density (ω) and \hat{f} is the Gibbs free energy density (f). For a non-conserved order parameter in an external field B , $\hat{\omega}$ is actually the Gibbs free energy density. It should also be emphasized that the Landau mean field theory entirely neglects temporal and spatial fluctuations and evaluates thermodynamic quantities at the most probable homogeneous state of the order parameter, $\bar{\phi}$.

The next steps in mean field theory involve the construction of the Landau field free energy density $\hat{f}(\phi) \equiv \hat{F}(\phi)/V$. Recalling that the mean value of ϕ vanishes in the disordered state (i.e. $\phi = \bar{\phi} = 0$), and

considering second order phase transitions in the vicinity of the critical point, or first order transformations where the order parameter in the ordered phase suffers only a small jump from $\phi = \bar{\phi} = 0$, $\hat{f}(\phi)$ is assumed to be expressible in a series expansion of the form

$$\hat{f}(\phi) = \hat{f}(T, \phi = 0) + \sum_{n=2}^M \frac{a_n(T)}{n} \phi^n \quad (2.37)$$

The coefficients of Eq. (2.37) are dependent of temperature as well as other thermodynamic variables. In what follows, the free energy in Eq. (2.37) will be tailored to several practical and pedagogical phase transformation phenomena. For convenience, the hat notation will be dropped from the Landau free energy density \hat{f} .

2.2.3 Phase transitions with a symmetric phase diagram

It is instructive to use Eq. (2.37) to construct a Landau free energy expansion corresponding to the simple binary mixture model and the ferro-magnetic Ising model, which were examined at the beginning of this chapter. In the case of magnetism, symmetry considerations can be used to guide the choice of coefficients. Specifically, the fact that turning a magnet 180 degrees does not change its thermodynamic state internally implies that the "upward" and "downward" pointing states (below T_c) are energetically equivalent. Similarly, in the simple binary model with a symmetric phase diagram the free energy is symmetric in the two states on either side of the spinodal concentration at $\phi = 1/2$. Moreover, in both cases above the critical temperature, there should only be one globally stable, disordered ($\phi = 0$) state.

The above considerations on symmetry imply that for both these simple systems, only even powers in the expansion of the Landau free energy density in Eq. (2.37) need to be retained, leading to

$$f(\phi) = a(T) + \frac{a_2(T)}{2} \phi^2 + \frac{a_4(T)}{4} \phi^4 + O(\phi^6) \quad (2.38)$$

The first of the extremization conditions in Eqs. (2.35) implies minimizing Eq. (2.38) with respect to the order parameter ($B = 0$ for the symmetric alloy or ferromagnet). This gives

$$\frac{\partial f}{\partial \phi} = 0 \implies \phi = \left(0, \pm \sqrt{\frac{-a_2}{a_4}} \right) \quad (2.39)$$

For the first root, $\phi = 0$, to be the only root above the critical temperature, both $a_2(T) > 0$ and $a_4(T) > 0$ ($T > T_c$). For the non-zero roots of Eq. (2.39), which emerge below the critical temperature, it is necessary that $a_2(T) < 0$ while $a_4(T) > 0$ ($T < T_c$). Assuming that a_2 changes sign continuously across the critical temperature, it is reasonable to expand it to first order in a Taylor series about $T = T_c$ according to $a_2(T) \approx a_2^o(T - T_c)$. Meanwhile $a_4(T)$ must be of the form $a_4(T) \approx a_4^o + b_4^o(T - T_c) + \dots$, where a_2^o , a_4^o and b_4^o are positive constants. Thus, close to and below T_c , mean-field theory predicts two minimum (i.e. stable) order parameter states given by

$$\phi \approx \pm \sqrt{\frac{a_2^o}{a_4^o} (T_c - T)}, \quad T < T_c \quad (2.40)$$

Note that as $T \rightarrow T_c$ Eq. (2.40) continuously approaches $\phi = 0$.

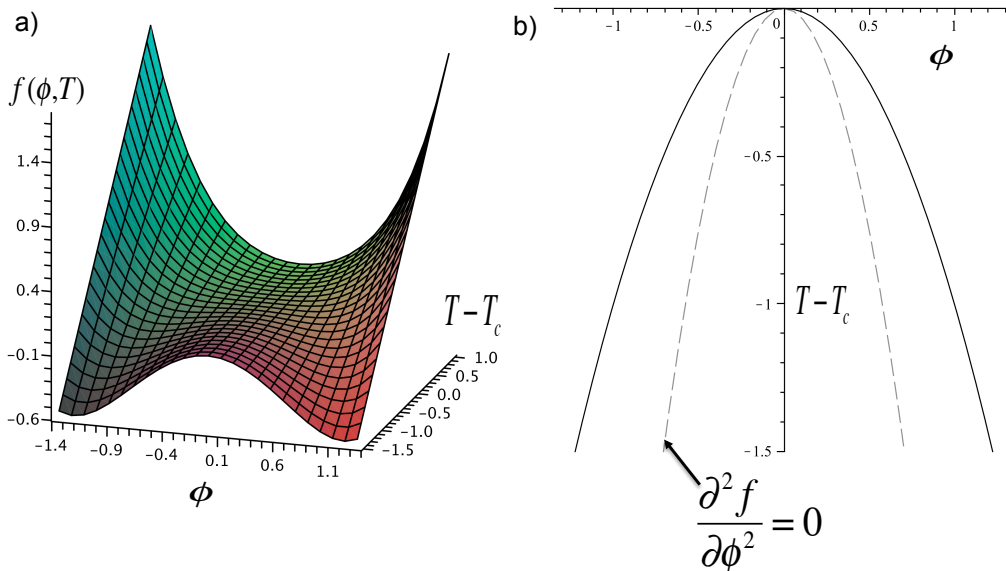


Figure 2.3: (a) Landau free energy of a simple binary mixture or Ising model. Two stable phases arise continuously from one for $T < T_c$. (b) Corresponding two-phase co-existence phase diagram for $T < T_c$. The spinodal line is indicated in grey dashed line.

Figure (2.3a) shows the energy landscape of Eq. (2.38), revealing the existence of one stable state above T_c ($\phi = 0$) and two below T_c . The figure shows that the disordered, $\phi = 0$, phase gives way to two minima, i.e. stable, states below $T = T_c$. Figure (2.3b) shows the corresponding phase diagram of coexisting minima of $f(\phi)$ in (T, ϕ) space. The dashed line indicates the so-called *spinodal* line defined by the locus of points where $\partial^2 f / \partial \phi^2 = 0$. It will be shown in section (4.6), when dynamics is examined, that an initial state with $\phi = \phi_o$ quenched below the spinodal line becomes linearly unstable to thermal fluctuations and spontaneously decomposes into the two stable phases whose order parameter is given by Eq. (2.40). This is referred to as *spinodal decomposition*. A high temperature phase corresponding $\phi_o = 0$ becomes immediately unstable to fluctuation for any temperature $T < T_c$, where T_c is the highest co-existence temperature, referred to as a critical or spinodal temperature. Critical fluctuations in ϕ grow continuously from their initial value toward their asymptotic values on the phase diagram, while the domain size of the two emerging phases become divergent in time (for an infinite size system). This is an example of a second order phase transformation. When an initial phase with $\phi_o \neq 0$ is quenched

below the two-state co-existence but above the spinodal line, is linearly stable to fluctuations and requires a threshold activation energy (i.e. nucleation) to begin the phase separation process. In this case there is an abrupt change in the order parameter to the value of the nucleated phase. This is an example of a first order transformation. It should also be noted that phase diagrams such as Fig. (2.3), terminating in a critical point typically describes phase transitions between two phases of the same geometric symmetry.

2.2.4 Phase transitions With a non-symmetric phase diagram

It is possible to represent asymmetry in a phase diagram containing a critical point by adding odd powers to the free energy expansion. An example of this is in a gas-liquid transition of a pure material. It is convenient to define, in this case, the order parameter to be the density difference from the critical density, i.e. $\phi = \rho - \rho_c$. It turns out that the asymmetry can be addressed by retaining at least one third order term in the Landau free energy density expansion of Eq. (2.37),

$$f(\phi, T) = a_o(T) + \frac{a_2(T)}{2}\phi^2 + \frac{a_3(T)}{3}\phi^3 + \frac{a_4(T)}{4}\phi^4 + O(\phi^6) \quad (2.41)$$

The choice of parameters can be "back-engineered" to obtain an appropriate phase diagram. It is once again assumed that $a_4(T) > 0$ for all temperatures in the neighborhood of the transition, which is still second order for the gas-liquid transition in the vicinity of the critical point.

The thermodynamics of this system is described by the grand potential density. In the context of Eq (2.36), B is found by noting that

$$\frac{\partial \omega}{\partial \phi} = 0 \rightarrow B = \frac{\partial f}{\partial \phi} = \mu - \mu_c \equiv \Delta\mu(T) \quad (2.42)$$

where the chemical potential has been referenced to its value at the critical point $\mu_c \equiv \mu(T_c)$. This implies that f itself is also referenced relative to that point, which does not change anything. The grand potential to be minimized in this system is therefore

$$\omega(\phi, T, \mu) = f(\phi) - \Delta\mu(T)\phi \quad (2.43)$$

The properties of a_2, a_3, a_4 can be better discussed by applying the extremum conditions in Eqs. (2.35) to Eq. (2.43) very close to the critical point, where it is assumed that $\Delta\mu \approx 0$ to lowest order in $T - T_c$ (to be confirmed below). This becomes the same as applying the extremum conditions to $f(\phi)$ (Eq. (2.41)), which gives

$$\begin{aligned} \phi(a_2 + a_3\phi + a_4\phi^2) &= 0 \\ a_2 + 2a_3\phi + 3a_4\phi^2 &> 0 \end{aligned} \quad (2.44)$$

The disordered phase is stable for $T > T_c$ for $a_2(T) > 0$. Conversely for a a continuous transition (a second order transformation) it is required that the three roots (i.e. states) of the cubic polynomial go to one as $T \rightarrow T_c$ from below. This can be achieved by demanding that both $a_2(T) \rightarrow 0$ and $a_3(T) \rightarrow 0$ as $T \rightarrow T_c$, and that they both become negative for $T < T_c$. Once again, it is sufficient for $a_4(T)$ to be positive and nearly constant in the neighbourhood of $T = T_c$. The lowest order temperature expansions of these constants satisfying these conditions is given by

$$\begin{aligned} a_2 &= a_2^o(T - T_c) \\ a_3 &= a_3^o(T - T_c) \\ a_4 &= a_4(T_c) \end{aligned} \quad (2.45)$$

In general, below the transition temperature, it is required to have two stable states whose grand potential is equal for both the liquid and gas phases. The density of these two states, however, will in general not be symmetrically positioned about ρ_c . The trial form of the grand potential satisfying these assumptions is

$$\omega(\phi, T, \mu) = \omega_o(T) + \frac{D(T)}{4}(\phi - \phi_L)^2(\phi - \phi_g)^2 \quad (2.46)$$

Comparing Eq. (2.46) to Eq. (2.43), where the free energy is expanded according to Eq. (2.41), gives

$$\begin{aligned} D(T) &= a_4(T) \\ \frac{1}{2}(\phi_L(T) + \phi_g(T)) &= -\frac{a_3(T)}{3a_4(T)} \\ (\phi_L(T) - \phi_g(T))^2 &= -\frac{4a_2(T)}{a_4(T)} + \frac{4a_3^2(T)}{3a_4^2(T)} \end{aligned} \quad (2.47)$$

from which the liquid-gas order parameters are determined to be, to lowest order in $T - T_c$,

$$\begin{aligned} \phi_L &= -\frac{a_3^o(T - T_c)}{3a_4(T_c)} + \sqrt{\frac{-a_2^o(T - T_c)}{a_4(T_c)}} \\ \phi_g &= -\frac{a_3^o(T - T_c)}{3a_4(T_c)} - \sqrt{\frac{-a_2^o(T - T_c)}{a_4(T_c)}} \end{aligned} \quad (2.48)$$

Once again, one minimum density is approached continuously as $T \rightarrow T_c$ from below. It is also seen that the chemical potential, given by

$$\Delta\mu(T) = \frac{a_4(T)}{2}(\phi_L(T) + \phi_g(T))\phi_L(T)\phi_g(T) \sim \mathcal{O}(T - T_c)^2 \quad (2.49)$$

2.2.5 First order transition without a critical point

First order transitions typically occur between phases of different geometric symmetry. As a result the phase diagram of a first order transition does terminate at a critical point, i.e. with the two co-existing phases merge into one. The simplest way to break this symmetry is by adding cubic term of negative sign to the Landau free energy density expansion of Eq. (2.37),

$$f(\phi, T) = a_0(T) + a_2(T - T_u)\frac{\phi^2}{2} - a_2\frac{\phi^3}{3} + u\frac{\phi^4}{4} \quad (2.50)$$

where a_2 , a_3 and u are positive constants and T_u is a reference temperature different from a critical point. This free energy exhibits a one global minimum at high temperature, two equal minima at transition temperature $T = T_m \equiv T_u + 2a_2^2/9a_3u$ and one global minimum, and a meta-stable minimum below T_m . The free energy landscape $f(\phi, T)$ for this case is shown in Fig. (2.4).

Above the transition temperature the free energy of the high symmetry phase ($\phi_h = 0$) is a global minimum –although it is evident that a second meta-stable low symmetry phase, $\phi_L > 0$, emerges even above T_m . Exactly at the transition temperature,

$$f(\phi_h, T_m) = f(\phi_L, T_m) \quad (2.51)$$

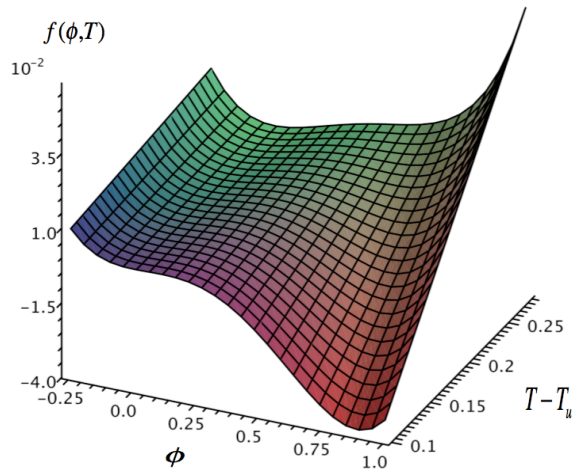


Figure 2.4: Landau free energy for a first order transformation. The double well curve with a cubic term in ϕ . One global minimum arises when the coefficient of the square term in $f_{\text{bulk}}(\phi, T)$ is positive. Below the melting temperature this phase becomes meta-stable and a new globally stable state of ϕ emerges.

Note that the minimum corresponding to ϕ_L (for $T < T_m$) does not emerge continuously from ϕ_h as in a second order transition. Instead it emerges as a global minimum at $T = T_m$ discontinuously, that is, at discrete distance from ϕ_h .

Once again the second derivative of the bulk free energy, $f'' \equiv \partial^2 f / \partial \phi^2$, plays an important role in determining the stability or meta-stability of a phase. If the high temperature minimum state ϕ_h (left well in Fig. (2.4)) is cooled to a temperature sufficiently below T_m , where $f'' < 0$, this phase (i.e. the initial phase ϕ_h) will be linearly unstable to all fluctuations, and decompose into the globally more stable state (right well in Fig. (2.4)). For temperature just below T_m , $f'' > 0$, and the initial high temperature phase will be metastable, implying that it will not be linearly unstable to all fluctuations. As a result large enough thermal fluctuations and nucleation are required to initiate the transition into the globally stable state. These considerations will be made more concrete in section (4.7) when the fluctuations and the stability of order parameters is discussed.

Chapter 3

Spatial Variations and Interfaces

Thus far only mean field free energies have been discussed. These describe only the bulk properties of the phases of a material. Only bulk thermodynamics can be considered with this type of free energy, which implies, among other things, that phases are infinite in extent and uniform. No consideration has been given to finiteness of phase and, more importantly, multiple phase and the interfaces separating them. As has been mentioned several times already, interfaces, their migration and interaction are perhaps the most important features governing the formation of microstructure in metals (and indeed most materials). This section incorporates interfacial energy into the mean field free energy, resulting in a free energy *functional* –coined the Ginzburg-Landau or Cahn-Hilliard [39] free energy functional. This is an expression that is dependent on the entire spatial configuration of a spatially dependent order parameter field. This modification allows the study of spatio-temporal fluctuations of order parameters, as well as the meso-scale dynamics that govern various pattern forming phenomena.

3.1 The Ginzburg-Landau Free Energy Functional

To show how to incorporate interfaces between phases, it is instructive to return to the simple binary model examined in section (2.1). It is reasonable to expect that the interaction energy between elements, previously assumed constant, is in fact spatially dependent and varies between any two elements i and j . Assuming for simplicity that $\epsilon_{AA} = \epsilon_{BB}$ ($b = 0$), the mean internal energy, $U \equiv \langle E[\{n_i\}] \rangle$ in Eq. (2.12), can be expressed as

$$U = \frac{1}{2} \sum_{i=1}^N \sum_{j \neq i} \epsilon_{ij} (\vec{x}_i - \vec{x}_j) \phi_i (1 - \phi_j) \quad (3.1)$$

where the constant term in Eq. (2.1) has been neglected. The interaction energy depends on the separation between elements ($\epsilon_{ij} = \epsilon_{ji}$) and the j summation is over the nearest neighbours of the i^{th} element for simplicity. To proceed, use is made next of the algebraic identity

$$\phi_i (1 - \phi_j) = ([\phi_i - \phi_j]^2 - [\phi_i^2 + \phi_j^2] + 2\phi_i)/2 \quad (3.2)$$

Equation (3.2) is substituted into Eq. (3.1), which is then simplified by making the assumption that for any i , ϵ_{ij} is negligible for any $j > \nu$ (which in this case spans the 4 nearest neighbours). These

assumptions make it possible to re-write Eq. (3.1) as

$$U = \frac{1}{4} \sum_{i=1}^N \sum_{j \neq i} \epsilon_{ij} (\phi_i - \phi_j)^2 - \frac{1}{2} \sum_{i=1}^N (1 - \phi_i) \phi_i \left(\sum_{j \neq i} \epsilon_{ij} \right) \quad (3.3)$$

Further, assume that the interaction energy per particle $\epsilon_{ij} \rightarrow \epsilon_i/\nu$, where ϵ_i is the isotropic mean energy over the ν nearest neighbours of element i .

In the limit where any two adjacent elements i and j represent two locations that are physically separated by an "infinitesimal" distance ¹ the sum

$$\begin{aligned} \frac{1}{2} \sum_{j \neq i} (\phi_i - \phi_j)^2 &= \frac{a^2}{2} \left[\left(\frac{(\phi_i - \phi_R)^2}{a^2} + \frac{(\phi_i - \phi_T)^2}{a^2} \right) + \left(\frac{(\phi_i - \phi_L)^2}{a^2} + \frac{(\phi_i - \phi_B)^2}{a^2} \right) \right] \\ &\approx a^2 |\nabla \phi(\vec{x}_i)|^2 \end{aligned} \quad (3.4)$$

in 2D, where ϕ_R , ϕ_T , ϕ_L and ϕ_B represent ϕ_j evaluated at the right, top, left and bottom neighbours of the i^{th} element, respectively. The large round brackets in the first line of Eq. (3.4) represent the magnitudes of one-sided gradients at the point i . The vector \vec{x}_i on second line of Eq. (3.4) represents the position centered at the element labelled by i . To make the transition to the continuum limit complete, the "i" summation in Eq. (3.3) is also replaced by its continuum analog, an integral. In d -dimensions this is accomplished by writing

$$\sum_i \rightarrow \int_V \frac{d^d \vec{x}}{a^d} \quad (3.5)$$

where the division by a^d is intended to encapsulate the volume that was previously contained within one element, which is the distance between two discrete points –the lattice constant.

With the definitions in Eqs. (3.4) and (3.5) the total internal energy in Eq (3.3) can be written, in the 3D continuum limit, as

$$E = \int_V \left(\frac{1}{2} |W_o \nabla \phi|^2 + \frac{1}{2a^3} \epsilon(\vec{x}) \phi(\vec{x}) (1 - \phi(\vec{x})) \right) d^3 \vec{x} \quad (3.6)$$

where the coefficient $W_o \equiv \sqrt{\epsilon(\vec{x})/(\nu a)}$ has been defined (a is replaced by $a^{(d-2)}$ in d dimensions). This parameter will be seen below to be intimately connected with surface energy since it multiplies a gradient in the the order parameter ϕ , which only varies significantly at interfaces where there is a change of order. In a similarly way the total entropic part of the free energy can be written as

$$S = -k_B \int_V (\phi(\vec{x}) \ln \phi(\vec{x}) + (1 - \phi(\vec{x})) \ln(1 - \phi(\vec{x}))) \frac{d^3 \vec{x}}{a^3} \quad (3.7)$$

where the integrand in Eq. (3.7) can now be seen as a local entropy density (i.e. $\phi \rightarrow \phi(\vec{x})$), making the the total entropy an integral of the entropy density overt the volume V of the system. Combining Eqs. (3.6) and (3.7) thus yields the total free energy of the binary alloy,

$$F[\phi, T] = \int_V \left\{ \frac{1}{2} |W_o \nabla \phi|^2 + f(\phi(\vec{x}), T(\vec{x})) \right\} d^3 \vec{x} \quad (3.8)$$

¹Here "infinitesimal" refers to a length scale which is small relative to the size of the interface width, but still large compared to the inter-atomic spacing of the solid.

where the bulk free energy density is given by

$$f(\phi(\vec{x}), T(\vec{x})) = \frac{\epsilon(\vec{x})}{2a^3} \phi(\vec{x})(1 - \phi(\vec{x})) + \frac{k_B T}{a^3} (\phi(\vec{x}) \ln \phi(\vec{x}) + (1 - \phi(\vec{x})) \ln(1 - \phi(\vec{x}))) \quad (3.9)$$

Equation (3.8) is the simplest representation of a free energy that combines the bulk thermodynamics of a simple binary alloy with a minimal description of interfacial energy. Equation (3.8) is often referred to the *Ginzburg-Landau* [96] or Cahn-Hilliard [39] free energy. The free energy of the form in Eq. (3.8) serves as a starting point for many phenomena that are modeled using the phase field methodology. In general, $f(\phi, T)$ can be a complex function like Eq. (3.9), or it can be approximated by a polynomial series that is interpreted as a Taylor series expansion of $f(\phi, T)$ about disordered phase (e.g. via the generalized free energy expansion of Eq. (2.37)). This formalism allows for a meso-scopic description of that accounts for bulk thermodynamics and interfaces. Consider, for example, the magnetic system studied in section (2.1.2). The gradient term in Eq. (3.8) describes a microscopic zone where the local magnetization varies abruptly between two magnetic domains .

3.2 Equilibrium Interfaces and Surface Tension

Statistical mechanics dictates that thermodynamic equilibrium is characterized by a state that minimizes some thermodynamic potential. For bulk phases (i.e. ignoring interfaces) this implies that $\partial G(x_i)/\partial x_i = 0$ for all x_i , where x_i represent all the intensive thermodynamic variables or internal degrees of freedom and G a relevant potential. For the case of the Ginzburg-Landau free energy defined in Eq. (3.8), equilibrium must, by construction, involve “states” that are actually continuum fields such as $\phi(\vec{x})$, $T(\vec{x})$, etc. An analogous example is one where it is required to find the form of the equilibrium curve of a cable stretched between two poles. That case is solved by finding the shape of the curve that minimizes the total potential energy, which is a functional of the cable profile. Analogously, in a system described by Eq. (3.8), “equilibrium” must involve achieving a state of the field variable $\phi(\vec{x})$ that minimizes the total Ginzburg-Landau free energy functional $F[\phi]$ (e.g. for the Ising ferromagnet) or the grand potential $\Omega = F[\phi] - \mu \int \phi d^3\vec{r}$ (e.g. for the alloy).

The minimization process of a functional $F[\phi]$ with respect to the function ϕ is achieved by a so-called *variational derivatives*, and is denoted by

$$\frac{\delta F[\phi]}{\delta \phi} = 0, \quad (3.10)$$

For a general free energy functional of the form

$$F[\phi] \equiv \int_{\text{vol}} f(\phi, \partial_x \phi, \partial_y \phi, \partial_z \phi) dV \quad (3.11)$$

the variational derivative of $F[\phi]$ with respect to the field ϕ is given by applying the theory of variational calculus. By definition,

$$F[\phi + \delta \phi] - F[\phi] = \int_V \left(\frac{\delta F}{\delta \phi} \delta \phi + \dots \right) dV \quad (3.12)$$

Applying this definition to Eq. (3.11) gives,

$$\frac{\delta F[\phi]}{\delta \phi} \equiv \frac{\partial f}{\partial \phi} - \left\{ \partial_x \left(\frac{\partial f}{\partial (\partial_x \phi)} \right) + \partial_y \left(\frac{\partial f}{\partial (\partial_y \phi)} \right) + \partial_z \left(\frac{\partial f}{\partial (\partial_z \phi)} \right) \right\} \quad (3.13)$$

The first term on the right hand side of Eq. (3.13) affects only the algebraic, or bulk, part of the Ginzburg-Landau free energy functional. The second term is a recipe for obtaining the variational of the free energy with respect to the gradient energy terms of ϕ .

Consider, as an example, minimizing the free energy in Eq. (3.8) for the Ising model with $B = 0$, and assuming W_o is constant. Using the free energy is given by Eq. (2.38), Eq.(3.10) becomes

$$W_o^2 \nabla^2 \phi_0 - \frac{\partial f}{\partial \phi_0} = W_o^2 \nabla^2 \phi_0 - a_2(T) \phi_0 - a_4(T) \phi_0^3 = 0 \quad (3.14)$$

where the notation ϕ_0 is used here to denote the minimizing state of $F[\phi]$. The solution of Eq. (3.14) in 1D (which represents an equilibrium one dimensional two-phase interface) is obtained by multiplying both sides of the equation by the $d\phi_0/dx$ and integrating from $-\infty$ to a position x . This gives,

$$\begin{aligned} \frac{W_o^2}{2} \int_{-\infty}^x \frac{\partial}{\partial x'} \left(\frac{\partial \phi_0}{\partial x'} \right)^2 dx' - \int_{-\infty}^x \frac{\partial \phi_0}{\partial x'} \frac{\partial f}{\partial \phi_0} dx' &= 0 \\ \frac{W_o^2}{2} \left(\frac{\partial \phi_0}{\partial x} \right)^2 - (f(\phi_0(x)) - f(\phi_0(-\infty))) &= 0 \end{aligned} \quad (3.15)$$

Substituting $f(\phi) = a_2\phi^2/2 + a_4\phi^4/4$ into Eq. (3.15) gives

$$\phi_0(x) = \sqrt{\frac{|a_2|}{a_4}} \tanh \left(\frac{x}{\sqrt{2}W_\phi} \right) \quad (3.16)$$

where $W_\phi = W_o/\sqrt{|a_2|}$ (recall that near a critical point, $a_2 = a_o(T - T_c)$) is the *correlation length* discussed previously. This is a mesoscopic length scale over which the change of order in ϕ occurs. The hyperbolic tangent solution has two limits: $\phi_0(x \rightarrow \pm\infty) = \pm\sqrt{|a_2|/a_4}$, which describes the order parameter in the bulk phases of the alloy. The transition region wherein $-\sqrt{|a_2|/a_4} < \phi_0(x) < \sqrt{|a_2|/a_4}$ defines the interface between the two phases.

To calculate the interface tension associated with the order parameter profile in Eq (3.16), ϕ_0 is substituted into full Ginzburg-Landau free energy Eq. (3.8), after which the bulk free energy, given by $f(\phi_0)$ (T dependence dropped), is eliminated using the the second line of Eq. (3.15). Thus,

$$\begin{aligned} F &= \int_{-\infty}^{\infty} \left\{ \frac{W_o^2}{2} \left(\frac{\partial \phi_0}{\partial x} \right)^2 + f(\phi_0(x)) \right\} dx \\ &= \int_{-\infty}^{\infty} \left\{ W_o^2 \left(\frac{\partial \phi_0}{\partial x} \right)^2 + f(\phi_0(-\infty)) \right\} dx \end{aligned} \quad (3.17)$$

The second term in the second line of Eq. (3.17) is the total free energy of a bulk solid phase. Subtracting it out leaves the remaining, interfacial, free energy, i.e.,

$$\sigma \equiv F - F_{\text{eq}} = W_o^2 \int_{-\infty}^{\infty} \left(\frac{\partial \phi_0}{\partial x} \right)^2 dx \quad (3.18)$$

where F_{eq} is the bulk free energy integrated over the volume of the system ².

²Note, that for the case of a conserved order parameter, the definition of surface energy is given in terms of the grand potential $\Omega[\phi]$. This will be used in the study of binary alloys in the next chapter.

The units of Eq. (3.18) can be made more apparent if the order parameter field $\phi_o(x)$ is written as $\phi_o(u)$ where $u \equiv x/\sqrt{2}W_\phi$. Substituting this scaling form into Eq. (3.18) gives

$$\sigma \equiv F - F_{\text{eq}} = W_o \sqrt{|a_2|} \sigma_\phi \quad (3.19)$$

where

$$\sigma_\phi \equiv \int_{-\infty}^{\infty} \left(\frac{\partial \phi_o(u)}{\partial u} \right)^2 du \quad (3.20)$$

Since W_o has units $[J/m]^{1/2}$ and a_2 has units of $[J/m^3]$, σ clearly has units of energy per unit area (or energy per unit length for a 1D interface). It is referred to as the surface tension because there is a force –or tension– that resists any increase in interface area.

Free energies similar to Eq. (3.8) and equilibrium profiles similar to Eq. (3.16) will be encountered frequently in phase field modeling of solidification or other phase non-equilibrium phase transformations. In the case of solidification, for example, the phase field ϕ will denote the local order of a solid liquid system. In that case, the equilibrium ϕ profile thus characterizes the solid liquid interface, an atomically diffuse region of order W_ϕ within which atomic order undergoes a transition from a disordered liquid to an ordered solid.

Chapter 4

Non-Equilibrium Dynamics

The previous chapter examined the significance of spatial variations in an order parameter. In the context of materials microstructure, these variations demarcate regions of bulk phase from phase boundaries or interfaces. Another important aspect that must be examined is the time dependence of order parameter changes. Along with the dynamics of other fields (e.g. temperature), the dynamics of order parameters are a critical ingredient in the development of a phenomenology for modeling the microstructure evolution of in phase transformations.

It is typical in non-equilibrium dynamics to use a *locally* defined equilibrium free energy or entropy to determine the *local* driving forces of a phase transformation. These generalized forces or their fluxes are used to drive the subsequent kinetics of various quantities. The premise of this approach is that matter undergoing phase transformation is assumed to be in *local* thermodynamic equilibrium and is driving toward a state of global thermodynamic equilibrium (a state which is, however, never actually realized in practice). This formalism thus constitutes a coarse-grained description where space can be thought of as a collection of volume elements, each large enough that it can be assumed to be in thermodynamic equilibrium (with respect to the local temperature, volume, particles, etc.) but still small enough to resolve micro-scale variations in microstructure.

Kinetic equations for order parameter fields are called *conserved* if they take on the form of a flux-conserving equation. This implies that an integral of the the field over all space is a constant (e.g. total solute concentration in a closed system). The time evolution of fields whose global average need not be conserved is typically governed by a *non-conserved* equation. These include magnetization and sublattice ordering. The kinetics of these quantities are typically formulated as a Langevin-type equation, which evolves field such as to minimize the total free energy (or, conversely, to maximize the total system entropy). In other words, non-conserved fields evolve according to the steepest functional gradient of the free energy, which hopefully pushes the order parameter to minimum of the free energy landscape.

The following subsections outline the basic evolution equations governing conserved and non-conserved order parameters. In all cases the free energy being referred to is in the context of the Ginzburg-Landau free energy functional in Eq. (3.8), where $f(\phi, T)$ depends on the particular phase transformation under consideration.

4.1 Driving Forces and Fluxes

Consider a system that is in thermal equilibrium. Its change in entropy is given by

$$dS = \frac{1}{T}dU + \frac{p}{T}dV - \sum_i \frac{\mu_i}{T}dN_i \quad (4.1)$$

where T is the temperature, V its volume and N_i the number of particles of species i . As this system undergoes a phase transformation, the second law of thermodynamics demands that $dS > 0$ in a closed system. In the case of a constant volume, the driving forces or so-called "affinities" driving the corresponding changes in internal energy (U) and particle number (N_i) are

$$\begin{aligned} \frac{dS}{dU} &= \frac{1}{T} \\ \frac{dS}{dN_i} &= -\frac{\mu_i}{T} \end{aligned} \quad (4.2)$$

If Eq. (4.1) is applied locally to a volume element, then the second law further implies that changes, or gradients, in S from one location in the system element to another must be mediated (i.e. accompanied by) a corresponding "flow" in the local internal energy and local number of particles. The flux of these two quantities is generally assumed to be given by the linear combination of gradients of the driving forces in Eq. (4.2), i.e.

$$\begin{aligned} \vec{J}_0 &= M_{00}\nabla\left(\frac{1}{T}\right) - \sum_{j=1}^N M_{0j}\nabla\left(\frac{\mu_j}{T}\right) \\ \vec{J}_i &= M_{i0}\nabla\left(\frac{1}{T}\right) - \sum_{j=1}^N M_{ij}\nabla\left(\frac{\mu_j}{T}\right) \end{aligned} \quad (4.3)$$

where \vec{J}_0 is associated with a flux of internal energy and \vec{J}_i is associated with the flux of particle number of species i . The coefficients of the tensor M_{ij} ($i, j = 0, \dots, N$) were derived by Osanger, who also showed that the Osanger coefficient matrix is symmetric. This is referred to as the *Osanger reciprocity theorem*. The derivation of Eqs. (4.3) presented here is empirical, based largely on intuition. The reader is referred to reference [18] for a more mathematically rigorous treatment of generalized driving forces based on entropy production.

4.2 The Diffusion Equation

It is instructive to illustrate how to use the driving forces in Eqs. (4.3) to derive Fick's second law of mass and heat diffusion. Consider, first, mass transport in a one-component alloy at a fixed, uniform temperature T . In the dilute limit, it suffices to consider only fluxes in the solute species and ignore fluxes in the host atoms, i.e. only the off-diagonal Osanger coefficient $M_{11} \neq 0$. Under these conditions the flux of mass is governed by $\vec{J}_1 = -M_{11}\nabla(\mu_1/T)$, i.e. that of the solute atoms. Since solute atoms must be conserved, their dynamics must obey the flux conserving equation of mass conservation, i.e.

$$\frac{\partial c}{\partial t} = -\nabla \cdot \vec{J}_1 \quad (4.4)$$

Substituting above the expression for the flux \vec{J}_1 into Eq. (4.4) gives

$$\begin{aligned}\frac{\partial c}{\partial t} &= \nabla \cdot \left(\frac{M_{11}}{T} \nabla \mu_1 \right) \\ &= \nabla \cdot \left(\frac{RM_{11}}{c} \nabla c \right)\end{aligned}\tag{4.5}$$

where c is the local solute concentration (in units of moles/volume) and the expression $\mu_1 \approx RT \ln c$ (R is the natural gas constant) has been used to obtain the second line of Eq. (4.5). Equation (4.5) implies that $M_{11} \propto c$, and can be immediately recognized as Fick's second law with

$$D = \frac{RM_{11}}{c}\tag{4.6}$$

It is interesting to note that the Onsager coefficient –which is inherently linked to microscopic parameters and essentially intractable to calculate analytically– can be experimentally approximated by measuring the the diffusion coefficient $D(c)$.

Fourier's law of heat conduction in a pure materials can similarly be derived by considering the flux of internal energy with only $M_{00} \neq 0$. The calculation proceeds identically to the one above, yielding

$$\frac{\partial H}{\partial t} = \nabla \cdot (k \nabla T)\tag{4.7}$$

where H is the local enthalpy density and k is the thermal conductivity coefficient, given by

$$k = \frac{RM_{00}}{T^2}\tag{4.8}$$

The Onsager coefficient M_{00} can be determined experimentally by measuring the heat conduction coefficient.

4.3 Dynamics of Conserved Order Parameters: *Model B*

Consider next the dynamics of a general order parameter that represents a quantity that is conserved. For the specific example of the simple binary alloy (see phase diagram in Fig. (2.3b)) the definition of the order parameter represents an impurity concentration. A high temperature disordered phase with average concentration $\phi = \phi_o$ will undergo phase separation once temperature is lowered below T_c . Under isothermal conditions, the dynamics of this process are fundamentally driven by gradients in chemical potential between or within phases (e.g. the second of Eqs. (4.2)). A local chemical potential must be derived from the Ginzburg-Landau free energy as a *functional* of the concentration. Following the approach of Cahn and Hilliard [39], this done by defining

$$\mu = \frac{\delta F[\phi]}{\delta c}\tag{4.9}$$

where the right had side of Eq. (4.9) represents a variational derivative rather than a partial derivative. In equilibrium, when the free energy density depends on local gradients of the order parameter ϕ , Eq. (4.9) defines a differential equation for the equilibrium order parameter profile. In mean field theory when spatial gradients are neglected, it reduces to the usual definition of the chemical potential.

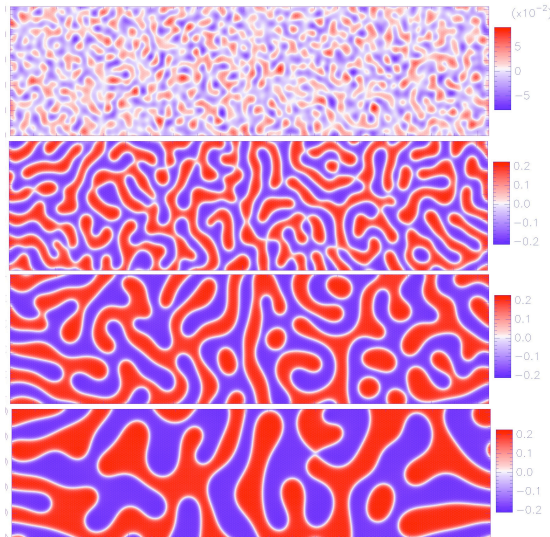


Figure 4.1: Top to bottom: time sequence showing phase separation during spinodal decomposition. Fluctuations on small length scales grow into larger domains, the size of which diverges with time according to a power law. Color represents solute concentration different in the two phases, with red being the solute rich phase and blue the solute poor phase.

Since ϕ represents a concentration difference, it must satisfy the mass conservation equation,

$$\frac{\partial \phi}{\partial t} = -\nabla \cdot \vec{J} \quad (4.10)$$

The flux in Eq. (4.10) is derived from Eq. (4.3) (assumed for simplicity that the non-diagonal Onsager coefficients are zero) as

$$\vec{J} = -M \nabla \cdot \mu \quad (4.11)$$

where

$$M \equiv \frac{M_{11}}{T} \approx \frac{M_{11}}{T_c} \quad (4.12)$$

is the mobility of solute. The replacement of $T \rightarrow T_c$ assumes that just below the critical point, temperature can be approximated by the critical temperature T_c to lowest order. Combining Eqs. (4.9)-(4.11) gives the following equation of motion for the order parameter of a phase separating alloy mixture.

$$\frac{\partial \phi}{\partial t} = \nabla \cdot \left(M \nabla \frac{\delta F}{\delta \phi} \right) \quad (4.13)$$

Equation (4.13) is the celebrated Cahn-Hilliard equation, or *Model B* as it is often called in the condensed matter physics literature, after the paper by Hohenberg and Halperin [92], which studied and classified the various order parameter models and the associated physical phenomena they can be used to describe.

As a specific example of the Chan-Hilliard equation for spinodal decomposition, $f(\phi, T)$ from Eq. (2.38) is substituted into Eq. (4.13). Applying the rules of variational derivatives in Eq. (3.13) gives

$$\frac{\partial\phi}{\partial t} = M\nabla^2 \left(-W_o\nabla^2\phi + \frac{\partial f}{\partial\phi} \right) \quad (4.14)$$

$$= M\nabla^2 (-W_o\nabla^2\phi + a_2\phi + a_4\phi^3) \quad (4.15)$$

where it has been assumed for simplicity that the mobility M is a constant. It should be noted that because of the conservation law a term of the form $\nabla^4\phi$ is generated. Figure (4.1) shows a simulation of the dynamics of Eq. (refcahn-hilliard) with $a_2 = -1$ and $a_4 = 1$ and $M = 1$. The concentration field ϕ was initially set to have random initial fluctuations about $\phi = 0$ and periodic boundary conditions were used in the simulation. It is seen that since $a_2 < 0$ (which is the case for $T < T_c$), phase separation occurs. The average alloy concentration satisfies $\langle\phi\rangle = \phi_o \approx 0$, the initial average of the order parameter. Stochastic noise (discussed in section (4.6)) which emulates thermal fluctuations was not used in this simulation. Since any for any temperature $T < T_c$ the system is unstable to any fluctuation, phase separation in this example was merely initiated using the randomness inherent in computer-based number generation. Numerical methods for simulating model B are discussed in further detail in section (4.9).

4.4 Dynamics of Non-Conserved Order Parameters: *Model A*

Some phase transformations involve quantities (order parameters) that do not evolve constrained to a conservation law. Well known examples include magnetic domain growth, order/disordered transitions, or isothermal solidification of a pure material in the absence of a density jump. In the presence of a small magnetic field, a disordered magnetic state with zero magnetization, quenched below the critical temperature will eventually develop a net magnetization. Even cooling below the Curie temperature without an external field will generally lead to a small net magnetization in a finite system. Similarly, a glass of water (disordered phase) cooled below the melting temperature will entirely transform to ice. This is in contrast to phase separation in an alloy mixture, where the the system evolves toward equilibrium under the constraint that total solute be conserved. Order parameters that evolve without global conservation are called *non-conserved* order parameters.

Motivated by Eq. (4.1), a new driving force for the rate of change of non-conserved order parameter is defined as $\delta F/\delta\phi$. Since there is no conservation imposed on $\langle\phi\rangle$, the simplest dissipative dynamical evolution for a non-conserved order parameter is given by Langevin type dynamics,

$$\frac{\partial\phi}{\partial t} = -M \frac{\delta F[\phi, T]}{\delta\phi} \equiv M \left(W_o\nabla^2\phi - \frac{\partial f(\phi, T)}{\partial\phi} \right) \quad (4.16)$$

where M is related to the time scale for atomic re-arrangement from the disordered phase to the ordered one. The right hand side of Equation (4.16) is a driving force that is Taylored to drive the system down gradients in the free energy landscape of $F[\phi]$. This equation is referred to as *model A* in Hohenberg and Halperin classification of phase field models[92]. It is a paradigm used to describe the evolution of an order parameter that does not satisfy a global conservation law. Using, once again, $f(\phi, T)$ from Eq. (2.38), the dynamics of a system of Ising spins in the absence of an external field evolves can be described by

$$\frac{\partial\phi}{\partial t} = M (W_o\nabla^2\phi - a_2\phi - a_4\phi^3) \quad (4.17)$$

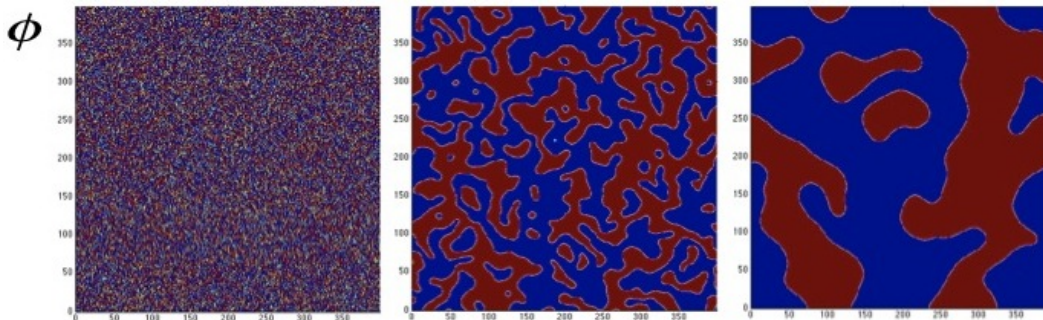


Figure 4.2: Left to right and top to bottom: time sequence of magnetic domain formation and coarsening under model A dynamics. The colour scale is the z-direction of magnetization, with blue representing downward magnetization and brown upward magnetization.

which is arrived at by substituting Eq. (2.38) has been substituted into Eq. (4.16). For a system of Ising spins in an external field, Eq. (2.50) can be used, where the constant a_3 can describe a coupling to the external field. Figure (4.2) shows a sequence of time slices in the evolution of magnetic domains simulated numerically using model A dynamics. The grey scale shows the magnitude of ϕ , which in this case defines the z-direction magnetization. The simulation starts with initial fluctuations, out of which magnetic domains eventually emerge and coarsen. Numerical methods for simulating equations such as the Cahn-Hilliard equation are discussed in more detail in section (4.9).

It is worth mentioning the tempting pitfall regarding the use of Model A dynamics to evolve the time evolution of a conserved order parameter. Specifically, it might appear feasible to use Eq. (4.16) to describe the dynamics of phase separation in a simple binary alloy by adding a Lagrange multiplier term of the form $\lambda \int \phi(\vec{x}) d^3\vec{x}$ to the free energy in order to conserve total solute. While conserving total mass, such a free energy allows for the possibility for a solute source in one part of the system to be countered by a solute sink many diffusion lengths away from the source. That would be unphysical for any propagating phenomenon, not to say the least about a slow diffusive process. Such an approach can only be used to describe the equilibrium properties and dynamics would be fictitious.

4.5 Generic Features of Models A and B

Equations (4.14) and (4.16) underlie the basic physics of many common *phase field* models in the literature. They have the following generic features: (i) an appropriate order parameter is defined for the phenomenon in question; (ii) a Ginzburg-Landau free energy density is constructed to reflect the symmetries of bulk phases as a function of temperature (and other intensive thermodynamics quantities), as well as the interfacial energy in the system; (iii) equations of motion for the order parameter constructed on the principle of free energy minimization and, if required, conservation laws. In chapter (5) model A and model B type equations will appear again, this time coupled to each other in the description of the solidification of a pure material.

A fourth ingredient that must strictly be included in Eqs. (4.14) and (4.16) is the addition of stochastic noise sources with which to model thermal fluctuations. These are crucial to properly describe all the degrees of freedom at the microscopic level (e.g. phonon vibrations in a solid or atomic collisions in a

liquid) that act on length scales below the correlation length ξ , which sets the scale over which changes of order occur (e.g. $\xi = W_o/\sqrt{|a_2|}$ in section (3.2)) and on atomic time scales. These are usually subsumed mathematically into a random variable appended to the end of the model. The role of noise on order parameter fluctuations are discussed further in section (4.6).

It should be noted that it is often not possible to define a well defined order parameter ϕ in the sense outlined in Landau theory. Indeed, in most phase field models the "free energy" is expanded in terms of a what is generally terms a "phase field parameter" ϕ , which is motivated from Landau theory but is otherwise phenomenological in nature. Conversely to the more fundamental approach taken here in the construction of models A and B, many phase field models and their dynamics are constructed to be consistent with a particular class of kinetics, sharp-interface equations, etc. This approach goes back to Langer [137].

4.6 Equilibrium Fluctuations of Order Parameters

The notion of equilibrium can often be misleading as it gives the impression that a system just sits there and all motion in time has stopped. Due to thermal fluctuation, all quantities of a system in equilibrium are actually continuously fluctuating in space and in time in a way that is consistent with the statistical thermodynamics. This section analyzes equilibrium fluctuations of order parameters governed by model A and model B dynamics.

4.6.1 Non-conserved order parameters

To take thermal fluctuations into account for a phase described by a non-conserved order parameter, Eq. (4.16) needs to be upgraded to

$$\frac{\partial\phi}{\partial t} = -\frac{\delta F[\phi, T]}{\delta\phi} = M \left(W_o^2 \nabla^2 \phi - \frac{\partial f(\phi, T)}{\partial\phi} \right) + \eta(\vec{x}, t) \quad (4.18)$$

where $\eta(\vec{x}, t)$ is a stochastic noise term, as described in section (4.5), which is added to incorporate thermal fluctuations that are microscopic in origin (e.g. phonon vibrations) which take place on length sales smaller than correlation length ξ , i.e. angstrom scales, and on *ps* time scales. As a result, their addition as a "noise" source superimposed onto the slower long wavelength dynamics of the order parameters field is in most situations justified. These were first added into phase field modeling by Cook [52]. The random noise term η is selected from a statistical distribution satisfying

$$\langle \eta(\vec{x}, t) \eta(\vec{x}', t') \rangle = A \delta(\vec{x} - \vec{x}') \delta(t - t') \quad (4.19)$$

where the primes denotes a different position/time than the un-primed variables and A is a temperature dependent constant. In plain english, Eq. (4.19) means that any two fluctuations in the system are uncorrelated in space (i.e. between positions \vec{x} and \vec{x}') and time (i.e. between time t and t').

The form of A in Eq. (4.19) is found by considering the dynamics of model A for a phase that is in a stable state of the free energy density (e.g. Eqs. (2.38) and (2.50)). In the case of small deviations in the order parameter, $\phi = \phi_{\min} + \delta\phi$, the bulk free energy can be approximated to lowest order by $f(\phi, T) \approx f_{\min} + (a_2/2)\phi^2$ for a stable, single-phase, state. Model A dynamics can thus be approximated by

$$\frac{\partial\delta\phi}{\partial t} = M (W_o \nabla^2 \delta\phi - a_2 \delta\phi) + \eta(\vec{x}, t) \quad (4.20)$$

Re-writing Eq. (4.20) in Fourier space gives

$$\frac{\partial \hat{\phi}_k}{\partial t} = -M (a_2 + W_o^2 k^2) \hat{\phi}_k + \hat{\eta}_k \quad (4.21)$$

where k is the magnitude of the wave vector $\vec{k} = (k_x, k_y, k_z)$, $\hat{\phi}_k$ represents the Fourier transform of $\delta\phi(x, t)$ and $\hat{\eta}_k$ is the Fourier transform of the noise source (assumed continuous on meso-scopic time and length scales where the order parameter is continuous). Equation (4.21) is a first order linear differential equation, whose solution is

$$\hat{\phi}_k(t) = e^{-M(W_o^2 k^2 + a_2)t} \left(\hat{\phi}_k(t=0) + \int_0^t e^{M(W_o^2 k^2 + a_2)t'} \hat{\eta}_k(t') dt' \right) \quad (4.22)$$

Consider next the *structure factor*, defined according to

$$S(k, t) = \langle |\hat{\phi}_k|^2 \rangle \quad (4.23)$$

(see Appendix (C.1) for details of arriving at Eq. (4.23)). The structure factor characterizes the statistics of spatio-temporal fluctuations in the order parameter of the phase and can be directly measured from an x-ray or neutron scattering experiment of a material or phase. The brackets in Eq. (4.23) denote *ensemble averages* or averages of $|\hat{\phi}_k|^2$ over many realizations of the system fluctuating in time, about equilibrium. Substituting the solution for $\hat{\phi}_k(t)$ into the definition of $S(k, t)$ gives,

$$S(k, t) = e^{-2\gamma_k t} S(k, t=0) + \frac{A}{2\gamma_k} (1 - e^{-2\gamma_k t}) \quad (4.24)$$

where the definition $\gamma_k \equiv M(W_o^2 k^2 + a_2)$ has been made. The transient dynamics of the structure factor describe the way fluctuations on certain length scales decay in a system. For example, the long wavelength $k \rightarrow 0$ modes decay exponentially with a time scale $t_c = 1/(Ma_2)$. Comparing the late time ($t \rightarrow \infty$) limit of Eq. (4.24) with its theoretical and experimentally determined form (the so-called Ornstein Zernike form [111]) gives,

$$S(k) = \frac{A}{2\gamma_k} = \frac{A/2Ma_2}{1 + (W_o^2/a_2)k^2} = \frac{(k_B T/f'')}{1 + (\xi k)^2}, \quad (4.25)$$

where f'' is the second derivative of the bulk free energy density $f(\phi, T)$ evaluated at the equilibrium order parameter, ϕ_{\min} and $\xi = W_o/\sqrt{a_2}$ is defined as the correlation length. The right hand equality in Eq. (4.25) A gives

$$A = 2Mk_B T \quad (4.26)$$

4.6.2 Conserved order parameters

The analysis of section (4.6.1) can be extended in a straightforward way to the fluctuations of a phase described by a conserved order parameter. Expanding once again the order parameter as $\phi = \phi_{\min} + \delta\phi$, linearizing the free energy about $\phi = \phi_{\min}$ and substituting into Eq. (4.14) now gives,

$$\frac{\partial \delta\phi}{\partial t} = M\nabla^2 \left(-W_o \nabla^2 + f'' \right) \delta\phi + \eta(\vec{x}, t) \quad (4.27)$$

where for conserved dynamics, the noise term at the end of Eq. (4.14) satisfies

$$\langle \eta(\vec{x}, t) \eta(\vec{x}', t') \rangle = A \nabla^2 \delta(\vec{x} - \vec{x}') \delta(t - t') \quad (4.28)$$

Equation (4.27) is different from Eq.(4.20) in the addition of the outer laplacian, due to the conservation law. The solution of Eq. (4.27) in Fourier space is exactly the same as Eq. (4.22), expect that now $\gamma_k = M k^2 (W_o^2 k^2 + f'')$, i.e there is an extra k^2 multiplying the γ_k of section (4.6.1). The different value of γ_k changes the transient decay rate of spatial fluctuations (i.e. k -modes) of ϕ for a conserved order parameter compared to that for a non-conserved order parameter. It turns out that the late time ($t \rightarrow \infty$) structure factor for a conserved order parameter remains identical to Eq. (4.25), yielding Eq. (4.26) for the strength of thermal fluctuations in this case as well.

Another important feature of the addition of noise to conserved, and non-conserved, dynamics is that it assures that systems evolve to an equilibrium defined by the probability $P[\phi]$ given by

$$P[\phi] \propto e^{-(F[\phi] - F_o) k_B T} \quad (4.29)$$

where F_o is some reference free energy.

4.7 Stability and the Formation of Second Phases

With a better understanding of the role of thermal fluctuations around equilibrium, it is instructive to return to the issue of stability of an initial phases cooled below a transition temperature during a phase transformation. This topic was examined qualitatively in sections (2.2.3) and (2.2.5).

4.7.1 Non-conserved order parameters

Consider a general bulk free energy $f(\phi, T)$ and a system prepared in a state $\phi = \phi_{\min}$ and which is initially a minimum of the free energy, and which is then lowered below a transition temperature. To make matters concrete, two cases are examined. The first involves a second order phase transition, where a system in a state with $\phi = 0$ is the minimum of the free energy defined by Eq. (2.38) above T_c (disordered phase) and becomes a maximum below the critical temperature T_c (see Fig. (2.3)). The second example considers a first order transition described by the free energy in Eq. (2.50) where the disordered phase with $\phi = 0$ that is stable above a transition temperature, T_m becomes a meta-stable below T_m (see Fig. (2.4)). In both cases, the initial state satisfies $\partial f / \partial \phi|_{\phi_{\min}} = 0$ after being cooled below the transformation temperature.

Consider, next, a small perturbation of the initial state, $\phi = \phi_{\min} + \delta\phi$. The dynamics of the perturbation $\delta\phi$ are determined by substituting ϕ into the model A dynamics of the Eq. (4.18). Expanding the non-linear terms of the free energy to second order in $\delta\phi$ yields,

$$\begin{aligned} \frac{\partial \delta\phi}{\partial t} &= M \left(W_o^2 \nabla^2 \delta\phi - \left. \frac{\partial f}{\partial \phi} \right|_{\min} - \left. \frac{\partial^2 f}{\partial \phi^2} \right|_{\min} \delta\phi \right) + \eta \\ &= M \left(W_o^2 \nabla^2 - f'' \right) \delta\phi - M f' + \eta \end{aligned} \quad (4.30)$$

$$= M \left(W_o^2 \nabla^2 - f'' \right) \delta\phi + \eta \quad (4.31)$$

where the bulk free energy $f(\phi, T)$ has been expanded to second order in $\delta\phi$ and substituted into Eq. (4.18). The notation f' and f'' denote the first and second derivatives of $f(\phi)$, respectively, evaluated

at the initial state, which is assumed to be an extremum of the free energy, i.e. $f' = 0$. Employing once again the Fourier transform technique, Eq. (4.31) can be transformed into

$$\frac{\partial \delta \hat{\phi}_k}{\partial t} = -M \left(W_o^2 k^2 + f'' \right) \delta \hat{\phi}_k + \hat{\eta}_k \quad (4.32)$$

the solution of which is

$$\delta \hat{\phi}_k = e^{-M(W_o^2 k^2 + f'')t} \left(\delta \hat{\phi}_k(t=0) + \int_0^t e^{-M(W_o^2 k^2 + f'')t'} \hat{\eta}_k(t') dt' \right) \quad (4.33)$$

The coefficient $\gamma_k \equiv W_o^2 k^2 + f''$ in the exponential of Eq. (4.33) is largest when $k = 0$. Therefore, $\delta \hat{\phi}_k$ will always become linearly unstable in at least the $k = 0$ mode (i.e. at least at the longest wavelengths) if $f'' < 0$, due to the sign of the argument of the exponential in Eq. (4.33). This situation is precisely satisfied by a first or second order phase transition when cooling below the spinodal line of the phase diagram, which is defined by $f'' < 0$. Right at the critical temperature $f'' = 0$, which is a saddle point in the free energy landscape of Fig. (2.3). Thermal fluctuations will cause a range of long wavelengths to become linearly unstable, leading to a separation of ϕ into one or both of the free energy minima, described by the phase diagram. The case $f'' > 0$, which occurs for initial states of the system away from the critical order parameter, corresponds to a state of a system that is stable state above the transition temperature and which remains meta-stable below the transition temperature T_m . This is a feature characteristic of a first order transformations. As discussed in section (2.2.5) this situation requires thermal fluctuations to exceed a threshold necessary to nucleate a critical seed of the precipitating phase.

4.7.2 Conserved order parameters

The stability of a conserved order parameter can be more complex than a non-conserved one since the average of the order parameter must be preserved when crossing below the transition temperature. An instructive example is found by considering a binary mixture described by the free energy in Eq. (2.38), with a spinodal phase diagram such as that in Fig. (2.3). Consider a specific alloy with a non-zero initial relative solute concentration ($\phi_o \neq 0$), cooled just below the co-existence region of the phase diagram. If the system is cooled below the coexistence but above the spinodal line (defined by $f'' = 0$), thermal fluctuations are required to nucleate and grow a second phase in accordance with conserved dynamics. If system is cooled below the spinodal line, phase separation will commence without nucleation. In both cases, growth of the second phase domains will be governed by conserved dynamics, which implies that both cases the final values of ϕ in the respective parent and daughter phases will be set by the Maxwell equal area construction, also known as the common tangent construction. Contrast this to a first order transitions involving non-conserved order parameters (e.g. solidification), where the stable high temperature phase can evolve completely into the stable ($T < T_m$) phase.

The linear stability of meta-stable of an initial phase evolving by conserved dynamics proceeds analogously to the section (4.7.1). Starting from Eq. (4.27), the linearized dynamics of $\delta \phi$ in Fourier space become

$$\frac{\partial \delta \hat{\phi}_k}{\partial t} = -Mk^2 \left(W_o^2 k^2 + f'' \right) \delta \hat{\phi}_k + \left(Mf' + \hat{\eta}_k \right) \quad (4.34)$$

the solution of which is

$$\delta \hat{\phi}_k = e^{-Mk^2(W_o^2 k^2 + f'')t} \left(\delta \hat{\phi}_k(t=0) + \int_0^t e^{-Mk^2(W_o^2 k^2 + f'')t'} \left(\hat{\eta}_k(t') + Mf' \right) dt' \right) \quad (4.35)$$

The stability coefficient to consider is now $\gamma_k \equiv k^2(W_o^2 k^2 + f'')$. Note also that in this example the initial state, $\phi = \phi_o$, is not necessarily an extremum of the free energy $f(\phi, T)$ and so $\partial f / \partial \phi|_{\phi_o} \neq 0$ (except at $\phi_o = 0$).

Unlike the case of non-conserved dynamics the $k = 0$ mode is always marginally stable here. It is thus the smaller wavelengths that become linearly unstable first, with their growth rate depending on their magnitude compared to $f''(\phi = \phi_o)$. To illustrate with a simple example, consider the binary mixture (or other thermodynamic system governed by this free energy) of section (2.2.3). For this free energy,

$$\gamma_k = Mk^2 (W_o^2 k^2 a_2^o (T - T_c) + 3u\phi_o^2) \quad (4.36)$$

Equation (4.36) shows that there will always be some non-zero wave-numbers that become unstable so long as

$$T < T_s \equiv T_c + \frac{3u}{a_2^o} \phi_o^2 \quad (4.37)$$

which also precisely coincides (or defines) the spinodal line in Fig. (2.3b).

4.8 Interface Dynamics of Phase Field Models (Optional)

Before Model A and Model B gained popularity for their role in more complex phase field models for solidification and related microstructure problems, they were regularly used in the condensed matter theory to derive governing equations of motion for interfaces between phases. While these topics are somewhat removed from the main thrust of this book, it is instructive to briefly reviewed some of the more interesting of these topics, without going into the more difficult mathematical details. The interested reader is invited to consult Ref. [64] and references therein for further mathematical details.

4.8.1 Model A

Consider for concreteness zooming into the interface of a large magnetic domain evolving under Model A dynamics. Let the position of the interface be denoted by the function $h(x, t)$, where the curvature of the domain is gradual enough that the position of the interface can be quantified by a one dimensional variable x , as illustrated in Fig. (4.3). The two phases are characterized by the order parameters ϕ_+ (spin up) and ϕ_- (spin down), which are defined as the minima of the bulk phase field free energy, enoted here by $f_{\pm}(\phi)$. In the remainder of this subsection an analysis of model A will be performed from which an equation for the dynamics $h(x, t)$ will be derived.

The starting point is model A, written here in the dimensionless form

$$\tau \frac{\partial \phi}{\partial t} = -\frac{\delta F}{\delta \phi} = W_\phi^2 \nabla^2 \phi - \frac{dg}{d\phi} - \frac{\partial f_{\pm}}{\partial \phi} + \eta(\vec{x}, t) \quad (4.38)$$

where W_ϕ is the characteristic length of the interface and τ is a characteristic time scale of the model. The variable $\eta(\vec{x}, t)$ is a stochastic noise variable, effectively subsuming the role of thermal fluctuations at the microscopic level. It will be assumed that the bulk part of the free energy, $f_{\pm}(\phi)$, can be written as

$$f_{\pm}(\phi) = \epsilon f(\phi) \quad (4.39)$$

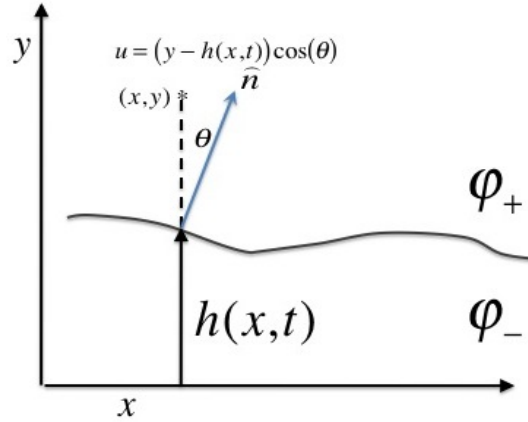


Figure 4.3: An interface separating two magnetic domains. The function $h(x,t)$ measures the distance to the interface from some reference line. It is assumed that the interface is sufficiently gently curved to be able to consider the portion of the interface in this one dimensional fashion.

where $\epsilon \equiv W_\phi/d_o \sim 1/H$ is redefined here as a small parameter, d_o is the capillary length and $f(\phi)$ is dimensionless and scaled by H , the energy barrier between the two phases¹. By scaling the bulk free energy with ϵ , the thermodynamic driving force effectively goes to zero when the interface becomes sharp or equivalently, when the energy barrier between the two phases becomes very large. The parameter ϵ thus controls the deviation of the ϕ field from its form corresponding to a flat stationary planar interface, denoted here as ϕ_0 .

It is instructive to transform the co-ordinates of Eq. (4.38) into a co-ordinate system that is local to the interface and which measures distances along to and normal to the interface. The co-ordinate along the arc of the interface is denoted s while that normal to the interface is denoted u (See Fig. (C.1) for an illustration). The transformation of the gradient squared and time derivative operators in interface-local (u, s) co-ordinates is discussed in section (A.2) of Appendix (A) and Appendix (C.2) (as well as in [64]), and will not be reproduced here. Specifically, the transformation of Eq. (4.38) to local interface co-ordinates becomes

$$\underbrace{\tau \left(\frac{\partial \phi}{\partial t} - V_n \frac{\partial \phi}{\partial u} + s_{,t} \frac{\partial \phi}{\partial s} \right)}_{\partial_t \phi \text{ in } (u,s) \text{ co-ordinates}} = \underbrace{W_\phi^2 \left(\frac{\partial^2 \phi}{\partial u^2} + \frac{\kappa}{(1+u\kappa)} \frac{\partial \phi}{\partial u} + \frac{1}{(1+u\kappa)^2} \frac{\partial^2 \phi}{\partial s^2} - \frac{u\kappa_{,s}}{(1+u\kappa)^3} \frac{\partial \phi}{\partial s} \right)}_{\nabla^2 \phi \text{ in } (u,s) \text{ co-ordinates}} - \frac{dg(\phi)}{d\phi} - \epsilon \frac{df(\phi, c)}{d\phi} + \eta \quad (4.40)$$

where κ is the local interface curvature and the notation $\kappa_{,s}$ denotes differentiation of curvature with respect to the arc length variable s . Similarly $s_{,t}$ is the time derivative of the local arc length at position on the interface with time.

¹The significance of this specific scaling will be dealt with again in later chapters and Appendix (A), when a more complex interface analysis of a model A type equation coupled to a model B type diffusion equation is performed to derive the sharp interface sharp interface boundary conditions of solidification and second-phase formation.

It is useful to examine the structure of ϕ near the interface by re-scaling the normal co-ordinate via $\xi = u/W_\phi$ and the dimensionless arc length via $\sigma = d_o\kappa = (\epsilon/W_\phi)s$. In terms of these definitions, curvature is re-scaled by $\bar{\kappa} = (W_\phi/\epsilon)\kappa$. Meanwhile, the characteristic rate of the kinetics of atoms across the interface is given by $v_c = W_\phi/\tau$, which implies that the characteristic time for motion of the interface is defined via $t_c = d_o/v_c = \tau/\epsilon$. Furthermore, the characteristic speed characterizing motion of the interface over the scale of the capillary length is defined by $v_s = D/d_o$, where $D \equiv W_\phi^2/\tau$ is like an effective diffusion coefficient of model A. In terms of t_c and v_s , a dimensionless velocity is defined by $\bar{v}_n = V_n/v_s = \tau/(W_\phi\epsilon)V_n$ and a dimensionless time by $\bar{t} = t/t_c = (\epsilon/\tau)t$. Equation (4.40) can now be re-written in terms of $(\xi, \bar{t}, \bar{v}_n)$. Retaining only terms up to order ϵ in the resulting scaled equation gives

$$\epsilon \frac{\partial \phi}{\partial \bar{t}} - \epsilon \bar{v}_n \frac{\partial \phi}{\partial \xi} + \epsilon \frac{\partial \sigma}{\partial \bar{t}} \frac{\partial \phi}{\partial \sigma} = \frac{\partial^2 \phi}{\partial \xi^2} + \epsilon \bar{\kappa} \frac{\partial \phi}{\partial \xi} - \frac{dg(\phi)}{d\phi} - \epsilon \frac{df(\phi, c)}{d\phi} + \epsilon \nu \quad (4.41)$$

It has been assumed without loss of generality that $\eta = \epsilon \nu$ where ν is a noise source or order one.

It will be assumed that ϕ can be expanded in a so-called asymptotic series in ϵ according to

$$\phi(\xi, \sigma, \bar{t}) = \phi_0(\xi) + \epsilon \phi_1(\xi, \sigma, \bar{t}) + \dots \quad (4.42)$$

where the ϕ_0 solution is, by construction, only a function of the normal co-ordinate since it represents the solution across a flat stationary profile. The expansion in Eq. (4.42) is substituted into Eq. (4.41). Collecting the terms not multiplying by ϵ (referred to as the "order ϵ^0 terms") gives

$$\frac{\partial^2 \phi_0}{\partial \xi^2} - g'(\phi_0) = 0 \quad (4.43)$$

Similarly collecting the ϵ terms leads to an equation for the perturbation ϕ_1 ,

$$\frac{\partial^2 \phi_1}{\partial \xi^2} - g''(\phi_0)\phi_1 = -(\bar{v}_0 + \bar{\kappa}) \frac{\partial \phi_0}{\partial \xi} + f_{,\phi}(\phi_0) + \nu \quad (4.44)$$

the first equation provides the so-called "lowest order" solution of the phase field ϕ . It suffices to recognize that it is some analytical solution based on the double-well function $g(\phi)$ and it need not be explicitly solved here. Equation (4.44) can be simplified by multiplied by $\partial \phi_0/d\xi$ and integrated from $\xi \rightarrow -\infty$ to ∞ , giving

$$\int_{-\infty}^{\infty} \frac{\partial \phi_0}{\partial \xi} \mathcal{L}(\phi_1) d\xi = -(\bar{v}_0 + \bar{\kappa}) \int_{-\infty}^{\infty} \left(\frac{\partial \phi_0}{\partial \xi} \right)^2 d\xi + \int_{-\infty}^{\infty} \frac{\partial \phi_0}{\partial \xi} f_{,\phi}(\phi_0) d\xi + \int_{-\infty}^{\infty} \frac{\partial \phi_0}{\partial \xi} \nu \quad (4.45)$$

where $\mathcal{L} \equiv \partial_{\xi\xi} - g''(\phi_0)$ and $g''(\phi_0)$ denoted the second derivative with respect to ϕ . Integrating the integral on the left hand side of Eq. (4.45) by parts to give

$$\int_{-\infty}^{\infty} \frac{\partial \phi_0}{\partial \xi} \mathcal{L}(\phi_1) d\xi = \int_{-\infty}^{\infty} \frac{\partial \phi_1}{\partial \xi} \left(\frac{\partial^2 \phi_0^{\text{in}}}{\partial \xi^2} - g'(\phi_0^{\text{in}}) \right) d\xi = 0 \quad (4.46)$$

based on Eq. (4.38).

Starting from Eq. (4.45), with the left hand side set to zero, leads to the following relation between the the local normal interface velocity V_n and curvature,

$$V_n = -D\kappa + \lambda + \zeta \quad (4.47)$$

where $D \equiv W_\phi^2/\tau$, $\lambda \equiv v_c \Delta f_\pm/\sigma_\phi$, with $\Delta f_\pm \equiv f(\phi_+) - f(\phi_-)$, σ_ϕ is given by Eq. (3.20) and $\zeta = v_c \int_{-\infty}^{\infty} \partial_\xi \phi_o \eta d\xi$ is just a re-scaled stochastic noise term.

The link between cartesian co-ordinates and the interface-local co-ordinates (in terms of which κ and v are defined) is made by defining the normal distance from the interface through the co-ordinate u given

$$u = (y - h(x, t)) \cos(\theta) \quad (4.48)$$

where θ is the angle that the normal to the interface (\hat{n}) makes with the y -axis in Fig. (4.3). The co-ordinate u to any point depends on the position on the acr of the interface from which u is measured. In this simple treatment, where the interface is assumed to be very gently curved, the arclength variable (s) is replaced simply by x . Thus $u \equiv u(x, t)$. (For a more thorough treatment of co-ordinates local to the interface, the reader is advised to review section (C.2)). Approximating the normal velocity by $V_n = -\partial u(x, t)/\partial t$ gives,

$$V_n = \frac{\partial h/\partial t}{\sqrt{(1 + (\partial h/\partial x)^2)}} + \frac{h(\partial h/\partial x)(\partial^2 h/\partial x \partial t)}{1 + (\partial h/\partial x)^2} \quad (4.49)$$

From basic calculus, it is found that for a gently curved interface, curvature is related to the interface position $h(x, t)$ by

$$\kappa = -\frac{\partial^2 h/\partial x^2}{(1 + (\partial h/\partial x)^2)^{3/2}} \quad (4.50)$$

The assumption of small curvatures makes it possible to neglect the second term in Eq. (4.49), which is third order in the gradients of h . Substituting the resulting expression and Eq. (4.50) into Eq. (4.47), and expanding the radicals to first order in $(\partial h/\partial x)^2$ gives,

$$\frac{\partial h}{\partial t} = D \frac{\partial^2 h}{\partial x^2} + \frac{\lambda}{2} \left(\frac{\partial h}{\partial x} \right)^2 + \nu + \lambda \quad (4.51)$$

The last term (λ) can be removed if a new height function $\tilde{h}(x, t) \equiv h(x, t) - \lambda t$ is defined. Equation (4.53) is the famous Kardar-Parisi-Zhang (KPZ) equation used to describe interface roughening in many phenomena, ranging from the growth of thin films to smoldering combustion fronts in paper [169].

Interestingly, for a quench just below the transition temperature, $\lambda \approx 0$ and Eq. (4.47) becomes the Allen-Cahn equation for curvature driven interface growth. In this limit the KPZ equation becomes

$$\frac{\partial h}{\partial t} = D \frac{\partial h}{\partial x^2} + \nu \quad (4.52)$$

which can be derived from the free energy functional \mathcal{H} given by

$$\mathcal{H} = \int_{-\infty}^{\infty} \left\{ \frac{1}{2} |\nabla h(x, t)|^2 \right\} dx \quad (4.53)$$

This implies that domain coarsening of a second order phase transformation, near the critical point, is essentially entirely driven by surface curvature minimization. Moreover, the absence of any polynomial terms makes it possible to move interfaces on all length scales with little energy. In Fourier space Eq. (4.52) has the solution $\hat{h} \sim e^{-q^2 t}$, where q is the wavevector. This leads to domain size scaling of the form $\sim (qt^{1/2})^2$.

4.8.2 Model B

The dynamics of an interface evolving under model B dynamics is considerably more complex than those of model A. Since model B is conservative, interface motion must evolve in a coupled fashion with the diffusion in the bulk phases. The complete description of model B interfaces constitutes what is referred to as a "sharp interface" model. These types of models comprise two boundary conditions relating the local interface velocity with local interface curvature. The boundary conditions are self-consistently coupled to a diffusion equation for the order parameter in the bulk. Models such as these are commonly used to describe diffusion limited growth of interfaces in pure materials and alloys. The first of the boundary conditions is the well-known Gibbs-Thomson condition, which relates the change of concentration at the interface from its equilibrium (i.e. stationary, flat interface) value to the local curvature (κ) and normal interface velocity (V_n). The second boundary condition is a relationship between V_n and the net mass flux crossing an interface along the normal direction. For thermally controlled microstructures, the appropriate sharp interface equations are given by Eqs. (1.1). This is discussed further in Chapter (5). In alloys, the appropriate sharp interface models are reviewed in section (6.2.2) (see Eqs. (6.3)-(6.5)). Their derivation from model B is shown in Ref. [64] in using a so-called first order perturbation analysis. They are also derived in Appendix (A) using a more general, second order perturbation analysis of an alloy phase field model, which admits both compositional and solid-liquid interfaces.

4.9 Numerical Methods

From the theoretical discussion thus far it should start becoming clear that the vast majority of non-linear models of any importance can be solved exactly analytically. The machinery of numerical modeling is required to explore its full range of complexity. This section introduces some numerical procedures for simulating model A and model B type equations studied in this chapter. It is recommended that readers without previous experience in computational modeling read appendix (B) before reading the sections of this book dedicated to numerical simulation. For simplicity only two spatial dimensions are treated. The transition to three is precisely analogous in most cases.

4.9.1 Fortran 90 codes accompanying this book

The CD that accompany this book contains codes (and references to codes) for reader to practice and learn from. The names and directories where these codes are found in each chapter, at the corresponding section dealing with numerical implementation.

Fortran 90 codes used for the simulations in this section are provided in subdirectories "ModelA" and "ModelB" of the folder "codes". The codes modules comprise a main program file named manager.f90 and separate modules for other tasks. For example, all variables are defined in the module variables_mod.f90 while printing is done in the util_mod.f90 module. The solver code is in solver_mod.f90. Both codes read input before commencing the simulation from a file called "input", whose entries have been defined as comments in the input file itself. The code has been tested on a MacBook running Mac OS X version 10.5.6. It uses standard Fortran 90 and should run on any platform. It comes with a file called "Makefile", which deals with the details of compiling and linking all program modules. To create an executable, simply type "make" in the same directory where the code files and "Makefile" reside. Be sure to replace the first line of the Makefile (i.e. F90 = /sw/bin/g95) with a path telling the operating system where your fortran compiler is located. Finally, a Matlab M-file called surff.m is also included in the code directories. This enables surface plotting to visualize a field of the form $\phi(i, j)$ in 3D. The M-file is run

by typing `surff(dim, skip, n1, n2)` in the Matlab command window, where `dim = 1` reads the first column of the output file produced by the code, `skip` is the number of discrete time steps between printed output files and `n1, n2` are the starting and ending discrete time steps to plot, one at a time. All plots are shown momentarily and then saved to a jpeg file labeled by the corresponding discrete time. Be sure to set the path in Matlab to where the output files created by the solver codes reside. If this all sounds like a foreign language to you, consult with your local system administrator.

4.9.2 Model A

Model A is simulated numerically by approximate $\phi(x, y, t)$ as a discrete representation that "lives" on a rectangular grid of points labeled by an index $i = 1, 2, 3, \dots$ and $j = 1, 2, 3, \dots$ in the x and y directions, respectively (See Fig. (B.1) for a 2D schematic). Values of $\phi(x, y, t)$ on this grid are represented on a computer by an array (matrix) of real numbers. The distance between grid points is assumed to represent a small distance Δx in the x -direction and Δy in the y -direction. (In most of what follows it is assumed that $\Delta x = \Delta y$ for simplicity.) Similarly, time is made discrete by introducing a numerical length scale Δt , labelled by the index $n = 0, 1, 2, \dots$. Dimensional time is measured as $t = n\Delta t$ and space by $x = (i-1)\Delta x$ (same for y). As computer memory is always limited, a grid can only represent a domain of length L in each spatial direction. This sets the maximum number of grid points in the numerical array to $N = L/\Delta x$ (it will be assumed for simplicity that L is chosen to be a multiple of Δx).

The simplest way to advance the solution of Eq. (4.16) forward in time is known as an *explicit* method. In this method the solution of ϕ at time $t = (n+1)\Delta t$ is determined entirely from that at $t = n\Delta t$, starting with an initial condition of $\phi((i-1)\Delta x, (j-1)\Delta y, 0)$ over $i, j = 1, 2, 3, \dots N$.² The discrete equation used to update model A on a uniform rectangular grid is derived in Appendix (B), re-written here as

$$\phi^{n+1}(i, j) = \phi^n(i, j) + \frac{\Delta \bar{t}}{\Delta \bar{x}^2} \bar{\Delta}^2 \phi^n(i, j) - \Delta \bar{t} \frac{\partial f(\phi^n(i, j))}{\partial \phi} \quad (4.54)$$

where the scaled variables $\bar{x} \equiv x/W_\phi$, $\bar{t} = Mt$ have been assumed. The notation $\bar{\Delta}^2 \phi^n(i, j)$ is short hand for the discrete Laplacian operator³

$$\bar{\Delta}^2 \phi^n(i, j) = \phi(i+1, j) + \phi(i-1, j) + \phi(i, j+1) + \phi(i, j-1) - 4\phi(i, j) \quad (4.55)$$

Equation (B.5)) can alternatively be used for a more isotropic Laplacian. The difference of the two laplacian formulae is basically one of accuracy and becomes irrelevant as the numerical mesh spacing Δx becomes very small. Of course, part of the challenge of numerical modeling is to accurately simulate phase field models with as large a Δx as possible. The choice of numerical laplacian must be guided by the type of equation being modeled and the degree of error that is acceptable.

Equation (4.54) comprises an iterative mapping and, as such, is only stable for sufficiently small time steps. From Appendix (B) it can be deduced that the time step in the explicit time marching algorithm of Eq. (4.54) is limited (in 2D) by the restriction

$$\Delta \bar{t} < \frac{\Delta \bar{x}^2}{4} \quad (4.56)$$

²For simplicity $\phi((i-1)\Delta x, (j-1)\Delta y, n\Delta t)$ will simply be written as $\phi^n(i, j)$ where the latter form is actually referencing the discrete array representation of $\phi(x, y, t)$ at the discrete time step n . Moreover, since fortran does not have a symbol for ϕ , the notation "PSI" will be used in the code itself.

³Where the $\Delta \bar{x}^2$ has been omitted from Eq. (4.55) since it already appears in Eq. (4.54).

The physical interpretation of this limitation is that it is not possible to advance a solution explicitly faster than the inherent diffusion time of the problem. This is seen clearly by writing Eq. (4.56) in dimensionless form as $\Delta t < \Delta x^2 / (4W_\phi^2 / \tau)$. Because the criterion in Eq. (4.56) come from linear stability theory (i.e. it ignores the non-linear term), it is advisable to use a Δt sufficiently smaller than the prescription in Eq. (4.56) to avoid stability issues.

A basic algorithm for solving Model A numerically is shown in Fig. (4.4). There are four basic steps

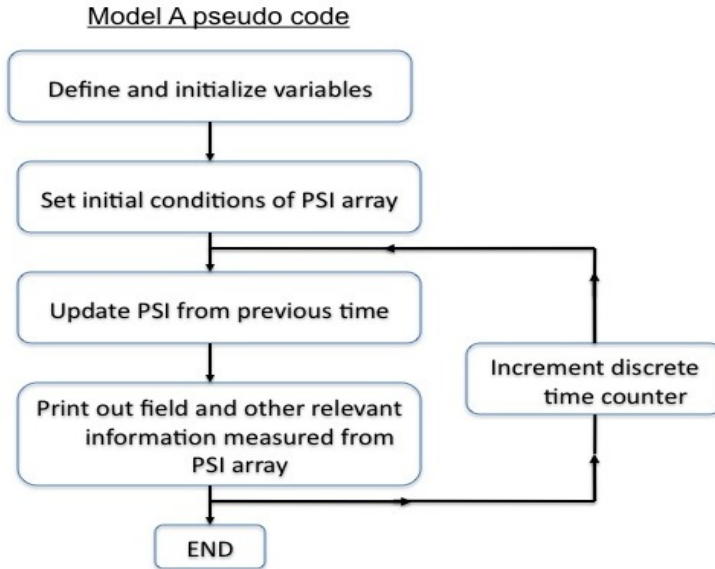


Figure 4.4: Flowchart of algorithm to simulate Model A.

in this simple code design. The first is to define all relevant variables, such as an $N \times N$ array to hold the values of the phase field (call "PSI" here), the mesh spacing (Δx , called "dx"), model parameters, etc. Parameters that change are best to be input at run time, either from the terminal or, a better practice, to have them read in from a file. After that the initial conditions are to be set on the array PSI. The third stage is to begin the "time marching" forward in time using Eq. (4.54). This involves a "do-loop" structure in each of the indices i and j of the array $\text{PSI}(i,j)$. The final stage is to print out the field PSI and any quantity calculated from it. The last two steps are embedded in a time loop that repeats this exercise as many times as needed to reach a certain point in the evolution of the ϕ (PSI) field. Note that it is wise *not* to print field configurations at every time step. As the array sizes become larger, the output files start to become huge and quickly fill up disc space. This is a trivial point that, however, nearly every first time graduate student makes when they write their first code. In general learning good data management will serve one in good stead later on.

Care must be taken in properly implementing boundary conditions in the third stage of the algorithm of Fig. (4.4). For example, if the array PSI is defined from 1 to N in each index i and j (e.g. `Real*8 :: PSI(1 : N, 1 : N)` in F90 syntax), the code will stop working properly when, at $i = N$ or $i = 1$, the code asks for the entry $\text{PSI}(N + 1, j)$ or $\text{PSI}(0, j)$ for some value of j . This will occur due to the laplacian formulae Eq. (B.5) or Eq. (B.5), which involve nearest neighbours of the point i, j . The resolution to this problem depends on the type of boundary conditions to be implemented. If periodic boundary conditions are to be

used, the system evolves as if it is on a 2D sheet wrapped around on itself. Thus, what goes out one end re-emerges on the other. The quickest and simplest way to implement periodic boundary conditions is to define the array `PSI` as `Real*8 :: PSI(0 : N + 1, 0 : N + 1)`. The physical domain on which Eq. (4.54) is defined is still `1 : N, 1 : N`. However, before each discrete time step begins, the column $i = 0$ is made a replica of the column $i = N$, the column $i = N + 1$ is made a replica of $i = 1$, and so on. In other words, the following modification is made to `PSI` before each time step commences,

$$\begin{aligned}
\text{PSI}(0, :) &= \text{PSI}(N, :) \\
\text{PSI}(N + 1, :) &= \text{PSI}(1, :) \\
\text{PSI}(:, 0) &= \text{PSI}(:, N) \\
\text{PSI}(:, N + 1) &= \text{PSI}(:, 1)
\end{aligned} \tag{4.57}$$

Conversely, if one wishes to implement zero flux boundary conditions, the following mapping is made prior to each time step,

$$\begin{aligned}
\text{PSI}(0, :) &= \text{PSI}(2, :) \\
\text{PSI}(N + 1, :) &= \text{PSI}(N - 1, :) \\
\text{PSI}(:, 0) &= \text{PSI}(:, 2) \\
\text{PSI}(:, N + 1) &= \text{PSI}(:, N - 1)
\end{aligned} \tag{4.58}$$

It is clear that where a so-called centered difference is used, Eq. (4.58) gives a zero flux at the left and right ends of the system since, for example, $\partial\phi(i, j)/\partial x \approx \text{PSI}(i + 1, j) - \text{PSI}(i - 1, j)$ and analogously for the y direction. If a specific flux is to be specified, then $2\Delta x J_{\text{BC}}$ is subtracted on the right hand side of the appropriate line of Eq. (4.58), depending on which edge the flux is coming in from. This case is discussed further in the next chapter. Note that this is not the most accurate way to implement flux boundary conditions. They will do to get started. For more advanced methods the reader is referred to more comprehensive texts on numerical modeling.

A simulation of model A is shown in Fig. (4.5). The order parameter $\phi^n(i, j)$ is evolved by simulating explicit finite difference algorithm discussed above. The domain for the simulation on the left frame is $1000 \times 1000 = 10^6$ grid points. Periodic boundary conditions were used. The field $\phi^0(i, j)$ was initially set to a gaussian distributed random variable with zero mean and a standard deviation of 0.001. In other words, $\phi^0(i, j)$ exhibits only small deviations from zero and the average $\langle \phi^0(i, j) \rangle = 0$. The right frame shows a time slice in 400×400 system. The random initial conditions of the smaller simulation were set using the same initialization seed of the random number generator used in the larger system. The free energy density of Eq. (2.38) was used for $f(\phi)$ with $a_2 = -1$, $a_4 = 1$, $W_\phi^2 = 0.25$, $\Delta t = 0.1$ and $\Delta x = 0.8$. Blue regions represents one minimum of $f(\phi)$ and brown the other.

The two frames of Fig. (4.5) appear self similar to each other, which means that the zoomed in region of the boxed portion of the left frame is a statistical replica of the larger domain. Since an initial state close to $\phi = 0$ is unstable below the transition temperature, it is equally likely that some domains will "fall into" one minimum of the double-well free energy density and some in the other. Thus, it may be expected that ϕ will evolve such that its average $\langle \phi \rangle = 0$. This is not the case in practice, however. Figure (4.6) plots $\langle \phi \rangle$ versus time for systems comprising 250×250 , 400×400 , 1000×1000 and 2000×2000 mesh points on a square grid. It is clear that for the smaller system sizes, the magnitude of $\langle \phi \rangle$ drifts, asymptotically attaining a constant value, the latter of which approaches zero very slowly with increasing system size.

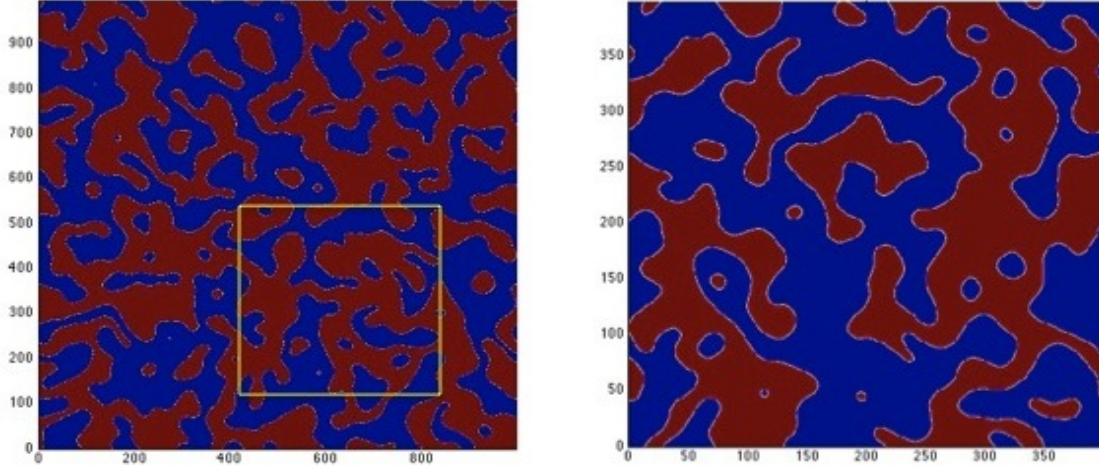


Figure 4.5: (left) Simulation of model A on a domain of size 1000×1000 . (Right) Analogous simulation of model A on a 400×400 domain (whose dimensions are indicated in yellow on the left frame, for comparison). Blue represents one minimum of the double well potential $f(\phi)$ and brown the other.

The reason for this so-called "finite-size effect" is better understood if one considers that Model A does not conserve $\langle \phi \rangle$. As a result there can be a drift as a function of time as domains try to minimize their surface area. Physically, this occurs because the selection of domain sizes is cut off for sizes greater than the size of the system. In other words, the distribution of domains that would give an average of zero is cut off due to the finite size of the simulation domain. Only in the thermodynamic limit of infinite –or at least very large– system sizes will the asymptotic average $\langle \phi^n(i, j) \rangle$ go to zero, as seen in the 2000×2000 simulation. In the case of a ferro-magnet this is why a small bias field is required to select a net magnetization.

Theoretical work by Ohta, Kawasaki and Jasnow [162] has shown that in model A the system becomes self-affine. This property is characterized by the structure factor (see Eq. (4.23) in section (4.6.1), and section (C.1) for definition), which can be shown to obey the following relation,

$$S(q, t) = t^{d/2} \mathcal{S}(qt^{1/2}) \quad (4.59)$$

where $q \equiv |\vec{q}|$ is the wave vector and $\mathcal{S}(u)$ is a *universal* function that is independent of the specific form of the free energy entering model A. These matters are beyond the scope of this book and will not be discussed further here. The interested reader is referred to the original reference cited above and references therein.

4.9.3 Model B

Numerical simulation of model B follows requires an additional step in the algorithm discussed above for model A. Specifically, a two step approach is now required in the update step in the pseudocode of Fig. (4.4). The order parameter update step becomes

$$\phi^{n+1}(i, j) = \phi^n(i, j) + \frac{\Delta \bar{t}}{\Delta \bar{x}^2} \bar{\Delta}^2 \mu^n(i, j) \quad (4.60)$$

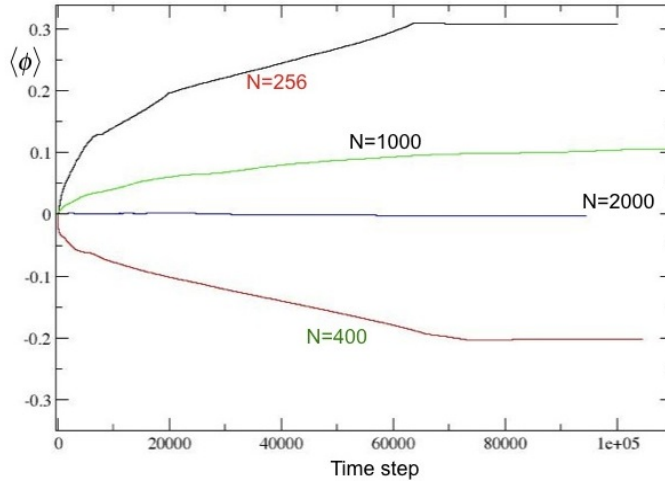


Figure 4.6: System size dependence on average of the order parameter ϕ for Model A simulations on a of 250^2 , 400^2 , 600^2 and 1000^2 grid points. Simulations were seeded with random fluctuations using the same random number seed. The 600^2 and 1000^2 cases were run a little longer to show a clearer saturation to a smaller value than the other two systems.

where an additional step (i.e. do-loop) must be added, prior to updating $\phi^{n+1}(i, j)$, which evaluates the array $\mu^n(i, j)$ (MU(i,j) in fortran syntax) for the n^{th} time step representation of the discrete chemical potential. The array for $\mu^n(i, j)$ is explicitly computed by

$$\mu^n(i, j) = -\frac{\bar{\Delta}^2 \phi^n(i, j)}{\Delta \bar{x}^2} + \frac{\partial f(\phi^n(i, j))}{\partial \phi} \quad (4.61)$$

As with model A the mapping in Eq. (4.60) is only stable below a threshold time step. In two dimensions, the the restriction on the time step is given by

$$\Delta \bar{t} < \frac{\Delta \bar{x}^4}{32} \quad (4.62)$$

This is more severe than the case of model A due to the Δx^4 . The reason, as shown in Appendix (B), is that the extra Δx^2 emerges is due to the extra laplacian in the conservation law of model B. Equations (4.60) and (4.61) can be integrated effectively with the numerical Laplacian in Equation (B.5)) (or using finite volumes, discussed in Section (B.2)). Both methods will yield $\langle \phi(\vec{x}, t) \rangle = 0$, withing machine precision, for all times, if $\langle \phi(\vec{x}, t = 0) \rangle = 0$.

Chapter 5

Introduction to Phase Field Modeling: Solidification of Pure Materials

This chapter extends the basic phenomenology of phase field theory into a more formal methodology for modeling isothermal and non-isothermal solidification in pure materials. Solidification serves as an important paradigm for many first order phase transitions and is the principal phenomenon describing the first stage of nearly all microstructure formation in metals. Solidification is also one of the most extensively studied topics using phase field methodology in the scientific literature. In pure materials, solidification proceeds through the competition between thermodynamics –driven by the local undercooling of the liquid ahead of the solidification front– and the ability of the system to diffuse latent heat of fusion (solidification is an exothermic reaction) away from the solid-liquid interface. Capturing the physics of this phenomenon thus requires combining an equation that describes the change of order to one that describes the diffusive processes accompanying solidification, such as in heat conduction in this case. The chapter starts off by introducing the concept of order parameters in crystal phases. Following this, the phenomenology of a phase field model for solidification of a pure material is derived.

5.1 Solid order parameters

Figure (5.1) shows a schematic of a cut through a hypothetical solid in co-existence with its liquid. The oscillating curve denotes the time-averaged atomic number density. This is the field that an atomic force microscope might reveal if imaging a hypothetical 1D solid. The decay to a constant density in the liquid occurs over a correlation length W_ϕ , which is atomically diffuse in most metals. The atomic number density can be seen as a temporal or ensemble average ¹ of the instantaneous solid density, $\rho(\vec{x}, t)$, i.e.

¹This assumption assumes that the system is *ergodic*. This implies that averaging a quantity in time as the system traces a trajectory in its phase space –of co-ordinates and momenta– is equivalent to averaging the same quantity over the system’s equilibrium distribution [146]. This assumption usually satisfied by most systems in the thermodynamic limit but it is not always for low dimensional dynamical systems.

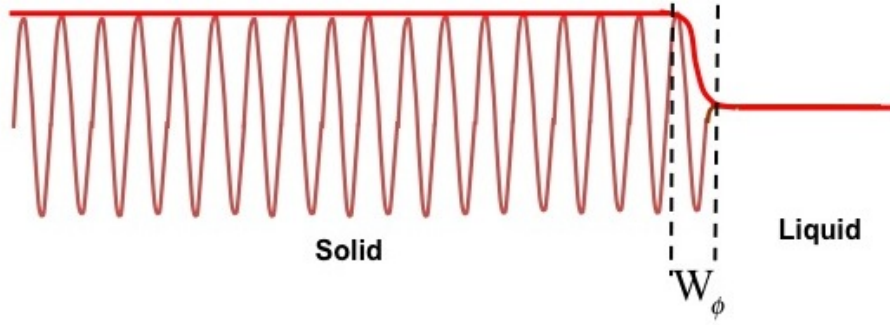


Figure 5.1: Schematic of the atomic density field of a 1D cut through a solid (oscillating line) in coexistence with liquid (constant). The decay of oscillating density to a constant occurs over a length scale W_ϕ

$\langle \rho(\vec{x}, t) \rangle_{\text{time}} = \langle \rho(\vec{x}, t) \rangle_{\text{ensemble}}$. The instantaneous density itself is given by the expression.

$$\rho(\vec{x}, t) = \sum_{n=1}^N \delta(\vec{x} - \vec{x}_n(t)) \quad (5.1)$$

where $\delta(\vec{x})$ is the Dirac delta function, N is the number of particles in the solid and $\vec{x}_n(t)$ denotes the position of the n^{th} particle. The delta function has units of V^{-1} , where V is the volume of the system.

Any density field can be equivalently represented by discrete Fourier transform of $\rho(\vec{x}, t)$,

$$\rho(\vec{x}, t) = \sum_{\vec{G}} \hat{\rho}_{\vec{G}}(t) e^{-i\vec{G}\cdot\vec{x}} + c.c. \quad (5.2)$$

where \vec{G} defines the principle reciprocal lattice vectors of the solid and *c.c.* the complex conjugate². The Fourier transform $\hat{\rho}_{\vec{G}}$ can be obtained by multiplying Eq. (5.2) by $e^{i\vec{G}\cdot\vec{x}}$ and integrating over the volume of the solid,

$$\hat{\rho}_{\vec{G}} = \int \rho(\vec{x}, t) e^{i\vec{G}\cdot\vec{x}} dV \quad (5.3)$$

(where the time label has been suppressed for simplicity). Substituting Eq. (5.1) into Eq. (5.3) gives $\hat{\rho}_{\vec{G}}$ in the form,

$$\hat{\rho}_{\vec{G}} = \frac{\bar{\rho}}{N} \sum_{n=1}^N e^{i\vec{G}\cdot\vec{x}_n(t)} \quad (5.4)$$

where $\bar{\rho}$ is the average atomic number density. Substituting Eq. (5.4) into Eq. (5.2) gives an alternate form for the density field,

$$\rho(\vec{x}, t) = \frac{\bar{\rho}}{N} \sum_{\vec{G}} \left(\sum_{n=1}^N e^{i\vec{G}\cdot\vec{x}_n(t)} \right) e^{-i\vec{G}\cdot\vec{x}} \quad (5.5)$$

The phase factors (complex exponential terms) in the round brackets of Eq. (5.5) are called *structure factors*. These are intimately connected to the solid's crystallography and its order parameters.

²To simplify the math, the complex conjugate will be assumed but not dealt with explicitly in the derivation below

This significance of the structure factors in Eq. (5.5) can be made more concrete by using Eq. (5.5) in the definition of the time-averaged density,

$$\langle \rho(\vec{x}, t) \rangle_{\text{time}} = \langle \rho(\vec{x}, t) \rangle_{\text{ensemble}} = \frac{\bar{\rho}}{N} \sum_{\vec{G}} \underbrace{\left\langle \sum_{n=1}^N e^{i\vec{G} \cdot \vec{x}_n(t)} \right\rangle}_{\phi_{\vec{G}}} e^{-i\vec{G} \cdot \vec{x}} \quad (5.6)$$

The quantities $\phi_{\vec{G}}$ define the order parameters of the solid –one for each reciprocal lattice vector \vec{G} . In the solid, the dot product $\vec{G} \cdot \vec{x}_n(t)$ will take on multiples of the same values along given directions and so the average will collect non-zero contributions from all n , since atoms are situated near ideal crystallographic positions; this is like constructive interference. In the liquid the phases $\vec{G} \cdot \vec{x}_n(t)$ will vary randomly and the phase factors will thus destructively interfere to make the ensemble average of structure factors zero. As an example, consider a one dimensional solid, i.e.

$$\langle e^{i\vec{G} \cdot \vec{x}_n} \rangle \equiv \left\langle \cos \left(\frac{2m\pi}{a} (n + \xi)a \right) \right\rangle + i \left\langle \sin \left(\frac{2m\pi}{a} (n + \xi)a \right) \right\rangle \quad (5.7)$$

where $\vec{G} = 2\pi m/a$ are the 1D reciprocal lattice vectors (m is an integer), a is the lattice constant and $x_n = (n + \xi)a$, with n being some integer associated with the n^{th} atom in the crystal. The variable ξ represents a Gaussian random number with zero mean. It represents a source of noise causing atom n to randomly vibrate about the position $x = na$ due to temperature fluctuations. Splitting up the sin and cos functions, noting that $\langle \sin(2\pi m\xi) \rangle = 0$ and $\langle \cos(2\pi m\xi) \rangle = 1$ since $\langle \xi \rangle = 0$, and noting that $\sin(2\pi mn) = 0$ and $\cos(2\pi mn) = 1$ gives,

$$\begin{aligned} \langle e^{i\vec{G} \cdot \vec{x}_n} \rangle &\equiv \cos(2\pi mn) \langle \cos(2\pi m\xi) \rangle + \sin(2\pi mn) \langle \sin(2\pi m\xi) \rangle \\ &+ i \cos(2\pi mn) \langle \sin(2\pi m\xi) \rangle + \sin(2\pi mn) \langle \cos(2\pi m\xi) \rangle \\ &= 1 \end{aligned} \quad (5.8)$$

In the liquid, the position x_n will itself be an uncorrelated random variable, unlike in the solid where it is always near a lattice position. As a result $\langle e^{i\vec{G} \cdot \vec{x}_n} \rangle = 0$ in the liquid. As a result, the parameter $\phi_{\vec{G}} \equiv \langle \hat{\rho}_{\vec{G}} \rangle = \langle \sum_n e^{i\vec{G} \cdot \vec{x}_n} \rangle$ is a constant in the solid ($\phi_{\vec{G}} \sim N$, since there are N atoms in its sum) and decays to zero in the liquid. Its behaviour is illustrated schematically in Fig. (5.2). It is noted that the $\vec{G} = 0$ is treated separately in the outer sum of Eq. (5.6). It merely adds a constant N to the sum, since the phase factors $e^{i\vec{G} \cdot \vec{x}_n}$ are always zero for the $\vec{G} = 0$ mode.

Taking the above considerations into account, the ensemble or time averaged atomic number density field in Eq. (5.6) can be written in terms of $\phi_{\vec{G}}$ as

$$\langle \rho(\vec{x}, t) \rangle = \bar{\rho} \left(1 + \frac{1}{N} \sum_{\vec{G} \neq 0} \phi_{\vec{G}} e^{-i\vec{G} \cdot \vec{x}} \right) \quad (5.9)$$

In general the average density $\bar{\rho}$ in changes from solid to liquid. The association of this quantity with the symbol $\phi_{\vec{G}}$ is intentionally made to associate it with the order parameter of Ginzburg-Landau theory studied in previous chapters. In the examples examined thus far, only one real order parameter was considered. The above derivation shows that, in fact, multiple complex order parameters are required

$$\phi_{\vec{G}} = \left\langle \sum_{n=1}^N e^{i\vec{G} \cdot \vec{x}_n(t)} \right\rangle$$

Figure 5.2: Schematic of solid order parameter corresponding to a reciprocal lattice vector \vec{G} .

to describe a solid completely, due crystallographic properties of crystals. The density in Eq. (5.9) represents the course-grained density field, where spatio-temporal variations on phonon time scales have been "washed" out by the averaging process. The order parameters $\phi_{\vec{G}}$ thus vary over length scales that are long compared to the solid liquid interface width, and change on long time scales compared to those involved in lattice vibrations. This density can loosely speaking be considered as a pseudo-equilibrium density on mesoscopic time scales.

5.2 Free Energy Functional for Solidification

Statistical thermodynamics provides a formalism called *classical density functional theory* through which a free energy functional for solidification can be developed in terms of $\langle \rho(\vec{x}, t) \rangle$ [177, 71, 111]. The basic idea is that the free energy expanded in an infinite *functional* series of the form,

$$F[\langle \rho(\vec{x}) \rangle, T] = F_{\text{ref}}[\bar{\rho}] + F_{\text{loc}}(\rho) + \int_V \langle \rho(\vec{x}) \rangle C^{(2)}(|\vec{x} - \vec{x}'|) \langle \rho(\vec{x}') \rangle + \dots \quad (5.10)$$

where $F_{\text{ref}}[\bar{\rho}]$ is the reference free energy of a liquid or gas phase with average density $\bar{\rho}$ and evaluated at solid-liquid coexistence. The free energy $F_{\text{loc}}(\rho)$ is a local function of the density, while the function $C^{(2)}(|\vec{x} - \vec{x}'|)$ is the so-called two-point direct correlation function [111]. Loosely speaking, this function represents a statistical averaging of all two-body interactions in the system. Equation (5.10) is a truncated density functional, cut off at second order. By specializing $C^{(2)}$, various atomic scale phase field theories of crystallization can be obtained. For example, the form $C^{(2)} = a + b\nabla^2\delta(\vec{x} - \vec{x}') + \nabla^4\delta(\vec{x} - \vec{x}')$ gives rise to a so-called *phase field crystal* (PFC) model developed by Elder and co-workers [65]. This is a phase field model whose order parameter varies of atomic scales, and can self-consistently model elasticity and plastic properties of solids. Phase field crystal theory will be the focus of chapters (8) and (9.1).

It is possible to homogenize or "course-grain" the free energy of Eq. (5.10) into an effective free energy that is valid on scales much larger than a single atom but still small enough to resolve metallurgically relevant microstructures. Loosely speaking, course graining proceeds by assuming density can be described by Eq. (5.9), which is then substituted into Eq. (5.10). It is then assumed that the order parameters $\phi_{\vec{G}}$ vary on long length scales compared to the periodic variation of $e^{i\vec{G} \cdot \vec{x}}$. This makes it possible to reduce, or "course grain" the free energy in Eq. (5.10) into a new form that depends only on the complex order

parameters $\phi_{\vec{G}}$. This coarse-graining procedure is denoted symbolically as

$$F[\langle\rho(\vec{x})\rangle, T] \rightarrow \tilde{F}[\{\phi_{\vec{G}}\}, T] \quad (5.11)$$

A more detailed discussion of the properties of $\tilde{F}[\{\phi_{\vec{G}}\}, T]$ will be given in chapter 8. The basic idea for now is that $\tilde{F}[\{\phi_{\vec{G}}\}, T]$ can be seen as a type of Ginzburg-Landau free energy functional, defined in terms of multiple *complex* order parameters. It turns out that the ability to express the free energy functional in terms of as many complex order parameters makes it possible to self-consistently include all elastic and plastic effects in the description of microstructure evolution (i.e. strain, dislocations and grain boundaries).

In solidification, which occurs at high temperatures in metals, elasto-plastic effects are often negligible. In this case, the simplest description of the solid is in terms of single *real* order parameter, ϕ , which has an analogous meaning to the order parameters discussed in the previous chapters. Assuming that the complex order parameters $\phi_{\vec{G}}$ are all real, and equivalent, further reduces $\tilde{F}[\{\phi_{\vec{G}}\}, T]$ to depend only on ϕ . This symbolically represented by

$$\tilde{F}[\{\phi_{\vec{G}}\}, T] \rightarrow \hat{F}[\phi, T] \quad (5.12)$$

The remainder of this chapter will consider the construction of a single order parameter model $\hat{F}[\phi, T]$ for the specific example of solidification of a pure material ³.

5.3 Single Order Parameter Theory of Solidification

As discussed above, the simplest description of solidification of a single crystal of pure material, it is reasonable to assume that all \vec{G} 's are the same, in which case the free energy in Eq. (5.11) becomes a single order parameter theory. This simplification precludes the study of grain boundary interactions and elastic and plastic effects. While the latter are not so important during solidification where temperatures are relatively close to the melting temperature, the former are crucial for the study of polycrystalline solidification. Nevertheless, a single order parameter theory is the first step for understanding the details of dendritic solidification, the precursor to grain boundary interactions and solid state reactions. It also provides a valuable pedagogical tool from which to build up more complex phase field models.

The simplest free energy functional for solidification for a pure materials is the familiar form

$$F[\phi, T] = \int_V \left\{ \frac{1}{2} \epsilon_\phi |\nabla\phi|^2 + f(\phi(\vec{x}), T) \right\} d^3\vec{x} \quad (5.13)$$

where T is the temperature, considered in this section as constant and ϵ_ϕ is the gradient energy coefficient setting the scale of the surface tension ⁴. The hat above \hat{F} has been dropped for simplicity. The gradient energy term has the same interpretation as in previous examples, describing the energy density across the interface defined by the order parameter. The magnitude of the surface energy scales with the energy density ϵ_ϕ . This coefficient will be shown below to be related to scale of the interface width (hereafter denoted W_ϕ in solidification models) and nucleation barrier (denoted H hereafter) according

³The formalism developed thus far has treated ϕ as fundamental parameter. In going forward it will sometimes be convenient to relax this assumption and treat ϕ as a phenomenological parameter that merely serves to modulate the free energy functional between two phases [137]. This freedom will make it easier to “manually” construct phase field models that emulate well-known sharp interface kinetics of microstructure evolution.

⁴The symbol ϵ will be reserved hereafter to denote a small parameter, and ϵ_ϕ will be associated with the gradient energy coefficient of the ϕ -field

to $\epsilon_\phi = \sqrt{HW}\phi$. In solidification the order parameter is usually taken to be zero in the liquid phase and finite in the solid, since it is a true order parameter in this phenomenon and should reflect the vanishing of any crystallographic order in the liquid.⁵

The bulk free energy $f(\phi, T)$ for solidification is postulated, once again, by invoking Eq. (2.37) up to fourth order in ϕ and first order in $T - T_m$ where T_m is the melting point at a given average density,

$$f(\phi, T) = f_L(T) + r(T)\phi^2 + w(T)\phi^3 + u(T)\phi^4 \quad (5.14)$$

The first order term has been dropped since it would be not possible to have $\phi_{\text{liquid}} = 0$ otherwise.

To proceed, the coefficients $r(T)$, $w(T)$, $u(T)$ and $f_L(T)$ are expanded to linear order in temperature, around T_m . This gives

$$\begin{aligned} f(\phi, T) = & f_L(T_m) + \left. \frac{df_L}{dT} \right|_{T_m} (T - T_m) \\ & + r(T_m)\phi^2 + w(T_m)\phi^3 + u(T_m)\phi^4 + (B_2 + B_3\phi + B_4\phi^2)\phi^2(T - T_m) \end{aligned} \quad (5.15)$$

where B_2 , B_3 and B_4 are the first derivatives of $r(T)$, $w(T)$ and $u(T)$, respectively, evaluated at $T = T_m$. The coefficients $r(T_m)$, $w(T_m)$ and $u(T_m)$ can be inter-related by demanding that at $T = T_m$ the resulting polynomial in ϕ has two stable minima, with equal free energies and an activation energy barrier separating these two states. This is accomplished by setting $r(T_m) = u(T_m) = H(T_m)$ and $w(T_m) = -2H(T_m)$, where $H(T_m)$ is a constant that depends on the melting temperature. With these choices the bulk free energy of the pure material reduces to,

$$f(\phi, T) = f_L(T_m) - S_L(T - T_m) + H\phi^2(1 - \phi)^2 + (B_2 + B_3\phi + B_4\phi^2)\phi^2(T - T_m) \quad (5.16)$$

where $S_L \equiv -df_L/dT|_{T_m}$ is the bulk entropy density of the liquid phase. The polynomial $g(\phi) = \phi^2(1 - \phi)^2$ can easily be seen to be a humped function with minima at $\phi = 0$ and $\phi = 1$, and symmetric around $\phi = 1/2$. The constant H controls the height of an energy hump that forms an activation barrier between the two phases at the melting temperature. The characteristic form of this function often leads it being called a "double-well" potential. It turns out that any function featuring the same double-well structure can also be used for $g(\phi)$.

The polynomial in ϕ multiplying the $T - T_m$ term must be chosen such that it interchanges the stability of the two stable states of $f(\phi, T)$ relative to each other above or below the melting temperature T_m . Specifically, the solid state should have a higher free energy than the liquid above T_m and a lower free energy than the liquid below T_m . These considerations are satisfied by setting

$$B_2 = 3\frac{L}{T_m}, \quad B_3 = -2\frac{L}{T_m}, \quad B_4 = 0 \quad (5.17)$$

where L is the latent heat of fusion. This choice of constants makes the free energy

$$f(\phi, T) = f_L(T_m) + H\phi^2(1 - \phi)^2 - S(\phi)(T - T_m) \quad (5.18)$$

where

$$S(\phi) = S_L - \frac{L}{T_m}(3 - 2\phi)\phi^2 \quad (5.19)$$

⁵The models derived as examples here can easily be modified to allow the order parameter to interpolate between other values in the solid and liquid. For example, many popular models in the literature scale ϕ from -1 to 1 in the liquid and solid, respectively.

The form of the bulk free energy $f(\phi, T)$ is particularly convenient in that the stable states of the order parameter –determined by $\partial f(\phi, T)/\partial\phi = 0$ – are given by $\phi_s = 1$ and $\phi_L = 0$. Moreover, it takes on the limits $S(\phi = 0) = S_L$ and $S(\phi = 1) = S_L - L/T_m$. Figure (5.3) shows a plot of $\Delta f \equiv f(\phi, T) - f_L(T)$.

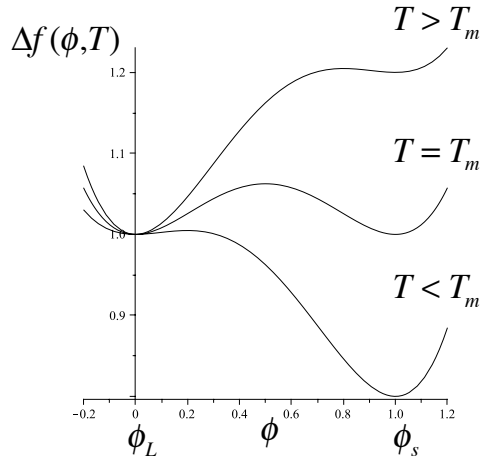


Figure 5.3: Free energy in Eq. (5.18) above, below and at the melting temperature. Energy is plotted relative the liquid free energy $f_L(T) \equiv f(\phi = 0, T)$.

5.4 Solidification Dynamics

5.4.1 Isothermal solidification: model A dynamics

Following the hypothesis of dissipative dynamics and the fact that the order parameter in solidification is a non-conserved quantity (i.e. an undercooled liquid can all crystalize), the simplest equation for the evolution of the order parameter is constructed by considering the variational of Eq. (5.13) as a driving force for the phase transformation, i.e.

$$\begin{aligned} \tau \frac{\partial \phi}{\partial t} &= -\frac{1}{H} \frac{\delta F[\phi, T]}{\delta \phi} + \eta'(\vec{x}, t) \\ &= W_\phi^2 \nabla^2 \phi - \frac{dg(\phi)}{d\phi} - \frac{L(T - T_m)}{HT_m} \frac{dP(\phi)}{d\phi} + \eta'(\vec{x}, t) \end{aligned} \quad (5.20)$$

where the parameters $\tau = 1/HM$ and $W_\phi = \epsilon_\phi/\sqrt{H}$ have been defined. The functions $g(\phi) = \phi^2(1 - \phi)^2$ and $P(\phi) = (3 - 2\phi)\phi^2$. Meanwhile, $\eta' = \eta/(MH)$, where η is a stochastic noise term that emulates the effect of thermal fluctuations. The statistics of ξ satisfy the fluctuation-dissipation theorem in Eq. (4.19).

This model can simulate the growth of isothermally growth crystals. The initial conditions can be a liquid phase ($\phi = 0$) seeded with a crystal of solid ($\phi = 1$) and the temperature $T < T_m$.

Equation (5.20) is similar in form as Model A studied in section (4.4). An important difference in this case, however, is that the free energy has been constructed to be asymmetrical, with the minima in the solid and liquid energies switching relative to one another at the melting temperature T_m . The tilting in this way is demanded by thermodynamics and is represented by the function $P(\phi)$, which is odd in ϕ . This is to be contrasted with the case studied previously where the free energy was symmetrical with respect to the two phases since the transition from one state (above T_c) to two (below T_c) occurred via the second order term in ϕ .

5.4.2 Anisotropy

In its current form, the phase field model in Eq. (5.20) cannot simulate anisotropic growth forms, such as dendrites. One of the most significant contributions to solidification that came out the late 1980's and 1990's was the so-called analytical theory of solvability (see section (5.8.1)), where the Stefan problem of Eq. (1.1) was solved analytically and numerically, demonstrating that dendrites can only grow along specific crystallographic directions if surface tension is anisotropic. In fact an isotropic surface tension can only lead to isotropic structures. This was later quantitatively demonstrated with phase field models [113, 170], which introduced anisotropy into surface energy by making the gradient energy coefficient W_ϕ and interface attachment kinetics time τ functions of the angle of the local interface normal \hat{n} . Specifically, the gradient energy term in the free energy functional and kinetic attachment time in the phase field dynamics become

$$\begin{aligned} \frac{1}{2}W_\phi^2|\nabla\phi|^2 &\rightarrow (1/2)|\tilde{W}(\theta)\nabla\phi|^2 \\ \tau &\rightarrow \tilde{\tau}(\theta) \end{aligned} \quad (5.21)$$

where

$$\theta \equiv \arctan\left(\frac{\partial\phi/\partial y}{\partial\phi/\partial x}\right) \quad (5.22)$$

defined the angle between the direction normal to the interface and a reference axis. With these definitions, the *anisotropic* phase field equation becomes

$$\begin{aligned} \tilde{\tau}(\theta)\frac{\partial\phi}{\partial t} &= -\frac{\delta F[\phi, T]}{\delta\phi} + \eta'(\vec{x}, t) \\ &= \nabla \cdot \left(\tilde{W}^2(\theta)\nabla\phi \right) - \partial_x \left[\tilde{W}(\theta)\tilde{W}'(\theta)\partial_y\phi \right] + \partial_y \left[\tilde{W}(\theta)\tilde{W}'(\theta)\partial_x\phi \right] \\ &\quad - \frac{dg(\phi)}{d\phi} - \frac{L(T - T_m)}{HT_m} \frac{dP(\phi)}{d\phi} + \eta'(\vec{x}, t) \end{aligned} \quad (5.23)$$

where $\tilde{W}'(\theta)$ denotes the derivative of $\tilde{W}(\theta)$ with respect to θ . A convenient choice for the describing the anisotropy is

$$\begin{aligned} \tilde{W}(\theta) &= W_\phi A(\theta) \\ \tilde{\tau}(\theta) &= \tau A^2(\theta) \end{aligned} \quad (5.24)$$

where the function $A(\theta)$ modulates the anisotropy of the interface width and interface kinetics time. A convenient form that is often used in the literature for square symmetry is

$$A(\theta) = 1 + \epsilon_4 \cos(4\theta) \quad (5.25)$$

where ϵ_4 describes the degree of anisotropy of the surface tension (or surface energy), with $\epsilon_4 = 0$ corresponding to the isotropic situation, defined by the length scales W_ϕ and time scales τ . The reason for the particular relationship between $\tilde{W}(\theta)$ and $\tilde{\tau}(\theta)$ is required to be able to model zero interface kinetics in the limit of a diffuse interface. This will become clear below.

5.4.3 Non-isothermal solidification: model C dynamics

In most cases of practical interest treating temperature isothermally –or even uniformly– is not a good approximation. Model A dynamics of section (5.4.1) can be augmented to consider non-isothermal temperature evolution by allowing the constant temperature $T \rightarrow T(\vec{x}, t)$, where t is time and \vec{x} is a position vector. The temperature evolves such that the flux of heat into a volume element lead to a corresponding change of entropy. This is expressed in the form of an entropy production equation [43, 18]

$$T \frac{\partial S}{\partial t} + \nabla \cdot \vec{J}_e = 0 \quad (5.26)$$

where \vec{J}_e is the entropy flux. If mass transport and convection are neglected $\vec{J}_e \approx \vec{J}_0$ in Eq. (4.3). Moreover, Eq. (5.26) becomes the same as Eq. (4.7) with the substitution

$$TdS = dQ = dH_p \quad (5.27)$$

where dH_p denotes the enthalpy at constant pressure. The enthalpy can be written in terms of the order parameter as

$$H_p = \rho c_p T - \rho L h(\phi) \quad (5.28)$$

where c_p is the specific heat at constant pressure and L is the latent heat of fusion for the liquid solid reaction. The function $h(\phi)$ assumed to be some smooth function with limits $h(0) = 0$ and $h(1) = 1$. It has been added to describe the generation of excess heat production if solid ($\phi = 1$) phase appears. In the liquid, where $\phi = 0$, the enthalpy is due only to temperature changes. In the solid, where $\phi = 1$, the enthalpy is reduced due to latent heat. The variation of $h(\phi)$ for $0 < \phi < 1$ corresponds to the solid-liquid interface. Substituting Eq. (5.28) into Eq. (5.27), TdS into Eq. (5.26) and making the replacement $\vec{J}_e \rightarrow \vec{J}_0$ gives

$$\rho c_p \frac{\partial T}{\partial t} - \rho L h'(\phi) \frac{\partial \phi}{\partial t} = -\nabla \cdot \vec{J}_0 \quad (5.29)$$

(where $h' \equiv dh/d\phi$). If convection effects are ignored the heat flux is $\vec{J}_0 = -k\nabla T$, where k is the thermal conductivity of the material and has the form of Eq. (4.8). This leads to Fourier's law of heat conduction, modified for changes of phase through the order parameter ϕ . The conductivity can be made a function of the phase by expressing it as $k = k_L q(\phi)$, where $q(\phi)$ is an unknown function that interpolates the conductivity across the solid-liquid interface.

Combining Eq. (5.29) with Eq. (5.23) gives a system of two coupled partial differential equations for the evolution of the order parameter (ϕ) and the temperature (T),

$$\tau A^2(\theta) \frac{\partial \phi}{\partial t} = W_\phi^2 \nabla \cdot (A^2(\theta) \nabla \phi) - \partial_x W_\phi^2 [A(\theta) A'(\theta) \partial_y \phi] + W_\phi^2 \partial_y [A(\theta) A'(\theta) \partial_x \phi]$$

$$\frac{\partial T}{\partial t} = \nabla \cdot \left(\alpha(\phi) \nabla T \right) + \frac{L(T - T_m)}{HT_m} \frac{dg(\phi)}{d\phi} - \frac{Lh'(\phi)}{c_p} \frac{\partial \phi}{\partial t} \quad (5.30)$$

where $\alpha \equiv k/\rho C_p$ is the thermal diffusion coefficient and $h'(\phi)$ denotes the derivative of $h(\phi)$ with respect to ϕ . As shown in section 5.6 this model can be recast in a form known as “Model C” [92]. We will for simplicity, therefore, refer to it as “model C” below. Many of the relevant physics of solidification of pure materials can be well described without too much error if the thermal diffusion coefficient α is made a constant. As will be discussed in future sections, this simplification also greatly simplifies the efficiency with which model C may be simulated so as to capture the kinetics of the sharp interface model in Eqs. (1.1). Furthermore, as with the ϕ equation there should strictly also be thermal noise sources added to the heat flux, i.e. $\vec{J}_e \rightarrow \vec{J}_e + \xi_e$. Its statistics must satisfy the fluctuation-dissipation theorem as well. Generally, thermal fluctuations are very important near a critical point, where interfaces become diffuse. For first order transformations such as solidification, the noise plays a major role during nucleation and the formation of side-branches [114] but does not strongly influence the stability near the dendrite tip region. The effects of stochastic noise have been examined in detail by Elder and co-workers [63] and Sekerka and co-workers [164, 165].

An early, isotropic, variant of the model C for solidification described above was used by Collins and Levine [51] and studied in detail by Caginalp [35]. The specific model of Eqs. (5.30) is the same as models developed by Sekerka and co-workers in the early 90’s [150, 15, 200, 199]. It is more thermodynamically consistent than the older models in its formulation but contains the same physics. In all cases the basic ingredients required are an order parameter –or phase field– equation that effectuates phase changes (solidification or melting) driven –via temperature– by a relative tilting of the solid and liquid free energy wells.

Comparing the various models in the literature to Eq. (5.20) one immediately notices differences in the specific form of the functions $g(\phi)$ and $P(\phi)$. These functions are known as interpolation functions since they interpolate between bulk thermodynamic values of the free energy of the solid ($\phi = 1$) and liquid ($\phi = 0$). Their form at intermediate values of the order parameter ($0 < \phi < 1$) captures the fundamental properties the boundary layer structure of the solid-liquid interface. In principle they can be deduced from first principles using classical density functional theory or molecular dynamics, or even fit using data from electron microscopy. To date there has not been much work to derive the precise form of these functions. Indeed, as will be discussed in the next section, inasmuch as the phase field model can be considered a “tool” for emulating sharp interface kinetics (e.g. Eqs. (1.1)), the precise form of these interpolation functions is immaterial.

5.5 Sharp and Thin Interface Limits of Phase Field Models

One of the most subtle but important issues regarding the use of phase field models in quantitative simulations of microstructure phenomena is the ability of models such as that described by Eqs. (5.30) to properly emulate the kinetics of the sharp-interface model described by Eqs. (1.1), at least in the limit where the interface can be considered sharp, that is, its presence neglected. In solidification, this occurs when the undercooling or cooling rates are sufficiently low that the interface can be assumed to be negligible compared to the other length scales (e.g. diffusion length, radius of curvature of a dendrite, etc.). In this limit it is also reasonable to assume that the interface is in local equilibrium, corrected for

by curvature effect described by the so-called Gibbs-Thomson conditions [167].

Two approaches for this have evolved through the years for choosing the interpolation functions and parameters of model C in Eqs. (5.30). The first is to operate in the limit where the interface width of the phase field equation becomes vanishingly small, i.e. $W_\phi \rightarrow 0$ or in physical terms $W_\phi \ll d_o$ (here d_o is the thermal capillary length). This known as the *sharp-interface limit* was pioneered by Caginalp and co-workers in the late 80's and early nineties [36, 37, 38]. The second approach recognizes that the interface width should disappear from the problem so long as it is much smaller than the diffusion length, i.e., $W_\phi \ll \alpha/v$, where v_s is a characteristic interface speed. This makes it possible for equations (5.30) to emulate the sharp interface model of Eqs. (1.1) even when W_ϕ/d_o is on the order unity. This is referred to as the *thin interface limit* and was recently introduced by Karma and co-workers [113, 112, 57, 74] by modifying a second order thin interface analysis introduced by Almgren [8].

The idea of mapping phase field models onto effective sharp interface models –known as asymptotic analysis– is illustrated in Figure (5.4). The figure shows a snapshot in time of the phase field $\phi(x)$ and reduced temperature $U \equiv c_p(T-T_m)/L$ across the interface of a solidifying front. The dashed lines are the projections of the phase field solutions onto those of the equivalent sharp interface model. When $W_\phi \neq 0$

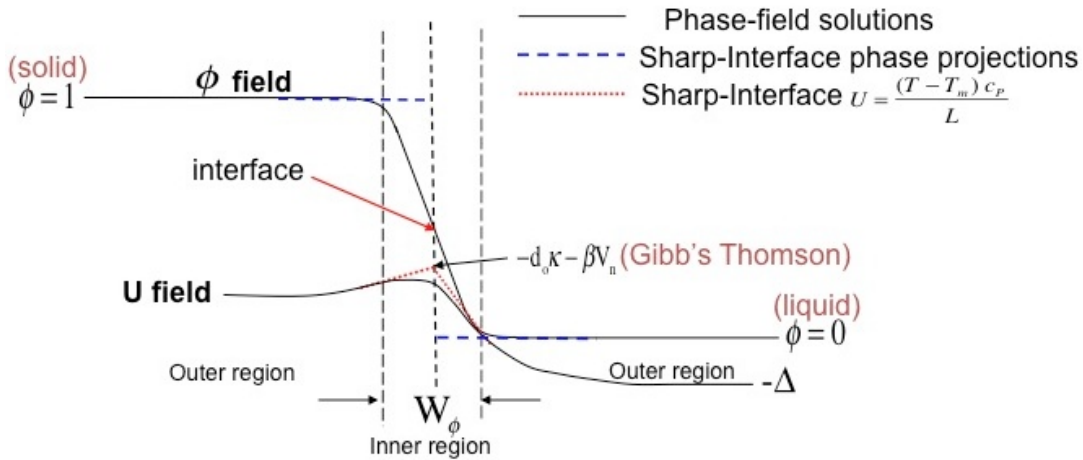


Figure 5.4: Schematic of the order parameter, reduced temperature fields and their projections to a sharp interface. Diffuse or "thin-interface" solutions of the phase field model become equivalent to the corresponding sharp-interface solutions when projected onto a sharp interface (denoted by the dashed lines) from the outside the interface region, of width W_o .

the phase field model must be constructed such that the local velocity and values of temperature (or concentrations in the case of alloys), when projected onto a hypothetical sharp interface, are equivalent to the corresponding values obtained if the precise sharp interface model itself was used. Thus, in the limit $\epsilon \equiv W_\phi/(\alpha/v_s) \ll 1$, $W_\phi \sim d_o$ and α/v_s large, the model should thus yield the same results as when $W_\phi \ll d_o$ and α/v_s small, i.e., the sharp interface limit.

The difference between the sharp and thin interface limits of a phase field model is extremely significant as far as numerical efficiency is concerned. The sharp interface limit is impractical to simulate numerically, since the grid resolution and time scale of the phase field model are both scaled with the width of the interface, simulating a phase field model in the sharp interface limit is completely impractical with current

computing. In contrast, the use of thin interface (i.e. small compared to the scale of microstructure but still comparable to or larger than the capillary length) allows the time scale of simulations to be accelerated dramatically. When combined with efficient adaptive mesh refinement algorithms [170], phase field simulations of microstructure formation can now be conducted in reasonable times.

In practice, the mathematics of extracting a sharp interface model from the phase field equations is rather messy and complex. The basic idea is to rescale the equations in two ways. The first scales the phase field equations such that space is scaled by a diffusion length, which controls patterns that occur on scales much greater than W_o . It is then assumed that the solutions of the phase field equations in the *outer region* can be expanded in an infinite series in a small parameter, ϵ , e.g. $\phi = \phi_0 + \epsilon\phi_1 + \epsilon^2\phi_2 + \dots$ and $U = U_0 + \epsilon U_1 + \epsilon^2 U_2 + \dots$. This solution ansatz is substituted into the phase field equations and terms of similar order of ϵ are grouped into distinct equations. A similar exercise is done when the phase field equations are re-scaled so that space is scaled by the interface width W_o . The final –and messiest– part of the procedure is to match the inner and outer solutions so that they overlap at approximately the scale of the boundary layer introduced by the phase field ϕ . A procedure of a formal matched asymptotic analysis of a generic version of Model C is shown in detail in Appendix (A). The next section discusses the results of that analysis for the special case of the Model C in Eqs. (5.30) for a pure materials, which was developed in this chapter.

5.6 Case Study: Thin interface analysis of Equations (5.30)

This section works through a concrete example that illustrates the details of selecting the parameters of model C such that it operates in the thin interface limit. Specifically, it summarizes the relation between the parameters of Eqs. (5.30) and the effective sharp interface coefficients one wishes to emulate in simulations; the capillary length (d_o) and interface kinetics coefficient (β). To do so the phase field equations must first be re-cast in the form of the generic phase field model C analyzed in Appendix (A), after which the the recipes of the appendix can be brought to bear on the parameters of model C presented in this chapter. Before proceeding the reader is encouraged to work through Appendix (A). For the reader not wishing to go through most of the tedious mathematical details of the appendix, it is sufficient to read only the first section of Appendix (A) –in order to become familiar with the parameters and definitions used– and the summary of the analysis presented in section (A.8).

5.6.1 Recasting phase field equations

Considering isotropic gradients for simplicity, Eqs (5.30) can be re-cast as

$$\tau \frac{\partial \phi}{\partial t} = W_\phi^2 \nabla^2 \phi - g'(\phi) - \frac{L}{HT_m} \left\{ c + \frac{L}{c_p} h(\phi) \right\} P'(\phi) \quad (5.31)$$

$$\frac{\partial c}{\partial t} = \alpha \nabla^2 \left(c + \frac{L}{c_p} h(\phi) \right) \quad (5.32)$$

where temperature has been replaced by $c = \Delta T - (L/c_p)h(\phi)$ ($\Delta T \equiv T - T_m$), which is suggestively labeled by the variable “ c ” as it is the analogue of concentration for alloys. Primes have been used to denote differentiation with respect to ϕ . Choosing $h(\phi) = P(\phi)$, Eqs (5.31) and (5.32) can be written, respectively, as

$$\tau \frac{\partial \phi}{\partial t} = - \frac{\delta F[\phi, c]}{\delta \phi} \quad (5.33)$$

$$\frac{\partial c}{\partial t} = \alpha \nabla^2 \mu, \quad (5.34)$$

where

$$F[\phi, c] = \int_V \left\{ \frac{1}{2} |\epsilon_\phi \nabla \phi|^2 + Hg(\phi) + \bar{f}_{AB}^{\text{mix}}(c, \phi) \right\} d^3 \vec{x} \quad (5.35)$$

$$\bar{f}_{AB}^{\text{mix}}(c, \phi) = \frac{c_p}{2T_m} \left(c + \frac{L}{c_p} P(\phi) \right)^2 \quad (5.36)$$

$$\mu = \frac{\delta F}{\delta c} = \frac{\partial \bar{f}_{AB}^{\text{mix}}(c, \phi)}{\partial c} = \frac{c_p}{T_m} \left(c + \frac{L}{c_p} P(\phi) \right) \quad (5.37)$$

Interpreted in the context of an alloy free energy, $\bar{f}_{AB}^{\text{mix}}(c, \phi)$ is a quadratic approximation of the free energy of a phase in term of its “concentration” c , while μ is analogous to a ”chemical” potential (see Appendix(A)).

The re-cast model above is mapped onto the generic model analyzed in Appendix (A)) by making the following associations. The parameter $H \rightarrow w \equiv 1/\lambda$ (where w is the nucleation barrier). The last term in Eq. (5.31) can be written as $\partial f_{AB}/\partial \phi$ where $f_{AB} \equiv \bar{f}_{AB}^{\text{mix}}/H$, exactly analogous to Eq. (A.3) of Appendix (A). Finally, the diffusivity function can be related to that of the generic model C in Appendix (A) by making the following associations:

$$\begin{aligned} M &\rightarrow \alpha q(\phi, c) \\ Q(\phi, c) &\rightarrow 1 \\ \frac{\partial^2 \bar{f}_{AB}^{\text{mix}}}{\partial c^2} &\rightarrow c_p/T_m \end{aligned} \quad (5.38)$$

Through the above correspondences, the parameter relations required to map the behaviour of model C for a pure material onto the corresponding sharp interface model for a pure material –the traditional Stefan problem– can now be acquired directly from the results of Appendix (A) as follows.

5.6.2 Effective sharp interface model

The coefficients of the effective sharp interface model require knowledge of the so-called lowest order phase and recuded ”concentration” fields. Here ”lowest order” refers to the expansion assumed for the c and ϕ fields in Eqs. (A.16) with respect to the parameter $\epsilon = W_\phi/d_o$, which is assumed formally to be small ⁶. The lowest order phase field ϕ_0 follows precisely from Eq. (A.51). It should be noted that for a pure material, equilibrium occurs at $T = T_m$, which leads to $\mu \rightarrow \mu_{\text{eq}}^F = 0$, where μ_{eq}^F denotes the chemical potential corresponding to a flat stationary interface in equilibrium. Therefore, the steady state phase field ϕ_0 of this model will be given by the solution of Eq. (A.51) in all cases, not only when $\epsilon \ll 1$, which is prescribed formally by the asymptotic analysis. Once $\phi_0(x)$ is known it can substituted into Eq. (5.37), which gives the corresponding lowest-order concentration field,

$$c_0(x) = -(L/c_p)P(\phi_0(x)) \quad (5.39)$$

⁶Note, that quantities in this analysis were extracted form a perturbation expansion that formally assumed the limit $W_\phi \ll d_o$, which i.e. the classical sharp interface limit. It turns out however, that the results of Appendix (A) are shown to hold even in the promised limit of $W_\phi > d_o$ so long as the magnitude of the driving thermodynamic driving force $\bar{f}_{AB}^{\text{mix}}$ is small, i.e. at small undercooling in the case of solidification.

Note that, strictly speaking, the actual "lowest order" $c_0(x)$ differs from the steady state concentration field by a small, additive, curvature and velocity correction, as discussed in Appendix (A). These corrections can be neglected in determining the coefficients of the effective sharp interface model of the present phase field model, as it turns out that only concentration differences enter the calculations.

The effective sharp interface equations of model C (see Eqs. (A.130) and (A.131)) contain three so-called "correction" terms, which otherwise alter the form of the traditional flux conservation equation and Gibbs-Tompson conditions. These corrections are associated with the terms ΔF , ΔH and ΔJ (defined in Appendix (A)). These terms exactly vanish for the model C presented in this chapter. This occurs because $q(\phi_0^{\text{in}}, c_0^{\text{in}})$ is a constant and $P(\phi)$ and $g(\phi)$ are symmetric. Consider the term ΔF as an example. This "correction" gives rise to a chemical potential jump in Eq. (A.85) and makes the Gibbs-Tompson condition in Eq. (A.107) two-sided. Substituting the zeroth order phase and concentration fields, ϕ_o and $c_0(x)$, for the lowest order fields, F^+ and F^- become

$$F^+ = \int_0^\infty \left\{ \frac{\Delta c}{q^+} - \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \right\} dx = \frac{L}{T_m} \int_0^\infty dx P(\phi_0(x)) dx \quad (5.40)$$

and

$$F^- = \int_{-\infty}^0 \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx = \frac{L}{T_m} \int_{-\infty}^0 dx (1 - P(\phi_0(x))) dx \quad (5.41)$$

Therefore, $\Delta F = 0$ and $F^+ = F^- \equiv F$ since $P(\phi)$ and $\phi(x)$ are symmetric functions around the interface, $x = 0$. It is similarly straightforward to show that $\Delta J = \Delta H = 0$, which imply no spurious correction to the flux conservation relation in Eq. (A.131). Moreover, the Gibbs-Thomson condition, which describes the chemical potential at the interface, is no longer two-sided as $F^+ = F^-$ (see Eq. (A.130)).

The coefficients appearing in the Gibbs-Thomson condition of the effective sharp interface model corresponding to model C are extracted from Eq. (A.130), after the latter equation is re-written in terms of temperature to read

$$\frac{T^o(0^\pm) - T_m}{L/c_p} = -d_o \kappa - \beta v_n \quad (5.42)$$

where d_o and β are the capillary length and kinetic coefficient, respectively, while v_n is the interface normal velocity and κ is the local interface curvature. The notation $T^o(0^\pm)$ denotes the temperature outside the interface projected back into the interface. The conversion of Eq. (A.130) to Eq. (5.42) is done by using Eq. (5.37) to write $\mu(\pm\infty) = \mu^o(0^\pm) = (c_p/T_m) (c(\pm\infty) + (L/c_p)P(\phi_o(\pm\infty)))$ and then substituting $c = (T - T_m) - (L/c_p)P(\phi)$ while noting that $T(\pm\infty) = T^o(0^\pm)$. This gives –after some algebra– Eq. (5.42) with

$$d_o = a_1 \frac{W_\phi}{\lambda} \quad (5.43)$$

$$\beta = \frac{a_1 \tau}{W_\phi \bar{\lambda}} \left\{ 1 - a_2 \frac{\bar{\lambda}}{D} \right\} \quad (5.44)$$

where $\bar{\lambda}$, a_1 , a_2 and σ_ϕ are given by

$$\bar{\lambda} = \frac{L^2}{c_p T_m} \lambda \quad (5.45)$$

$$a_1 = \sigma_\phi \quad (5.46)$$

$$a_2 = \frac{\bar{K} + \bar{F}}{\sigma_\phi} \quad (5.47)$$

$$\sigma_\phi = \int_{-\infty}^{\infty} \left(\frac{\partial \phi_o}{\partial x} \right)^2 dx \quad (5.48)$$

and where

$$\bar{K} = \int_{-\infty}^{\infty} \frac{\partial \phi_0}{\partial x} P'(\phi_0(x)) \left\{ \int_0^x [P(\phi_o(\xi)) - 1] d\xi \right\} dx \quad (5.49)$$

while $\bar{F} \equiv T_m F/L$ and $\bar{D} \equiv \alpha\tau/W_\phi^2$.

It is noteworthy that the pre-factor outside the curly brackets in Eq. (5.44) is precisely the expression obtained if the asymptotic analysis of Appendix (A) is stopped only at first order in ϵ , i.e. Eq. (A.72). Using just this level of approximation requires that $\tau \rightarrow 0$ in order to simulate vanishing interface kinetics. This leads to unrealistically long simulation time, particularly if $W_\phi, \lambda \rightarrow 0$ while maintaining a constant ratio W_ϕ/λ , as required by the classical asymptotics –which originally went up to order ϵ . The practical feature of Eq. (5.44) is that one can emulate $\beta = 0$ exactly *without* having to make $\tau \rightarrow 0$. Indeed, it is seen that β vanishes when $\tau \sim W_\phi^2 \lambda$, which can be quite large since it turns out that $W_\phi/d_o \sim \lambda$ (i.e. Eq. (5.43)) can hold to quite large values of λ . This was first shown by Karma and Rappel [113].

5.7 Numerical Simulations of Model C

A code for simulating thermally limited dendritic crystals is included in the CD. It is found in the directory called “ModelC_pure” and follows the same naming principles as the previous codes discussed for models A and B. For details of the derivations of some of the discrete numerical equations presented below, the reader is again referred to Appendix (B).

The solidification model in Eqs. (5.30) comprises one model B type diffusion equation coupled to one model A type order parameter equations. The former controls the rate of solidification through the diffusion of heat, while the second is essentially “slaved” to the first to update the position of interfaces. The logistics for defining variables for a code to simulate model C follows analogously to that described in the case of model A (section (4.9.2)). A notable difference in this case is that at least one new array for the temperature must be defined, which implies that this simulation immediately requires double the computer memory of models A or B. As can be expected, the numerical simulation involves a combination of the update steps previously used for solving models A and B. An algorithm to update model C is shown in Fig. (5.5). After updating the ϕ (represented by the array $PSI(i, j)$) from time n to time $n + 1$, the difference in PSI array between the two times must be separately stored and used to generate the latent heat term in the update of the heat equation, represented by the U array.

5.7.1 Discrete equations

The simplest way to update the heat diffusion equation component of model C (step four in Fig. (5.5)) is by using the explicit scheme in Eq. (B.10),

$$U^{n+1}(i, j) = U^n(i, j) + \frac{\bar{D}\Delta\bar{t}}{\Delta\bar{x}^2} \bar{\Delta}^2 U^n(i, j) + \Delta\bar{t} h'(\phi^n(i, j)) \left(\frac{\phi^{n+1}(i, j) - \phi^n(i, j)}{\Delta\bar{t}} \right) \quad (5.50)$$

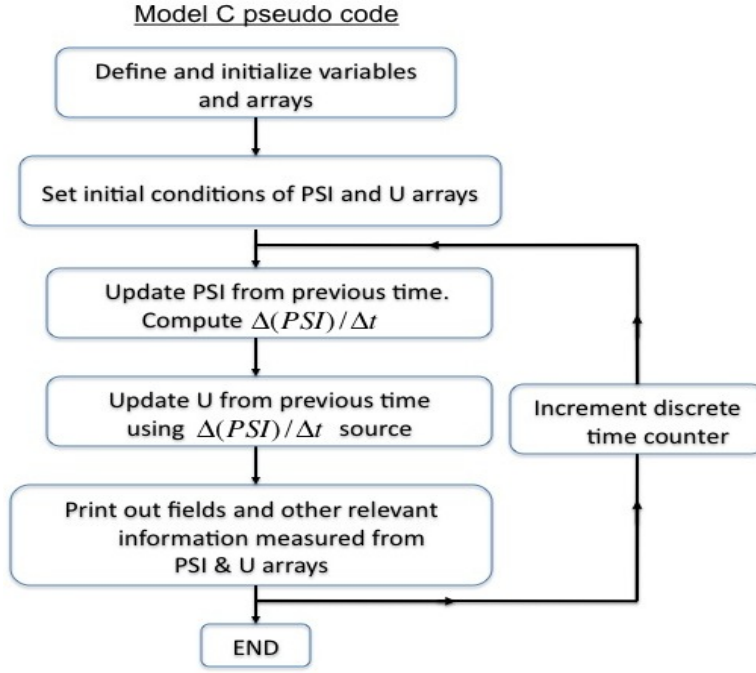


Figure 5.5: Flowchart of algorithm to simulate Model C for solidification of a pure material.

where the reduced temperature U is defined by

$$U \equiv \frac{T - T_m}{(L/c_P)} \quad (5.51)$$

and

$$\bar{D} \equiv \frac{\alpha\tau}{W_\phi^2} \quad (5.52)$$

Time and space are made dimensionless through the re-scaling $\bar{x} \rightarrow x/W_\phi$ and $\bar{t} = t/\tau$. A one-sided finite difference is used to discretize the time derivative. In Eq. (5.50) $\phi^n(i, j)$ is known from the previous (n^{th}) time step, while $\phi^{n+1}(i, j)$ is the latest update of ϕ .

The update of $\phi^{n+1}(i, j)$ (step three in Fig. (5.5)) is quite effectively done using a finite volume approach. Specifically, a do-loop structure computes $\phi^{n+1}(i, j)$ at each mesh point using the following adaptation of Eq. (B.16),

$$\begin{aligned} \phi^{n+1}(i, j) &= \phi^n(i, j) \\ &+ \frac{\Delta\bar{t}}{A^2[\phi(i, j)]} \left\{ \frac{1}{\Delta\bar{x}} (JR(i, j) - JL(i, j)) + \frac{1}{\Delta\bar{x}} (JT(i, j) - JB(i, j)) \right. \\ &\left. - g'(\phi^n(i, j)) - \bar{\lambda}UP'(\phi^n(i, j)) \right\}, \end{aligned} \quad (5.53)$$

where $\bar{\lambda}$ is given by Eq. (5.45). The arrays $JR(i, j)$, $JL(i, j)$, $JT(i, j)$, $JB(i, j)$ respectively handle the gradient terms ("order parameter fluxes") from the ϕ equation on the right, left, top and bottom edges of the finite volume centered around the point (i, j) (see Fig. (B.1)). They are given by

$$\begin{aligned}
JR(i, j) &= A[\phi^n(i+1/2, j)] \left\{ A[\phi^n(i+1/2, j)] DERX(i+1/2, j) - A'[\phi^n(i+1/2, j)] DERY(i+1/2, j) \right\} \\
JL(i, j) &= A[\phi^n(i-1/2, j)] \left\{ A[\phi^n(i-1/2, j)] DERX(i-1/2, j) - A'[\phi^n(i-1/2, j)] DERY(i-1/2, j) \right\} \\
JT(i, j) &= A[\phi^n(i, j+1/2)] \left\{ A[\phi^n(i, j+1/2)] DERY(i, j+1/2) + A'[\phi^n(i, j+1/2)] DERX(i, j+1/2) \right\} \\
JB(i, j) &= A[\phi^n(i, j-1/2)] \left\{ A[\phi^n(i, j-1/2)] DERY(i, j-1/2) + A'[\phi^n(i, j-1/2)] DERX(i, j-1/2) \right\} \quad (5.54)
\end{aligned}$$

where $A[\phi^n(i, j)]$ is shorthand notation for $A(\theta(\phi^n(i, j)))$, with the angle $\theta(\phi)$ defined in Eq. (5.22). The expressions $DERX(i \pm 1/2, j \pm 1/2)$ and $DERY(i \pm 1/2, j \pm 1/2)$ denote discrete x and y derivatives of ϕ , evaluated at the centres of the four edges of the finite volume (see Fig. (B.1)). For example, the explicit form of the x derivatives evaluated at the right and left edges are given by

$$\begin{aligned}
DERX(i + 1/2, j) &\equiv (\phi^n(i + 1, j) - \phi^n(i, j)) / \Delta \bar{x} \\
DERX(i - 1/2, j) &\equiv (\phi^n(i, j) - \phi^n(i - 1, j)) / \Delta \bar{x} \quad (5.55)
\end{aligned}$$

The y derivatives on the top and bottom edges ($DERY(i, j \pm 1/2)$) are defined analogously in terms of the index j . For the y derivative on the right edge of the finite volume, interpolation from the nearest and next nearest neighbours of the point (i, j) must be used. For example,

$$\begin{aligned}
DERY(i + 1/2, j) &\equiv \left(\phi^n(i + 1, j + 1) + \phi^n(i, j + 1) + \phi^n(i, j) + \phi^n(i + 1, j) \right) / 4\Delta \bar{x} \\
&\quad - \left(\phi^n(i + 1, j) + \phi^n(i, j) + \phi^n(i, j - 1) + \phi^n(i + 1, j - 1) \right) / 4\Delta \bar{x} \\
DERY(i - 1/2, j) &\equiv \left(\phi^n(i, j + 1) + \phi^n(i - 1, j + 1) + \phi^n(i - 1, j) + \phi^n(i, j) \right) / 4\Delta \bar{x} \\
&\quad - \left(\phi^n(i, j) + \phi^n(i - 1, j) + \phi^n(i - 1, j - 1) + \phi^n(i, j - 1) \right) / 4\Delta \bar{x} \quad (5.56)
\end{aligned}$$

Equations (5.56) are similarly extended for the x derivatives defined on the top and bottom edges of the finite volume. The final order of business is to derive a numerical expression for $A[\phi^n(i \pm 1/2, j \pm 1/2)]$. Substituting Eq. (5.22) into Eq. (5.25) and suffering a little with trigonometric identities gives the following recipe ⁷,

$$\begin{aligned}
A[\phi^n(i, j)] &= a_s * \left(1 + \epsilon' \left\{ \frac{DERX^4(i, j) + DERY^4(i, j)}{MAG2(i, j)} \right\} \right) \\
A'[\phi^n(i, j)] &= -a_{12} * DERX(i, j) * DERY(i, j) \left(\frac{DERX(i, j)^2 - DERY^2(i, j)}{MAG2(i, j)} \right)
\end{aligned}$$

⁷To obtain $A[\phi^n(i, j)]$ and $A'[\phi^n(i, j)]$, start with Eq. (5.22) (and its derivative with respect to θ for the case of $A'[\phi^n(i, j)]$) and re-express these quantities in terms of $\tan(\theta) = \partial_y \phi / \partial_x \phi$.

$$MAG2(i, j) \equiv \left(DERX^2(i, j) + DERY^2(i, j) \right)^2 \quad (5.57)$$

The constants a_s , a_{12} and ϵ' are defined here by

$$\begin{aligned} a_s &= 1 - 3\epsilon_4 \\ \epsilon' &= 4\epsilon_4/a_s \\ a_{12} &= 4a_s\epsilon' \end{aligned} \quad (5.58)$$

where ϵ_4 is defined as the anisotropy parameter as in Eq. (5.25).

It is noted that Eqs. (5.57) are evaluated numerically using an *if-endif* structure, so that when $MAG2(i, j) \leq 10^{-8}$ (or some similarly small constant), $A[\phi^n(i, j)] = a_s$ and $A'[\phi^n(i, j)] = 0$. It should be noted that the update step defined by Eq. (5.53), along with the rules defined by Eqs. (5.54)-(5.57) are *local* at each mesh point (i, j) . It is thus not necessary to define the additional arrays $JR(i, j)$, $JL(i, j)$, $JT(i, j)$, $JB(i, j)$, $DERX(i, j)$, $DERY(i, j)$, $MAG2(i, j)$. Each of these variable be defied merely as a single scalar variable that is re-assigned a corresponding value at each mesh point. That will save a significant amount of computer memory when running large systems.

Since both Eqs. (5.50) and (5.53) are use explicit time marching, they are both subject to constraints on the maximum Δt that can be used. In both cases, they both contain only second order gradients in ϕ or U . Linear stability for both in two dimensions demands that $\Delta t < \Delta x^2 / (4 \max(D))$ where $\max(D)$ is the larger of \bar{D} and $1/A[\phi(i, j)]$. It is typically the thermal equation that sets the scale for the smallest time step as this is the fastest process.

5.7.2 Boundary conditions

The above algorithm is made complete by specifying appropriate boundary condition, which is required to properly deal with gradients of U at the boundaries of the system. For example, to implement fixed flux boundary conditions on the thermal field U , the first step is to define PSI and U on a set of *ghost* nodes outside the system (see also section (4.9.2)). For example, the discretization of U as $U(1..N, 1..M)$ (using Fortran 90 notation) would be represented on an array $U(0..N + 1, 0..M + 1)$. Prior to entering the update phase for concentration, the following *buffering* condition should be applied:

$$\begin{aligned} U(0, :) &= U(1, :) - q\Delta x \\ U(N + 1, :) &= U(N, :) + q\Delta x \\ U(:, 0) &= U(1, :) - q\Delta x \\ U(M + 1, :) &= U(M, :) + q\Delta x \end{aligned} \quad (5.59)$$

where q is the imposed boundary flux for the field U at the system boundaries. Similar buffering is made for the PSI array, although in this case of array, mirror boundary conditions are most appropriate. These can be implemented by the mapping

$$\begin{aligned} \phi(0, :) &= \phi(1, :) \\ \phi(N + 1, :) &= \phi(N, :) \\ \phi(:, 0) &= \phi(1, :) \\ \phi(M + 1, :) &= \phi(M, :) \end{aligned} \quad (5.60)$$

5.7.3 Scaling and convergence of model

To illustrate a specific numerical example, model C was simulated using a set of phase field interpolation functions also used in Karma and Rappel [113], namely,

$$\begin{aligned} g'(\phi) &= -\phi + \phi^3 \\ P'(\phi) &= (1 - \phi^2)^2 \\ h'(\phi) &= \frac{1}{2} \end{aligned} \quad (5.61)$$

Use of these functions requires that the order parameters be defined from $-1 \leq \phi \leq 1$, which does not change the physics from the usual definition from $0 \leq \phi \leq 1$ in any way. Also, these definitions give $a_2 = 0.6267$ (in Eq. (5.46)) and $a_1 = 0.8839$ (in Eq. (5.47)). Figure (5.6) shows the initial growth sequence of a thermally controlled crystal growing into an undercooled melt. The reduced temperature



Figure 5.6: (Left) Early growth sequence of a thermally controlled dendrite growing as a circular seed. Left half is ϕ while the right is U , with green being the lowest and red the highest temperatures. (Right) Later time morphology of crystal. Four-fold branches are governed by anisotropy.

was initially set everywhere to $\Delta \equiv c_p(T_m - T_\infty)/L_f = 0.55$, while the initial order parameter field satisfied $\phi^0(i, j) = -\tanh(\text{dist}(i, j)/\sqrt{2})$, where $\text{dist}(i, j) \equiv [(i-1)\Delta x]^2 + [(j-1)\Delta x]^2 - R_o^2$, where $R_o = 10(W_\phi)$ is the size of a circularly shaped seed crystal nucleation from which solidification begins. Zero flux boundary conditions were used. The simulation emulates zero interface kinetics ($\beta = 0$ in the Gibbs-thomson condition), which implies from Eq. (5.44) that $\bar{D} = a_2\bar{\lambda}$. Other parameters are $\bar{\lambda} = 3.19$, $\epsilon_4 = 0.06$, $\Delta\bar{t} = 0.014$, $\Delta\bar{x} = 0.4$ and the system size is $400(W_\phi) \times 400(W_\phi)$. The four-fold anisotropy of Eq. (5.25) is evident at $\bar{t} = 65000\Delta\bar{t}$.

Conversion of the simulation results of Fig. (5.6) to real length and time scales is made via Eqs. (5.43) for the capillary length d_o and $\bar{D} = a_2\bar{\lambda}$ from 5.44. For example, taking the thermal diffusion coefficient of pure Nickel to be $\alpha \approx 1 \times 10^{-5} m^2/s$ and its capillary length $d_o \approx 2 \times 10^{-10} m$, gives

$$\begin{aligned} W_\phi &= \frac{\bar{\lambda}d_o}{a_1} \approx 1 \times 10^{-9} m \\ \tau &= \frac{a_2W_\phi^2\bar{\lambda}}{\alpha} \approx 3 \times 10^{-13} s \end{aligned} \quad (5.62)$$

These are very small time and length scales! In terms of these the physical system corresponding to the simulation domain is $400 \times \Delta x \times W_\phi \approx 0.16 \mu m$, while the total simulation time corresponds to $100000 \times \Delta t \times \tau = 4.2 \times 10^{-10} s$. The only reason that anything at all is visible in less than a micron in half a nanosecond is due to the very high cooling rate (i.e. very rapid solidification rate) simulated in this example. In particular, taking the latent heat of Ni to be $L = 8 \times 10^9 J/m^3$ and the specific as $c_P = 2 \times 10^7 J/m^3 K$, the undercooling $\Delta = 0.55$ corresponds to a quench temperature of about $220 K$ below the melting point. A physical system that has some [remote] relevance to this situation is a rapidly cooled levitated liquid drop of dimensions on the order $\sim 10 \mu m$ in diameter and which typically solidifies on the order of a millisecond. Even for such a system, however, complete simulation of the solidification process requires mesh of order $\sim 25000 \times 25000$ nodes and $\sim 10^{11}$ iterations.

The issue of spatial resolution highlighted in the example of the previous paragraph can nowadays be dealt with using the methods of *adaptive mesh refinement (AMR)*, otherwise the memory management becomes unmanageable and the computational time per time step becomes too long. Despite the advantages of AMR, the small value of τ still make the total number of time iterations prohibitive. To overcome this problem, it turns out that $\bar{\lambda}$ can be treated as a convergence parameter through which the characteristic length scale W_ϕ and time scale τ can be self-consistently increased, without compromising the sharp interface limit of the phase field solutions. The idea is that results will be independent of $\bar{\lambda}$ once quantities are re-scaled back appropriately using τ and W_ϕ , which are functions of $\bar{\lambda}$ via Eqs. (5.62). Consider, for example, the steady state dendrite tip seed V . Once this quantity is extracted from a simulation for a particular $\bar{\lambda}$, it must become independent of $\bar{\lambda}$ when re-scaled as

$$\bar{V} = \frac{V d_o}{\alpha} = \frac{a_1 \tau V}{a_2 \bar{\lambda}^2 W_\phi} \quad (5.63)$$

This is illustrated in Fig. (5.7), which plots the dendrite tip velocity at $\Delta = 0.55$ and $\epsilon_4 = 0.05$, for $\bar{\lambda} = 3.19$ and $\bar{\lambda} = 1.8$. All other parameters and conditions are the same as that in Fig. (5.6). It is clear that the scaling of velocity as in Eq. (5.63) leads to dimensionless steady state crystal growth rates that are independent of the value of $\bar{\lambda}$. In the next section a discussion of dendritic tip selection rates will show that the dimensionless tip velocity depends only on Δ and ϵ_4 .

Using Eqs. (5.62) to tune the sharp interface properties of the phase field model leads to remarkable CPU speed up, a very important result first demonstrated for this case by Karma and Rappel [113]. For example, going from $\bar{\lambda} = 3.19$ to $\bar{\lambda} = 10$ increases τ by a factor of 27, while the increase in the spatial resolution only increases in proportion to $\bar{\lambda}$ (i.e. ~ 3). With this value of $\bar{\lambda}$, the example discussed above would require about 8000×8000 nodes on a conventional uniform mesh. Moreover, when simulated on an adaptive mesh, this simulation requires only on the order of about $\sim 10^2 \times 10^2$ nodes on an adaptive mesh. In this case, it is possible to perform a about a millisecond of simulation with 10^9 iterations. These days, the “marriage” of thin-interface relations such as those studies in this chapter and adaptive mesh refinement has made it possible to use phase field models in a *quantitative* way, i.e. to simulate experimentally relevant parameters and processing conditions. Adaptive mesh refinement is illustrated in Figure (5.8), which shows the growth of a thermally controlled dendrite crystal growing into an undercooled melt. The advantage of this approach is that CPU time scales with the available amount of interface in the problem being simulated, not the physical size of the domain. This essentially reduces the dimensionality of the problem as the computer algorithm spends most of its time computing near interfaces and only a negligible amount of time doing calculations far from interfaces. The approach makes it possible to simulate experimentally relevant systems sizes over much longer solidification time scales than is possible with a uniform mesh, the latter of which would fail on account of the memory required to be stored and the CPU time per time step inherent at every iteration.

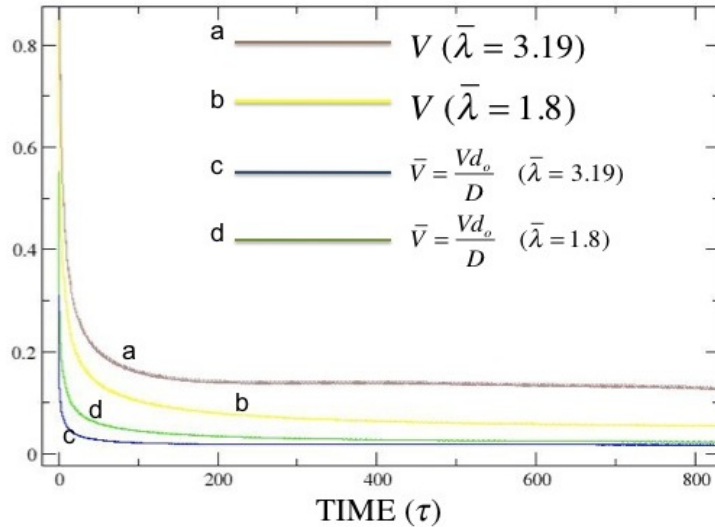


Figure 5.7: Dendrite tip speeds for two values of the inverse nucleation barrier $\bar{\lambda}$. The parameter $\bar{\lambda}$ is chosen to self-consistently fix the interface kinetics time (τ) and interface width (W_ϕ) in a manner consistent with the sharp interface model. As such, scaling the tip speed τ/W_ϕ (equivalent to d_o/D) makes the dimensionless tip speed universal and dependent only on undercooling and anisotropy.

5.8 Properties of Dendritic Solidification in Pure Materials

Since solidification in metals is difficult to study in-situ, much of the fundamental solidification research has focused on transparent organic analogues of metals, which included compounds such as succinonitrile (SCN) and pivalic acid (PVA). These materials are attractive because they solidify near room temperature and exhibit many features of metals in their solidification; for example, SCN molecules arrange themselves positionally into a BCC lattice during solidification. Early research focused on predicting the tip speed and radius of curvature of isolated crystals of a pure material growing into an undercooled melt. There were several theories developed to explain the operating state of a thermally controlled dendrite. One in particular, coined *microscopic solvability theory*, involved a direct self-consistent solution of the Stefan sharp interface problem described by Eqs. (1.1). This theory is of particular importance as it was later found to be in excellent agreement with phase field model simulations and some experiments. The main properties of dendritic solidification predicted by microscopic solvability and some subsequent phase field results on dendritic growth are summarized in this section. For a more encompassing review of these and other theories, the reader is referred to a comprehensive review by Saito [183] or Langer [138].

5.8.1 Microscopic solvability theory

It is fairly straightforward to show that for a pure material there is no steady state solution for a planar or spherical solidifying into an undercooled liquid. Assuming, however, a parabolic crystal morphology, Ivantsov [103] showed that there are stable solutions of the thermal diffusion equation and the associated sharp interface boundary conditions of solidification in Eqs. (1.1) ⁸. Specifically, Ivantsov found that a

⁸The Ivantsov analysis ignores curvature effects.

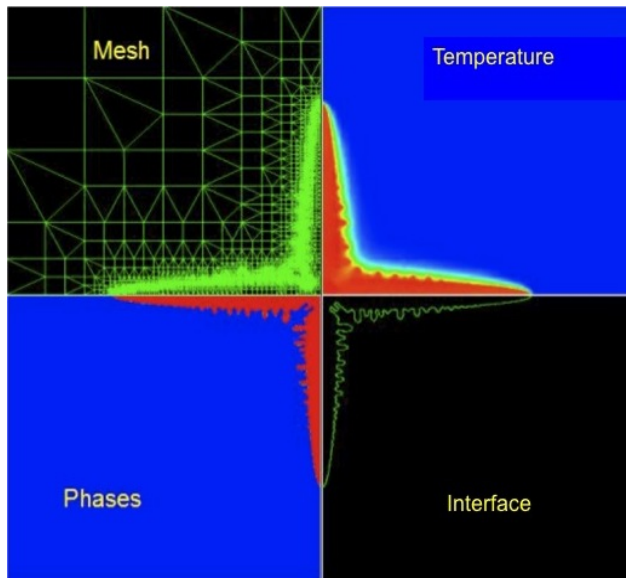


Figure 5.8: *Snapshot in time of a thermal dendrite evolving under the dynamics of Eqs. (5.30) for a pure material. A four fold-crystal is growing into an undercooled liquid. The four frames show from top right clockwise: temperature, with red being the warmest and blue representing the lowest temperature; the interface position, defined by $\phi = 0$; the solid, in red, and liquid, in blue; the dynamically adapted mesh resolving the temperature and phase field.*

stable solution must satisfy

$$\Delta = \sqrt{\pi P} e^P \operatorname{erfc}(\sqrt{P}), \quad (5.64)$$

where $\Delta = c_p(T_m - T_\infty)/L_f$ is the undercooling and P is the Peclet number defined as

$$P = \frac{R}{l_d} = \frac{RV}{2\alpha}, \quad (5.65)$$

where R is the parabolic tip radius of crystal, V the tip velocity, and α the thermal diffusivity. A modified version Eq. (5.64) by Fisher [45] included capillarity. This gave rise a V vs. R relation that goes through a maximum as $R \rightarrow 0$. The Ivantsov relation, Eq. (5.64) predicts steady states for an infinite number of (V, R) combinations, for a given undercooling Δ . Experiments, however, suggest, that only one steady state tip speed and radius is possible for a pure materials growing inter an undercooled melt. Many early metallurgical theories assumed that the operating state of a dendrite was defined by the (R, V) at the maximum. This was not supported by experiments. A second equation relating V and R is thus required to uniquely determine the tip speed and radius as a function of materials parameters (e.g. anisotropy ϵ_4) and process parameters (Δ).

A second equation between V and R can be motivated by exploiting a linear stability analysis performed by Mullins and Sekerka [156, 157]. The Mullins and Sekerka analysis considers the stability and growth rate of thermal fluctuations of a planar front advancing into an undercooled melt at a steady velocity. Considering a noisy front as a collection of sinusoidal modes, Mullins and Sekerka derived a linear dispersion relationship that governs the growth rate, $\omega(q)$, of each sinusoidal mode of wave vector

q as a function of material parameters and solidification conditions⁹. This is given by

$$\frac{\omega(q)}{\alpha} = \left(\frac{2}{l_d} - d_o q^2\right) |q| \sqrt{1 - \frac{2d_o}{l_d} + \frac{d_o^2 q^2}{4}} - \frac{3d_o q^2}{l_d} + \frac{d_o^2 q^4}{2}. \quad (5.66)$$

where q is the inverse wavelength, $l_d = 2\alpha/V$ is the thermal diffusion length and d_o is the thermal capillary length. A negative $\omega(q)$ implies that a mode of that q will decay and give rise to a planar front. For a q with a positive $\omega(q)$, the mode will grow. Equation (5.66) predicts a range of unstable q modes. These modes are amplified and ultimately give rise to dendritic branches (if you view this as happening on a sphere). The maximum of Eq. (5.66) occurs for $\lambda_{\text{ms}} = 2\pi\sqrt{d_o l_d}$, which corresponds to the fastest growing interface perturbation mode. It is reasonable to expect that R will scale with λ_{ms} and so an index, referred to as the *stability parameter* in some theories, is defined according to

$$\sigma = \frac{d_o l_d}{R^2} = \frac{d_o}{RP} = \frac{2\alpha d_o}{VR^2} = \frac{d_o V}{2\alpha P^2}. \quad (5.67)$$

Indeed, a more rigorous treatment of the problem by Langer and co-workers [135, 136] shows that in the limit where $P \ll 1$, σ is the only parameter that enters the solution of the inverse problem for the perturbed thermal field around a dendrite. The solution to the operating state of the dendrite thus comes down to determining the constant σ . Then Eqs. (5.67) and (5.64) can be solved for V and R .

The aforementioned analysis of Langer and Muller-Krumbhaar [135, 136] considered dendritic growth in the presence of surface tension. They found that below a certain value of σ , a dendrite becomes unstable to tip splitting instabilities. They postulated the so-called *marginal stability theory*, which predicted that the selected value of σ is such that where the is just marginally stable to tip splitting. They estimated $\sigma \approx 0.026$, which was close to experiments on SCN, which gave $\sigma = 0.0195$. However, their method of approximating σ was very crude and it is likely that the agreement is simply fortuitous. Another approach is to treat σ as fitting parameter. This however, does not lead to a fully self-consistent theory and will not be discussed further here.

A self-consistent approach for finding σ is provided by the theory of *microscopic solvability*. The theory considers the full non-linear inverse problem corresponding to the sharp interface model for a pure material. An integral equation for the thermal field around a dendrite is developed, from which a boundary integral equation for the crystal interface can be projected. Three interesting predictions arose during the development of microscopic solvability. The first is that the boundary integral equation only has non-trivial solutions if at least one the capillary length (d_o) or interface kinetic coefficient (β) are anisotropic [34, 23, 22, 129]. The second is that acceptable solutions arise only for quantized values of V and R . The third is that only the solution with the fastest velocity is linearly stable [2, 32, 166]. These considerations lead to one unique operating value of $\sigma \equiv \sigma^*(\epsilon_4)$, which is a function of the surface tension anisotropy (ϵ_4). Substituting the explicit form of $\sigma^*(\epsilon_4)$ into the left hand side of Eq. (5.67), and taking the limit of small ϵ_4 , yields the following analytical approximations for V and R ,

$$R = \frac{d_o \epsilon_4^{-7/4}}{\sigma_o P(\Delta)} \sim d_o \frac{\pi}{\sigma_o} \Delta^{-2} \epsilon_4^{-7/4} \quad (5.68)$$

$$V = \frac{2\alpha\sigma_o P^2(\Delta)\epsilon_4^{7/4}}{d_o} \sim \frac{2\alpha\sigma_o}{\pi^2 d_o} \Delta^4 \epsilon_4^{7/4}. \quad (5.69)$$

⁹It is assumed that the amplitude of a sinusoidal perturbation $h(x, t)$ grows according to $\hat{h} \sim e^{\omega(q)t}$, where \hat{h} is the Fourier transform of h and q is the wave vector of a perturbation.

where σ_o is a constant of the theory. For general values of ϵ_4 , numerical integration must be used. The results of microscopic solvability have been validated for $\Delta < 0.6$ in pure nickel solidified by levitation [31]. For higher undercooling, non-ieuilibrium interface kinetics become important and must be considered.

5.8.2 Phase field predictions of dendrite operating states

The first quantitative test of microscopic solvability theory by phase field models was made by Karma and Rappel [113]. They used a model like the one discussed in this chapter was used to simulate free dendritic growth and compared its predictions of dendrite tip speed and radius to microscopic solvability theory, which –at the very least– constitutes an analytical solution of the the sharp interface equations of solidification. Later work further confirmed these results in tests of a novel adaptive mesh algorithm for simulating phase field models [170].

At low undercooling the diffusion of heat (pure materials) or impurities (alloy) occurs over a length scale that increases with decreasing undercooling (or supersaturation in the case of alloy dendrites). In this limit the approach to the steady state predictions of solvability theory follows a long-lived transient period. During this regime, dendritic branches are strongly interact with each other or with the boundaries of their container [170, 182]. As a result the tip speed and radius will converge very slowly, with the

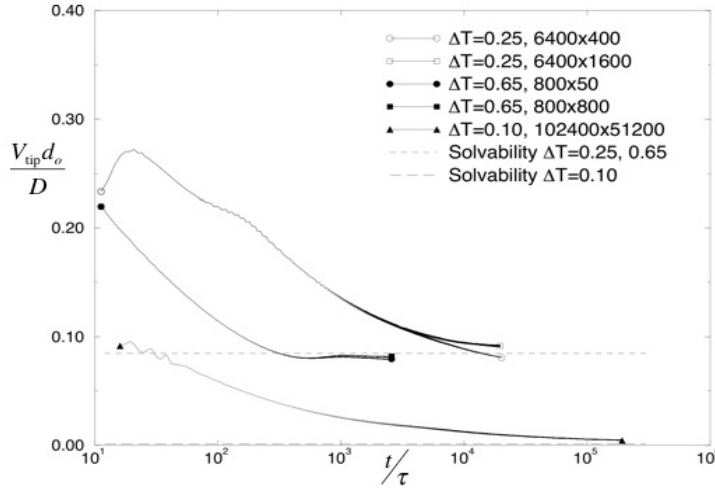


Figure 5.9: *Steady-state growth speed of 2D thermal dendrites (curves) at low undercooling. The horizontal lines show the predictions of solvability theory. The scales are logarithmic.*

approximate time to convergence scaling as $t_{\text{con}} \sim 9D/V^2$. This is seen in Fig. (5.9), which shows the dimensionless tip speed (Vd_o/D) vs. dimensionless time (t/τ_o) for thermal dendrites grown in the limit of low undercooling. Also shown in the figure is the case where one of two perpendicular dendrite branches (see Fig. (5.8)) is abruptly eliminated from the simulation. The result is a change in the velocity vs. time curve of the surviving branch, evidence of the strong interaction between branches.

Interestingly, even though the dendrite tip speed (V) and radius (R) follow a log lived transient, the stability parameter σ^* does not. Figure (5.10) shows σ^* versus dimensionless time for the corresponding undercooling values of Fig. (5.9). It is seen that the stability parameter very rapidly attains the value

predicted by microscopic solvability. This further suggests that the solvability predictions of Eqs. (5.68) and (5.69) will, in theory, be achieved eventually. It should be noted that the low undercooling simula-

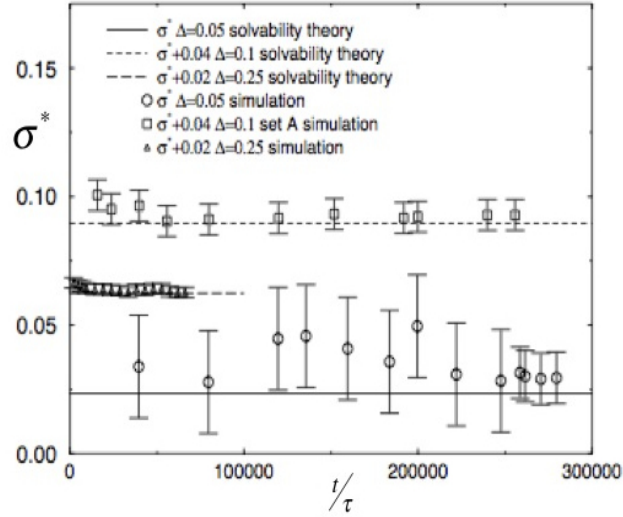


Figure 5.10: *2D simulation data of σ^* vs time for $\Delta = 0.25, 0.1$, and 0.05 . For clarity, the $\Delta = 0.1$ and 0.25 data have been shifted along the y axis by 0.04 and 0.02 , respectively*

tions are practically impossible to conduct numerically using any fixed-grid approaches such as the ones discussed in Appendix (B). The disparity of length scales between the diffusion length and the interface width necessitates the use of dynamical AMR techniques, as well as the use of a large ratio of interface width to capillary length W_ϕ/d_o , which exploits the benefits discussed in section (5.7.3).

Since the time to converge toward a steady state diverges at low undercooling, for most practical applications of solidification interactions and transient dynamics is the rule, not the exception, even in the simple case of isolated dendrite growth. Transient dynamics at low undercooling is characteristic of competitive interactions that occur in complex solidification problems [109, 219, 215, 185, 144, 151, 10, 22, 130, 182]. In this regime, the dendrite evolves sufficiently slowly that the thermal diffusion can be modeled *quasi-statically*, i.e. by solving $\nabla^2 T = 0$ after each time step of the phase field equation. The dynamics and morphology of the dendritic growth in the presence of long-range diffusion interactions can be examined using concepts of crossover scaling theory. Specifically, consider a dendrite arm growing along the positive x -axis. Rescale the y -axis by the transverse length, Y_{\max} of the dendrite,

$$y_N = \frac{y}{Y_{\max}}, \quad (5.70)$$

and the x -axis by the total length, X_{\max} , of the dendrite arm along its centre line,

$$x_N = \frac{x - x_{\text{root}}}{X_{\max}}, \quad (5.71)$$

where $X_{\max} = x_{\text{tip}} - x_{\text{root}}$ and x_{root} defines the base of the dendrite where it emerges from the seed nucleus. Plotting a sequence of time slices of the the dendrite arms under this re-scaling of coordinates shows that the dendrite morphology is described by a similarity solution. Figure (5.11) shows the collapse

of multiple time sequences of simulated 2D and 3D dendrites onto one similarity solution [171]. The numerical simulations do not have noise and thus do not exhibit sidebranches. However, it is expected that the scaling of the primary branch shape will remain essentially unchanged in the presence of noise. It is found that X_{\max} and Y_{\max} obey power-law type scaling, where $Y_{\max} \sim t^\alpha$, where $\alpha \approx 0.5$ and $X_{\max} \sim t^\beta$ where $\beta \approx 0.75$ at early times and crosses over to $\beta \approx 1$ at late times. Also shown in Fig. (5.11) is the scaling of an experimental time sequence of PVA dendrites grown in microgravity by Glicksman and co-workers [172].

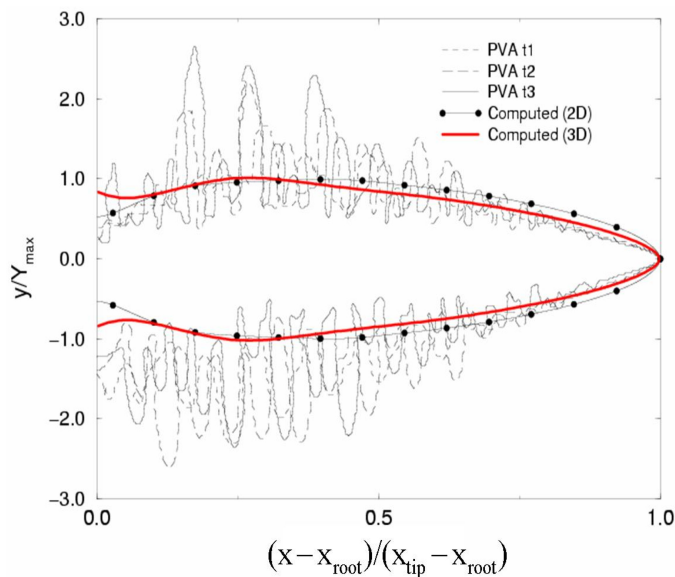


Figure 5.11: *Dynamic scaling of computed 2D and 3D dendritic crystal morphology for crystals of a pure material. The figure also contains experimental PVA dendrite arms scaled at times $t_1=42.48s$, $t_2=62.73s$ and $t_3=82.98s$.*

The transient scaling of the dendrite arm along directions parallel and transverse to the tip suggest that there is a scaling relationship obeyed by these two dimensions. In particular, it is found that these two dimensions can be described by

$$\begin{aligned} \frac{X_{\max}(t)}{L_D} &= \frac{t}{\tau_D} F_X \left(\frac{t}{\tau_D} \right) \\ \frac{Y_{\max}(t)}{L_D} &= \frac{t}{\tau_D} F_Y \left(\frac{t}{\tau_D} \right) \end{aligned} \quad (5.72)$$

where L_D and τ_D are characteristic length and diffusion scales for the transient regime. The functions $F_X(z)$ and $F_Y(z)$ are crossover scaling functions that obey one type of power law at small $z = t/\tau_D$ and cross over to another at large values of z . Figure 5.12 show the numerical form of $F_X(z)$ and $F_Y(z)$ computed from phase fields simulations.

It should be noted that there are several pictures of dendritic scaling that can emerge depending on the boundary conditions used. In the data presented above, zero-flux boundary conditions were used. Moreover, analyzing only dendritic as in tip [9, 145] will give different growth exponents in the transient

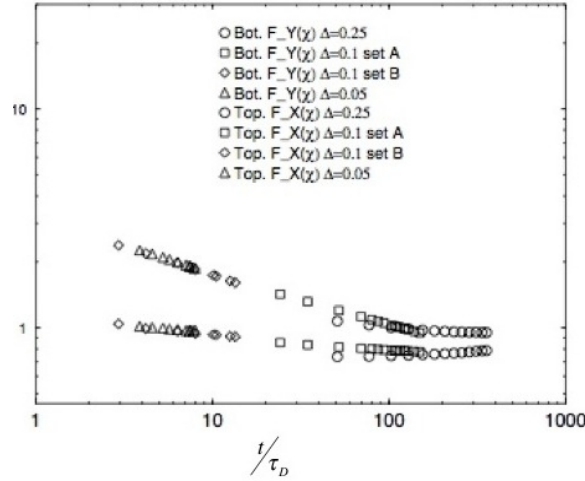


Figure 5.12: *Crossover scaling functions describing lateral width of simulated dendrite arm Y_{\max} and tip-to-base distance X_{\max} , for $\Delta = 0.25, 0.1, 0.05$ corresponding to Fig.(5.10).*

scaling regime. The main result of data such as that in Figs. (5.11) and (5.12) is that it predicts that the morphology and growth kinetics of dendrite growth is self-affine.

5.8.3 Further study of dendritic growth

The above subsection was intended to wet one's appetite with the complex physics involved in the growth of a single crystal. It is far from complete and it would go beyond the scope of this book to discuss such matters further. Armed with the basics of phase field modeling in pure materials the reader is now advised to consult the scientific literature for further study on dendritic growth, including works involving phase field modeling. An important question, in particular, which has not been discussed here involve the physics of side branch formation. The formation of side branches has been studied extensively in experiments [97, 132] but a proper theoretical understanding of their origin and formation is still lacking. Early analytical theories based on WKB approximations [19, 33] studied the effect of thermal nose as the main source that give rise to side branches. This was later also followed up using phase field modeling [41], where the amplitude of the side branches away from the dendrite tip were examined in detail. Recent work by Echebarria and co-workers suggest that both mechanisms may be at work [58] reveals that side branching may in fact be caused by both thermal noise and a non-linear deterministic mechanism, as was originally proposed in the 1980's [148]. This is an area where phase field modeling is likely to play a leading role in the future due to the complex nature of side branch morphology, which makes it challenging for analytical theories to deal with.

Chapter 6

Phase Field Modeling of Solidification in Binary Alloys

This chapter extends the phase field methodology to include alloys –a mixture of two or more components. Following a brief review of some nomenclature regarding alloys and phase diagrams, the kinetics describing the sharp interface evolution of solidification or solid state microstructure formation in an alloy are discussed. This will be used as a backdrop against which to develop a phase field free energy for a class of two component (binary) alloys. This free energy will be used to derive equations of motion for the evolution of the order parameter (phase field), impurity concentration and heat during the growth of an alloy phase. The last stage, as in the case of pure materials, is to make a connection between phase field simulations –which inherently employ a diffuse interface– and the corresponding alloy sharp interface models. The reader is assumed to have (or advised to acquire) some background knowledge of binary alloys and their basic thermodynamics.

6.1 Alloys and Phase Diagrams: A Quick Review

An alloy is a mixture of two or more components which can be elements or compounds. For example, the designation Al-Cu refers to a mixture of aluminum with copper. Similarly MgO-AL₂O₃ is an alloy of magnesium oxide with aluminum oxide. An alloy can have more than one phase depending on the number of components and their relative ratio. Figure 6.1 shows two solid phases of an Al-Cu alloy and illustrates their corresponding atomic makeup. The two phases are discerned only by the relative amount of copper to aluminum and each phase is physically and chemically distinct from its constituent component, Al and Cu. An alloy is parameterized by the concentration of impurity (usually the minority component). Concentration is measured either by weight or number of atoms, to the total weight or number of atoms of the entire mixture. Therefore, an alloy of aluminum alloyed (mixed) with 4.5% by weight copper is denoted Al-4.5%Cu.

A phase diagram is a map that tells us what phases of an alloy are possible at a given impurity concentration and temperature. Constructing phase diagrams is a complex business depending on the number of alloy components. The starting point is the free energy of all phases that an alloy can form, each parameterized in terms of its component concentrations and temperature. A fixed pressure is typically assumed. The free energy of a phase is typically determined by fitting experimental data using

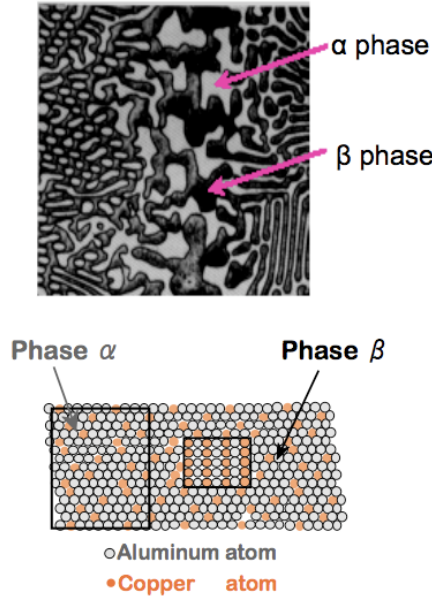


Figure 6.1: Top: two phases of an Al-Cu alloy. Solid alloy phases are denoted by Greek letters. Bottom: corresponding atomic make up of each phase. (Adapted from Fig. 9.9 of Ref. [40]).

various fitting functions. These functions are typically phenomenological but motivated by thermodynamic considerations, as will be shown below for simple binary alloys. For binary alloys, minimizing the total free energy of a two-phase system under the condition of mass conservation leads to the so-called *common tangent construction* [167], a rule by which a binary phase diagram can be calculated. Considering an example of a solid in coexistence with its liquid, the common tangent construction is expressed mathematically as

$$\mu_{\text{eq}} = \frac{f_L(c_L^{\text{eq}}) - f_s(c_s^{\text{eq}})}{c_L^{\text{eq}} - c_s^{\text{eq}}} = \frac{\partial f_L(c_L^{\text{eq}})}{\partial c} = \frac{\partial f_s(c_s^{\text{eq}})}{\partial c} \quad (6.1)$$

where μ_{eq} is the equilibrium chemical potential, while $f_L(c)$ and $f_s(c)$ are the free energies as a function of concentration of the liquid and solid phase, respectively. The self-consistent solution of all three equalities in Eq. (6.1) yields μ_{eq} and the equilibrium liquid and solid concentrations, denoted c_L^{eq} and c_s^{eq} respectively. By applying this construction at different temperatures, a phase diagram is constructed. Figure 6.2 illustrates a binary eutectic phase diagram containing two solid phases (α and β) and one liquid phase. Colored regions in the figure denote regions of concentration and temperature where a single phase can exist. Other regions denote concentrations and temperature where phases can co-exist. The concentration 18.3wt% Sn is called the *solubility limit* of the alloy; the largest concentration of Sn that can be mixed with Pb in the solid phase. Beyond the solubility limit, and for temperature below the eutectic temperature (T_E), solid α will precipitate a second solid phase β . At $T = T_E$ it is possible to have liquid and the two solid phases co-exist.

One of the key assumptions guiding the description of microstructure evolution is that an interface between two phases remains in local equilibrium. This is only really true at low levels of cooling. Luckily this apparently limiting condition just happens to describe more commercial casting conditions. Emerging

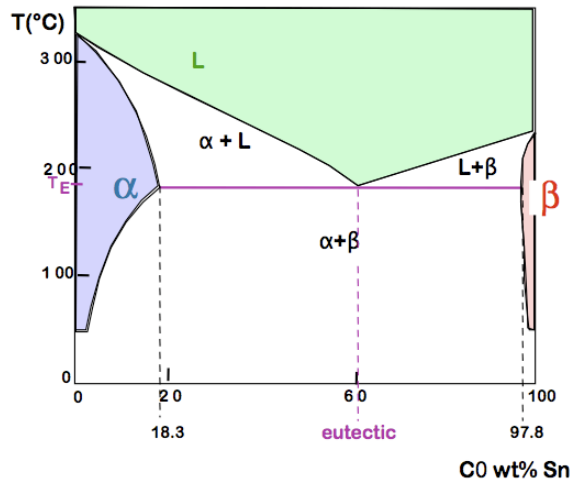


Figure 6.2: Phase Diagram of lead (Pb) alloyed with tin (Sn). Colored fields denote single phases, while fields denote coexistence regions. Solid phases are labeled with Greek letters. (Adapted from Fig. 9.16 of Ref. [40]).

technologies (e.g. strip-casting of aluminum) are starting to move towards processing thinner materials. This implies a more rapid cooling rate and, hence, finer microstructure. A consequence of this is that the interface can not always be considered to be in local equilibrium during the during solidification. Non-equilibrium interface kinetics lead to both morphological differences or microstructure and non-equilibrium phases that do not follow the equilibrium phase diagram.

6.2 Microstructure Evolution in Alloys

The growth of microstructures in alloys is more complex than in pure materials because the phase transformation kinetics are limited by both heat and mass transport. Fortunately, these two processes occur on sufficiently different time scales that for many cases of practical importance only the slower of the two –mass transfer– need be considered. The faster, heat conduction, can typically be treated as either isothermal or “frozen”, wherein temperature is assumed to evolve so rapidly compared to solute redistribution that it is in a quasi-steady state. This assumption is not unreasonable for low levels of cooling as the ratio of thermal diffusion (α) to solute diffusion D ranges in many metals from $10^{-4} < \alpha/D < 10^{-2}$. Of course there is nothing to stop one from formulating multiple equations for phase, concentration [of impurities], heat, etc. However, the more equations that must be simulated numerically, the longer the simulation times will be, thus making it more difficult to attain experimentally relevant times.

6.2.1 Sharp interface model in one dimension

Figure 6.3 illustrates a typical temperature quench ($T \rightarrow T_1$ from T_2) into the two phase co-existence of an alloy. In the particular case shown, the liquid phase L of average concentration C_0 will precipitate a second, solid, phase α . The growth rate of the α phase within the liquid will depend on the driving force,

which is proportional to the depth of cooling into the co-existence region. The growth rate is, however, also limited by the ability for solute atoms of element B to diffuse away from the interface of precipitated phase. This is because, as illustrated in Fig. 6.3, the α phase can only exist at a lower B concentration than the L phase. As a result, solute atoms of B are *rejected* from the crystal as it grows, in order that it may attain a lower concentration.

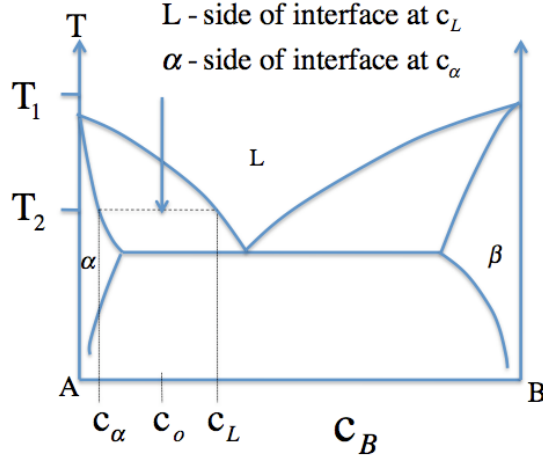


Figure 6.3: Quench into a two phase (solid-liquid) coexistence region of a A-B eutectic alloy. When cooling from T_1 to T_2 , the L (liquid) phase gives rise to a solid phase α .

A kinetic model of the growth of a second phase precipitate must model diffusion of solute atoms away from the $\alpha - L$ interface, keep track of the driving force of the reaction and account for the local concentration of solute on either side of the interface. These effects are non-linearly coupled. For example, the higher this accumulation of solute atoms at the interface and/or the slower the diffusion of solute atoms in the liquid, the slower the precipitate can grow. The lower the accumulation and/or the faster the diffusion the faster it can growth. If it is assumed that the $\alpha - L$ interface remains in equilibrium ¹ the precipitation reaction is described (in 1D) by

$$\begin{aligned} \frac{\partial C}{\partial t} &= D_L \frac{\partial^2 C}{\partial z^2} \\ v_{\text{int}} &= \frac{J}{\Delta C_0} \equiv -\frac{D_L}{(1-k)C_L} \frac{\partial C}{\partial z} \Big|_{z=\text{int}} \end{aligned} \quad (6.2)$$

where k is the ratio of the equilibrium solid to liquid concentrations is $C_s/C_L = k$, obtained from the phase diagram at the quench temperature. In the second of Eqs. (6.2), the notation ΔC_0 is the concentration difference between coexisting α and L phases at equilibrium and J is the mass flux, described by Fick's first law. This example also assumes the so-called *one-sided* diffusion model, wherein diffusion is only assumed to take place –to any significant degree– in the parent (in this case liquid L) phase. Solute flux

¹this assumes that the diffusion of atoms near the interface and their attachment to the solid from the disordered liquid proceeds so rapidly that atoms have enough time to achieve their equilibrium proportions –on the solid and liquid sides of the interface– on time scales much smaller than those governing meso-scale diffusion

in the precipitate phase is thus assumed to be zero, which implies that either the precipitate diffusion coefficient $D_s \approx 0$ or $\partial C/\partial z \approx 0$. The second of Eqs. (6.2) imply that everywhere except the interface the transport of impurity atom occurs by simple mass diffusion.

The considerations above can be equivalently applied to any generic transformation where one phase emerges (precipitates) from a parent (matrix) phase. Another very important reaction that is amenable to the kinetic equations above is a so-called precipitation reaction. In the context of Fig. (6.2), this occurs when the solid α phase is cooled to a temperature below the solvus line. This then causes particles of the β phase. It should be noted that the kinetic equations discussed here will have to be expanded to involve elasticity, in cases where the precipitated and matrix phases elastically interact at phase boundaries. Such strain-induced phase transformations will be discussed further in Chapter (7).

6.2.2 Extension of sharp interface model to higher dimensions

In two or three dimension the sharp interface kinetics of Eq. (6.2) can be extended in a relatively straightforward manner. To formalize the nomenclature a bit, consider, again, a sharp interface model of single-phase solidification/precipitation in a binary alloy made of components A and B , whose phase diagram has arbitrary solidus and liquidus lines. Starting with a liquid phase and cooling into the co-existence regions will initiate solidification of the solid phase. Assuming for the moment isothermal conditions, solidification is described by solute diffusion in each of the bulk phases and two corresponding boundary conditions at the solid-liquid interface: flux conservation and the Gibb's-Thomson condition. In the limit where the interface can be assumed to be mathematically sharp, these processes are expressed, respectively, as:

$$\partial_t c = \nabla \cdot (M_{L,s} \nabla \mu) \quad (6.3)$$

$$(c_L - c_s)V_n = D_s \partial_n c|^- - D_L \partial_n c|^+ \quad (6.4)$$

$$c_{L,s} - c_{L,s}^{eq} = -\frac{2\sigma\Omega}{\Delta C_o \Lambda^\pm} \kappa - \beta V_n \quad (6.5)$$

where $c \equiv c(\vec{x}, t)$ is the concentration field, μ is the chemical potential, $M_{s,L}(c) = \Omega D_{s,L} c(1-c)/RT$ is an expression for the mobility, with Ω the molar volume of the phases, $D_{s,L}$ the solid/liquid diffusion coefficients, respectively, T the temperature and R the natural gas constant. The notation $\partial_n c|^\pm$ represents the normal derivative on the liquid/solid sides of the interface. In the last two equations, $c_{L,s}$ represents the concentrations on the liquid/solid side of the interface, σ is the surface tension of the solid-liquid interface, κ is the local interface curvature and $\Delta C_o = c_L^{eq} - c_s^{eq}$ where $c_{L,s}^{eq}$ represent the equilibrium liquid/solid concentrations at the given temperature. The parameters $\Lambda^\pm = \partial^2 G_{L,s}(c)/\partial c^2|_{c_{L,s}^{eq}}$, where $G_{L,s}$ is the molar Gibb's free energy of the phase. Finally, V_n is the local interface velocity and β is the interface kinetics coefficient

For a general binary alloy, standard but lengthy manipulations [181] can be used to express Eq. (6.5) as

$$\frac{c_{L,s}}{c_{L,s}^{eq}} = 1 - (1 - k(T)) \left[\frac{2\sigma T/L}{|m_{L,s}(T)|(1 - k(T))c_{L,s}^{eq}} \right] \kappa - \beta' V_n \quad (6.6)$$

where the constants $m_{L,s}$ are defined by

$$|m_{L,s}(T)| = \frac{RT^2(1 - k(T))[\hat{G}''(c_{L,s}^{eq})c_{L,s}^{eq}]}{\Omega L} \quad (6.7)$$

and where the partition coefficient $k(T)$ is defined by

$$k(T) = \frac{c_s^{\text{eq}}(T)}{c_L^{\text{eq}}(T)} \quad (6.8)$$

The notation β' denotes a re-scaled form of β . In general, the partition coefficient is temperature dependent as the phase diagrams are curved. The notation, $\hat{G}''(c_{L,s}^{\text{eq}})$ is the second derivative of the dimensionless molar Gibb's free energy evaluated at the equilibrium concentrations $c_{L,s}^{\text{eq}}$, and made dimensionless by redefining $\hat{G} \equiv G/RT$. The parameter L is the latent heat of fusion per volume of the alloy. For the case of an ideal dilute alloy, $G''(c_s^{\text{eq}})c_s^{\text{eq}} = G''(c_L^{\text{eq}})c_L^{\text{eq}} = 1$, $k(T) = k_e$ is a constant and $m_s = m_L \equiv m$ is a constant, where m is the slope of the liquidus line. These simplifications reduce the last of Eqs. (6.6) to

$$\frac{c_{L,s}}{c_{L,s}^{\text{eq}}} = 1 - (1 - k_e) \underbrace{\left[\frac{2\sigma T/L}{|m_L|(1 - k_e)c_L^{\text{eq}}} \right]}_{d_o} \kappa - \beta' V_n \quad (6.9)$$

where the traditional expression for the so-called solutal capillary length of the dilute ideal binary alloy is indicated.

6.3 Phase Field Model of a Binary Alloy

This section begins by proposing a free energy functional of a binary alloy that incorporates a solid-liquid order parameter field (or phase field) $\phi(\vec{x})$ and the usual solute concentration field $c(\vec{x})$ and temperature field $T(\vec{x})$. The free energy density has contributions from bulk phases and from interfaces in the system. Various binary alloy systems will be explored. The evolution of the phase, concentration and temperature fields, the equation of motion of which will be introduced in the following section, will be seen to follow directly from the global minimization of this free energy functional. Essentially, the free energy functional provides the driving force for non-equilibrium phase transformations in alloys.

6.3.1 Free Energy Functional

The complete free energy functional of an alloy must incorporate chemical and temperature effects of bulk phases as well as gradient energy terms. As was seen for dendritic growth in pure materials, the properties of dendritic growth are strongly controlled by surface tension effects. Indeed, there can be no dendritic morphology without anisotropy that appears either in the surface tension at low undercooling or the interface kinetics at high undercooling. In alloys there are two types of interfaces, one due to a transition from an ordered solid to a disordered liquid. The other can arise when crossing across a compositional transition, which can occur even within the same ordered crystal. The complete free energy functional that incorporates bulk and interface effects is given by

$$\Delta F = \int_V \left\{ \frac{|\epsilon_c \nabla c|^2}{2} + \frac{|\epsilon_\phi \nabla \phi|^2}{2} + f(\phi, c, T) \right\} dV \quad (6.10)$$

where $\epsilon_\phi \equiv \sqrt{H}W_\phi$ and $\epsilon_c \equiv \sqrt{H}W_c$ are constants that set the scale of the solid-liquid and compositional domain interface energy, respectively, and have units $[J/m]^2$, while $[H] = J/m^3$. The constants W_ϕ and W_c define the length scales of the solid-liquid interface and a compositional boundary. To make a

clearer connection with the nomenclature in Appendix (A), the bulk free energy expressions in Eqs. (6.13), (6.15), (6.17) below are separated into the barrier terms $Hg(\phi)$, which depends only on phase, and the remaining bulk free energy part, $\bar{f}_{AB}^{\text{mix}}$, which depends, in general, on c , ϕ and T . Thus,

$$f(\phi, c, T) = Hg(\phi) + \bar{f}_{AB}^{\text{mix}}(\phi, c, T) \quad (6.11)$$

In most problems the ϵ_c term can be neglected since ϵ_ϕ can be tuned to account for the total surface energy.

6.3.2 General form of $f(\phi, c, T)$

One way of constructing the free energy of an alloy is to assume that the alloy is comprised of two pure phases of A atoms and B atoms, each phase weighted by the relative concentration of A and B atoms. To this are added the interactions emerging from the fact that the alloy is, in fact, a mixture of A and B atoms in either phase. This includes both entropic and enthalpic interactions. Differences in of these affects between the solid and liquid phases are modulated the usual phase field or order parameter ϕ . These consideration can be modeled mathematically as

$$\begin{aligned} f(\phi, c, T) = & (1 - c)f_A(\phi, T) + cf_B(\phi, T) \\ & + RT \{(1 - c) \ln(1 - c) + c \ln c\} \\ & + c(1 - c) \{g(\phi)M_s(c, T) + (1 - g(\phi))M_L(c, T)\} \end{aligned} \quad (6.12)$$

The functions f_A and f_B in Eq. (6.12) are the individual energies of bulk A and B components, respectively. The logarithmic terms represent the entropic free energy of mixing. The final terms $M_s(c, T)$ and $M_L(c, \phi)$ are phenomenological additions encapsulating the net effect of the interactions between atoms of A and B . The function $g(\phi)$ is a phenomenological interpolation function with limits $g(\phi \rightarrow \phi_L = 0) = 0$ and $g(\phi \rightarrow \phi_s) = 1$. This function can be thought of as modulating the free energy between the two phases being modeled. As in the study of pure materials, the form of $g(\phi)$ must be chosen such as to reduce $f(\phi, c, T)$ to the appropriate bulk thermodynamics form for each phase. The single phase free energy that might be, for example, obtained from a thermodynamic database is related to the free energy in Eq. (6.12) by $f_L(c) = f(\phi = 0, c, T)$ for the liquid and $f_s(c) = f(\phi = \phi_s, c, T)$ for the solid.

Equation (6.12) is general and can only becomes useful if specific forms for f_A , f_B , M_s , M_L are prescribed. The following subsections present three models that chooses these functions to model three different alloy systems, a dilute binary alloy, an isomorphous binary alloy and a eutectic binary alloy.

6.3.3 $f(\phi, c, T)$ for isomorphous alloys

One of the simples alloys that Eq. (6.12) can describe is an idealized, isomorphous alloy, which has only one solid phase. An example is Cu-Ni. The free energy in Eq. (6.12) can be specialized to this situation by using f_A and f_B from Eq. (5.18). For components with similar atomic radius, it can also be assumed that nucleation barriers are the same, i.e., $H_A = H_B \equiv H$. Finally, both non-ideal terms, M_s and M_L , are set to zero. This gives,

$$\begin{aligned} f(\phi, c, T) = & (f_L(T_A) - (T - T_A)s_A^L)(1 - c) + (f_L(T_B) - (T - T_B)s_B^L)c \\ & - \left(\frac{L_A(T_A - T)}{T_A}(1 - c) + \frac{L_B(T_B - T)}{T_B}c \right) P(\phi) \\ & + Hg(\phi) + RT \{(1 - c) \ln(1 - c) + c \ln c\} \end{aligned} \quad (6.13)$$

where T_A and T_B are the melting temperature of components A and B , respectively, L_A and L_B are latent heats of fusion of A and B , respectively and s_A^L and s_B^L are the entropy densities of liquid A and B . The interpolation function $P(\phi)$ satisfies the limits $P(0) = 0$ and $P(\phi = \phi_s) = 1$. In this model atoms only interact via entropic interactions, i.e. they tend to avoid each other by randomizing their configurations on a lattice. It should be noted that the validity of Eq. (6.13) (as well as the models in the next two sections) assumes that $(T - T_A)/T_A \approx (T - T_B)/T_B$ so that the linear temperature expansions of components A and B are valid in the neighborhood of $T \approx T_A$.

Applying the common tangent criteria in Eq. (6.1) to the model in Eq. (6.13) gives a simple analytical prediction for the equilibrium solid and liquid concentrations, referred to as the (*solidus*) and liquidus lines. They are given by

$$\begin{aligned} c_s^{\text{eq}}(T) &= \frac{1 - e^{-2\Delta T_A/RT}}{e^{-2\Delta T_B/RT} - e^{-2\Delta T_A/RT}} \\ c_L^{\text{eq}}(T) &= c_s^{\text{eq}}(T) e^{-2\Delta T_B/RT} \end{aligned} \quad (6.14)$$

where $\Delta T_{A,B} \equiv L_{A,B}(T_M^{A,B} - T)/(2T_m^{A,B})$. It is recommended that interested reader try to obtain these as a way of brushing up on basic thermodynamics.

6.3.4 $f(\phi, c, T)$ for eutectic alloys

The free energy Eq. (6.12) can also be specialized for a binary eutectic alloy. Once again, the functions f_A and f_B can be set to the form in Eq. (5.18) it will be assumed that $H_A = H_B \equiv H$. If the liquid phase is assumed to be ideal, the function $M_L = 0$. A non-ideal solid can then be modeled via M_s . One example, of M_s is the empirical form $M_s = (a_1T - a_2)(2c - 1) - (a_3T + a_4)$, where the constants a_1 - a_4 are to be determined from thermodynamic databases for a particular alloy. ² This gives,

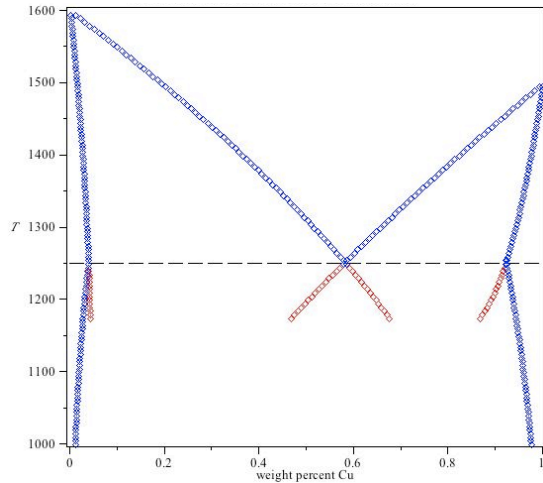


Figure 6.4: Phase diagram of Silver-copper. Blue lines represent equilibrium co-existence lines. Red lines are meta-stable projections.

$$\begin{aligned}
f(\phi, c, T) &= (f_L(T_A) - (T - T_A)s_A^L)(1 - c) + (f_L(T_B) - (T - T_B)s_B^L)c \\
&\quad - \left(\frac{L_A(T_A - T)}{T_A}(1 - c) + \frac{L_B(T_B - T)}{T_B}c \right) P(\phi) \\
&\quad + c(1 - c) \{ (a_1T - a_2)(2c - 1) - (a_3T + a_4) \} P(\phi) \\
&\quad + Hg(\phi) + RT \{ (1 - c) \ln(1 - c) + c \ln c \}
\end{aligned} \tag{6.15}$$

For the case $a_1 = 1.73$, $a_2 = 5600$, $a_3 = 9.19$, $a_4 = -44600$, a common tangent construction applied numerically to Eq. (6.15) leads to the phase diagram in can reasonably model the phase diagram in Fig. (6.4), which is a fairly good approximation of the of Ag-Cu phase diagram.

6.3.5 $f(\phi, c, T)$ for dilute binary alloys

An important practical limit of the ideal free energy in Eq. (6.13) is the limit of very small solute concentrations. Expanding the logarithms in Eq. (6.13) and taking the limits $c \ll 1$ gives

$$\begin{aligned}
f(\phi, c, T) &= Hg(\phi) + f_L(T_A) + cf_L(T_B) - s_L^A(T - T_A) - s_L^B(T - T_B)c \\
&\quad + \frac{L_A(T - T_A)}{T_A}P(\phi) + \frac{L_B(T - T_B)}{T_B}cP(\phi) + RT \{ c \ln c - c \}
\end{aligned} \tag{6.16}$$

Expanding temperature as $T = T_A + \Delta T$, where $\Delta T \equiv T - T_A$, and neglecting $\Delta T c \ll 1$ further simplifies Eq. (6.16) to

$$f(\phi, c, T) = Hg(\phi) + f_L(T_A) - \Delta TS(\phi) + E(\phi)c + RT \{ c \ln c - c \} \tag{6.17}$$

where

$$\begin{aligned}
S(\phi) &= s_A^L - \frac{L_A}{T_A}P(\phi) \\
E(\phi) &= (T_B - T_A) \left(s_B^L - \frac{L_B}{T_B}P(\phi) \right)
\end{aligned} \tag{6.18}$$

The above derivation neglects the $f_L(T_B)c$ term, which is reasonable only if $f_L(T_A)$ is not too different from $f_L(T_B)$. The function $S(\phi)$ interpolates the bulk entropy from liquid to solid via $P(\phi)$, while $E(\phi)$ modulates the change of internal energy due to a solute concentration c . As mentioned previously, there is a certain degree of freedom in choosing their specific form, so long as the quantities they interpolate attain their thermodynamically predicted far field values. Moreover, as far as the thermodynamics of the bulk phases are concerned, it does not even matter if a *different* $P(\phi)$ is used in $S(\phi)$ than that in the internal energy $E(\phi)$. It will be shown in section (6.7) how this property can be exploited to significantly simplify the calculation of surface tension for binary alloy phase field model using Eq. (6.17).

6.4 Equilibrium Properties of Free Energy Functional

As discussed previously, the bulk free energy of a phase is captured in the non-gradient term of the phase field free energy. Inclusion of the gradient expressions further makes it possible to model the surface

²The constants a_1 - a_4 used here are different from the corresponding variables used in the Landau free energy construction in Chapter 1.

tension of equilibrium interfaces. In order to compute the surface tension associated with the free energy functional of Eq. (6.10), it is necessary to first calculate the corresponding equilibrium concentration and phase field profiles. At equilibrium, a flat crystal-melt interface will be characterized by a constant chemical potential $\mu_{\text{Eq}}^{\text{F}}$ and corresponding steady state profiles for concentration, $c_o(x)$, and phase field, $\phi_o(x)$. Minimizing the grand potential with respect to c and the free energy in with ϕ gives the equilibrium profiles ϕ_o and c_o as the simultaneous solutions of the following equations:

$$\begin{aligned} \mu_{\text{Eq}}^{\text{F}} &= \frac{\delta F(\phi, c)}{\delta c} = \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(c_o, \phi_o)}{\partial c} - \epsilon_c^2 \frac{d^2 c_o}{dx^2} \\ \left. \frac{\delta F}{\delta \phi} \right|_{\phi_o} &= W_\phi^2 \frac{d^2 \phi_o}{dx^2} - g'(\phi_o) - \frac{1}{H} \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_o, c_o)}{\partial \phi} = 0 \end{aligned} \quad (6.19)$$

Where $\mu_{\text{Eq}}^{\text{F}}$ is obtained by considering the equilibrium of the two phases from the interface. The partial derivatives in Eq. (6.19) can be replaced by ordinary derivatives as the profile are one dimensional in equilibrium. Equations (6.19) must be solved subject to the boundary conditions $c_o(x \rightarrow \infty) = c_L$, $c_o(x \rightarrow -\infty) = c_s$, $\phi_o(x \rightarrow \infty) = 0$ and $\phi_o(x \rightarrow -\infty) = \phi_s$.

The far field values $\{c_s, c_L, \phi_s, \phi_L = 0\}$ are determined by considering Eqs. (6.19) far from the interface –in the of the bulk material– where derivatives vanish. The bulk free energy $f(\phi, c)$ (T dependence suppressed for simplicity) is first minimized with respect to ϕ giving two solutions, $\phi_s(c)$ for the solid and $\phi_L = 0$ in the liquid (this assumes a fourth order ϕ expansion of $f(\phi, c)$). Substituting $\phi_s(c)$ and $\phi_L = 0$ back into the bulk free energy gives $f_s(c) \equiv f(\phi_s(c), c)$ for the solid and $f_L(c) \equiv f(\phi_L = 0, c)$ for the liquid. Applying Eq. (6.1) to $f_s(c)$ and $f_L(c)$ gives $\mu_{\text{Eq}}^{\text{F}}$, c_s and c_L , with which the corresponding order parameters, ϕ_s and $\phi_L = 0$ can also be computed. It should be emphasized that while the discussion has been in the context of a solid-liquid interface, the procedure above can be applied equivalently to coexisting solid phase or other two phase interfaces as well. Moreover, while the discussion thus far has assumed that $\phi_L = 0$, different choices of $g(\phi)$ and $\bar{f}_{\text{AB}}^{\text{mix}}(\phi, c)$ can lead to minima where $\phi_L \neq 0$.

6.4.1 Simple example of a “toy” model

These above ideas are best illustrated by an example. Consider an example of a “toy” bulk free energy of the form

$$f(\phi, c) = \frac{a_0}{2}(c - c_1)^2 - \frac{a_2}{2}(c - c_2)\phi^2 - \frac{a_4}{4}\phi^4 + \frac{\phi^6}{4} \quad (6.20)$$

where the constants a_0, a_2, a_4 are in principle temperature dependent. This form of free energy is chosen specifically to illustrate the generality of the ideas discussed herein to phase transformations different from solidification. Indeed, this form of free energy density is used in Ref. [201] to model precipitation of multiple ordered structures from a matrix phase of a binary alloy. By construction it represents each phase by a quadratic approximation in concentration. The left frame of Fig. (6.5) shows $f(\phi, c)$ for the constants $a_0 = 30, a_2 = -4, a_4 = 2.8, c_1 = 0.3, c_2 = 0.2$.

The bulk liquid and solid order parameter and found by minimizing $f(\phi, c)$ with respect to ϕ . This gives

$$\phi_L = 0, \quad \phi_s = \pm \frac{1}{2} \sqrt{2a_4 + 2\sqrt{a_4^2 + 4a_2(c - c_2)}} \quad \phi_q = \pm \frac{1}{2} \sqrt{2a_4 - 2\sqrt{a_4^2 + 4a_2(c - c_2)}} \quad (6.21)$$

where ϕ_L represents the disordered or matrix phase and ϕ_s and ϕ_q four ordered variants (i.e. precipitates). Here only ϕ_s is considered. Note that ϕ_s , or is concentration dependent (contrast this to the case of pure

model in section (5.3)). Substituting ϕ_L and ϕ_s back into $f(\phi, c)$ gives the chemical free energies of the bulk solid and liquid,

$$\begin{aligned} f_L(c) \equiv f(\phi = \phi_L = 0, c) &= \frac{a_0}{2} (c - c_1)^2 \\ f_s(c) \equiv f(\phi = \phi_s(c), c) &= \frac{a_0}{2} (c - c_1)^2 - \frac{a_2}{8} (c - c_2)R(c) - \frac{a_4}{64} R(c)^2 + \frac{1}{384} R(c)^3 \end{aligned} \quad (6.22)$$

where

$$R(c) \equiv 4\phi_s(c)^2 \quad (6.23)$$

The right frame of Fig. (6.5) plots $f_s(c)$ and $f_L(c)$. It should be clear that $f_s(c)$ is the $\phi = \phi_s(c)$ contour of $f(\phi, c)$ and $f_L(c)$ is the $\phi = \phi_L = 0$ contour. Applying the common tangent rule in Eq. (6.1) gives the

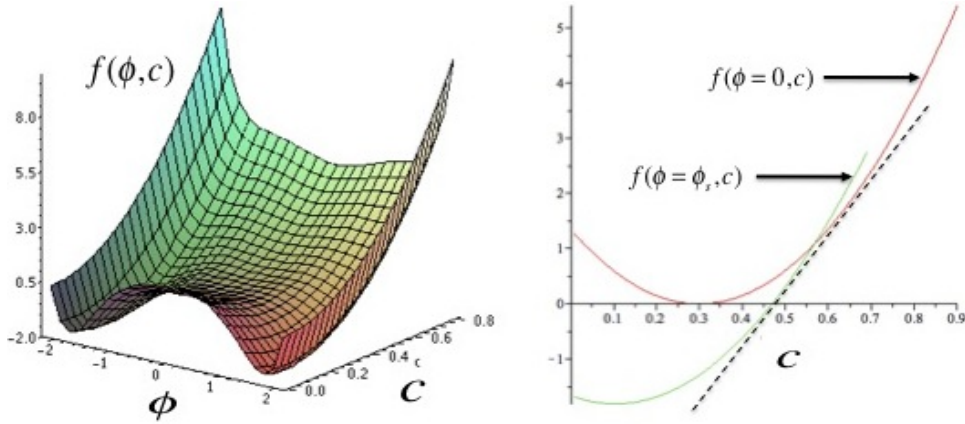


Figure 6.5: (Left) Free energy landscape of an alloy versus composition c and ϕ . (Right) free energies of solid, $\phi = \phi_s$ contour, and liquid, $\phi = 0$ contour. The dashed line is the common tangent line.

compositions c_L and c_s , and $\mu_{\text{Eq}}^{\text{F}}$, the slope of the common tangent line, shown by the dashed line in the figure.

Following the calculation of $\{\phi_s, \phi_L, c_s, c_L, \mu_{\text{Eq}}^{\text{F}}\}$, these values served a boundary conditions to the two differential equations in Eq. (6.19) for the equilibrium profiles $c_o(x)$ and $\phi_o(x)$. In the special case when $\epsilon_c = 0$, the first of Eq. (6.19) shows that the equilibrium concentration field is actually "slaved" to the phase field ϕ , i.e.

$$c_o(x) = c_o(\phi_o(x)) \quad (6.24)$$

This then makes the second equation an ordinary [non-linear] differential equation in ϕ_o , i.e.

$$W_\phi^2 \frac{d^2 \phi_o}{dx^2} - g'(\phi_o) - \frac{1}{H} \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_o, c_o(\phi_o))}{\partial \phi} = 0 \quad (6.25)$$

The example in this subsection is of relatively little practical value but it serves to illustrate that the process of calculating the equilibrium properties and profiles for the order parameter and concentration, while straightforward, can be quite tedious if not impossible, depending on the order of the polynomial part of the free energy density $f(\phi, c)$. Simplicity of the algebra involved in calculating the thermodynamics of the phase field free energy is a key factor that guides the choice of interpolation functions. This will be highlighted below in a case study.

6.4.2 Calculation of surface tension

The calculation of the surface tension of an alloy interface is calculated by considering the surface excess of the grand potential in a system with a planar interface. Formally,

$$\sigma = \int_{-\infty}^{\infty} \{\Omega(\phi_o, c_o) - \Omega_{\text{eq}}\} dx \quad (6.26)$$

where the grand potential Ω and its equilibrium value Ω_{eq} are defined by

$$\begin{aligned} \Omega(\phi_o, c_o) &= \frac{\epsilon_\phi^2}{2} \left(\frac{\partial \phi_o}{\partial x} \right)^2 + f(\phi_o, c_o) - \mu_{\text{Eq}}^{\text{F}} c_o \\ \Omega_{\text{eq}} &= f(c_s) - \mu_{\text{Eq}}^{\text{F}} c_s = f_L(c_L) - \mu_{\text{Eq}}^{\text{F}} c_L \end{aligned} \quad (6.27)$$

Equation (6.26) is evaluated in two pieces, one from $-\infty \leq x \leq 0$ and the other from $0 \leq x \leq \infty$. Doing this and substituting, for example, Eq. (6.11) gives

$$\begin{aligned} \sigma &= \int_{-\infty}^0 \left(\frac{\epsilon_\phi^2}{2} \left(\frac{\partial \phi_o}{\partial x} \right)^2 + H [g(\phi_o) - g_m] + [\bar{f}_{\text{AB}}^{\text{mix}}(\phi_o, c_o) - f_s(c_s)] - \mu_{\text{Eq}}^{\text{F}} [c_o(x) - c_s] \right) dx \\ &+ \int_0^{\infty} \left(\frac{\epsilon_\phi^2}{2} \left(\frac{\partial \phi_o}{\partial x} \right)^2 + H [g(\phi_o) - g_m] + [\bar{f}_{\text{AB}}^{\text{mix}}(\phi_o, c_o) - f_L(c_L)] - \mu_{\text{Eq}}^{\text{F}} [c_o(x) - c_L] \right) dx \end{aligned} \quad (6.28)$$

where $g_m \equiv g(\phi_s) = g(\phi_L)$ is the minimum of the potential barrier between the two phases.

Equation (6.28) is simplified by multiplying both side of the second of Eqs. (6.19) by $d\phi_o/dx$ and integrating from $-\infty$ to a point x . This gives

$$\frac{W_\phi^2}{2} \left(\frac{d\phi_o}{dx} \right)^2 - \int_{-\infty}^x g'(\phi_o) \frac{d\phi_o}{dx} dx - \frac{1}{H} \int_{-\infty}^x \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}}{\partial \phi} \frac{d\phi_o}{dx} dx = 0 \quad (6.29)$$

The integrand of the third term in Eq. (6.29) can be expanded as

$$\frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_o, c_o)}{\partial \phi} \frac{d\phi_o}{dx} = \frac{d\bar{f}_{\text{AB}}^{\text{mix}}}{dx} - \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_o, c_o)}{\partial c} \frac{dc_o}{dx} = \frac{d\bar{f}_{\text{AB}}^{\text{mix}}}{dx} - \mu_{\text{Eq}}^{\text{F}} \frac{dc_o}{dx}, \quad (6.30)$$

which is substituted into Eq. (6.29) to give

$$\begin{aligned} \frac{\epsilon_\phi^2}{2} \left(\frac{d\phi_o}{dx} \right)^2 &= H [g(\phi_o) - g_m] + [\bar{f}_{\text{AB}}^{\text{mix}}(\phi_o, c_o) - f_s(c_s)] - \mu_{\text{Eq}}^{\text{F}} [c_o(x) - c_s] \\ &= H [g(\phi_o) - g_m] + [\bar{f}_{\text{AB}}^{\text{mix}}(\phi_o, c_o) - f_L(c_L)] - \mu_{\text{Eq}}^{\text{F}} [c_o(x) - c_L] \end{aligned} \quad (6.31)$$

where $W_\phi^2 H = \epsilon_\phi^2$ was used. The first line of Eq. (6.31) is obtained by integrating the second equation in Eq. (6.19) from $-\infty$ to x , while the second line is obtained by integrating from x to ∞ . Substituting the two [equivalent] right hand sides of Eq. (6.31) for the corresponding expressions in Eq. (6.28) gives

$$\sigma = W_\phi^2 H \int_{-\infty}^{\infty} \left(\frac{d\phi_o}{dx} \right)^2 dx \quad (6.32)$$

Equation (6.32) is analogous to Eq. (3.18) for the surface tension of model A. The main difference for an alloy is that the equilibrium phase field ϕ_o now has a concentration dependence through the interface for an alloy. While this is a physical result, it is clearly tedious to determine c_o , particularly for a highly non-linear form of $\bar{f}_{AB}^{\text{mix}}$ or if $\epsilon_c \neq 0$. A more serious complication arises in Eqs. (6.28) and (6.31) when one wishes to emulate a particular surface energy with a diffuse interface. It turns out that for realistic values of interface energy, the extra terms on in the large round brackets of Eq. (6.31) limit the largest interface width that can be used to a few nanometers. This is shown elegantly by Kim and co-workers in Ref.[119]. Clearly this is a limiting feature if one wishes to consider matter of numerical efficiency. Way of getting around this limitation will be discussed below.

6.5 Phase Field Dynamics

The dynamics of the alloy solidification proceed analogously to those in a pure material. At low rates of solidification, the diffusion of heat occurs much more rapidly than the diffusion of solute impurities in a binary alloy. As a result, the temperature can be considered a "frozen" on the time scale of mass transport, which this become the rate limiting step in the solidification process. Under these conditions, it is reasonable to consider only solute diffusion and phase field dynamics. It is straightforward to extend the equations below to include temperature evolution by including the enthalpy entropy production, Eq. (5.26), and enthalpy, Eq. (5.28). This is left to the reader.

The changes in solute concentration are governed by the well-know mass conservation equation

$$\frac{\partial c}{\partial t} = -\nabla \cdot \vec{J} \quad (6.33)$$

where \vec{J} denotes the flux of solute. When $\vec{J} = -\nabla c$, the usual Fick's law of diffusion is recovered. In more general cases, however, the flux of solute is given by $\vec{J} = -M(c, \phi)\nabla\mu$ where $M(c, \phi)$ is the mobility and $\mu \equiv \delta F/\delta c$ is a generalized inter-diffusion potential [14, 90]. This form of the flux is derived from the entire free energy functional and considers bulk and gradient energy contributions. For ideal alloys $M(c, \phi) = D_L q(\phi, c) = D_L(\Omega/RT)Q(\phi)c(1-c)$, where Ω is the molar volume of the alloy and D_L is the liquid phase diffusion. The function $Q(\phi)$ interpolates the diffusion across the interface. It can either be determined experimentally – a difficult task – or constructed so that the alloy phase field equations emulate the sharp interface models described earlier in this chapter. Substituting the inter-diffusion potential into the mass conservation gives

$$\begin{aligned} \frac{\partial c}{\partial t} &= D_L \nabla \cdot \{q(\phi, c)\nabla\mu\} \\ &= D_L \nabla \cdot \left\{ q(\phi, c)\nabla \left(\frac{\partial \bar{f}_{AB}^{\text{mix}}(c, \phi)}{\partial c} - \epsilon_c^2 \nabla^2 c \right) \right\} \end{aligned} \quad (6.34)$$

where $q(\phi, c)$ is given by

$$q(\phi, c) = Q(\phi) / \frac{\partial^2 \bar{f}_{AB}^{\text{mix}}(\phi, c)}{\partial c^2} \quad (6.35)$$

with $Q(\phi)$ being used to interpolate mobility between different phases. This function is yet another interpolation function that can either (a) be in theory fit to microscopic measurements or (b) used as a degree of freedom to help map the behavior of a phase field model onto the corresponding sharp interface model.

In analogy with the case for a pure materials, the second equation in the phase field model for binary alloys is the standard first order equation describing the dissipative dynamics of the phase field ϕ , i.e.,

$$\tau \frac{\partial \phi}{\partial t} = -\frac{\delta F}{\delta \phi} = W_\phi^2 \nabla^2 \phi - \frac{dg}{d\phi} - \frac{1}{H} \frac{\partial \bar{f}_{AB}^{\text{mix}}(c, \phi)}{\partial \phi} \quad (6.36)$$

where $\tau \rightarrow 1/(M_L H)$. It should be noted that the alloy phase field model is another instance of a "model C" discussed for a pure materials; it comprises a flux conserving diffusion equation coupled to an equation for a non-conserved order parameter. For simplicity, Eq. (6.36) has omitted surface energy anisotropy. To model anisotropy, it is necessary to modify the gradient term in Eq. (6.36) and τ according to

$$\begin{aligned} W_\phi^2 \nabla^2 \phi &\rightarrow \nabla \cdot \left(\tilde{W}^2(\theta) \nabla \phi \right) - \partial_x \left[\tilde{W}(\theta) \tilde{W}'(\theta) \partial_y \phi \right] + \partial_y \left[\tilde{W}(\theta) \tilde{W}'(\theta) \partial_x \phi \right] \\ \tau &\rightarrow \tilde{\tau}(\theta) \end{aligned} \quad (6.37)$$

where $\tilde{W}(\theta) = W_\phi A(\theta)$ and $\tilde{\tau}(\theta) = \tau A^2(\theta)$ with the form of $A(\theta)$ given by Eq. (5.25).

6.6 Thin Interface Limits of Alloy Phase Field Models

The thin interface limit of Eqs. (6.34) and (6.36) is obtained by connecting these equations to the alloy model in Appendix (A), which is of the same form as the one studied here (when the notational change $H \rightarrow w$ is made). In the limit when the phase field interface becomes "sharp" (i.e. $W_\phi \ll d_o$) the alloy phase field equations presented above rigorously reduce to the corresponding sharp interface kinetic equations presented earlier in this chapter. This limit, however, is of little practical value in 2D or 3D numerical simulations of complex microstructure formation due to the grid resolution required and the very small associated time scale τ required to eliminate interface kinetics. If there is any hope of using phase field models quantitatively at experimentally relevant microstructure growth rates two ingredients are required. The first is the use of a diffuse interface W_ϕ , which can dramatically increase the usefulness of efficient numerical algorithm such as adaptive re-meshing. The second is the ability to self-consistently and easily relate τ to W_ϕ to a unique surface tension and interface kinetics coefficient (for example, $\beta = 0$), even in the limit $W_\phi \sim d_o$.

Emulating an effective sharp interface limit with a diffuse phase field interface is more difficult for an alloy than it is for a pure material for two main reasons. As already discussed at the end of section (6.4.2) the coupling of solute and order parameter fields in the steady state solutions makes the determination of surface energy quite tedious. Another issue deals with the fact that it is not possible to self-consistently relate the surface energy to the nucleation barrier height ($\sim \lambda^{-1}$) and the interface thickness (W_ϕ) for arbitrarily diffuse interface widths. This has been shown quite nicely by Kim and co-workers [119]. As will be shown in the examples below, this limitation can be removed by eliminating $\partial \bar{f}_{AB}^{\text{mix}}(\phi_o, c_o)/\partial \phi$ at steady state. This is done either by the choice of interpolation functions, as is done by Karma, Plapp and co-workers [112, 57, 74], or by introducing fictitious concentration field, as is done by Kim [122] and others (see section (6.9)).

The second difficulty arising in attaining a desired thin interface limit of an alloy phase field model arises because solute diffusion in the solid phase is essentially zero on the time scales over which microstructure selection occurs. This so-called *two-sided* or *non-symmetric* diffusion gives rise to spurious kinetic effects to the standard sharp interface model of section (6.2.2). Specifically, it contains extra terms in the flux conservation equations that scale with the interface width and there is a jump in the chemical

potential that scales with the interface width, which makes the Gibbs-Thomson conditions two sided. The generic form of these so-called “corrections” (referred to in Section (A.8) as ΔF , ΔJ and ΔH) was already discussed in section (5.6) and shown to identically vanish for pure materials. In alloys they do not formally vanish as they are physically linked to solute trapping effects that emerge due to the existence of a finite interface thickness. Typically, since these correction terms scale with the dendrite tip speed and the interface width, they are essentially irrelevant at low solidification rates and a realistic values of W_ϕ . On the other hand, as discussed previously, *efficient* simulations of phase field models require the use of rather diffuse interfaces, which can be much larger than the solutal capillary length. As a result, to perform quantitative phase field simulations it is critical that these kinetic corrections must be made to vanish, otherwise they will be artificially amplified.

It turns out that an efficient way to make the correction terms ΔF , ΔJ and $\Delta H = 0$ are vanish requires altering the variational form of Eqs. (6.34) and (6.36). Specifically, this involves the addition of a so-called *anti-trapping* current to the mass transport equation. The general idea of the anti-trapping flux is to correct for the spurious solute trapping cause by the diffuse interface. Along with the freedom to choose the form of the function that interpolates diffusion through interface, there are enough degrees of freedom to eliminate the spurious kinetics in the thin interface limit. This “illegal” move of adding an unphysical source of flux addresses the computational inefficiency that arises from simulating the phase field model with a “sharp interface” (i.e. interface width of order 1-2 nm) by morphing the original model into a mathematical tool that merely emulates the results of a sharp interface efficiently, even when the interface width utilized is rather diffuse –or “thin”.

A detailed discussion of how an alloy phase field model can emulate the sharp interface model of Eqs. (6.34) and (6.36), as well as the subtleties of eliminating undesired kinetics effects is discussed in detail in Appendix (A). For the reader wishing to forego the mathematical details, it is sufficient to review the first sections of Appendix (A) and summary in section (A.9). The ideas discussed in those subsections are applied to a specific example in section (6.7).

6.7 Case Study: Analysis of a Dilute Binary Alloy Model

It is instructive at this work through a concrete example that explicitly illustrates the ideas discussed thus far in this chapter. The starting point of this section is the free energy functional in Eq. (6.10) with $\bar{f}_{AB}^{\text{mix}}(\phi, c, T)$ given in Eq. (6.17), and the dynamical equations of Eq. (6.34) and (6.36). The idea here is to analyze model’s properties, including its thin interface properties, a pre-requisite limit if one wishes to simulate low undercooling regime quantitatively. Readers of the phase field literature will recognize the development of this model as the special case studied in Echebarria et. al. [57].

6.7.1 Interpolation functions for $f(\phi, c)$

It should be clear that the choice of $P(\phi)$ that modulates the bulk behavior of $S(\phi)$ and $G(\phi)$ is irrelevant; the only requirement is that all choices have the same bulk limits. In fact, $S(\phi)$ and $G(\phi)$ can each have its own, separate interpolation function, i.e.,

$$\bar{f}_{AB}^{\text{mix}}(\phi, c, T) = \frac{RT_m}{\Omega} [c \ln c - c] + f^A(T_m) - \Delta T \left[s_L - \frac{L}{T_m} \tilde{g}(\phi) \right] + [\epsilon_L + \Delta \epsilon \bar{g}(\phi)] c \quad (6.38)$$

where $\tilde{g}(\phi)$ is some function that interpolates entropy between solid ($\phi = \phi_s$) and liquid ($\phi = 0$), while $\bar{g}(\phi)$ in another function that similarly interpolates the internal energy between its two bulk values. Other

definitions are $T_m \equiv T_A$ is the melting temperature of species A , $\Delta T = T - T_m$, R is the natural gas constant and Ω is the molar volume of the alloy ³. The parameter s_L is the entropy of the liquid, $\epsilon_L(\epsilon_s)$ are the internal energy of the liquid(solid), $\Delta\epsilon = \epsilon_s - \epsilon_L$ and L is the latent heat of fusion.

The function $\bar{g}(\phi)$ is constructed to satisfy $\bar{g}(\phi = 0) = 0$, $\bar{g}(\phi = \phi_s) = 1$ and $0 < \bar{g}(\phi) < 1$ for other values of ϕ . An explicit form that will be used in the calculations that follow is $\bar{g}(\phi)$ is chosen as $\bar{g}(\phi) = \phi^3(6\phi^2 - 15\phi + 10)$. The function $\tilde{g}(\phi)$ is chosen to have the same limits as $\bar{g}(\phi)$. Its explicit form is chosen to be

$$\bar{g}(\phi) = \frac{1}{\ln k} \ln [1 - (1 - k)\tilde{g}(\phi)] \quad (6.39)$$

where k is the partition coefficient of the dilute binary alloy. It appears that the specific choice of $\bar{g}(\phi)$ in Eq. (6.39) has been dropped out of thin air. It will be appreciated below that $\bar{g}(\phi)$ has, in fact, been "back-engineered" so that the phase field and concentration fields completely decouple at steady state for a flat, stationary interface, a "trick" first used in Ref. [57].

6.7.2 Equilibrium Phase Diagram

Consider the mean field properties of the bulk terms of the free energy Eq. (6.38), starting first with the calculation of the equilibrium phase diagram of this alloy. The starting point is the generalized bulk chemical potential

$$\mu \equiv \frac{\partial \bar{f}_{AB}^{\text{mix}}(\phi, c)}{\partial c} = \frac{RT_m}{\Omega} \ln c + \epsilon_L + \Delta\epsilon \bar{g}(\phi) \quad (6.40)$$

The chemical potential within each phase Eq. (6.40) is written as

$$\begin{aligned} \mu_s^{\text{eq}} &= \frac{RT_m}{\Omega} \ln c_s + \Delta\epsilon + \epsilon_L \\ \mu_L^{\text{eq}} &= \frac{RT_m}{\Omega} \ln c_L + \epsilon_L \end{aligned} \quad (6.41)$$

where c_s and c_L represent equilibrium solid and liquid concentrations at temperature T . In equilibrium $\mu = \mu_{\text{eq}}$ and so setting $\mu_s^{\text{eq}} = \mu_L^{\text{eq}} \equiv \mu_{\text{eq}}$ gives the equilibrium partition coefficient, i.e.

$$k \equiv \frac{c_s}{c_L} = e^{-\Omega\Delta\epsilon/RT_m} \quad (6.42)$$

or, equivalently, $\Delta\epsilon\Omega/RT_m = -\ln k$.

Solving $\mu_{\text{eq}} = \mu_s^{\text{eq}}$, $\mu_{\text{eq}} = \mu_L^{\text{eq}}$ and $f(c_s, \phi_o = \phi_s) - f(c_L, \phi_o = 0) = \mu_{\text{eq}}(c_L - c_s)$, gives μ_{eq} and the liquidus line of a dilute ideal binary alloy. The results is

$$T = T_m - \underbrace{\left[\frac{RT_m^2(1-k)}{L\Omega} \right]}_{m_L} c_l \quad (6.43)$$

where the liquidus slope of the alloy, m_L , is indicated in the large square bracket.

³The division by Ω merely makes the units of the free energy density from $J/mole$ to $J/volume$, to make it appropriate for integration in the free energy functional.

6.7.3 Steady state c_o and ϕ_o profiles

The equilibrium (i.e. steady state) concentration profile across a stationary planar solid-liquid interface is found by considering the equilibrium the chemical potential μ_{eq} . This is a constant given by

$$\mu_{\text{eq}} = \frac{RT_m}{\Omega} \ln c_o(x) + \epsilon_L + \Delta\epsilon\bar{g}(\phi_o(x)) \quad (6.44)$$

where $c_o(x)$ is the equilibrium concentration field across the solid liquid interface of some grain and $\phi_o(x)$ tracks the planar steady state interface profile between solid and liquid. Solving for $c_o(x)$ and using the second of Eqs (6.41) to eliminate $\epsilon_L - \mu_{\text{eq}}$ gives

$$\frac{c_o(x)}{c_o^l} \equiv \frac{c_o(\phi_o(x))}{c_o^l} = e^{[\ln k\bar{g}(\phi_o(x))]} \quad (6.45)$$

where c_o^l has been defined as the reference liquid concentration at a given quench temperature. Using Eq. (6.39) the steady state concentration can equivalently be written in terms of $\tilde{g}(\phi_o)$,

$$\frac{c_o(\phi_o(x))}{c_o^l} = [1 - (1 - k)\tilde{g}(\phi_o(x))] \quad (6.46)$$

The equilibrium phase field profile, $\phi_o(x)$ across a planar solid-liquid interface (parameterized by x) is given by solving the Euler Lagrange equation $\delta F/\delta\phi = 0$ in 1D,

$$W_\phi^2 \frac{d^2\phi_o}{dx^2} - \frac{\partial g(\phi_o)}{\partial\phi_o} - \left[\frac{\Delta TL}{T_m} \frac{\partial\tilde{g}(\phi_o)}{\partial\phi_o} + \Delta\epsilon \frac{\partial\bar{g}(\phi_o)}{\partial\phi_o} c_o(\phi_o) \right] = 0 \quad (6.47)$$

(where $W_\phi = \sqrt{\epsilon_\phi/H}$). Expressing L in terms of ΔT using Eq. (6.43) and using Eqs. (6.39) and (6.45) shows that the large bracketed term in Eq. (6.47) actually vanish, i.e.,

$$\frac{-\Delta TL}{T_m} \left[\tilde{g}'(\phi_o) + \frac{T_m\Delta\epsilon}{L\Delta T} \bar{g}'(\phi_o) c_o(\phi_o) \right] = 0 \quad (6.48)$$

(primes denote derivatives with respect to ϕ_o). The steady state phase field profile is thus determined analytically by solving

$$W_\phi^2 \frac{d^2\phi_o}{dx^2} - \frac{\partial g(\phi_o)}{\partial\phi_o} = 0 \quad (6.49)$$

For $g(\phi) = \phi^2(1 - \phi)^2$, the solution of Eq. (6.49) is a simple hyperbolic tangent profile, $\phi_o(x) = [1 - \tanh(x/\sqrt{2}W_\phi)]/2$, where x denotes the distance normal to the interface. It should be emphasized that it is only possible to make ϕ_o independent of $c_o(x)$ for the specific relationship between $\bar{g}(\phi)$ and $\tilde{g}(\phi)$ made in Eq. (6.39). For general choices of these functions, $\phi_o(x)$ will depend on $c_o(x)$. Substituting $\phi_o(x)$ into Eq. (3.18) gives the surface tension of this dilute binary alloy model,

$$\sigma_{sl} = \frac{\sqrt{2}}{6} W_o H \quad (6.50)$$

Comparing Eq. (6.49) and the Eq. (A.40) in section (A.6.1) shows that Eq. (6.49) is the same as the lowest order phase field equation (A.40). The lowest order phase field formally determines the surface

tension of the phase field model (i.e. Eq. (6.50)) only in the limit of small W_ϕ/d_o . It turns out, however, that the property in Eq. (6.48) actually makes it possible to model the surface energy of this model with Eq. (6.50) for *all* values of the interface width W_ϕ ⁴.

6.7.4 Dynamical equations

It is instructive to re-cast the dynamical phase field equations (6.34) and (6.36) for the dilute alloy into a form that will be useful when examining the model's thin interface limit. This is done by first re-expressing $\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c, T)/\partial \phi$ as follows:

$$\begin{aligned}
\frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c, T)}{\partial \phi} &= \frac{\Delta T L}{T_m} \tilde{g}'(\phi) + \Delta \epsilon \bar{g}'(\phi) c & (6.51) \\
&= \frac{\Delta T L}{T_m} \tilde{g}'(\phi) - \Delta \epsilon \frac{(1-k)\tilde{g}'(\phi)}{\ln k [1 - (1-k)\tilde{g}'(\phi)]} c \\
&= \left(\frac{\Delta T L}{T_m} - \frac{c_o^l \Delta \epsilon (1-k)}{\ln k} \frac{c}{c_o(\phi)} \right) \tilde{g}'(\phi) \\
&= \left(\frac{c_o^l \Delta \epsilon (1-k)}{\ln k} \right) \left(\frac{\ln k \Delta T L}{c_o^l T_m \Delta \epsilon (1-k)} c_o(\phi) - c \right) \frac{\tilde{g}'(\phi)}{c_o(\phi)} \\
&= \frac{c_o^l \Delta \epsilon (1-k)}{\ln k} \{ c_o(\phi) - c \} \frac{\tilde{g}'(\phi)}{c_o(\phi)}
\end{aligned}$$

where Eq. (6.39) was used to eliminate $\bar{g}'(\phi)$ from the second line of Eq. (6.51), while Eq. (6.46) was used to go from the third to the fourth line. Using the liquidus line to express the latent heat as $L = RT_m^2(1-k)/(\Omega m_L)$ and eliminating L from the fifth line results in the sixth line. Use is also made of the identity from the equilibrium phase diagram, $\Delta T/(m_L c_o^l) = 1$, and the definition of $\ln k$ following Eq. (6.42). It is noted that Eqs. (6.39) and (6.46) can also be used to write $\tilde{g}'(\phi)/c_o(\phi) = -[\ln k/(1-k)] \bar{g}'(\phi)/c_o^l$, which can be used to express Eq. (6.51) in the equivalent form

$$\begin{aligned}
\frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c, T)}{\partial \phi} &= -\Delta \epsilon (c_o(\phi) - c) \bar{g}'(\phi) & (6.52) \\
&= -\frac{RT_m \ln k}{\Omega} \frac{\Delta T}{m_L c_o^l} (c - c_o(\phi)) \bar{g}'(\phi)
\end{aligned}$$

The form of $\partial \bar{f}_{\text{AB}}^{\text{mix}}/\partial \phi$ can be further simplified by eliminating $c(\equiv c(\vec{x}))$ in Eq. (6.52) with respect to a dimensionless chemical potential, u , defined relative to the equilibrium chemical potential of the liquid μ_{eq} (e.g. Eq. (6.41)), i.e.,

$$\begin{aligned}
u &= \frac{\Omega}{RT_m} (\mu - \mu_E) & (6.53) \\
&= \frac{\Omega}{RT_m} \left(\frac{RT_m}{\Omega} \ln c + \Delta \epsilon \bar{g}(\phi) + \epsilon_L - \frac{RT_m}{\Omega} \ln c_o^l - \epsilon_L \right) \\
&= \ln \left(\frac{c}{c_o^l} \right) - \ln k \bar{g}(\phi)
\end{aligned}$$

⁴This is possible because for the particular choices of $\bar{g}(\phi)$ and $\tilde{g}(\phi)$ made here, $\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c)/\partial \phi$ vanishes to all orders for a steady state corresponding to a flat stationary interface.

$$= \ln \left(\frac{c}{c_o^l [1 - (1-k)\tilde{g}(\phi)]} \right)$$

where the definition of μ from Eq. (6.40) has been used in the first line of Eq. (6.53), while the relation $\ln k = -\Omega/RT_m$ has been used in the second line and Eq. (6.39) has been used in the third line. Equations (6.46) and (6.53) can be used to write

$$\begin{aligned} \left(\frac{c(\bar{x})}{c_o^l} - \frac{c_o(\phi)}{c_o^l} \right) \bar{g}'(\phi) &= [1 - (1-k)\tilde{g}(\phi)] (e^u - 1) \bar{g}'(\phi) \\ &= -\frac{(1-k)}{\ln k} (e^u - 1) \bar{g}'(\phi) \end{aligned} \quad (6.54)$$

where \bar{g} has been eliminated in favour of \tilde{g} using Eq (6.39). Substituting Eq. (6.54) in Eq. (6.52) gives

$$\begin{aligned} \frac{1}{H} \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c, T)}{\partial \phi} &= \frac{RT_m \ln k}{\Omega H} \frac{\Delta T}{m_L c_o^l} (c(\bar{x}) - c_o(\phi)) \bar{g}'(\phi) \\ &= \frac{RT_m \ln k}{\Omega H} \frac{\Delta T}{m_L c_o^l} \frac{(1-k)c_o^l}{\ln k} (e^u - 1) \tilde{g}'(\phi) \\ &= \bar{\lambda} \Delta c_F (e^u - 1) \tilde{g}'(\phi) \end{aligned} \quad (6.55)$$

where

$$\begin{aligned} \Delta c_F &\equiv (1-k)c_o^l \\ \bar{\lambda} &= \frac{RT_m}{\Omega H} \end{aligned} \quad (6.56)$$

Using the manipulations above, the final form of the dynamics for the phase field equations for the dilute alloy become

$$\tau \frac{\partial \phi}{\partial t} = W_\phi^2 \nabla^2 \phi - \frac{\partial g(\phi)}{\partial \phi} - \bar{\lambda} \Delta c_F (e^u - 1) \tilde{g}'(\phi) \quad (6.57)$$

$$\frac{\partial c}{\partial t} = \nabla \cdot (D_L Q(\phi) c(1-c) \nabla u) \quad (6.58)$$

$$u = \ln \left(\frac{c}{c_o^l [1 - (1-k)\tilde{g}(\phi)]} \right) \quad (6.59)$$

It is clear that at steady state, time derivatives vanish, $u = 0$ and $c_o(x)$ and $\phi_o(x)$ are automatically described by their equilibrium solutions. By re-scaling time by $\bar{t} = t/\tau$ and space by $\bar{x} = x/W_\phi$, Eqs. (6.57)-(6.59) can be characterized by three dimensionless parameters: $\bar{\lambda}$, $\bar{D} \equiv D_L \tau / W_\phi^2$ and c_o^l .

It is noted that Eqs. (6.57)-(6.59) can further be modified to deal with directional solidification by making the substitution

$$e^u \rightarrow e^u + \frac{G(z - V_p t)}{\Delta T_o} \quad (6.60)$$

where $\Delta T_o = |m_L|c_o^l$ is the directional solidification temperature range on the phase diagram, where V_p is the pulling speed of the sample through a thermal gradient G . This extension is treated in detail in [57] and will not be discussed further here.

6.7.5 Thin interface properties of dilute alloy model

Appendix (A) derives the thin interface limit of the Eqs. (6.57)-(6.59). This analysis expands the ϕ and c fields to second order in the small parameter $\epsilon = W_\phi/d_o$. It should be noted that this ϵ the same small parameter used in classical sharp interface analyses. It is shown, however, that the results of this specific analysis are *also* valid in the diffuse interface limit, $W_\phi \sim d_o$, so long as the thermodynamic driving force for solidification (or any other transformation described by the model) is small.

Equations (6.57)-(6.59) are related to those of the generic alloy model in Appendix (A) by making the following associations:

$$\begin{aligned}
 w &\rightarrow H \\
 \frac{1}{w} \frac{\partial \bar{f}_{AB}^{\text{mix}}(\phi, c)}{\partial \phi} &= \bar{\lambda} \Delta c_F (e^u - 1) \bar{g}'(\phi) \\
 q(\phi, c) &= \frac{\Omega}{RT_m} Q(\phi) c \\
 \mu &= \mu_{\text{eq}} + \frac{RT_m}{\Omega} u \\
 \epsilon_c &= 0
 \end{aligned} \tag{6.61}$$

The parameters τ , W_ϕ and D_L have the same meaning in Appendix (A) as they do in this chapter.

It is shown in Appendix (A) that, in their present form, Eqs. (6.57)-(6.59) cannot be exactly mapped onto the sharp interface model of section (6.2.2), for a diffuse interface. Several so-called "correction" terms emerge in the corresponding flux conservation and Gibbs-Thompson conditions. These terms are summarized in section (A.8) (labelled as ΔF , ΔH and ΔJ)⁵. As discussed previously, these terms are vanishingly small at low solidification rates or when $W_\phi \ll d_o$. When the interface is smeared for numerical expedience however, they are artificially amplified. They must thus be eliminated –or kept under control– in order to self-consistently be able to emulate the precise sharp interface kinetics of the model in section (6.2.2) –and to be able to obtain tractable relationships for d_o and β (see Eqs. (6.73) and (6.74)). Subsections (6.7.6) and (6.7.7) examine a modification of the above dilute alloy model to make the aforementioned correction term vanish.

Readers wishing to skip the details of the asymptotic analysis of this model can simply make use of the modified model defined in subsection (6.7.6), the sharp interface limit of which is described by Eqs. (6.72)-(6.77).

6.7.6 Non-variational version of model (optional)

Section (A.9) shows how ΔF , ΔH and ΔJ can be eliminated from the thin interface limit of Eqs. (6.57)-(6.59) by altering their form so that they are no longer derivable from a free energy functional. Specifically,

⁵(Optional) The reader following Appendix (A) will have noticed that section (A.7.5) formally requires that $\partial_\phi f(\phi_0^{\text{in}}, c_0^{\text{in}})$ be independent of the co-ordinate (ξ) normal to the interface. This is indeed the case here since it can be shown that

$$\frac{1}{H} \frac{\partial \bar{f}_{AB}^{\text{mix}}(\phi, c)}{\partial \phi} = \bar{\lambda} \Delta c_F (e^u - 1) \bar{g}'(\phi) = \bar{\lambda} \Delta c \left\{ \exp\left(\frac{\mu - \mu_0^o(0^\pm)}{RT_m/\Omega}\right) - \left(\frac{\mu_0^o(0^\pm) - \mu_{\text{Eq}}^F}{RT_m/\Omega}\right) - 1 \right\} \bar{g}'(\phi) \tag{6.62}$$

where $\Delta c \equiv c_L - c_s$ and c_L and c_s are the lowest order liquid and solid concentrations at the interface (which contain a small curvature and velocity correction from their equilibrium values), while μ_{Eq}^F is the equilibrium chemical potential and $\mu_0^o(0^\pm)$ is the lowest order chemical potential at either the solid("–") or liquid("+") interface, also dependent on curvature, as shown in sections (A.7.2) and (A.7.3).

the phase field model is converted into a modified system of non-linear partial differential equations that are mathematically "rigged" so as to emulate a desired sharp interface model. For the model in this section, these alterations have already been developed by Echebarria and co-workers [57]. Specifically, Eqs. (6.57)-6.59) are modified to

$$\tau \frac{\partial \phi}{\partial t} = W_\phi^2 \nabla^2 \phi - \frac{\partial g(\phi)}{\partial \phi} - \bar{\lambda} \Delta c_F (e^u - 1) \tilde{g}'(\phi) \quad (6.63)$$

$$\frac{\partial c}{\partial t} = \nabla \cdot (D_L Q(\phi) c \nabla u) + \nabla \cdot \underbrace{\left(W_\phi a(\phi) U(\phi, c) \frac{\partial \phi}{\partial t} \frac{\nabla \phi}{|\nabla \phi|} \right)}_{\text{add } \vec{J}_a} \quad (6.64)$$

$$u = \ln \left(\underbrace{\frac{c}{c_o^l [1 - (1 - k)h(\phi)]}}_{\text{changed } \tilde{g}(\phi) \text{ to } h(\phi)} \right) \quad (6.65)$$

In these phase field equations the chemical potential has been modified by the replacement of $\tilde{g}(\phi)$ by $h(\phi)$, a free function that has the same limits as $\tilde{g}(\phi)$. Its form will be specified below. The added flux source, \vec{J}_a , is added to correct for the effects of diffuse interface; U will be specified below. It is also required that $\partial_\phi \bar{f}_{AB}^{\text{mix}}(\phi_0^{\text{in}}, c_0^{\text{in}})$ satisfy Eq. (A.134), which is, indeed, the case for this model.

The next subsection will study a specific example of Eqs. (6.63)-(6.65). To do so, it is instructive to re-scale ϕ such that it varies from $\phi_L = -1$ in the liquid to $\phi_s = 1$ in the solid. This is done by defining a "new" order parameter $\phi_{\text{new}} = 2\phi_{\text{old}} - 1$ ($0 \leq \phi_{\text{old}} \leq 1$). The previous interpolation functions and dimensionless chemical potential u now become

$$\begin{aligned} g(\phi) &= -\frac{\phi^2}{2} + \frac{\phi^4}{4} \\ \tilde{g}(\phi) &= \frac{15}{16} \left(\phi - \frac{2\phi}{3} + \frac{\phi^5}{5} \right) \\ u &= \ln \left(\frac{2c}{c_o^l [1 + k - (1 - k)h(\phi)]} \right) \end{aligned} \quad (6.66)$$

where now τ , W_ϕ and H appearing in the equations are effective constants, rescaled from their original definitions by a constant. Finally, the remaining functions in Eq. (6.63)-(6.65) are chosen as

$$\begin{aligned} h(\phi) &= \phi \\ Q(\phi) &= \frac{(1 - \phi)}{[1 + k - (1 - k)\phi(x)]} \\ U(\phi, c) &= (1 - k)c_o^l e^u \\ a(\phi) &= a_t \equiv \frac{1}{2\sqrt{2}} \end{aligned} \quad (6.67)$$

6.7.7 Effective sharp interface parameters of non-variational model (optional)

Calculating the effective sharp interface parameters of Eqs. (6.63)-(6.65) (with Eqs. (6.66) and (6.67)) requires knowledge of lowest order concentration and phase field, which are given by the given by the

solutions of Eq. (A.52) for $\phi_0^{\text{in}}(x)$ and Eqs.(A.58) and (A.72) for $c_0^{\text{in}}(x)$. These are given by ⁶,

$$\begin{aligned} c_0(x) &= \frac{c_L}{2} [1 + k - (1 - k)h(\phi_o(x))] \\ \phi_o(x) &= -\tanh\left(x/\sqrt{2}\right) \end{aligned} \quad (6.68)$$

where c_L is the concentration on the liquid side of the interface of the corresponding sharp interface model. For the specific definitions adopted in Eqs. (6.66) and (6.67), the following relations are derived: $q(\phi_o, c_o) = (\Omega/RT_m)Q(\phi_o)c_o(\phi_o) = (\Omega/RT_m)c_L(1 - \phi_o)/2$, which has limits $q^- = 0$ and $q^+ = \Omega c_L/RT_m$. Moreover, $c_o(x) - c_s = c_L(1 - k)[1 - \phi_o]/2$ while $c_o(x) - c_s = c_L(k - 1)[1 + \phi_o]/2$.

Using the above forms of $c_o(x)$ and $\phi_o(x)$ it is instructive to first check that the so-called correction terms $\Delta\mathcal{F}$, ΔH and ΔJ identified in Appendix A -which would otherwise spoil the phase field model's connection to the tradition sharp interface model- vanish. From Eqs. (A.150)

$$\Delta\mathcal{F} \equiv \mathcal{F}^+ - \mathcal{F}^- = \frac{RT_m(1 - k)}{2\Omega} \left\{ \int_0^\infty (\phi_o(x) + 1) dx - \int_{-\infty}^0 (1 - \phi_o(x)) dx \right\} \quad (6.69)$$

It is clear from the symmetry imposed on ϕ_o about $x = 0$ that $\Delta\mathcal{F} \equiv \mathcal{F}^+ - \mathcal{F}^- = 0$. In the same manner ΔH becomes

$$\Delta H = H^+ - H^- = \frac{(1 - k)c_L}{2} \left\{ \int_0^\infty (\phi_o(x) + 1) dx - \int_{-\infty}^0 (1 - \phi_o(x)) dx \right\} \quad (6.70)$$

which is proportional to $\Delta\mathcal{F}$ and also vanishes. Finally, the ΔJ correction becomes,

$$\Delta J = J^+ - J^- = \frac{\Omega c_L}{RT_m} \left\{ \int_0^\infty (\phi_o(x) + 1) dx - \int_{-\infty}^0 (1 - \phi_o(x)) dx \right\} \quad (6.71)$$

which also vanishes. Note that the above equations (which come from Appendix (A)) formally use c_L , the lowest order concentration on the liquid side of the interface, which has a small curvature and velocity dependent shift from its equilibrium flat interface value c_o^l . This does not affect the vanishing of the correction terms as c_L scales out of Eqs.(6.69)-(6.71). Furthermore, the difference between using c_o^l versus c_L in the integrals $\mathcal{F} \equiv \mathcal{F}^+ = \mathcal{F}^-$ and $H \equiv H^+ = H^-$ and $J \equiv J^+ = J^-$ will be seen below to yield only higher order curvature and velocity corrections to the effective sharp interface model (discussed further below). It is thus reasonable to simply approximate $c_L \rightarrow c_o^l$ in integrals that arise from the asymptotic analysis of this model.

As a result of the above considerations, the effective sharp interface model emulated by Eqs. (6.63)-(6.65) (using the definitions in Eqs. (6.66) and (6.67)) is thus specified by Eq. (A.130) for the Gibbs-Thomson condition and the Eq. (A.131) for the flux conservation equation, with $\Delta\mathcal{F} = \Delta H = \Delta J = 0$ as shown above. It now remains only to compute the effective capillary length d_o and interface kinetic coefficient, β . To do so, the chemical potential on left hand side of Eq. (A.130) is expanded near the solid or liquid equilibrium value. Considering the liquid side gives, $\mu^o(0^+) - \mu_{\text{Eq}}^{\text{F}} = \Lambda^+(c^o(0^+) - c_o^l)$, where $\Lambda^+ \equiv \partial_c \bar{f}_{\text{AB}}^{\text{mix}}(\phi_o = -1, c_o^l) = (RT_m/\Omega c_o^l)$. Substituting this into the left hand side of the Gibbs-Thomson condition gives

$$\frac{c^o(0^+)}{c_o^l} = 1 - (1 - k) d_o \kappa - (1 - k) \beta v_n \quad (6.72)$$

⁶For those simultaneously reading Appendix (A), lowest order is in the sense of the matched asymptotic series expansion of ϕ and c expressed in Eqs. (A.16). For simplicity, the notation $c_o^{\text{in}}(x)$ and $\phi_0^{\text{in}}(x)$ has been dropped in this subsection in favour of the simpler notation $c_o(x)$ and $\phi_o(x)$.

where

$$d_o = \sigma_\phi \frac{W_\phi}{\hat{\lambda}} \quad (6.73)$$

$$\beta = \frac{\tau \sigma_\phi}{W_\phi \hat{\lambda}} \left(1 - \frac{a_2 \hat{\lambda}}{\bar{D}} \left[\frac{c_L}{c_o^l} \right] \right) \quad (6.74)$$

with $\bar{\lambda}$ and a_2 defined by

$$\hat{\lambda} = (1-k)^2 c_o^l \bar{\lambda} = \frac{RT_m(1-k)^2 c_o^l}{\Omega H} \quad (6.75)$$

$$a_2 = \frac{\bar{K} + J\bar{F}}{2J\sigma_\phi} \quad (6.76)$$

and

$$\begin{aligned} J &\equiv 16/15 \\ \bar{F} &\equiv \int_0^\infty (\phi_o(\xi) + 1) d\xi \\ \bar{K} &\equiv \int_{-\infty}^\infty \frac{\partial \phi_o}{\partial \xi} \bar{g}(\phi_o) \left\{ \int_0^\xi \phi_o(x) dx \right\} d\xi \\ \bar{g}(\phi) &= \phi - \frac{2\phi}{3} + \frac{\phi^5}{5} \end{aligned} \quad (6.77)$$

It is noted that to arrive at the coefficients in Eqs. (6.73)-(6.76), one begins with Eq. (A.130) where K is given by Eq. (A.151), while \mathcal{F} is given by either of Eqs. (A.150) and σ_ϕ by Eq. (A.64). Straightforward algebra then gives

$$\frac{K + \mathcal{F} \Delta c}{\sigma_\phi} = \left(\frac{RT_m(1-k)^2 c_L}{\Omega} \right) \frac{\bar{K} + J\bar{F}}{2J\sigma_\phi} \quad (6.78)$$

Unlike the case for a pure material, it is not possible for alloys to simulate the limit $\beta = 0$ exactly. That is because of the extra factor c_L/c_o^l in Eq. (6.74). Indeed, to do so precisely requires that $\bar{D} = a_2 \bar{\lambda} (c_L/c_o^l)$, which requires that the curvature-dependent deviation of c_L from c_o^l is computed at each point at the solid-liquid interface. However, it is relatively straightforward to show from the $\mathcal{O}(\epsilon)$ treatment of the ϕ equation (see Appendix (A)) that $c_L/c_o^l \approx 1 - c_1 d_o \kappa - c_2 (\tau/\lambda W_\phi) v_n$, where c_1 and c_2 are constants. As discussed above, in most cases the curvature and velocity dependent corrections can be approximated to be very small, particularly for experimentally relevant solidification rates, such as those achieved in continuous casting and even some forms of thin slab and strip casting. As a result such curvature and velocity correction can be neglected and it is reasonable to set $c_L/c_o^l \approx 1$ in Eq. (6.74).

For the function chosen here $\bar{F} = \sqrt{2} \ln 2$, $\bar{K} = 0.1360$ and $\sigma_\phi = 2\sqrt{2}/3$. For readers wishing to connect this derivation to the one published in Ref. [57] it should be noted that their $\hat{\lambda}$, call it $\hat{\lambda}^E$, is related to the one here by $\hat{\lambda}^E = (15/16)\hat{\lambda}$. Substituting this re-scaling into their expressions for d_o and β gives Eq. (6.73) where σ_ϕ is replaced by the variable $a_1 \equiv \sigma_\phi/J \approx 0.8839$ and Eq. (6.74) with a_2 replaced by $(\bar{K} + J\bar{F})/(2\sigma_\phi) \approx 0.6267$.

Using Eqs. (6.73) and Eq. (6.74), two of $\bar{\lambda}$, τ and W_ϕ can be determined by connecting the phase field equations to the measurable constants d_o and β . One parameter, however, still remains undetermined.

This implies, for example, that it is possible to easily model a unique surface tension and kinetic coefficient (even $\beta = 0$), with a diffuse W_ϕ (compared to d_o). This is not possible in the strict limit of the sharp interface limit (when $W_\phi \rightarrow 0$). This was demonstrated in section (5.7) for thermally controlled solidification. The ability to obtain converged results independent of the ratio W_ϕ/d_o for the binary alloy model was demonstrated quantitatively in Refs. [112, 57, 74, 194], and will be studied in the next section. As discussed before, the incentive to make W_ϕ diffuse (or "thin") is to dramatically reduce simulation times, a feature critical to quantitative modeling of solidification.

6.8 Numerical Simulations of Dilute Alloy Phase Field Model

Numerical simulation of the a binary alloy phase field model proceeds analogously to that of model C for a pure material. A code for studying the dilute alloy model are found in the directory *ModelC_alloy* on the CD that accompanies this book. The pseudo-code for modeling an alloy is shown in Fig. (6.6) using the model studied in section (6.7.6) as an example. The main differences here is the change of

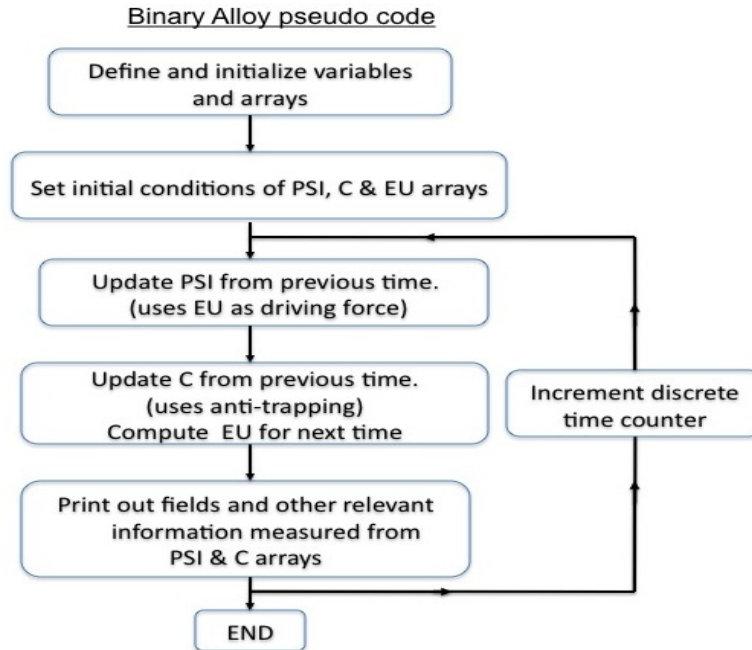


Figure 6.6: Flowchart of algorithm required to simulate Model C for binary alloy solidification.

driving force to $e^u - 1$ in the phase field equation and the use of the fictitious anti-trapping flux in the concentration equation.

6.8.1 Discrete equations

The discrete version of equation Eqs. (6.63) for ϕ is given by

$$\phi^{n+1}(i, j) = \phi^n(i, j)$$

$$\begin{aligned}
& + \frac{\Delta \bar{t}}{A^2[\phi(i,j)]} \left\{ \frac{1}{\Delta \bar{x}} (JR(i,j) - JL(i,j)) + \frac{1}{\Delta \bar{x}} (JT(i,j) - JB(i,j)) \right. \\
& \left. - g'(\phi^n(i,j)) - \frac{\hat{\lambda}}{1-k} (EU^n(i,j) - 1) \tilde{g}'(\phi^n(i,j)) \right\}, \tag{6.79}
\end{aligned}$$

where $(\bar{t} = t/\tau)$ and space $(\bar{x} = x/W_\phi)$. The array $EU^n(i,j) \equiv \exp[u(\phi^n(i,j), c^n(i,j))]$ and u is the reduced chemical potential given by the last of Eqs. (6.66). It is constructed by the phase field $(\phi^n(i,j))$ and concentration $(c^n(i,j))$ at the time step n . The fluxes JR, JL, JT, JB are calculated exactly as in Eqs. (5.54) using the definitions in Eqs. (5.55)-(5.56). Surface energy anisotropy can similarly be simulated here using the same form of the anisotropy as in section (5.7), calculated by Eqs. (5.57).

The update of the concentration equation can be efficiently done using a finite volume method since it is a flux conserving equation. The discrete update equation for the concentration $c^{n+1}(i,j)$ is given by

$$c^{n+1}(i,j) = c^n(i,j) - \frac{\Delta \bar{t}}{\Delta \bar{x}} \{ (J_R^n - J_L^n) + (J_T^n - J_B^n) \} \tag{6.80}$$

where it is assumed that $\Delta x = \Delta y$. The notation $J_R^n \equiv \vec{J} \cdot \hat{i}$, with \hat{i} being the unit normal of the right edge of the finite volume in Fig. (B.1), while \vec{J} is given by [112, 57, 118]

$$\vec{J} = -\bar{D} Q(\phi) c \nabla u - a_t (1-k) e^u \frac{\partial \phi}{\partial t} \underbrace{\frac{\nabla \phi}{|\nabla \phi|}}_{\hat{n}} \tag{6.81}$$

where concentration and diffusion have been rescaled according to

$$\begin{aligned}
\bar{D} & \equiv D_L \tau / W_\phi^2 \\
c & \rightarrow c^{\text{actual}} / c_o^l \tag{6.82}
\end{aligned}$$

The fluxes J_L^n, J_T^n and J_B^n are similarly defined as the normal components of the flux along the left, top and bottom edges of the finite volume, respectively. It is seen in Fig. (B.1) that J_R^n requires that \vec{J} be evaluated at the locations $(i \pm 1/2, j)$ and $(i, j \pm 1/2)$. However, no explicit information is known at these points, as the mesh is designed to track ϕ and c at discrete co-ordinates which, as shown in the figure, jump by whole integers. To avoid this problem, interpolation from neighboring points at $(i \pm 1, j \pm 1)$ needs to be used. The procedure for doing this follows.

Referring to the right hand edge of the control volume in Fig. (B.1), the quantities that enter J_R (i.e. the component of \vec{J} in the direction of \hat{i}) are evaluated at $(i + 1/2, j)$ as follows,

$$\begin{aligned}
Q(\phi^n(i+1/2, j)) c^n(i+1/2, j) & = Q \left(\frac{\phi^n(i+1, j) + \phi^n(i, j)}{2} \right) \left(\frac{c^n(\phi(i+1, j)) + c^n(\phi(i, j))}{2} \right) \\
\nabla u \cdot \hat{i} & \equiv \frac{\partial u^n}{\partial x} \Big|_{i+1/2, j} = \frac{EU^n(i+1, j) - EU^n(i, j)}{\Delta x (EU^n(i+1, j) + EU^n(i, j)) / 2} \\
\left[e^u \frac{\partial \phi}{\partial t} \right]_{(i+1/2, j)}^{n+1} & = \left(\frac{e^{u(\phi^n(i+1, j), c^n(i+1, j))} + e^{u(\phi^n(i, j), c^n(i, j))}}{2} \right) \left(\frac{\partial_t \phi|_{(i+1, j)}^{n+1} + \partial_t \phi|_{(i, j)}^{n+1}}{2} \right) \\
\frac{\partial \phi^n}{\partial x} \Big|_{i+1/2, j} & = \frac{\phi(i+1, j) - \phi(i, j)}{\Delta x} \tag{6.83}
\end{aligned}$$

where $\partial\phi/\partial t$ at time $n + 1$ is evaluated after the ϕ equation is updated ⁷ Note that for calculating y derivatives of ϕ at the right edge of the volume (for $\nabla\phi$) requires both the neighbors and next nearest neighbors of the point $(i + 1, j)$ (labelled by "x" in Fig. (B.1)). Thus,

$$\left. \frac{\partial\phi}{\partial y} \right|_{i+1/2,j} = \frac{(\phi(i, j + 1) - \phi(i, j - 1)) + (\phi(i + 1, j + 1) - \phi(i + 1, j - 1))}{2(2\Delta y)} \quad (6.84)$$

Equation (6.84) is simply the average of two y direction derivatives at (i, j) and $(i + 1, j)$. With the above discretizations, J_R becomes

$$J_R = -\bar{D}Q \left(\phi^n(i + 1/2, j), c^n(i + 1/2, j) \right) \left. \frac{\partial u^n}{\partial x} \right|_{i+1/2,j} - a_t(1 - k) \left[e^u \frac{\partial\phi}{\partial t} \right]_{(i+1/2,j)}^{n+1} \hat{n}_x^R \quad (6.85)$$

where

$$\hat{n}_x^R = \frac{\left. \frac{\partial\phi^n}{\partial x} \right|_{i+1/2,j}}{\left\{ \left(\left. \frac{\partial\phi^n}{\partial x} \right|_{i+1/2,j} \right)^2 + \left(\left. \frac{\partial\phi}{\partial y} \right|_{i+1/2,j} \right)^2 \right\}^{1/2}} \quad (6.86)$$

The fluxes in the other directions are calculated analogously.

Analogously to the case of the pure material, the natural choice of boundary conditions for concentration are zero flux boundary conditions (since generally mass does not enter or leave the system, and mirror boundary conditions. This requires that the c , ϕ and EU arrays are buffered with one layer of ghost nodes in each spatial dimension. The ghost nodes are set prior to each time iteration as shown in Eq. (5.7.2). It also noted that the stability of the numerical scheme presented here is analogous to the one for a pure material studied in section (5.7). In this case mass transfer, as the fastest process, controls the stability by requiring that $\Delta\bar{t} < \Delta\bar{x}^2 / (4\bar{D})$.

6.8.2 Convergence properties of model

Figure (6.7) shows an image sequence in the simulation of dendrite in a dilute binary alloy. An initial seed crystal is placed in an initially supersaturated liquid phase. The concentration shown is relative to c_o^l , the equilibrium concentration on the liquid side of the interface at the quench temperature. The average alloy concentration c_∞ was chosen such that the supersaturation was

$$\Omega \equiv \frac{c_o^l - c_\infty}{(1 - k)c_o^l} = 0.55 \quad (6.87)$$

The anisotropy was set to $\epsilon_4 = 0.05$. An initial seed was placed in the bottom-left corner of the simulation domain. Its radius was $R = 10W_\phi$. The ϕ field was set to $\phi = 1$ in the solid and $\phi = -1$ in the liquid. The chemical potential was initialized from the the initial condition $e^u(t = 0) = 1 - (1 - k)\Omega$, which also uniquely defines the initial concentration field c . The coupling coefficient was chosen to be $\hat{\lambda} = 3.19$, while $\Delta\bar{x} = 0.4$ and $\Delta\bar{t} = 0.008$.

⁷the function $\partial_t\phi$ can be considered a "known" function from the point of view of the concentration equation since it updated in a separate application of the discrete phase field equation prior to entering the subroutine where concentration is updated

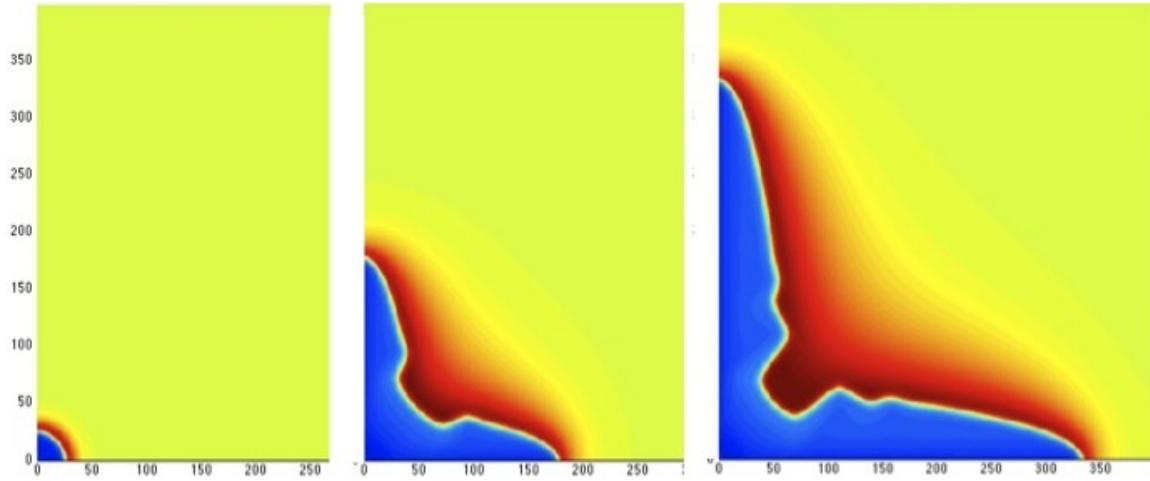


Figure 6.7: *Isothermal dendrite growth sequence in an alloy. The colour map represents concentration. Cold colours represent low concentration and warm colours high concentration.*

The sharp interface dynamics of the solid-liquid interface in Fig. (6.7) are governed by Eqs. (6.73) and (6.74), which relate the capillary length and interface kinetics coefficient to the interface width W_ϕ and characteristic time scale τ using precisely the same form that was used in the case of a pure material in Eq. (5.62).⁸ This is not a coincidence but rather by construction of the specific free energy of the dilute alloy model studied in this section. Indeed, much of the essential physics of the pure model in section (6.8.2) remain unchanged in binary alloy (where, essentially thermal diffusion in that case is replaced by mass transport in this case). As with solidification of a the pure material, it turns out that simulations of the dimensionless steady state dendritic tip speed will be independent of the choice of $\hat{\lambda}$, or equivalently W_ϕ , for sufficiently small W_ϕ . This is demonstrated in Fig. (6.8), which compares the dendrite tip speed for the same undercooling and two values of $\hat{\lambda}$. This figure is the alloy analogue of Fig. (5.7).

It also is instructive to examine the convergence properties afforded by the use of the the antri-trapping flux in Eq. (6.64). Recall that this flux term was introduced as a mathematical remedy to eliminate the so-called spurious kinetics and excess solute trapping that occurs in the limit of a diffuse interface in an alloy phase field model with very asymmetric diffusion between the solid and liquid phases. Figure (6.9) compares the centre-line concentration in of the horizontal branch of the dendrite shown in Fig. (6.7) with and without the use of anti-trapping. The characteristic concentration jump and solute rejection profile in the liquid is shown. It is clear from Fig. (6.9) that neglecting the use of the anti-trapping flux in the phase field equations (i.e. $a(\phi) = 0$) exaggerates the impurity level in the solid. This is mainly due to the effect of solute trapping imposed by the so-called ΔF correction term, which was discussed in section (6.7.5). This effect scales with the interface width and so it will be amplified even further for larger values of W_ϕ or, equivalently $\hat{\lambda}$, which is typical of more efficient calculations.

⁸This equivalence is true within higher order curvature and interface velocity corrections.

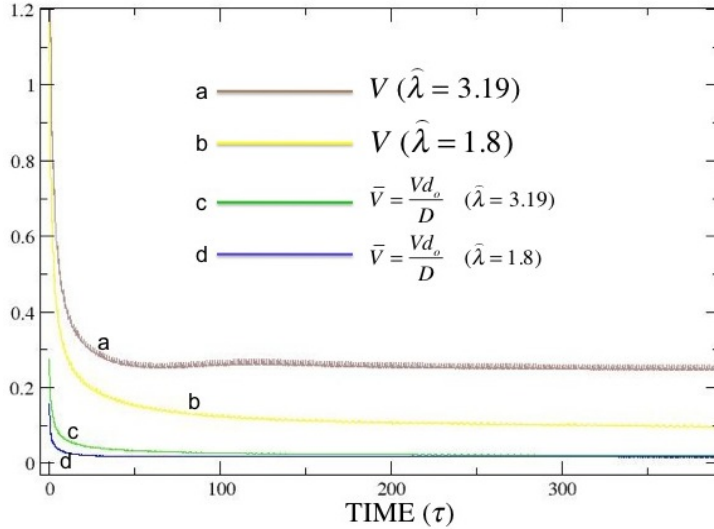


Figure 6.8: Dendrite tip speeds for two values of the inverse nucleation barrier $\hat{\lambda}$. The parameter $\hat{\lambda}$ is chosen via Eqs. (6.73) and (6.74) to fix the interface kinetics time (τ) and interface width (W_ϕ) in a manner consistent with the sharp interface model. Scaling the tip speed τ/W_ϕ (equivalent to d_o/D) thus makes the dimensionless tip speed universal and dependent only on the supersaturation.

6.9 Other Alloy Phase Field Formulations

Thus far phase field theories have been presented in terms of two physically motivated parameters; the order parameter and concentration field. This section studies an alloy phase field methodology that is somewhat different from the standard form that has been discussed thus far, but which is very often used in the literature. Once again this approach begins with the standard alloy phase field model in Eqs. (6.34)-(6.36). The use of these equations with a general bulk free energy was originally introduced by Boettinger and co-workers [209, 210] (hereafter referred to as the WMB model). As discussed above, this model has the severe limitation that in equilibrium $\partial_\phi f(\phi_o, c_o) \neq 0$ for a general bulk free energy. That makes it impossible to reproduce an given interface energy reliably using very diffuse interfaces. In the previous section it was shown that one approach to remedy this problem is to judiciously choose the entropy and total energy interpolating functions. In this section studies a different phase field formulation for binary alloys due to Kim and co-workers [120]. In this approach rather than modify interpolation functions, two new, fictitious concentration fields are introduced. These are made implicit functions of the phase field ϕ and concentration c in such a way as to achieve a similar decoupling as in the example studied above.

6.9.1 Introducing fictitious concentrations

Kim and co-workers extended the quantitative applicability of the WMB model by introducing two fictitious concentration fields $C_L(\vec{x})$ and $C_S(\vec{x})$, associated with each phase. It is assumed in their formalism that the physical concentration c can be expressed as an interpolation of C_L and C_s according

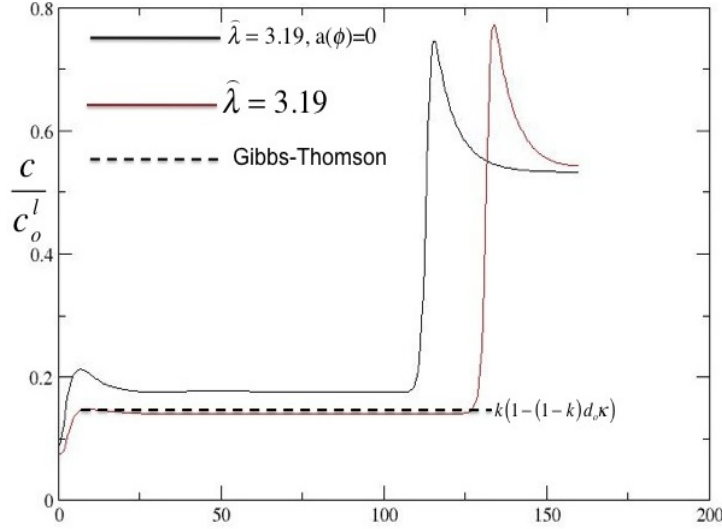


Figure 6.9: Dendrite centre line concentration for the cases of $\hat{\lambda} = 3.19$ with (bottom) and without (top) the use of anti-trapping. The straight dashed line is the prediction of the curvature-corrected solid concentration in the solid, as predicted by the Gibbs-Thomson condition.

to

$$c = h(\phi)C_s + (1 - h(\phi))C_L \quad (6.88)$$

where $h(\phi)$ is an interpolation function that satisfies $h(\phi = \phi_s) = 1$ in the solid phase and $h(\phi = \phi_L) = 0$ in the liquid phase. The idea of Eq. (6.88) is that the interface region is actually a certain fraction of solid ($h(\phi)$) and liquid ($1 - h(\phi)$). The total composition in the interface is the weighted combination of the solid and liquid concentrations, C_s and C_L . The concentrations C_L and C_s are constrained such that the solid and liquid fractions through the interface to satisfy equal chemical potentials in terms of C_L and C_s i.e.,

$$\frac{\partial f_s(C_s)}{\partial c} = \frac{\partial f_L(C_L)}{\partial c} \quad (6.89)$$

where $f_s(C_s)$ and $f_L(C_L)$ are the free energies of the solid and liquid phase, respectively. (The notation $\partial_{,c} f_s(C_s) \equiv \partial_{,c} f_s(c)|_{c=C_s}$). It should be noted that Eqs. (6.88) and (6.89) make C_L and C_s functions of ϕ and c .

Another modification to the original WMB model make by Kim and co-workers is that the original bulk free energy $f(\phi, c)$ appearing in the phase field model is written as

$$f(\phi, c) = Hg(\phi) + h(\phi)f_s(C_s) + (1 - h(\phi))f_L(C_L) \quad (6.90)$$

It is clear that the above definition of $f(\phi, c)$ reduces to the appropriate bulk phase expression far from the interface where ϕ transitions between phases. The decomposition of $f(\phi, c)$ in terms of the non-physical fields C_L and C_s , and the associated conditions on C_L and C_s , offers an alternative to manipulating the choice of interpolation functions (i.e. the method used in section (6.7) for the ideal, dilute binary alloy). The outcomes in both cases is the same; the ability to decouple concentration from the surface tension calculation and the ability to relate surface energy to interface width even for arbitrarily diffuse interfaces.

The only [minor] trade-off in this case is that some extra work has to be done to determine $C_s(\phi, c)$ and $C_L(\phi, c)$ at any time. This is discussed next.

6.9.2 Formulation of phase field equations

In order to be able to solve the phase field equations of the WMB model, it is required to relate $f_c(\phi, c)$, $f_\phi(\phi, c)$ and $f_{cc}(\phi, c)$ to C_s and C_L . This is done by differentiating both sides of Eqs. (6.88) and (6.89) implicitly with respect to c and ϕ , giving

$$\begin{aligned}
1 &= h(\phi) \frac{\partial C_s}{\partial c} + (1 - h(\phi)) \frac{\partial C_L}{\partial c} \\
0 &= h'(\phi) (C_s - C_L) + h(\phi) \frac{\partial C_s}{\partial \phi} + (1 - h(\phi)) \frac{\partial C_L}{\partial \phi} \\
0 &= \frac{\partial^2 f_s(C_s)}{\partial c^2} \frac{\partial C_s}{\partial c} - \frac{\partial^2 f_L(C_L)}{\partial c^2} \frac{\partial C_L}{\partial c} \\
0 &= \frac{\partial^2 f_s(C_s)}{\partial c^2} \frac{\partial C_s}{\partial \phi} - \frac{\partial^2 f_L(C_L)}{\partial c^2} \frac{\partial C_L}{\partial \phi}, \tag{6.91}
\end{aligned}$$

where the prime denotes differentiation with respect to ϕ . The solution of these equations gives

$$\begin{aligned}
\frac{\partial C_s}{\partial c} &= \frac{\partial_{cc} f_L(C_L)}{R(\phi, C_L, C_s)} \\
\frac{\partial C_L}{\partial c} &= \frac{\partial_{cc} f_s(C_s)}{R(\phi, C_L, C_s)} \\
\frac{\partial C_s}{\partial \phi} &= \frac{h'(\phi) (C_L - C_s) \partial_{cc} f_L(C_L)}{R(\phi, C_L, C_s)} \\
\frac{\partial C_L}{\partial \phi} &= \frac{h'(\phi) (C_L - C_s) \partial_{cc} f_s(C_s)}{R(\phi, C_L, C_s)} \tag{6.92}
\end{aligned}$$

where $R(\phi, C_L, C_s) \equiv h(\phi) \partial_{cc} f_L(C_L) + (1 - h(\phi)) \partial_{cc} f_s(C_s)$. From Eqs. (6.92) it is now straightforward to derive the following useful relations

$$\frac{\partial f(\phi, c)}{\partial \phi} = Hg(\phi) - \left(f_L(C_L) - f_s(C_s) - \frac{df_L(C_L)}{dc} (C_L - C_s) \right) h'(\phi) \tag{6.93}$$

$$\mu = \frac{\partial f(\phi, c)}{\partial c} = \frac{df_L(C_L)}{dc} = \frac{df_s(C_s)}{dc} \tag{6.94}$$

$$\frac{\partial^2 f(\phi, c)}{\partial c^2} = \frac{\partial_{cc} f_L(C_L) \partial_{cc} f_s(C_s)}{R(\phi, C_L, C_s)} \tag{6.95}$$

$$\frac{\partial^2 f(\phi, c) / \partial \phi \partial c}{\partial^2 f(\phi, c) / \partial c^2} = (C_L - C_s) h'(\phi) \tag{6.96}$$

with which the final form of the phase field and impurity diffusion equations can be written in terms of C_L and C_s ,

$$\tau \frac{\partial \phi}{\partial t} = W_\phi^2 \nabla^2 \phi - \frac{dg}{d\phi} + \frac{1}{H} \left(f_L(C_L) - f_s(C_s) - \frac{df_L(C_L)}{dc} (C_L - C_s) \right) h'(\phi) \tag{6.97}$$

$$\frac{\partial c}{\partial t} = D_L \nabla \cdot \left[\frac{Q(\phi)}{\partial_{cc} f(\phi, c)} \nabla \left(\frac{\partial f(\phi, c)}{\partial c} \right) \right] \quad (6.98)$$

$$= D_L \nabla \cdot \left[\frac{Q(\phi)}{\partial_{cc} f(\phi, c)} \nabla \left(\frac{\partial f_{L,s}(C_L, s)}{\partial c} \right) \right] \quad (6.99)$$

$$= D_L \nabla \cdot \left[Q(\phi) \left(h(\phi) \nabla C_s + (1 - h(\phi)) \nabla C_L \right) \right] \quad (6.100)$$

Equations (6.98)-(6.100) are three equivalent choices for the dynamics of impurity concentration. The last version of the chemical diffusion equation (Eq. (6.100)) is obtained by noting that $\nabla f_c = f_{cc} \nabla c + f_{c\phi} \nabla \phi$ and using Eq. (6.88). It is emphasized that expression $\partial_\phi f(\phi, c)$ in the large curly brackets of Eq. (6.97) is in fact a function of ϕ and c through the implicit dependence of C_s and C_L on these fields.

To model anisotropic surface tension in Eqs. (6.97) and (6.99), the gradient term $W_\phi^2 \nabla^2 \phi$ in Eq. (6.97) has to be modified as in Eq. (6.37).

6.9.3 Steady state properties of model and surface tension

At equilibrium $\partial c / \partial t = 0$ the concentration equation gives $\partial_c f_L(C_L) = \partial_c f_s(C_s) = \mu_{\text{Eq}}^{\text{F}}$, where $\mu_{\text{Eq}}^{\text{F}}$ is a constant. This can only be true at all points if $C_L(x) = C_L^{\text{eq}}$ and $C_s(x) = C_s^{\text{eq}}$ where C_L^{eq} and C_s^{eq} are constants. The corresponding steady state ϕ equation thus becomes

$$W_\phi^2 \frac{d^2 \phi_o}{dx^2} - g'(\phi_o) + \frac{1}{H} \left(f_L(C_L^{\text{eq}}) - f_s(C_s^{\text{eq}}) - \frac{df_L(C_L^{\text{eq}})}{dc} (C_L^{\text{eq}} - C_s^{\text{eq}}) \right) h'(\phi_o) \quad (6.101)$$

Multiplying Eq. (6.101) by $d\phi_o/dx$ and integrating from $-\infty \leq x \leq \infty$ immediately gives

$$\frac{f_L(C_L^{\text{eq}}) - f_s(C_s^{\text{eq}})}{C_L^{\text{eq}} - C_s^{\text{eq}}} = \mu_{\text{Eq}}^{\text{F}} \quad (6.102)$$

Equation (6.102) along with $\partial_c f_L(C_L^{\text{eq}}) = \partial_c f_s(C_s^{\text{eq}}) = \mu_{\text{Eq}}^{\text{F}}$ are the standard conditions for determining the equilibrium solid and liquid concentrations, as well as the equilibrium chemical potential through the interface, $\mu_{\text{Eq}}^{\text{F}}$.

Since at equilibrium, since C_L and C_s are constant, the the steady state concentration profile is simply given by

$$c_o(x) = h(\phi_o) C_s^{\text{eq}} + (1 - h(\phi_o)) C_L^{\text{eq}} \quad (6.103)$$

This is analogous to the way that the model studied in section(6.7.3) has a steady state concentration profile that depends only on the order parameter ϕ . Moreover, substituting Eq. (6.102) back into the steady state ϕ equation gives

$$W_\phi^2 \frac{d^2 \phi_o}{dx^2} - g'(\phi_o) = 0, \quad (6.104)$$

which is identical to Eq. (6.49) and does *not* involve the concentration in ϕ_o . As a result, using Eq. (6.32) the surface energy for the alloy phase field model of Eqs.(6.97) and (6.100) can be determined uniquely in terms of W_ϕ and H , for arbitrarily diffuse interfaces. Thus the model of Kim and co-workers can simulate an arbitrary free energy and emulate any surface tension, for diffuse interfaces.

6.9.4 Thin interface limit

It was seen that because at steady state with a flat interface, $\partial_\phi f(\phi_o, c_o) = 0$, the phase field model studied in this section enjoys the property that the expression for the surface energy can be simply expressed in terms the gradient energy coefficient and potential barrier height, for all interface widths W_ϕ . As it stands however, this model is not immune to aforementioned thin interface kinetics that otherwise alter the form of its effective sharp interface limit in the diffuse interface limit. As discussed above, since C_L and C_s are functions of ϕ and c , both $\partial_\phi(\phi, c)$ and $\mu = \partial_c f(\phi, c)$, and hence the phase field model itself, are fundamentally of the form studied in Appendix (A) ⁹. Thus, the usual kinetic and thin interface corrections ΔF , ΔH and ΔJ discussed in Appendix (A) (see section (A.8) for a summary) also plague this alloy phase field model.

Kim [118] recently extended the phase field model presented in this section so that the concentration equation contains an anti-trapping flux term like that used in the dilute alloy model of section (6.7.5). This modification is designed to eliminate the aforementioned spurious kinetic corrections. As discussed in Appendix (A), the introduction of a fictitious flux term in the mass transport equation leads to a non-varational form of the original phase field equations model but leads to a mathematical equivalence of the thin interface limit of the phase field equations to the sharp interface model. Modification of the model involves two steps. The first is the introduction of an anti-trapping flux to the concentration equation, i.e. it of the form

$$\frac{\partial c}{\partial t} = D_L \nabla \cdot \left[\frac{Q(\phi)}{\partial_{cc} f(\phi, c)} \nabla \left(\frac{\partial f_{L,s}(C_{L,s})}{\partial c} \right) - \vec{J}_a \right] \quad (6.105)$$

where \vec{J}_a denoted the anti-trapping flux. The second change required is that the interpolation function in the chemical potential which modulates $c_o(x)$ between one phase and another via ϕ_o must be altered. In this case, the chemical potential $\partial_c f_{L,s}(C_{L,s})$ (either s or L) is implicitly related to $c(x)$ and $\phi(x)$ through $h(\phi_o)$ in Eq. (6.88). Thus $h(\phi)$ can be altered to some arbitrary $\tilde{h}(\phi)$, which has the same limits as $h(\phi)$ in the bulk phases. The anti-trapping, the new interpolation function $\tilde{h}(\phi)$ and $Q(\phi)$ provide three degrees of freedom which can be chosen to make $\Delta F = \Delta H = \Delta J = 0$. Given the length of such calculations, these details will not be discussed further here. The interested reader is referred to the recent calculation of Ohno and co-workers [161] for the case of an ideal, dilute binary alloy. Furthermore, Kim has recently extended the model described in this section to multiple solute components [118].

6.9.5 Numerical determination of C_s and C_L

It is instructive to conclude this section by briefly discussing the numerical solution of Eqs. (6.97) and (6.100). The simplest numerical algorithm for solving these these equations is as follows: Starting with the fields $\{\phi, c, C_L, C_s\}$ at time $t = n\Delta t$, Eqs. (6.97) is updated using a simple finite difference method (see Appendix (B.1)). Equation (6.100) is then updated using a finite differences or a finite volume method (see Appendix (B.2)). This yields ϕ and c at $t = (n+1)\Delta t$. Using the updated c and ϕ fields, Eqs. (6.88) and (6.89) are next solved self-consistently at all lattice sites to yield C_L and C_s at time $t = (n+1)\Delta t$. The solution of C_L and C_s in terms of c and ϕ at any given lattice cite on the numerical grid is done by solving

$$f_1(C_s, C_L) \equiv h(\phi)C_s + (1 - h(\phi))C_L - c = 0$$

⁹As required by the conditions of the main calculation of Appendix (A), it can be also shown that to lowest order $\partial_\phi f(\phi_0^{\text{in}}, c_0^{\text{in}})$ does not depend on the co-ordinate ξ normal to the interface.

$$f_2(C_s, C_L) \equiv \partial_c f_S(C_s) - \partial_c f_L(C_L) = 0 \quad (6.106)$$

The simplest way of solving these non-linear equations is using Newton's method, outlined in Appendix (C.3). This is an iterative scheme that start with an initial estimate for C_s and C_L and progressively improves this estimate via the iterative mapping

$$\begin{pmatrix} C_s^{n+1} \\ C_L^{n+1} \end{pmatrix} = \begin{pmatrix} C_s^n \\ C_L^n \end{pmatrix} + \frac{1}{W(C_s^n, C_L^n)} \begin{pmatrix} \partial_{,cc} f_L(C_L^n) & 1 - h(\phi) \\ -\partial_{,cc} f_S(C_s^n) & h(\phi) \end{pmatrix} \begin{pmatrix} f_1(C_s^n, C_L^n) \\ f_2(C_s^n, C_L^n) \end{pmatrix} \quad (6.107)$$

where $W(C_s^n, C_L^n) \equiv h(\phi)\partial_{,cc} f_L(C_L^n) + (1 - h(\phi))\partial_{,cc} f_S(C_s^n)$. Here n denotes the iteration step. Equation (6.107) is iterated until C_s^n and C_L^n stop changing appreciably, to some accuracy. This method while simple demands that the initial guess is close to the real answer. This should not be a problem if ϕ and c change slowly at each lattice site. The solution of Equation (6.107) at each time step of the phase field equations (6.97) and (6.100) is very inefficient. The best way to proceed is to solve for a pre-determined 2D array one of whose dimensions represents small increments of ϕ between $[0, 1]$ and the other of c between $[0, 1]$. For each entry of the array, which represents a unique (ϕ, c) combination, Equation (6.107) is iterated to yield the corresponding a unique $(C_s(\phi, c), C_L(\phi, c))$ pair.

6.10 Properties of Dendritic Solidification in Binary Alloys

The first step in the process of casting metal alloys is the solidification of dendrites that nucleate, grow and impinge on one another. The scale of these structures is largely controlled by inter-dendritic morphology and interactions. Toward the centre of the cast, the temperature is nearly uniform and a many individual dendrites form, a condition known as *equiaxed* dendrite growth. Near the mould wall, dendrites grow cooperatively in a direction perpendicular to the chill surface, following the gradient that is established as heat is drawn out of the cast as it cools. Understanding this process of dendrite spacing selection has been the topic of great industrial interest because of the link of microstructure to mechanical properties.

There have been many theories and models proposed to explain directional solidification in alloy. Phase field modeling has also made its contribution to this field and, indeed, promises to be a very robust way to simulate the complexities of competitive dendritic growth which is beyond the scope of analytical and so-called geometrical theories. This section reviews some of the theoretical work on directional solidification, including more recent contributions to this topic made with phase field modeling.

6.10.1 Geometric models of directional solidification

A traditional paradigm for the study of casting microstructures is directional solidification. The typical laboratory set up for directional solidification is studied using an apparatus analogous to that illustrated in Fig. (6.10). In this process a sample is pulled at a constant velocity through a fixed temperature gradient. The value of the temperature gradient (G), pulling speed (V) and alloy composition (C_o) lead to a complex dependence of the dendritic spacing and morphology on the experimental parameters [196, 21, 195, 123, 139, 29, 141, 140, 197]. Low pulling speeds lead to cellular arrays of dendrites. Increased pulling speed leads to dendrite arrays with side-branching. At large enough speeds, absolute stability is reached and a planar solidification front is attained. A typical situation where an initially flat interface becomes unstable and destabilizes into an array of dendrites is shown in Fig. (6.11). A very large body of work has been produced to elucidate the spacing selection in this process. Most experiments on organic

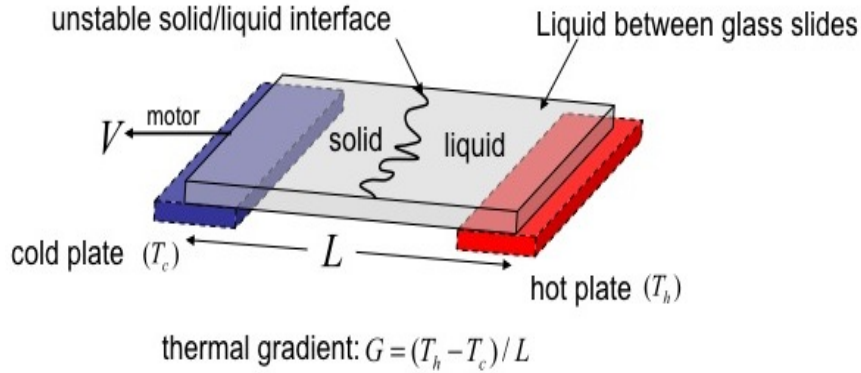


Figure 6.10: *Experimental set for directional solidification of organic alloys. The alloy is placed between two glass plates and solidified at a constant speed V through a constant thermal gradient G , where $T_c < T_h$.*

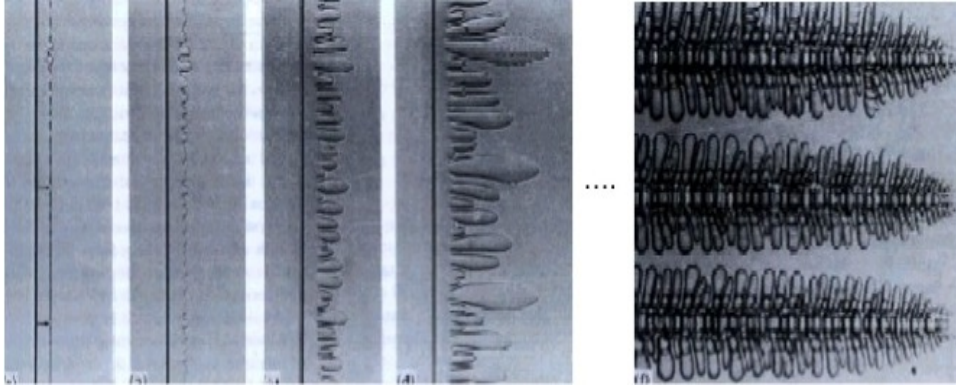


Figure 6.11: *Directional solidification of Succinonitrile-acetone. Adapted from [196].*

alloys reveal that the primary dendrite spacing λ_1 is reproducible as a function of [constant] pulling speed V , or assuming this changes very slowly [196, 139]. The need to explain the selection process in directional solidification has led to a plethora of so-called geometric models that assume the existence of a steady state dendrite array, and attempt to derive λ_1 in terms of the geometry of the array and the fundamental length scales of the solidification problem.

Theories of steady state primary spacing in directional solidification of alloy usually assume a power law scaling of the form $\lambda_1 = KG^{-a}V^{-b}$ [195], where the exponents a and b are different in the cellular and dendritic regimes and K is a constant of proportionality. The constants K , a and b typically vary between theories. Assuming the dendrite tips can be described as spheres, Hunt [100] proposed a primary spacing model of the form

$$\lambda_1 = B \left(\frac{T_m m_L (k-1) c_o \sigma D}{L} \right)^{1/4} G^{-1/2} V^{-1/4} \quad (6.108)$$

where $B = 2.8$. Kurz and Fisher [131] used an elliptical approximation to describe dendrite tip and arrived

at the same equation, except $B = 4.3$. The derivation of Hunt's geometrical model proceeds by assuming that the dendrites are arranged geometrically in a hexagonal array, as shown in a 2D cross section in Fig. (6.12). The minor axis of an ellipse is b and the major axis is $a = \Delta T/G$, where $\Delta T \equiv T_L - T_E$ with T_L being the temperature at the dendrite tips, which is close to the liquidus temperature, and T_E is the temperature at the groove of the dendrites, typically close to the eutectic temperature for hypereutectic alloys¹⁰. The radius of curvature at the tip of an ellipse is $R = b^2/a$ and, by construction, $\lambda_1 = 2b$, which gives $\lambda_1 = 2\sqrt{\Delta T R/G}$. At this point the theory heuristically relates R to the fastest growing

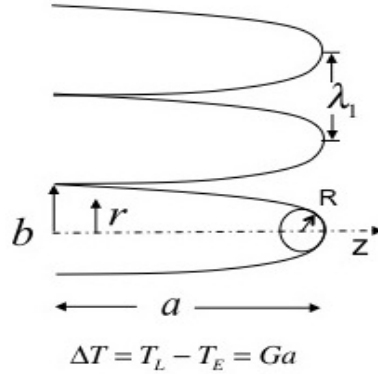


Figure 6.12: *Elliptic dendrite array used to represent steady state dendrite array in geometrical models.*

linearly unstable wavelength, the Mullins and Sekerka wavelength, determined by the maximum of the linear dispersion analog of Eq. (5.66) for directional solidification [138]. This is given by $\lambda_{ms} = \sqrt{l_D d_o}$ ¹¹. Setting $R = \lambda_{ms}$ gives λ_1 in the form of Eq. (6.108).

More complex geometrical theories have also been formulated which consider such things as solute-modified surface tension [124] or which give rise to a maximum in λ_1 by considering growth regimes separately [131, 123, 139]. Such geometrical theories are usually in qualitative agreement with experiments over certain ranges of pulling velocity. However, K –or other tunable parameters– must be fit to experimental data to obtain quantitative agreement [123, 139]. It is also noteworthy that even for slow cooling rates, Eq. (6.108) does not describe the transient development of primary branches. To address the transient scaling regime, heuristic formulae of the form $\lambda_1 \sim (GR)^{-1/2}$ have been developed. As with their steady state counterparts, they are found to work well in metal alloys only when phenomenological parameters of the theory are fit to experimental data [29].

While geometrical models have provided important insight about spacing selection problem in solidification, they have several deficiencies. First, their exponents are not unique over the entire regime of V and G . Experiments show a crossover between different power law regimes as pulling speed is varied [123, 139, 197]. A more serious concern is that geometrical models only work quantitatively by introducing *ad-hoc* adjustable constants, such as B in Eq. (6.108). Clearly, a self-consistent theory should be able to determine λ_1 with as few as possible fitting parameters. Another limitation of geometric models of directional solidification is that their predictions do not actually correspond to realistic casting situations.

¹⁰This is an alloy whose average concentration lies above the saturation limit and below the eutectic concentration. For example, the hypereutectic range in Fig. (6.2) is $18.3\text{wt}\% \text{Sn} \leq c_o \leq 60\text{wt}\% \text{Sn}$.

¹¹This approximation of the Mullins and Sekerka wavelength is accurate in the limit where the thermal length $l_T = m_L c_o (1 - k)/k$ is much larger than the thermal diffusion length $l_D = 2D_L/V$.

Experiments of solidified casts clearly show that the notion of a "steady state" array is an abstraction that does not exist. Experimental data would suggest that spacing selection should be measured and reported using the notion of "ensemble averages", which captures their statistical nature, i.e. $\lambda_1 \rightarrow \langle \lambda_1 \rangle$.

6.10.2 Spacing selection theories of directional solidification

While experiments reveal that under dendrite arrays go to a particular, *reproducible*, primary spacing as a function of a constant pulling velocity V , it is still not clear if or how this spacing can be uniquely established under *dynamical* selection. Self-consistent analytical theories [138, 207, 208] and specialized experiments aimed to test the stability of dendrite arrays [143, 140] suggest that a particular primary spacing, λ_1 , of a dendrite array can be stable over a range of pulling speeds V . Alternatively, these theories and experiments imply that for a given pulling speed V there is a range of stable primary spacings. This would suggest an initial dependence on λ_1 , reminiscent of highly non-linear dynamical systems.

Warren and co-workers were the first to perform a linear stability analysis of a steady state array of weakly interacting dendrites [207]. Their theory can only be applied to high pulling speeds where dendrite tips interact weakly¹² and where each tip is assumed to evolve according to microscopic solvability theory. They predicted that for a given initial λ_1 , there is a lower critical velocity below which λ_1 period doubles via cell elimination, whereby every other dendrite tip survives. Interestingly, a stability analysis of an accelerating interface [208] suggested that λ_1 will period double to its final value *before* the dendrite array reaches the steady state pulling speed. The predictions of Warren and Langer set lower bounds for the spacing observed in traditional directional solidification experiments such as those conducted by Trivedi and co-workers [196].

A series of experiments by Losert and co-workers supported the predictions of the Warren and Langer theory [143, 140, 141, 142]. In one set of experiments [143] they first solidify an organic alloy sample until a primary spacing, λ_1^o is achieved. They then begin to decrease the pulling speed V in steps, observing that the dendrite array gradually increases its λ_1 . Below some critical velocity V_c the array becomes unstable and λ period doubles to approximately $\lambda_1 \approx 2\lambda_1^o$. The transition velocity is close to the one predicted theoretically [207, 208]. The same group later tested the stability of the dendrite array by using laser heating to modulate the amplitude of the dendrite tip envelope [140]. The decay of the envelope amplitude back to the originally established λ_0 followed the linear growth exponent predicted by the Warren and Langer theory. Interestingly the spacing selected in all their dendrite arrays always fluctuated within a range of values, not a well defined one. Figure (6.13) shows data reprinted from Losert et. al [143], which shows how λ_1 changes (bottom figure) as pulling velocity is decreased (top figure) from its original value from which the initial steady state array was achieved. Other experiments by Huang and co-workers similarly showed that after establishing a steady state dendrite array with λ_1^o at pulling speed V_o , the new λ_1 that emerges after changing the pulling speed from $V_o \rightarrow V_p$ depends on the initial V_o .

Dynamical selection theories and associated experiments have been very successful in predicting how an established dendrite array may change upon modification of the original pulling speed V . They have not, however, addressed the questions of how the initial dendrite array is established from arbitrary initial conditions such as that of a flat interface perturbed by thermal fluctuations, or a collection of nucleated crystals near a mould wall. Moreover, it is not clear how the experiments of Losert et. al depend on the rate of change of the pulling speed; as mentioned previously, experiments consistently appear to give rise to reproducible values of λ_1 vs V when V is held constant long enough under a given set of processing

¹²The theory assumes solute contributions from different dendrite tips are independent line sources.

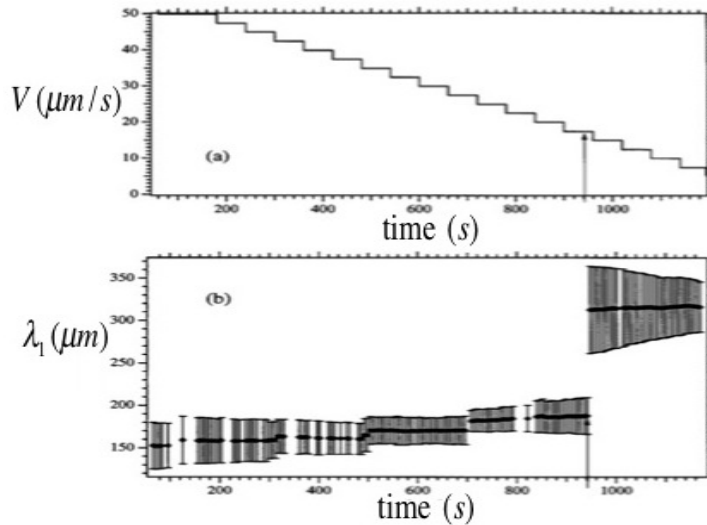


Figure 6.13: (a) Step-wise decrease in pulling speed of a directionally solidified SCN-C152 alloy. an initial dendrite array is established at the speed corresponding to $t = 0$. (b) the corresponding change in the initial dendrite array spacing λ_1 . Below a critical speed there is an approximate period doubling of the spacing. Figure adapted from Ref. [143].

conditions. Present theoretical and experimental work leaves open the possibility that under a given class of fixed initial interface conditions and processing conditions, there can be a reproducible set of spacings versus pulling speeds. However, it seems likely that the selection function $\lambda = f(V, G)$ will be dependent on initial conditions and the particular solidification process.

6.10.3 Phase field simulations of directional solidification

In recent years, phase field modeling of solidification has emerged as perhaps the most robust way to simulate the complex morphologies and inter-dendritic interactions "virtually", thus avoiding the various challenges that enter analytical theories. Moreover, in the case of a dilute alloy, it is possible to use equations such as Eqs.(6.63)-(6.65) to model dendritic growth *quantitatively* [57]. Figure (6.14) shows a phase field simulation of a directionally solidified dendrite array in SCN-ACE. As in Fig. (6.11), there is a clear competition between primary branches that causes the familiar branch elimination, which ultimately leads to a dynamic change of λ_1 far away from the initial spacing predicted by the Mullins and Sekerka linear instability theory.

Phase field simulations such as the one shown in Fig. (6.14) have become quantitatively comparable to experiments owing almost entirely to two innovations. The first is the development of thin interface relations such as the ones discussed earlier in this chapter. Another crucial innovation is the efficient use of adaptive mesh refinement (AMR). As discussed in section (5.7.3), AMR is a computational methodology that makes it possible for numerical meshing to track only those parts of the system where a phase transformation occurs. Figure (6.15) illustrates these ideas by showing how the grid the simulation of Fig. (6.14) adapts itself around the solid-liquid interfaces. The ability to perform calculations only near the interface reduces the dimensionality of the domain, making it possible to simulate such problems as

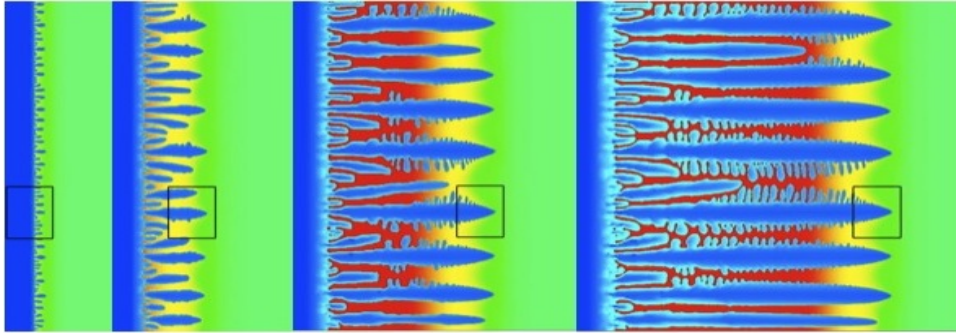


Figure 6.14: Directional solidification of Succinonitrile-4wt%acetone. Pulling speed is $V = 4\mu\text{m/s}$ and $G = 5\text{K/mm}$. Warm/cold colors represent high/low concentration, respectively.

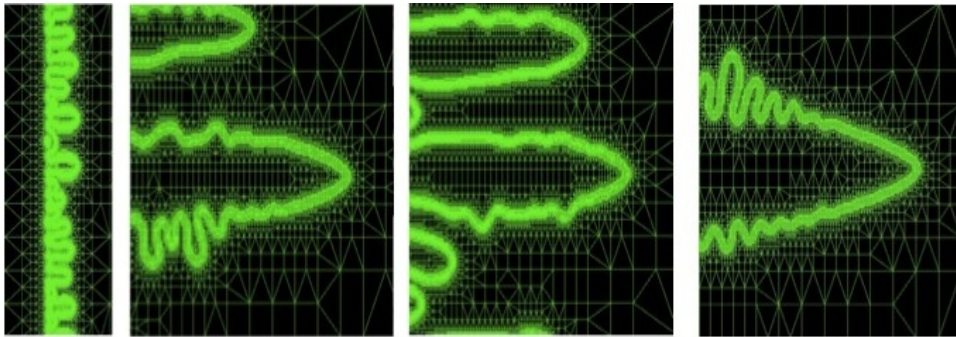


Figure 6.15: Time sequence of the adaptive mesh corresponding to the boxed region in Fig. (6.14). Time sequences shown are different from those in Fig. (6.14).

dendrite growth, precipitate growth and directional solidification type problems on very large domains and on much smaller real time scales.

Recently Greenwood and co-workers conducted phase field simulations to analyze the spacing selection problem using power spectrum analysis of the solidification front [86]. The primary branch spacing λ_1 is identified by using mean of the power spectrum $P(k) = \hat{h}(k)\hat{h}^\dagger(k)$, where $\hat{h}(k)$ is the Fourier transform of the interface profile $h(z)$, defined as the distance to the interface along the x -axis from some origin and the z coordinate is transverse to the growth direction. The 1D wavevector $k = 2\pi/\lambda$ is a measure of the inverse length scale λ . The profile $h(z)$ is made monotonic by following the contours of the dendritic envelopes. The power spectrum $P(k)$ can be used to construct the inverse wavelength probability density. This density can be used to analyze the statistical character of the spacing selection problem. The distribution $P(k)$ contains information about the importance of all length scales influencing the dendrite array. Figure (6.16) shows the time evolution of a typical dendritic array and its corresponding power spectrum. The dendrite array in the figure has not yet reached a true steady state, nor is it clear if such an ideal state will ever be reached. However, there is an apparent or characteristic spacing evident in the array, which corresponds to the primary peak in the power spectrum. Greenwood and co-workers plotted k_{mean} versus $1/t$ and extrapolated the data to infinite time, to estimate the average array spacing $\langle\lambda_1\rangle$.

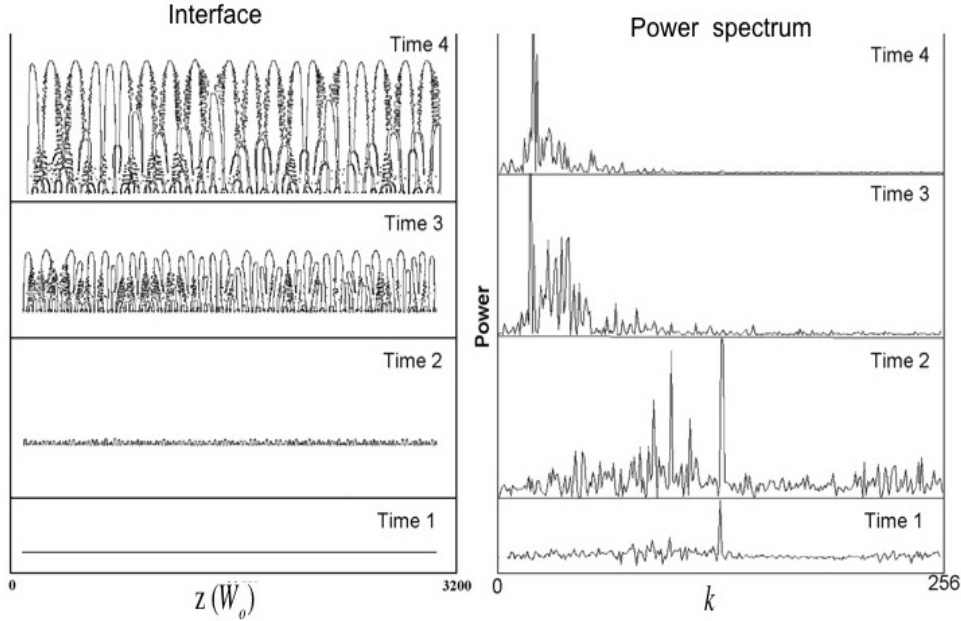


Figure 6.16: (Left) Solid-liquid interface of a dendritic array at different times. Pulling speed of $V_s = 150\mu\text{m/s}$ and thermal gradient is $G = 1500\text{K/mm}$. (Right) power spectrum of corresponding interfaces at left. Units of length are all in the phase-field interface width W_o .

They also noted that the main peak develops very rapidly, before approach to a steady state becomes apparent in the array.

The work of Ref. [86] conducted simulations like the ones shown in Fig. (6.16) for several sets of phase-field parameters (G , V , C_o , k , λ) [86]. Here, λ is the coupling coefficient in Eq. (6.75), and C_o is the alloy composition. Their simulations found cellular structures emerge at small V , while at high V dendritic arrays emerge. The spacing $\langle\lambda_1\rangle$ attains a maximum for intermediate values of V , near where the thermal length approaches the solute diffusion length, i.e. $l_T \approx l_D$. The presence of such a maximum has been predicted theoretically [131] and observed in experiments [21, 139]. Figure (6.17) shows simulated $\langle\lambda_1\rangle$ data collapsed onto a plot of dimensionless wavelength vs. a dimensionless velocity. On the same plot are superimposed three experimental data sets from Ref.[139], in which directional solidification of organic alloys of SCN and PVA were studied. The three experiments in Fig. (6.17) are for SCN-0.25mol % Salol at 13K/mm, SCN-0.13mol %ACE at $G=13\text{K/mm}$ and PVA-0.13mol % Ethanol at $G=18.5\text{K/mm}$. The change in the two slopes corresponds to where V in the raw data reaches a maximum.

Dantzig and co-workers extended phase field simulations to the study of microstructure selection in directional solidification in three dimensions [109, 108, 12, 13]. Their simulations studied directional solidification of an SCN-Salol alloy in the thermal gradient $G = 4\text{K/mm}$ and with a thermal length $l_T = 4.9 \times 10^{-4}\text{m}$. As in the two dimensional simulations of Ref. [86], the the 3D simulations were started from an initially flat interface perturbed by uniformly random fluctuations. Figure (6.18) shows the emergence of cellular arrays arising for pulling speeds and for different glass plate spacings δ (units of interface width W_ϕ). As the thickness of the channel, δ becomes smaller, the scaling of the 3D dendrites

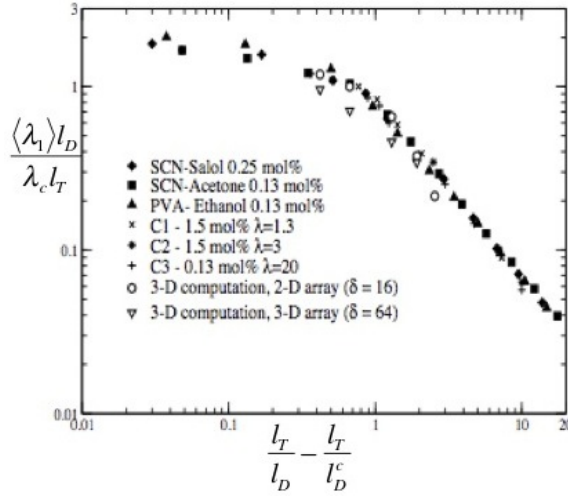


Figure 6.17: *Dendrite spacings from computations and experiments from Ref. [139] scaled to material properties, producing a single scaling function for primary spacings λ_1*

approaches that of the 2D dendrites, as expected. Specifically, after a sufficient transient time, they analyzed their data using a Fourier technique as described in the 2D simulations. For the smallest values of δ , they found that through a suitable re-scaling, the computed $\langle \lambda_1 \rangle$ vs. V data collapsed onto the curve shown in Fig. (6.17).

The simulations of Greenwood et. al and Dantzig and co-workers suggests that $\langle \lambda_1 \rangle$ can be described by a crossover scaling function of the form

$$\frac{\langle \lambda_1 \rangle}{\lambda_c} = \frac{l_T}{l_D} f \left(\frac{l_T}{l_D} - \frac{l_T}{l_D^*} \right) \quad (6.109)$$

where λ_c is a characteristic wavelength at the transition from the planar-to-cellular instability and $l_D^* \equiv 2D/V_c$ and V_c is the pulling speed where a planar front becomes unstable to cellular solidification. The characteristic wavelength λ_c has been evaluated numerically and found to be consistent with several theoretical predictions in the literature. Figure (6.19) compares λ_c for the 2D data of Fig. (6.17) to $\lambda_{theory} \equiv \sqrt{\lambda_{ms} l_{TR}(V_p = V_c)}$, where λ_{ms} denotes the Mullins-Sekerka wavelength at the planar-to-cellular onset boundary (i.e., where $V = V_c$), and $l_{TR}(V_p)$ is a velocity-dependent generalization of l_T , implicitly determined from $l_{TR} = l_T(1 - \exp(-\frac{l_{TR} V_p}{D}))$. Physically, $l_{TR}(V_p)$ is proportional to the amplitude of cellular fingers and satisfies $l_{TR} \approx l_T(1 - l_D^*/2l_T)$ at the onset of cellular growth, while in the limit ($V_p \gg V_c$), $l_{TR} \rightarrow l_T$. This form of λ_{theory} is similar to an analytical prediction of λ_c from a geometrical model [131]. Figure (6.19) also compares λ_c to $\lambda_{theory} = (d_o l_D l_T)^{\frac{1}{3}}$, which represents the geometric mean of the three length scales, empirically suggested to be proportional to the wavelength at the planar-to-cellular onset [195]. Figure (6.19) suggests that for both cases $\lambda_c = \alpha \lambda_{theory}(1 + \beta d_o / \lambda_{theory})$, where α and β are material independent constants.

Boettinger and Warren also examined directional solidification in an isomorphous alloy [27] using a phase field model they previously developed [204, 26], which employed a frozen, linear thermal field and a free energy of the form discussed in section (6.3.3). Using parameters approximately corresponding

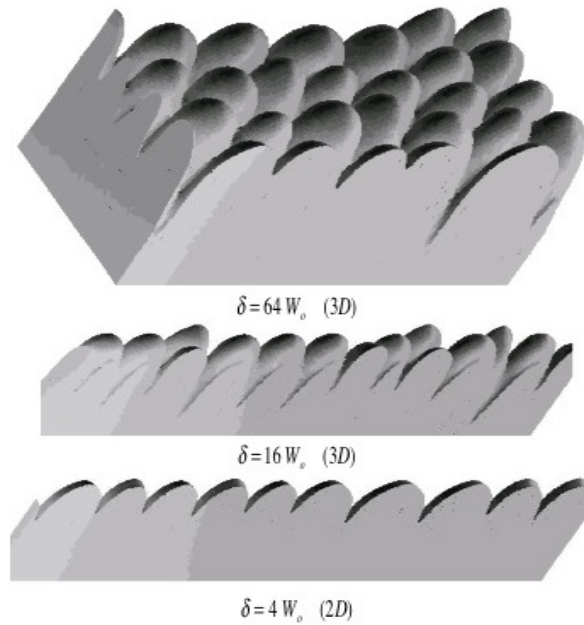


Figure 6.18: *Directional solidification of an SCN-Salol alloy in 3D. As the spacing between the glass plates becomes smaller than the tip radius the simulations effectively becomes two dimensional. Adapted from Ref. [13]*

to Ni-Cu they also found evidence of a monotonic relationship between a band of dendrite spacing λ_1 and pulling velocity. It is not clear if their simulations can be quantitatively compared to the ones of Greenwood et. al and Dantzig et. al. The latter investigators used quite a small simulation domain, making their results amenable to strong finite size effects. Also they used a dilute binary alloy "tuned" using the asymptotic analysis discussed in this chapter in order to emulate the interface equilibrium conditions specified in section (6.2.2). The former investigators used a different model and did not apply any thin-interface correction; indeed the work of Boettinger et. al is aimed at investigating the role of solute trapping on the interface stability. Nevertheless, the qualitative agreement with the previous phase field simulations is apparent. Interestingly, the work of Boettinger et. al also shows that the different realizations of uniformly random perturbations of an initially flat initial interface gives rise to spread in the final λ_1 for a given V . This is consistent with some statistical selection mechanism rather than exact dynamical selection.

The combination of phase field modeling, analytical theories and experiments of directional solidification raise some interesting questions. On the one hand, it appears that the primary spacing displays, at least in the statistical sense, a scaling theory for a given class of initial conditions and the case of constant pulling speeds and thermal gradients. On the other hand, it also appears that the *precise* steady state of a dendritic array is not deterministic and may flow into an ensemble of states that depends on initial and cooling conditions. Is there a way to reconcile these apparently contradictory conclusions? The answer may lie in what is meant by "dendrite spacing". It is clear from experiments that dendritic spacing does fall into at least a range of reproducible values, for slowly varying cooling conditions. In

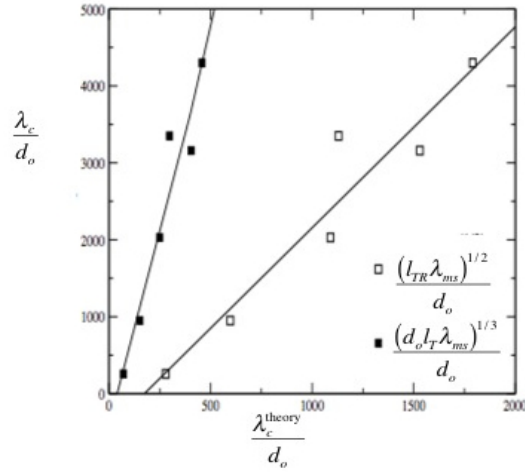


Figure 6.19: Plot of λ_c/d_o versus two previously published theoretical prediction of the same quantity.

this case, the average spacing $\langle \lambda_1 \rangle$ is characterized analogously to that in Fig. (6.16). It is therefore plausible the precise values of λ_1 , as influenced by finer oscillations of the tip [58], breathing modes, etc., can all comprise finer structure to a larger scale selection principle characterized by $\langle \lambda_1 \rangle$, and which is determinable by the fundamental length scales of the solidification problem. That would also explain why the phenomenological power-law theories of Hunt, Kurz, Kirkaldy and others are robust enough have the same trend as experiments. From the perspective of materials engineering, a coarse approximation such as that given by geometric models or scaling theories like that of Greenwood et. al are probably more than adequate. However, from the perspective of understanding the fundamental physics during pattern formation in solidification more research is required to elucidate the non-linear dynamics controlling dendrite array selection.

6.10.4 Role of Surface Tension Anisotropy

It was previously discussed that an isolated crystal requires anisotropy in surface tension or interface kinetics in order to select dendritic growth directions. In the absence of any anisotropy, a solidifying crystal will meander, forming a "seaweed" like patterns formed through successive tip splitting of the primary branches as they grow. Seaweed are also possible in directional solidification [7, 197, 102] where they can emerge when the temperature gradient is mis-oriented with respect to preferred growth direction corresponding to the minimum in surface tension. The resulting competition between the driving force provided by the thermal gradient and the lower free energy along the axis of surface tension anisotropy can cause the dendrite growth tip to undergo a succession of tip splittings (a key feature of seaweed evolution) as it attempts to follow two growth directions. Figure (6.20) shows a 2D phase field simulation of seaweed. In the figure the anisotropy of the surface tension is oriented at 45 degrees from the x axis, while the direction of heat extraction is along the negative y axis.

Reference [174] used phase field modeling to examine the morphological transition in two dimensional directional solidification. it was found that a mis-orientation between the direction of a thermal gradient, G , and the direction of minimum surface tension leads to a transition in dendrite microstructures [174].

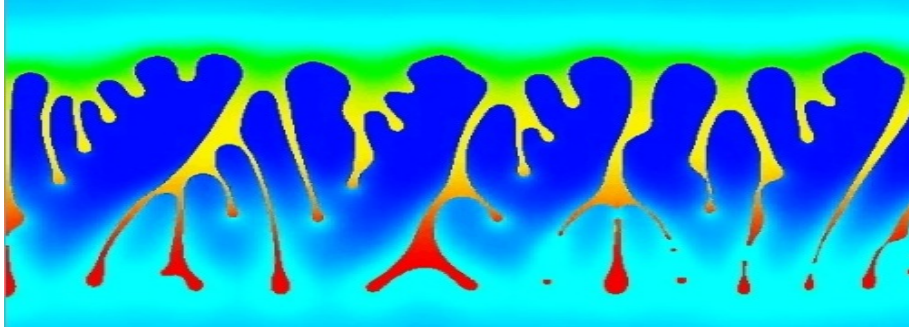


Figure 6.20: Phase field simulation of a typical seaweed structure emerging when two sources of anisotropy compete.

Figure (6.21) shows a phase field simulation of a dendritic array where the surface tension is minimal at directions 45° from the z -axis (horizontal) and where the thermal gradient is one dimensional along the z -axis. The thermal gradient in this simulation is set low enough that the surface tension anisotropy controls the minimization of free energy. This results in dendritic crystal array oriented in the direction of the surface tension anisotropy (45° with respect to the z -axis). In Fig. (6.22), the thermal gradient (i.e.,

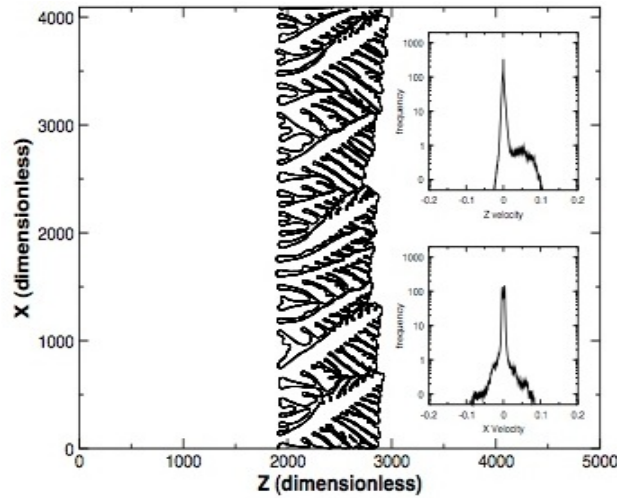


Figure 6.21: Directional solidification with the surface tension anisotropy oriented at 45° with respect to the z -axis. $G = 0.8k/mm$ and $V_p = 32\mu m/s$. Below a critical thermal gradient (oriented along the z -axis) the surface tension anisotropy controls the growth and dendritic structures emerge, oriented very closely the 45° axis. The insets show the velocity distribution in the x and z directions, respectively.

driving force along z -direction) is increased and a competition sets in between the preferential direction of surface tension anisotropy and the cooling direction. The ensuing competition leads to the characteristic seaweed-like structures seen in the figure, structures characterized by a continuous succession of growth

and splitting of a rather bulbous primary and –to a lesser extent– secondary tips.

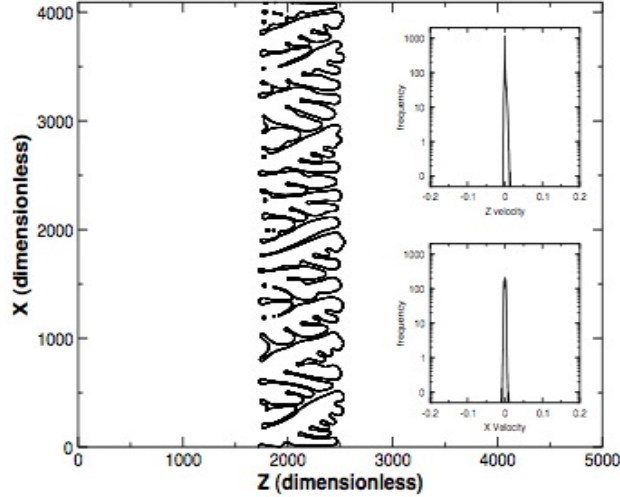


Figure 6.22: *Directional solidification with the surface tension anisotropy oriented at 45° with respect to the z -axis. Cooling parameters are the same as in Fig. 6.21. As the thermal gradient increases a competition between growth in the forward direction and the direction of surface tension anisotropy leads to multiple dendritic tip splittings, and a subsequent crystal structure that resembles seaweed. The insets show the velocity distribution in the x and z directions, respectively*

One way to characterize the morphological change from 2D dendrites to 2D seaweed is the distribution of local interface velocities. This is shown in the insets of Figs. (6.21) and (6.22). It is typical for seaweed structures to exhibit a sharp velocity distribution, while a broadening of the distribution is typical as dendrites emerge. Another way to quantify the transition exemplified in Figs. (6.21) and (6.22) is by a semi-analytical argument presented in [174]. For the parameters used to generate the data shown here, this analysis predicts that for a given ϵ_4 , a morphological change from seaweed to oriented dendrites will occur when the cooling gradient G is below

$$G^* \approx P_f \sqrt{(V_p \cos \theta) / (D d_o [1 + 15 \epsilon_4 \cos 4 \theta])} \quad (6.110)$$

where $P_f \approx 0.004$, V_p is the pulling speed, θ is the angle of anisotropy, D is the diffusion constant, d_o is the capillary length and ϵ_4 is the anisotropy strength. This selection criterion defines a morphological phase diagram in $V_p - G$ space for a fixed ϵ_4 . It predicts a crossover from seaweed to oriented dendrites as a function of V_p . At sufficiently large V_p it is expected the fastest growing unstable wavelength to occur in the forward direction regardless of the angle of anisotropy. It is quite plausible that the phenomenon described here is ubiquitous and presents itself in other forms when two or more anisotropies controlling growth directions are present.

The transition between competing dendritic growth directions becomes significantly more complex in three dimensions. For example, molecular dynamics has shown [95] that a correct characterization of the surface energy of a 3D crystal requires the angles θ and Φ of the spherical coordinate system to be

parameterized. Specifically, the stiffness γ of a crystal is given by

$$\gamma(\theta, \Phi) = \gamma_o (1 + \epsilon_1 K_1(\theta, \Phi) + \epsilon_2 K_2(\theta, \Phi)) \quad (6.111)$$

where γ_o is the isotropic surface tension and K_1 and K_2 are cubic harmonics, which are simply combinations of spherical harmonics [95]. The parameters ϵ_1 , ϵ_2 are the 3D analogues of ϵ_4 used in 2D. They can be used to define preferential growth along multiple directions depending on their relative strength. For example, in FCC metals $\epsilon_2 < 0$ and $\epsilon_1 > 0$. A positive term K_1 favours growth in the $\langle 100 \rangle$, while a negative K_2 term favors growth in the $\langle 110 \rangle$ direction. The direction that is eventually selected will clearly depend on the relative strength of these two terms. A recent phase field study Haximali and co-workers [89] showed that competition between ϵ_1 and ϵ_2 will cause a transition between equiaxed $\langle 110 \rangle$ oriented dendrites to seaweed and back to equiaxed $\langle 100 \rangle$ dendrites. Figure (6.23) shows an example of the emergent dendrite morphologies of a pure material when ϵ_2 is held fixed and ϵ_1 is varied [89]. Haximali and co-workers also considered the combined effect of ϵ_1 and ϵ_2 , predicting a phase diagram containing a region of $\langle 110 \rangle$ dendrites, a region of $\langle 110 \rangle$ dendrites and a region of seaweed structures.

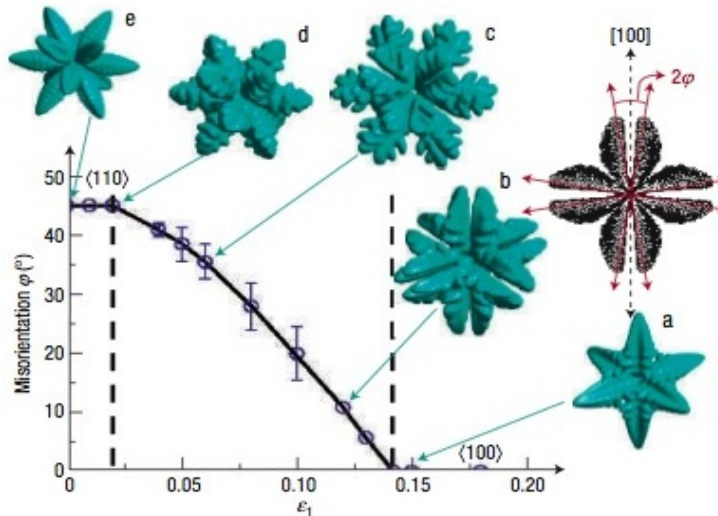


Figure 6.23: Figures (a)-(e) show the dendritic growth forms versus ϵ_1 for $\epsilon_2 = -0.02$. The azimuthal mis-orientation between branches changes continuously $\Phi = 0$ to $\Phi = 45^\circ$. The top right figure shows the interface cross sections at equal time intervals along a $\langle 100 \rangle$ plane of sub-image (b). Projected contours show the mis-orientation between growth directions, quantified by the azimuthal angle Φ . Reproduced from Ref. [89].

The study of Haximali and co-workers also considered the role of the the anisotropy parameters ϵ_1 and ϵ_2 in binary alloys. Interestingly, they conjectured that increasing the nominal alloy composition in a binary alloy (e.g. wt%Zn in Al) will result in a simultaneous change in both the anisotropies,. This hypothesis was found to be consistent with molecular dynamics work of Hoyt and co-workers [95]. The implication of their finding is that changing the impurity content of an alloy will led to different dendritic morphologies. Specifically they estimated that the change in anisotropy parameters would make

the corresponding dendritic morphology transition from a $\langle 100 \rangle$ equiaxed structure to seaweed. Evidence of this transition was found in experiments in directionally solidified of Al-Zn alloys.

Chapter 7

Multiple Phase Fields and Order Parameters

In recent years, the basic principles of phase field theory have been used to develop an large number of so-called multi-phase or multi-order parameter phase field models, which have been applied to the study of poly-crystal, multi-phase or multi-component phenomena in phase transformations. Generally speaking these models fall in three classes. Models incorporating multiple order parameters goes back to the work of Khachaturyan and co-workers [48, 49]. The introduction of orientational order parameters to examine poly-crystalline solidification goes back to the work of Kobayashi and Warren [127, 128]. The introduction of multiple, phase fields, which are interpreted as volume fractions, has been championed by Steinback and co-workers [192, 104, 28]. Since the inception of these models many other works that have used or expanded on the ideas developed in the above references. The reader is referred to the following small, but by no means exhaustive, list of such works includes: [3, 201, 202, 205, 191, 75, 126, 159, 116, 42, 160, 184, 81, 84, 83, 88, 221, 211, 121, 76, 17, 155, 118, 125]. The majority of multi-order parameter or multi-phase field models have found applications in solid state grain growth and coarsening and more recently in multi-phase precipitation. Some models also incorporate elastic effects in order to study the role of strain in phase transformations. Others, particularly ones that employ an orientational order parameter, have been used predominately to examine dendritic solidification and the subsequent formation of polycrystalline network.

As with single phase field theories, multi-order and multi-phase field models are typically constructed so as to respect the thermodynamic symmetries of bulk phases and to consistently reproduce the correct sharp interface kinetics in the limit when phase field interfaces become mathematically sharp. These models are not immune from the diffuse-interface problems discussed previously. A thin interface limit analogous to that discussed in conjunction with single order parameter theories is generally lacking for such models [75, 56]. This does not pose a big problem in solid state problems where the disparity in diffusion coefficients is small and the kinetics is largely curvature or diffusion controlled. It can be a problem, however, when using multiple phase fields to simulate the entire solidification path of multiple phases or crystals. The same general comments can be made about orientational order parameter models –or multi-order parameter models in general. There are several notable exception to these general observations. One is is the multi-phase field work of Folch and Plapp [74]. They have used three volume fraction fields to simulate eutectic solidification in binary alloys using diffuse interfaces. They

employ a free energy functional that reduces along any two-phase boundaries into the thin-interface model of Echebarria and co-workers [57]. More recently, Kim [120, 118] also extended the use of the anti-trapping formalism discussed in the last chapter to a single phase solidification model with multiple concentration fields. This technique was recently used by Steinbach [189] to associate an anti-trapping for each concentration field of a multi-phase field model.

Delving into the technical details of multi-phase field and multi order parameter models is beyond the scope of an introductory text. In order, therefore, to keep the length of this book manageable, this chapter will only introduce the basic aspects of such models. The reader is directed to the various works cited in this section –and references therein– for a more complete analysis on this subject and its applications.

7.1 Multi-Order Parameter Models

The original concept of a multiple solid order parameters was already discussed in section (5.1), where a separate order parameter was associated with each reciprocal lattice vector of a crystal. In that context, each order parameter was complex and could be used to reconstruct atomic-scale structure in a crystal, as will be discussed in later chapters. In a slightly different context, Khachaturyan and co-workers introduced multiple *real* order parameters, ϕ_i , to distinguish between different ordered structures (e.g. as occurs in solid state transformations). In this case, a phenomenological free energy functional is constructed to respect the appropriate symmetries in each order parameter and, in the case of alloy, the appropriate thermodynamics in each phase. Dynamics for each ϕ_i follow the usual minimization principle examined in the context of single order parameter theories. Dynamics of compositions and temperature follow the standard conservation laws.

7.1.1 Pure materials

The simplest multi-order free energy that can represent transformations that involve the reduction of symmetry between a parent phase and different ordered daughter phases has the form [50, 47, 116]

$$F[\{\phi_i\}] = \int dV \left[\sum_{i=1}^N \frac{\epsilon_{\phi_i}^2}{2} |\vec{\nabla} \phi_i|^2 + f(\phi_1, \phi_2, \phi_3, \dots, \phi_N) \right] \quad (7.1)$$

where the fields $\{\phi_i\} \equiv \phi_1, \phi_2, \phi_3, \dots, \phi_N$ describe each order phase $f(\phi_1, \phi_2, \phi_3, \dots, \phi_N) \equiv f(\{\phi_i\})$ denotes the local or "bulk" part of the free energy. A simple form of $f(\{\phi_i\})$ that is the analogue of the "double-well" potential is given by

$$f(\{\phi_i\}) = \sum_{i=1}^N \left(-\frac{A}{2} \phi_i^2 + \frac{B}{4} \phi_i^4 \right) + \alpha_{obs} \sum_{i=1}^N \sum_{j \neq i}^N \phi_i^2 \phi_j^2 \quad (7.2)$$

The first term in Eq. (7.1) gives rise to gradient energy and therefore grain boundary energy of a phase, proportional to the coefficient ϵ_{ϕ_i} . The second term represents a multi-well potential having $2N$ minima, making it possible to theoretically consider a large number of crystals for single phase systems (or several phases). In this case where $A = B = 1$, the multi-well has minima at $\phi_i = \pm 1$ and $\phi_j = 0 \forall j \neq i$. Other forms of the free energy can be constructed that give minima at $\phi_i = 0, 1$. The constants A and B can also depend on temperature, as do in that case the minima of the multi-well potential. The last term containing α_{obs} called *obstacle potential*. This is an interaction energy that penalizes fields for

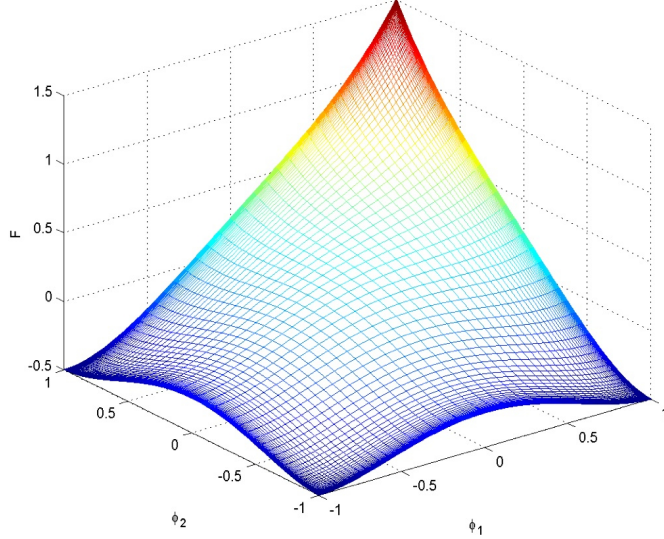


Figure 7.1: *Multi-Phase field free energy functional, neglecting gradient term and with $\alpha_{obs} = 1$.*

overlapping, in proportion to the barrier α_{obs} . This free energy functional, for the case of $N = 2$ and neglecting the gradient term is plotted in Figure (7.1). The free energy in Eq. (7.1) has been used to study simple properties of grain growth and coarsening.

By extending the free energy to a sixth order polynomial it is possible to generate a free energy landscape that allows transitions to meta-stable states. Khachaturyan and co-workers [203] also introduced a sixth order free energy of the form

$$f(\phi_1, \phi_2, \phi_3) = \sum_{i=1}^3 \left(-\frac{A}{2}\phi_i^2 + \frac{B}{4}\phi_i^4 \right) + \frac{C}{6} \left(\phi_1^2 + \phi_2^2 + \phi_3^2 \right)^3 + \alpha_{obs} \sum_{i=1}^N \sum_{j \neq i}^N \phi_i^2 \phi_j^2 \quad (7.3)$$

to study the transition from a cubic phase to a meta-stable martensitic phase. In this case a cubic disordered phase gives rise to one of three variants daughter phases with tetragonal symmetry, where each cubic phase can take on two orientations. A very important realization of this transformation occurs when austenite is converted to martensite steel. This transformation is induced by rapidly quenching austenitic steel (cubic symmetry), which leads to a metastable martensite phase having tetragonal symmetry. Martensite is a very hard brittle phase, while austenite is more soft and ductile. Forming a certain fraction of martensite in austenite is a common way to harden steels.

Dynamics of multiple order parameters proceeds analogously to the case of single order parameters theories. Each ϕ_i evolves according to dissipative dynamics that dynamically minimize $F[\{\phi_i\}]$ according to

$$\begin{aligned} \frac{\partial \phi_i}{\partial t} &= -\Gamma_{\phi_i} \frac{\delta F}{\delta \phi_i} + \eta_i(\vec{x}, t) \\ &= -\Gamma_{\phi_i} \left[\frac{\partial f(c, \phi_i)}{\partial \phi_i} - \epsilon_{\phi_i}^2 \nabla^2 \phi_i \right] + \eta_i(\vec{x}, t), \end{aligned} \quad (7.4)$$

The noise term η_i can in principle be different for each order parameter, although is typically drawn from a Gaussian distribution with zero mean and variance consistent with the fluctuation dissipation theorem [44].

7.1.2 Alloys

Structural transformations typically occur in alloys, which involve the precipitation one or more ordered phase from a disordered phase and mass transport. An interesting metallurgical example is the $\gamma' \rightarrow \gamma$ transition in AN-Al alloys, there the γ' phase can assume one of four crystal symmetries (i.e. $i = 1, 2, 3, 4$) [221]. To include impurity effects, the coefficients in the free energy density of the previous sub-section must be made to depend on the concentration c , which is the weight or mole percent of impurities in the solvent element of the alloy.

Wheeler *et al* [209] and later Fan and Chen [72] extended multi-order parameter approach to study grain growth in two-phase solids of a binary alloy. These were then extended by Fan *et al.* [73] to study Ostwald ripening in a poly-phase field model of a binary alloy. The basic form the the free energy functional has the form

$$F[\{\phi_i\}, c] = \int dV \left[\sum_{i=1}^N \frac{\epsilon_{\phi_i}^2}{2} |\vec{\nabla} \phi_i|^2 + \frac{\epsilon_c^2}{2} |\vec{\nabla} c|^2 + f(\{\phi_i\}, c) \right], \quad (7.5)$$

For a general bulk free energy $f(\{\phi_i\}, c)$, this model will be plagued by similar mathematical difficulties as its 1D analogue studied in section (6.4). Finding the equilibrium order parameters, ϕ_i^{eq} , requires multi-variable minimization in this case, which can be quite complex. Moreover, the ϕ_i^{eq} are concentration dependent. Furthermore, the surface energy will depend on the properties of the steady state concentration and order parameter profiles. While straightforward to calculate, these properties become very tedious for multi-order parameter models. In addition, there will also be an upper bound on the gradient energy coefficient(s) that can be used while self-consistently representing a particular surface energy.

To overcome these problems Chen and co-workers [222, 223] have extended the method of Kim and co-workers studied in section (6.9) to multiple order parameters ¹. For the case of chemically identical precipitates of N different crystal symmetries, two fictitious concentration fields are defined, one for a precipitate phase, C_p , and another for the matrix phase, C_m . The physical concentration, c is then interpolated by

$$c = C_p p(\{\phi_i\}) + C_m (1 - p(\{\phi_i\})). \quad (7.6)$$

where

$$p(\{\phi_i\}) = \sum_i^N P(\phi_i) \quad (7.7)$$

and $h(\phi_i)$ is any convenient interpolation function that restricts each order parameter between ($0 \leq \phi_i \leq 1$). A simple form used in Ref. [221] is

$$P(\{\phi_i\}) = \sum_i^N \phi_i^3 (6\phi_i^2 - 15\phi_i + 10) \quad (7.8)$$

¹This approach was also developed at the same period of time in the context of multi-phase field models by Taiden *et. al* [104].

In addition to Eq. (7.6), the fictitious concentrations C_m and C_p are restricted to satisfy a constant chemical potential at all points by imposing the condition

$$\frac{\partial f_p(C_p)}{\partial c} = \frac{\partial f_m(C_m)}{\partial c} \quad (7.9)$$

where f_p and f_m are the free energies of the precipitate and matrix phases, respectively. Together, Eqs. (7.6) and (7.9) imply that for any combination of $\{\phi_i\}$ and c in the system, there is a unique C_p field and C_m field. Physically this implies that any diffuse interface is a mixture of matrix and precipitate phases with a constant chemical potential. Equations. (7.6) and (7.9) can be self-consistently solved numerically using the method of Eq. (6.107) where $h(\phi) \rightarrow p\{\phi_i\}$.

In terms of C_m and C_p , the free energy density $f(\{\phi_i\}, c)$ is then written as [120, 222, 223],

$$f(\{\phi_i\}, c) = p(\{\phi_i\})f_p(C_p, T) + (1 - p(\{\phi_i\}))f_m(C_m, T) + Hf_D(\{\phi_i\}) \quad (7.10)$$

where H is the height of the double well, i.e. nucleation barrier and $f_D(\phi_i)$ is a multi-well potential given by

$$f_D(\{\phi_i\}) = \sum_{i=1}^N \phi_i^2 (1 - \phi_i)^2 + \alpha_{obs} \sum_{i=1}^N \sum_{j \neq i}^N \phi_i^2 \phi_j^2 \quad (7.11)$$

It is noted that f_p and f_m can be directly chosen from thermodynamic databases, leading to a quantitative evaluation of driving forces. The first term in Eq. (7.11) sets the nucleation barrier for each variant and the "obstacle" term α_{obs} models an interaction penalty for the overlap of any two or more interfaces.

The evolution equations for ϕ_i , once again, follow

$$\begin{aligned} \frac{\partial \phi_i}{\partial t} &= -\Gamma_{\phi_i} \frac{\delta F}{\delta \phi_i} + \eta_i(\vec{x}, t) \\ &= -\Gamma_{\phi_i} \left[\frac{\partial f(\{\phi_i\}, c)}{\partial \phi_i} - \epsilon_{\phi_i}^2 \nabla^2 \phi_i \right] + \eta_i(\vec{x}, t), \end{aligned} \quad (7.12)$$

while the impurity concentration evolves according to mass conservation,

$$\begin{aligned} \frac{\partial c}{\partial t} &= \vec{\nabla} \cdot \left[\Gamma_c(\phi, c) \vec{\nabla} \frac{\delta F}{\delta c} \right] \\ &= \vec{\nabla} \cdot \left[\frac{D(\{\phi_i\})}{\partial_{,cc} f(\{\phi_i\}, c)} \vec{\nabla} \left(\frac{\partial f(\{\phi_i\}, c)}{\partial c} - \epsilon_c^2 \nabla^2 c \right) \right] \end{aligned} \quad (7.13)$$

where $D(\{\phi_i\})$ is the phase dependent diffusion coefficient. A typical choice often used in the literature is $D(\{\phi_i\}) = D_p p(\{\phi_i\}) + D_m (1 - p(\{\phi_i\}))$. This choice is phenomenological through the interface region because of the arbitrariness of the choice of $p(\{\phi_i\})$. It is possible, however, to replace this function by a new one, say $H(\{\phi_i\})$, with the same bulk phase limits and different interface properties that match some desired measurements. The partial derivatives on the right hand sides of Eqs. (7.12) and (7.13) can be cast in terms of C_m and C_p using Eqs. (6.93)-(6.95), where $\phi \rightarrow \phi_i$, $h(\phi) \rightarrow p\{\phi_i\}$ and $h'(\phi) \rightarrow P'(\phi_i)$.

The multi-order parameter formulation discussed here can be analyzed similarly to the model of section (6.9) to obtain the equilibrium properties of the model. Specifically, because of the method chosen to interpolate concentration, the chemical potential becomes constant through the interface, thus

removing any explicit dependence of concentration from the surface energy calculation. The resulting phase field steady state equation (i.e Euler-Lagrange equation) for ϕ_i describing the transition across an equilibrium matrix-precipitate boundary becomes the familiar form leading to a hyperbolic tangent solution. The resulting expression for surface tension and interface width are determined as in Ref. [120],

$$\begin{aligned}\sigma &= \frac{\epsilon_\phi \sqrt{H}}{3\sqrt{2}} \\ W &= \frac{\sqrt{2}\epsilon_\phi}{\sqrt{H}}\end{aligned}\quad (7.14)$$

Where the specific factor of $\sqrt{2}$ depends on the definition used to define the interface width (i.e. where the ϕ is sufficiently close to 0 or 1). For overlapping interfaces, these constants have a more complex dependence on the order parameters. As discussed earlier, the diffuse or thin interface limit of this and most multi-order parameter formulations is presently lacking. This is likely not to be a problem for many solid state transformations, where the difference in diffusion coefficients can be small (in some cases) and which are curvature or diffusion controlled. Of course, care must always be taken how diffuse the interface is made so that particle overlap is not induced artificially. Furthermore, in the in the limit of rapid interface kinetics, the diffuse interface is expected to generate spurious terms of the form discussed in the connection with solidification modeling in previous sections (e.g. ΔF , ΔH and ΔJ) will become significant.

7.1.3 Strain effects on precipitation

A common application of multi-phase field models is the study of second phase particle precipitation from a solid matrix. This phase transformation is usually strongly influenced by the effect of elastic strains that are generated by the mis-fitting of atoms of different crystal structures across their common boundary. For instance in the $\gamma' \rightarrow \gamma$ transition discussed above the tetragonal and cubic phases can generate a lattice mis-match of order 10^{-2} . To include this and related elastic effects an additional free energy contribution, $f_{el}(\phi)$ is added to Eq. (7.10). This leads to a elastic component to the free energy functional,

$$F_{el}[\phi, c] = \frac{1}{2} \int_V \left[\left(\epsilon_{ij} - \epsilon_{ij}^o(\{\phi_i\}, c) \right) C_{ijkl}(\{\phi_i\}) \left(\epsilon_{ij} - \epsilon_{ij}^o(\{\phi_i\}, c) \right) \right] dV \quad (7.15)$$

where subscripts denote tensor components and repeated indices imply summation ². The tensor C_{ijkl} is the elastic modulus tensor, which generally depends on phase via the order parameters ϕ_i , as well as possibly on concentration c . The tensor ϵ_{ij} is the local heterogeneous strain, defined by

$$\epsilon_{ij} = \frac{1}{2} \left(\frac{\partial u_i}{\partial x_j} + \frac{\partial u_j}{\partial x_i} \right) \quad (7.16)$$

where u_i is the i^{th} component of the displacement \vec{u} and x_i is the i^{th} cartesian coordinate ($i = 1, 2, 3$). The tensor ϵ_{ij}^o is a so-called *eigenstrain* or stress-free strain. This is a strain the material assumes in order to relieve itself of internal stresses. It serves as a reference state or strain. It generally depends on the local composition, order (i.e. phase) and temperature. Eigenstrain is illustrated intuitively by considering the free expansion of a bar heated through a temperature difference ΔT . The strain on

²It is assumed here that there is no macroscopic change in volume of the materials during the phase transformation.

the bar is $\epsilon^o = \Delta L/L_o = \alpha\Delta T$, where L_o is the original length of the bar. Any strain additional strain –internal or external– applied to the bar must be referenced with respect to ϵ^o ³.

An important source of stress-free strain in alloys arise because the difference in size of a solute atom from its host locally distorts the host lattice. The form of stress-free strains from this mechanism is known as Vagard’s law [70], and takes the form

$$\epsilon_{ij}^o \equiv \epsilon_{ij}^{\text{vag}} \equiv \frac{1}{a} \frac{da}{dc} \delta_{ij} \quad (7.17)$$

where a is the lattice parameter of a given phase Analogously, crystal structures of different lattice constants that meet at an interface locally distort (near the interface) in order to accommodate as much bonding, or partial binding, as they can. The local distortion on either side of the interface causes a elastic distortion throughout the two phases. The stress-free strain associated with misfitting lattices is modeled by a an additional contribution to ϵ_{ij}^o of the form

$$\epsilon_{ij}^o \equiv \epsilon_{ij}^{\text{mis}} \equiv \sum_{n=1}^N \epsilon_{ij}^n \phi_n^2 \quad (7.18)$$

where N is the number of crystal phases or variants that minimize the bulk free energy below the transition temperature. Here, the coupling of each term to ϕ_n makes each term in the sum ”activate” only in the ordered precipitate phase. Thus, misfit is measured relative to the cubic matrix phase. For each variant phase the eigenstrain is a diagonal tensor. For instance, in the cubic to tetragonal transformation example discussed above, $\epsilon_{ij}^n = \epsilon_i^n \delta_{ij}$, where the components of the misfit strain are: $\epsilon_i^1 = (\epsilon_3, \epsilon_1, \epsilon_1)$, $\epsilon_i^2 = (\epsilon_1, \epsilon_3, \epsilon_1)$ and $\epsilon_i^3 = (\epsilon_1, \epsilon_1, \epsilon_3)$, where $\epsilon_1 = (a_1 - a_2)/(a_2\phi_{\text{eq}}^2)$ and $\epsilon_3 = (a_3 - a_2)/(a_2\phi_{\text{eq}}^2)$, where a_1, a_2, a_3 are the lattice parameters of the cubic unit cell. Since the lattice constant depends on local composition, the misfit strains can also, strictly, have a concentration dependence [185].

Incorporating the change of order parameters of the strain energy requires an additional $\partial f_{\text{el}}(\{\phi_i\})/\partial\phi_i$ term in the large square bracket on the right hand side of the phase field equation (7.12). Moreover, strain relaxation is simulated alongside the dynamical phase field equations, Eq. (7.12) and (7.13) by solving the continuum equations of mechanical equilibrium. This is modeled by

$$\frac{\partial\sigma_{ij}}{\partial x_j} = \frac{\partial}{\partial x_j} \left(\frac{\delta F_{\text{el}}}{\delta\epsilon_{ij}} \right) = \frac{\partial}{\partial x_j} \left(\frac{\partial f_{\text{el}}}{\partial\epsilon_{ij}} \right) 0 \quad (7.19)$$

where σ_{ij} is the stress tensor. The explicit forms of $\partial f_{\text{el}}/\partial\phi_i$ and $\partial f_{\text{el}}/\partial\epsilon_{ij}$ are worked out explicitly for the $\gamma \rightarrow \gamma'$ transformation in [216] (see Eqs.(26) and (28), respectively). Use of the static -equilibrium equations implicitly assumes that strains are relaxed on much shorter time sales than any other process associated with the phase transformation in question. This assumption becomes invalid for transformations that are occur on phonon time scales.

Figure (7.2) shows evolution of γ' precipitates in a Ni-Al alloy. This simulation was done by Zhu and co-workers [221] using a multi-phase field model with elastic misfit strain similar to the one described in this section. The initial precipitates are typically seeded by a nucleating many random precipitate seeds, whose distribution is motivated by experiments [186]. As coarsening proceeds, precipitates take on a conspicuous cuboidal form. The first frame in the image shows the precipitate particles immediately

³Note that if there is a homogeneous strain ϵ_{ij}^h in the material, the eigenstrain must then be subtracted from this, i.e. $\epsilon_{ij}^o \rightarrow \epsilon_{ij}^o - \epsilon_{ij}^h$.

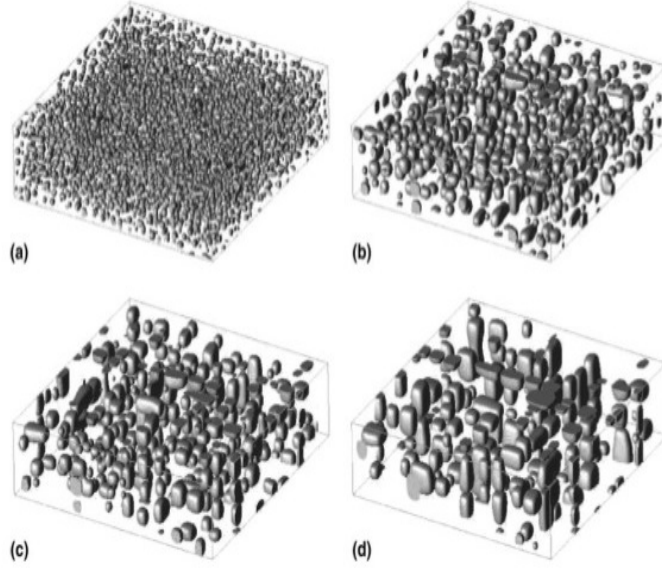


Figure 7.2: *Multi-phase field simulation of the evolution of γ' precipitates in a Ni-13.8at%Al alloy. Reprinted from Ref. [221].*

following nucleation of initial seed particles. Subsequent frames show the coarsening process, wherein particle merger reduces the number of particle. The typical particle size was mathematically characterized by $L^3(t) = L_o^3 + K(t - t_o)$, where L is the average linear dimension of the particles while L_o is the particles size at the onset of coarsening, which corresponds to the time t_c . Figure (7.3) compares this theoretical form to experiments.

7.1.4 Anisotropy

As with single order parameter theories, anisotropy of surface energy is modeled through the angular dependence on the gradient energy and the mobility coefficients. For instance, Kazaryan and co-workers [115, 116] modulate the angular dependence of surface energy anisotropy of each grain via the gradient energy coefficient ϵ_{ϕ_i} and the mobility Γ_{ϕ_i} . Specifically, they set $\epsilon_{\phi_i} = E_o^2 A(\theta, \psi)^2$ and $\Gamma_{\phi_i} = \Gamma_o A(\theta, \psi)$ where

$$A(\theta, \psi) = (|\cos \psi| + |\sin \psi|) \theta \left[1 - \ln \frac{\theta}{\theta_m} \right] \quad (7.20)$$

and θ and ψ are the two angles required to measure a tilt boundary mis-orientation, and E_o and Γ_o are isotropic reference values of surface energy and mobility, respectively. it is found that anisotropic mobility leads to a modification of the usual Allen-Chan relationship [39] which related growth of grain boundary area in a polycrystalline sample according to

$$A(t) - A(t = 0) = -kMt, \quad (7.21)$$

where k is a constant and M is related to the interface mobility, corrected for anisotropy [115].

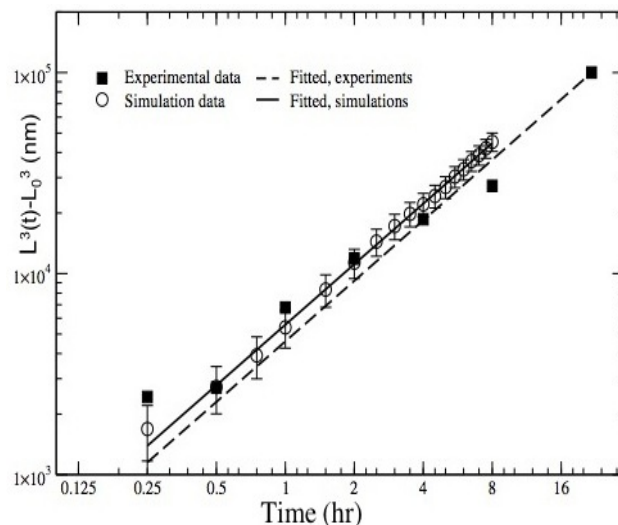


Figure 7.3: Comparison of simulated particles sizes in Fig. (7.2) to corresponding experiments. Also shown are fits to the data. Reprinted from Ref. [221].

Another source of inherent anisotropy occurs in particles precipitation when strain relaxation is considered. In this case the source of the anisotropy is the different growth rates along different crystallographic directions caused by misfit strains. Yeon and co-workers examined how this anisotropy is enhanced or reduced as a function of particle density [216] using a single phase field variant of the model discussed here. At low density they found free dendrites tips growing along the $\langle 11 \rangle$ directions. The morphology of these solid state dendrites resembles in every way the dendrites discussed earlier in the context of solidification. Figure (7.4) shows a comparison of a phase field simulation with experiments. The work of Yeon and co-workers showed that the interaction of overlapping diffusion fields during precipitation can stunt or entirely retard the anisotropic dendritic morphology shown in Fig. (7.4). Similar dendritic morphologies are expected when the elastic coefficients of precipitate particles are anisotropic [152].

When the anisotropies of surface energy and elastic coefficients are mis-aligned, it is expected that the competing dendritic orientations will lead to interesting morphologies, such as the seaweed-like structures discussed in the context of solidification in section (6.10.4). Greenwood and co-workers recently examined the precipitation of elastically anisotropic particles in an isotropic matrix using a single phase field model with elastic strain effects [87]. Their modeled followed the approach of Karma and co-workers, which judiciously selects the model's interpolation functions in order to make surface energy free of concentration in order to cope with diffuse interfaces. The precipitates in the study of Greenwood et. al have a 4-fold anisotropy in both their surface energy and their elastic coefficients. Surface energy anisotropy is given by Eq. (5.25). Cubic elastic coefficients are considered in each phase, for which the surviving elements of the elastic tensor are C_{11}, C_{12}, C_{44} . Anisotropy is introduced into cubic elastic coefficients by introducing a small parameter $\beta = C_{44} - (C_{11} - C_{12})/2$, which characterizes the deviation of C_{44} from its isotropic value. Their study showed that as β and ϵ_4 were varied a morphological transition from surface energy dominated dendrites [152] to dendrites that grow along the elastic anisotropy directions (the latter are also reported in Ref. [190]). Figure (7.5) illustrates this phenomenon. The red line indicates the (β, ϵ_4)

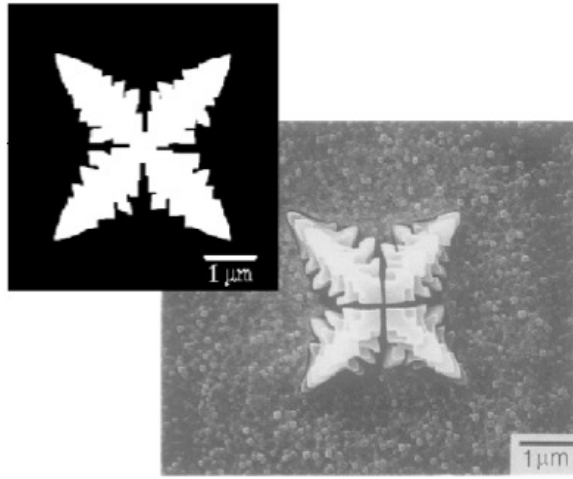


Figure 7.4: Comparison between experimental solid state dendrite (top left) and simulated solid state dendrite (main). Reprinted from Ref. [216].

phase space where morphologies are isotropic and resembles many features of seaweed.

7.2 Multi-Phase Field Models

Multi-phase field models differ from the methods above in that they treat the phase field as a volume fraction. This imposes a constraint that must self-consistently be incorporated into the dynamics. As with the very similar looking multi-order parameter method, the concentration is partitioned into individual components that are mathematically tied to each phase. As a result, two phase interfaces can maintain a simple expression for the surface energy even for very diffuse interfaces⁴. Like their "cousin" multi-order parameter phase field models, no thin interface mapping has been calculated presently for most of these models. As a result, they may lack accuracy in problems involving moderate to rapid solidification rates from a melt. However in the description of precipitation and related transformations whose kinetics can be assumed to be limited by diffusion and curvature, these models are quite accurate. Indeed, at present, there even exists a successful commercial software⁵ used by some industries to predict features of microstructures in metal alloys.

7.2.1 Thermodynamics

Another and one of the earliest class of multi-phase field models assign the concept of a volume fraction to N phases, each of which is represented by a volume fraction field ϕ_α , where α indexes a phase in the

⁴These are still very small compared to the scale of a typical microstructure and diffusion length of impurities

⁵MICRESS, Part of the software ACCESS, Aachen.

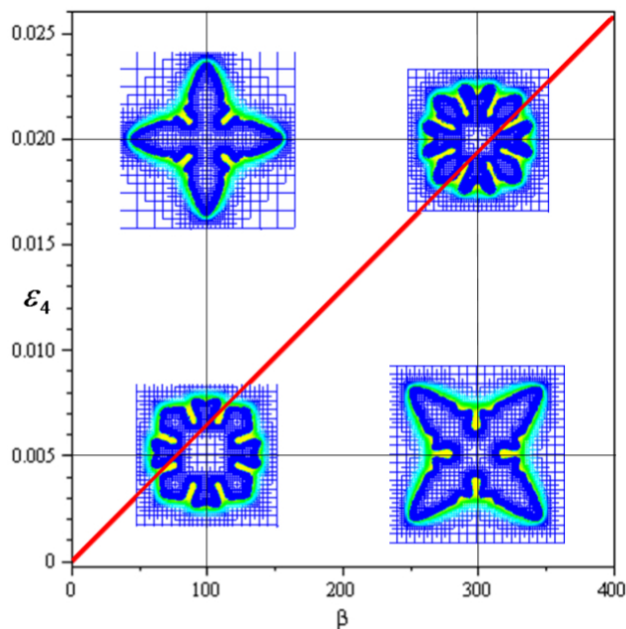


Figure 7.5: *Morphological phase space of dendritic precipitate growth. For parameters above the red line, dendrite tip growth proceeds along the surface energy dominate directions. Below the line, precipitates grow branches in the directions governed by the anisotropy of the elastic constants. Along the line, isotropic structures similar to seaweed emerge. Reprinted from Ref. [87].*

system. As such, the following fundamental constraint must be applied to the N volume fractions

$$\sum_{i=1}^N \phi_{\alpha} = 1 \quad (7.22)$$

As with the formulation of Kim and co-workers the idea is that a two-phase interface is made up of a combination of the two phases. Moreover, this formalism also decomposes the concentration into a linear combination of separate concentrations C_{α} corresponding to the phase α , i.e.

$$c = \sum_{\alpha=1}^N h(\{\phi_{\alpha}\}) C_{\alpha} \quad (7.23)$$

The function $h(\{\phi_{\alpha}\})$ is an interpolation function that is one when $\phi_{\alpha} = 1$ for some α and $\phi_{\beta} = 0$ when $\alpha \neq \beta$. Once again the constraint of equal chemical is applied between any two phases, i.e.

$$\frac{\partial f_{\alpha}(C_{\alpha})}{\partial c} = \frac{\partial f_{\beta}(C_{\beta})}{\partial c} \quad (7.24)$$

for any two $\alpha - \beta$ pairs of phases. Equations (7.23) and (7.24) define N equations in N unknowns, the solution of which determines the C_{α} from any combination of volume fractions $\{\phi_{\alpha}\}$ and concentration field c .

The free energy of the multi-volume fraction formalism is given by

$$F[\{\phi_\alpha\}, c] = \int_V \left[\sum_{\alpha, \beta, \alpha < \beta}^N \left(\frac{k_{\alpha\beta}}{2} |\phi_\alpha \nabla \phi_\beta - \phi_\beta \nabla \phi_\alpha|^2 \right) + g(\{\phi_\alpha\}) + f(\{\phi_\alpha\}, \{C_\alpha\}) \right] dV, \quad (7.25)$$

where the gradient term now takes a more general form that makes it possible to manipulate the surface energy of each $\alpha - \beta$ interface separately. The bulk free energy in this formalism interpolated between phases by

$$f(\{\phi_\alpha\}, \{C_\alpha\}) = \sum_{\alpha=1}^N h(\phi_\alpha) f_\alpha(C_\alpha, T) \quad (7.26)$$

where $f_\alpha(C_\alpha, T)$ is the corresponding free energy of phase α . The function $g(\{\phi_\alpha\})$ is takes on various forms depending on the multi-volume fraction method. The simplest is a multi-well type of the form

$$g(\{\phi_\alpha\}) = \sum_{\alpha, \beta, \alpha < \beta}^N w_{\alpha\beta} \phi_\alpha^2 \phi_\beta^2 \quad (7.27)$$

Other forms of the obstacle potential have also been proposed for $g(\{\phi_\alpha\})$ [17, 28]. Their use here is related to the possible emergence of third phases in two-phase interfaces. In addition, Nestler and co-workers have also developed the formalism to incorporate non-isothermal solidification [75, 76, 17]. These developments are left to the reader and will not be discussed further here.

As with the multi-order parameter method discussed in the previous section, the application of Eqs. (7.23) and (7.24) removes any explicit contribution from the impurity concentration from the resulting steady state free energy ⁶. As a result, the excess energy of any $\alpha - \beta$ interface is uniquely described only by the constants $k_{\alpha\beta}$ and $w_{\alpha\beta}$. In particular, the surface energy $\sigma_{\alpha\beta}$ and associated interface width of each phase boundary $W_{\alpha\beta}$ work out to [192, 59] be

$$\begin{aligned} \sigma_{\alpha\beta} &= \frac{\sqrt{k_{\alpha\beta} w_{\alpha\beta}}}{3\sqrt{2}} \\ W_{\alpha\beta} &= \frac{\sqrt{2k_{\alpha\beta}}}{\sqrt{w_{\alpha\beta}}} \end{aligned} \quad (7.28)$$

Which are the same as Eqs. (7.14). As an example, of how Eqs. (7.28) are derived, consider the simple case of an $\alpha - \beta$ interface. In this case Eq. (7.22) requires that $\phi_\alpha = 1 - \phi_\beta$. Considering this constraint on volume fractions and ignoring the concentration terms, the steady state free energy becomes

$$F[\{\phi_\alpha\}, \phi, \beta] = \int_V \left(\frac{k_{\alpha\beta}}{2} |\nabla \phi_\beta|^2 + w_{\alpha\beta} \phi_\beta^2 (1 - \phi_\beta)^2 \right) dx, \quad (7.29)$$

The solution of which is $\phi_\beta = [1 - \tanh(x/\sqrt{2}W_\phi)]/2$ and the solutions of which are given by Eq. (6.50) with $W_\phi \equiv W_{\alpha\beta}/\sqrt{2}$.

⁶What this means is that the variation of the steady state concentration fields through the interface are “slaved” to the variation of the volume fraction (phase) fields and thus completely determined in terms of them.

7.2.2 Dynamics

The dynamics of multi-volume fraction methods must preserve Eq. (7.22). This is done by replacing Eq. (7.25) by $F_{\text{tot}} = F + F_{\text{cons}}$, where F_{cons} is given by

$$F_{\text{cons}}[\{\phi_\alpha\}, c] = \int_V \lambda \left[\sum_{\alpha=1}^N \phi_\alpha - 1 \right] dV, \quad (7.30)$$

Here λ is a Lagrange multiplier determined such as to impose the conservation of volume fraction. Minimizing F_{cons} with respect to λ and substituting the expression back into F_{cons} , and then applying the usual variational minimization for each volume fraction field ϕ_α gives,

$$\frac{\partial \phi_\alpha}{\partial t} = -\frac{\Gamma_{\phi_\alpha}}{N} \sum_{\alpha} \left(\frac{\delta F}{\delta \phi_\alpha} - \frac{\delta F}{\delta \phi_\beta} \right) + \eta_i(\vec{x}, t) \quad (7.31)$$

Equation (7.31), combined with Eq. (7.13) for the evolution of concentration, completely specifies the multi-volume fraction dynamics. As in section (7.1.2), variational derivatives with respect to ϕ_α require partial derivatives of $f(\{\phi_\alpha\}, \{C_\alpha\})$, which in turn require knowledge of $\partial C_\alpha / \partial \phi_\alpha$. The procedure for evaluating these partial derivatives is precisely analogous to that presented in sections (6.9) for single phase solidification. Finally, a noise term has been appended to Eq. (7.31) to simulate interface fluctuations, even though it is not clear how to connect volume fraction fluctuations and true atomic-scale fluctuations. Further discussion of the properties of multi-phase field models, with applications to second phase formation, is given in Ref [107].

7.3 Orientational Order Parameter for Polycrystalline modeling

Perhaps the most self-consistent way of describing multiple crystal orientations in traditional phase field theory is via an orientational order parameter $\theta(\vec{x})$, which can be loosely interpreted as a phase factor implicit in the crystal order parameters $\langle e^{i\vec{G}\cdot\vec{x}_n} \rangle$, which were defined in section (5.1). In this type of phase field model, the orientational order parameter $\theta(\vec{x})$ is coupled to *one* solid-liquid order parameter ϕ . In the case of solidification, ϕ controls defines transitions between solid and liquid and θ defines orientational changes between different grains. A free energy functional expressed in terms of these two fields, in addition to the usual concentration and temperature, can be used to derive equations of motion for solidification and interactions of grain boundaries. The $\theta - \phi$ formalism began with the work of Kobayashi and co-workers [127, 205] as an alternative to the multi-phase field approach. A polycrystalline model for solidification of a pure material was first examined, with preliminary two dimensional test results. A more detailed work for solidification of a pure material and a full extension to two dimensional simulations, which considered grain boundary energy, impingement, coarsening and grain boundary melting was later presented [206]. This formalism was then extended to binary alloy solidification by Gránásy and co-workers [81, 82, 84], who also considered nucleation and the subsequent growth processes in a binary alloy.

7.3.1 Pure materials

The starting point for phase field for a pure polycrystalline material is a free energy expressed in terms of θ , ϕ and T (temperature is often non written explicitly but is understood to enter the free energy

parameters). Its basic form is developed by Kobayashi and co-workers [127, 128] and later studied more extensively by Warren and co-workers [206]. It is given by

$$F = \int_V dV \left[\frac{\epsilon_\phi^2(\nabla\phi, \theta)}{2} |\nabla\phi|^2 + f(\phi) + S p(\phi) |\nabla\theta| + \frac{\epsilon_\theta}{2} h(\theta) |\nabla\theta|^2 \right], \quad (7.32)$$

where ϵ_ϕ is the usual gradient energy coefficient, which is dependent of the orientation of the interface normal (determined by $\hat{n} = \nabla\phi/|\nabla\phi|$) with a respect to an frame of reference in the crystal, which is oriented at an angle θ with respect to the laboratory frame of reference. The function $f(\phi)$ sets the bulk free energy of the solid and liquid phases. The $|\nabla\theta|$ term is the simplest rotationally invariant ⁷ expression that describes the grain boundary energy due to orientational mismatch between grains. The interpolation function $p(\phi)$ here assures that this term is only active in solid and zero in liquid. The parameter S is treated as a constant that can be temperature dependent. Finally, the gradient squared term is introduced in order to describe rotation of grains with $h(\theta)$ an interpolation function that also activates this term only in the solid.

Equation of motion for ϕ and θ are given by

$$\tau \frac{\partial\phi}{\partial t} = \Gamma_\phi \left[\epsilon_\phi^2 \nabla^2 \phi - f'_D(\phi) - \frac{\epsilon_\theta}{2} h'(\theta) |\nabla\theta|^2 - S p'(\phi) |\vec{\nabla}\theta| \right], \quad (7.33)$$

$$\tau_\theta \frac{\partial\theta}{\partial t} = \Gamma_\theta S \vec{\nabla} \cdot \left[\epsilon_\theta^2 h(\phi) \nabla^2 \theta + p(\phi) \frac{\vec{\nabla}\theta}{|\vec{\nabla}\theta|} \right]. \quad (7.34)$$

For simplicity, the above equations assume isotropic coefficients for the kinetic time constants τ and gradient energy coefficient ϵ_ϕ . The phase field equation is straightforward to derive, as is the θ equation, save for the last term. For the rather involved mathematical details of deriving this term, the reader is referred to Ref. [77, 126]. To the equations above can be added the energy equation to manage thermal diffusion,

$$\frac{\partial T}{\partial t} = \alpha \nabla^2 T + \frac{L}{c_p} \frac{\partial\phi}{\partial t}, \quad (7.35)$$

which is precisely the same form as "model c" for solidification of a pure material. As mentioned above, these phase field equations can describe solidification and subsequent grain boundary interactions.

To consider the static properties of this model, consider an isothermal, "dry boundary" described by the phenomenological function $f(\phi) = (a/2)(1-\phi)^2$, which defines only one well, i.e. a single [solid] phase. For the case $\epsilon_\theta = 0$ and isothermal conditions, the surface energy is computed for the case $p(\phi) = \phi^2$ from the steady state equations

$$\begin{aligned} \epsilon_\phi^2 \frac{d^2\phi}{dx^2} + a(1-\phi) - S\phi |\partial_x\theta| &= 0 \\ \frac{d}{dx} \left(\phi^2 \frac{\partial_x\theta}{|\partial_x\theta|} \right) &= 0 \end{aligned} \quad (7.36)$$

These have been solved explicitly by Kobayashi and workers [128]. Their solution is $\theta_o(x) = |\Delta\theta|\delta(x)$ and $\phi_o(x) = 1 - (1 - \phi_s) \exp(-|x|/\nu)$, where $\Delta\theta$ is the difference in orientations between adjacent grains,

⁷Meaning that the free energy functional does not change if there is a uniform rotation of θ .

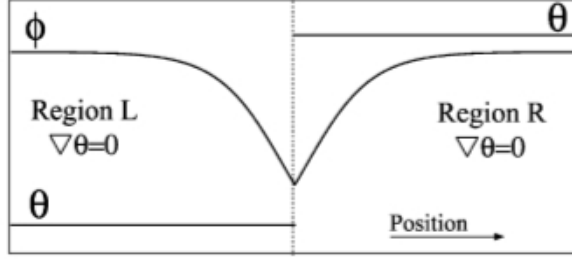


Figure 7.6: Sketch of the ϕ_o and θ_o profiles in the limit when $\epsilon_\theta = 0$. In this limit θ is a delta function and there is a sharp cusp (with a minimum ϕ_{\min}) in ϕ_o . In practice the phase field equations are simulated with $\epsilon_\theta \neq 0$ which makes these fields smoother. Re-printed from Ref. [206].

$\nu \equiv \epsilon\phi/a$ and $\phi_s \equiv 1/(1+\Theta_o)$ where $\Theta_o \equiv S\Delta\theta/(a\epsilon_\phi)$. The form of these solutions is shown in Fig. (7.6). Substituting these profiles back into the free energy, and subtracting the reference solid energy, gives

$$\sigma = \frac{S\Delta\theta/a^2}{1 + (S/\epsilon_\phi a)\Delta\theta} \quad (7.37)$$

where $\Delta\theta$ is the misorientation between crystals. To leading order in $\Delta\theta$ Eq. (7.37) gives $\sigma \sim \Delta\theta$ which is precisely what is expected by the Read and Shockly formula.

For a more general bulk free energy it is expected that the excess energy associated with the surface energy of a poly-crystal grain boundary will contain contributions from the both change of orientation and a from the change of order. The form of the grain boundary energy has been derived by Warren and co-workers [206]. Procedurally, this is done by integrating the steady state form of Eqs.(7.33) and (7.34) and substituting the result (ϕ_o and θ_o) into the free energy functional and subtracting the reference bulk solid energy. This gives, in the $\epsilon_\theta = 0$ limit,

$$\sigma = Sp(\phi_{\min})\Delta\theta + \int_{-\infty}^{\infty} (f(\phi_o(x)) - f_s) dx \quad (7.38)$$

where ϕ_{\min} is the value of the steady state phase field $\phi_o(x)$ in the centre of the grain boundary (the general forms of ϕ_o and θ_o in this case are again analogous to that in Fig. (7.6)). It is a reference point, which arises here from a constant of integration of the steady state phase field equation for ϕ_o . The model can be dealt with analytically for the simple choices $f(\phi) = (a^2/2)\phi^2(1-\phi)^2 + f_s P(\phi)$ where $P(\phi) = \phi^3(10 - 15\phi + 6\phi^2)$, $p(\phi) = \phi^2$ and $f_s = L(T/T_m - 1)$, where L and T_m are the latent heat and melting temperature, respectively. For these choices, the solution of Eq. (7.33) gives a very simple expression for ϕ_o at $T = T_m$, when $f_s = 0$. For the special case of $\epsilon_\theta = 0$, this solution gives

$$\phi_{\min} = 1 - \frac{\Delta\theta}{\Delta\theta_c} \quad (7.39)$$

where $\Delta\theta_c \equiv a\epsilon_\phi/S$.

An interesting feature of Eq. (7.39) is that it predicts the for $\Delta\theta > \Delta\theta_c$, there is no steady state solution to the phase field equation (i.e. ϕ_{\min} becomes less than zero). Physically this implies that at the melting temperature, the grain boundary will melt for a sufficiently high grain boundary misorientation.

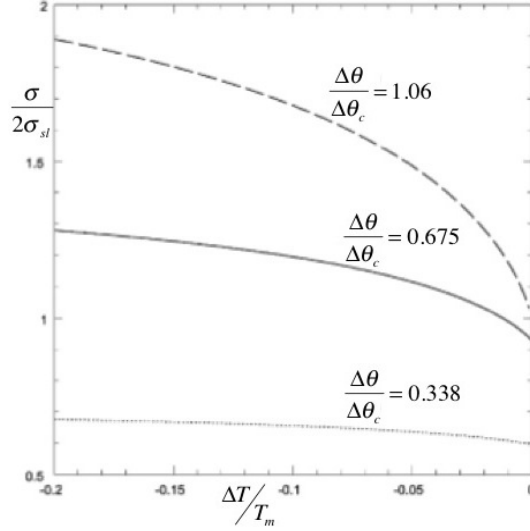


Figure 7.7: Plots of the surface energy, normalized with respect to the solid-liquid surface energy, versus undercooling. Different curves correspond to different grain mis-orientation. Re-printed from Ref. [206].

This is also seen by considering the width of the grain boundary, which is given by (see Ref.[206] for mathematical details),

$$W_{\text{gb}} = -\frac{2\epsilon_\phi}{a} \ln \left(1 - \frac{\Delta\theta}{\Delta\theta_c} \right) \quad (7.40)$$

Equation (7.40) shows that the width of the grain boundary increases logarithmically as the critical mis-orientation angle is approached. For general temperatures $T \leq T_m$, Eq. (7.38) can be plotted to give the grain boundary energy as a function of undercooling $\Delta T \equiv T - T_m$. Figure (7.7) plots σ vs. ΔT for different values of mis-orientation $\Delta\theta$. The different curves in the figure show that for a given mis-orientation the grain boundary energy rises with undercooling. This is a consequence of the fact that as temperature drops below the melting point, the amorphous (i.e. metastable) material within the grain boundary finds itself progressively more undercooled, which adds to the energy of the entire grain boundary. Note that for mis-orientations greater than $\Delta\theta_c$, the grain boundary energy becomes precisely $2\sigma_{\text{sl}}$, i.e. twice the solid-liquid surface energy. That implies that above a critical mis-orientation all grain boundaries melt into a small liquid pool at the melting temperature $T = T_m$.

The actual grain boundary energy versus orientation requires that a grain boundary definition be given. For a given mis-orientation, Warren and co-workers define the grain boundary, σ_{gb} as that value of σ corresponding to a specific grain boundary width $W_{\text{gb}} < W^*$ where W^* is determined by experiments⁸. Plotting σ_{gb} versus $\Delta\theta$ gives the well-known Read-Shockley function. Other definitions of what defines a grain boundary, (degree of order, etc) lead to the same Read-Shockley trend. It should be noted that all the properties discussed here remain qualitatively the same when $\epsilon_\theta \neq 0$, although the algebra becomes more messy. The reader is advised to work through the algebra of Ref. [206] for further practice with orientational dependent phase field models.

⁸This is likely a very difficult parameter to measure practically.

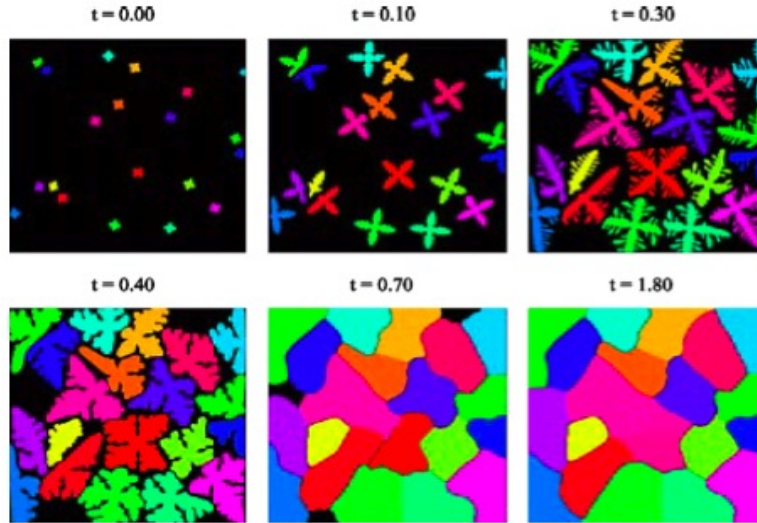


Figure 7.8: Simulation of growth, impingement and coarsening of multiple seeded grains. Color represent different orientations. The virtual sample is initially held at some fixed undercooling and then, after some time, continuous heat extraction is applied. Re-printed from Ref. [206].

As an illustration of the robustness of the $\theta - \phi$ model to handle solidification, grain impingement and coarsening, Fig. (7.8) shows a simulation of multiple grains that grow dendritically and then merge and start to coarsen. In this simulations $\epsilon_\theta \neq 0$ and thus grain rotation is evident. The only other way to simulate this effect is via the so-coined *phase field crystal* model discussed later in this book. Also, in order to dendritic features of the grains, anisotropy has to be added to the gradient energy coefficient, as is the case in all model. In this simulation is was only added to the $\epsilon_\phi |\nabla \phi|^2$ term in the free energy functional. It could (and should from the perspective of the asymptotic analysis of this model) be added to τ as well. The simulation of Fig. (7.8) also solved Eq. (7.35) to treat non-isothermal conditions.

As discussed at the beginning of this chapter the diffuse interface limit of the $\theta - \phi$ model –or any other current multi-order parameter or multi-phase field model– is presently lacking. As such results such as those of Fig. (7.8) are only qualitative in the solidification phase. The slower solid state dynamics of this model are not as prone to artificially induced kinetics caused largely by rapidly moving diffuse interfaces. As such, $\theta - \phi$ type models, as well as the other ”brand” of phase field models studied in this chapter are a very robust way of elucidating the properties of grain boundary formation and coarsening kinetics. It should be noted, however, that certain features of grain boundaries and elasticity cannot be studied using these –or previous– types of phase field models since they do not contain atomic-scale effects.

7.3.2 Alloys

The $\theta - \phi$ can also be extended to study polycrystalline solidification in alloys. The basic version of this model was developed by Granasy and co-workers based on the original work of Kobayashi, Warren and co-worker for a pure material. The basic alloy $\theta - \phi$ model presented here is presented in Ref. [88]. The

starting point is this specific model is the free energy functional

$$F = \int_V dV \left[\frac{\epsilon_\phi^2}{2} |\vec{\nabla}\phi|^2 + \frac{\epsilon_c^2}{2} |\vec{\nabla}c|^2 + f(\phi, c) + f_{\text{ori}}(\phi, \vec{\nabla}\theta) \right], \quad (7.41)$$

where ϵ_ϕ and ϵ_c are the usual gradient energy coefficient for the order change and concentration. In this particular model the solid is defined by $\phi = 0$ and the liquid by $\phi = 1$. The the bulk free energy density $f(\phi, c)$ is thus given by

$$f(\phi, c) = H(c)f_D(\phi) + p(\phi)f_l(c, T) + (1 - p(\phi))f_s(c, T) \quad (7.42)$$

where l denotes liquid and s solid. The function $p(\phi)$ is an interpolation function that is zero in the solid and one in the liquid. The orientational energy density f_{ori} used here is

$$f_{\text{ori}}(\phi, \vec{\nabla}\theta) = S(1 - p(\phi)) |\vec{\nabla}\theta| \quad (7.43)$$

The function $H(c) = (1 - c)H_A + cH_B$ sets the energy scale proportional to the nucleation barrier height. The function $f_D(\phi)$ is an interpolation function that sets an energy barrier between solid and liquid. Particularly useful choices of these functions are $f_D = \phi^2(1 - \phi)^2$ and $p(\phi) = \phi^3(6\phi^2 - 15\phi + 10)$. The parameter S is a constant chosen to reproduce the energy of low-angle boundaries. In $\theta - \phi$ models θ is defined only in the crystalline phase ($\phi = 1$), scaled between 0 and 1, while it chosen to fluctuates –or do something innocuous– in the disordered phase. Anisotropy of the solid-liquid surface energy is added to the model by letting $\epsilon_\phi \rightarrow \epsilon_\phi (1 + \epsilon \cos(m\Theta - 2\pi\theta))$ where $\Theta = \arctan(\partial_y\phi/\partial_x\phi)$. The angle Θ measures the angle of the interface normal with respect to the laboratory frame. Thus, $\Theta - \theta$ measures the angle of the interface normal relative to the orientation of the grain.

The dynamics of c and ϕ in the above formulation follow from the usual variation principles. The of the phase field evolves according to

$$\frac{\partial\phi}{\partial t} = \Gamma_\phi \left[\epsilon_\phi^2 \nabla^2 \phi - H(c)Tf_D'(\phi) - p'(\phi) \left(f_s(c, T) - f_l(c, T) + ST|\vec{\nabla}\theta| \right) \right], \quad (7.44)$$

The concentration of impurities follows the usual mass conservation law

$$\frac{\partial c}{\partial t} = \vec{\nabla} \cdot \left(M(\phi, c) \vec{\nabla}\mu \right) \quad (7.45)$$

where

$$M(\phi, c) = \frac{v_o}{RT} c(1 - c) [D_s p(\phi) + D_l (1 - p(\phi))] \quad (7.46)$$

and

$$\mu = \frac{\delta F}{\delta c} = \vec{\nabla} \cdot \left[(H_B - H_A)Tf_D(\phi) + p(\phi) \frac{\partial f_s}{\partial c}(c, T) + (1 - p(\phi)) \frac{\partial f_l}{\partial c}(c, T) - \epsilon_c^2 \nabla^2 c \right] \quad (7.47)$$

Care must be is taken in deriving the equation for the orientation order parameter and its treatment during simulation, since it is prone to produce singular diffusivities. Kobayashi and Giga [126], have outlined the proper steps to be taken in deriving such a variational and how it should be dealt with. The evolution equation is then,

$$\frac{\partial\theta}{\partial t} = \Gamma_\theta ST \vec{\nabla} \cdot \left[p(\phi) \frac{\vec{\nabla}\theta}{|\vec{\nabla}\theta|} \right]. \quad (7.48)$$

This and the previous $\theta - \phi$ formulation for a pure material is mapped onto classical sharp interface equations in the limit of vanishing interface width. In closing it is noted that the thin interface limit of the alloy $\theta - \phi$ model presented is also currently lacking.

Chapter 8

Phase Field Crystal Modeling of Pure Materials

Previous chapters used a *scalar* field that is spatially *uniform* in equilibrium to model solidification. In this description a liquid/solid surface is represented by a region in which the field rapidly changes from one value to another. While the simplicity of this description is advantageous for computational and analytic calculations there exist situations in which the approach is inadequate. For example crystal symmetry can influence the shape and eventual anisotropic shape of the dendrite. While this detail can be integrated into traditional models other aspects of crystal growth are more difficult to account for. For example consider the common phenomenon of the nucleation (heterogeneous or homogeneous) of a crystalline phase in a supercooled liquid as depicted in Fig. (8.1). Initially small crystallites of arbitrary orientation nucleate and grow until impingement occurs and grain boundaries and triple junctions form. Further growth is then dominated by motion of the grain boundaries and triple junctions. To model this phenomena a model must incorporate the physics associated with liquid/solid surfaces, elasticity, dislocations, anisotropy, grain boundaries and crystals of arbitrary orientation. While these features are quite difficult to incorporate into standard phase field models of solidification, it turns out they are naturally included in models that are minimized by fields that are spatially *periodic* in equilibrium. One such model is the so-called *phase field crystal methodology (PFC)*, which exploits this feature for modeling crystal growth phenomena.

The PFC model essentially resolves systems on atomic length and diffusive time scales and as such lies somewhere in between standard phase field modeling and atomic methods. The advantage of incorporating atomic length scales is that mechanisms associated with the creation, destruction and interaction of dislocations in polycrystalline materials are automatically captured. It turns out that it is relatively simple to model these features by introducing a free energy that, is a functional of a *conserved* field, is minimized by *periodic solutions* and is *rotationally invariant*. In fact many such free energy functionals have been proposed for various physical systems that form periodic structures. This chapter studies the phase field crystal (PFC) model, which is just a conserved version of a model developed for Rayleigh-Bénard convection, known as the Swift-Hohenberg equation [193]. Before outlining the details of this model it is useful to first discuss general aspects of periodic systems and how such free energies can model many features of crystalline systems.

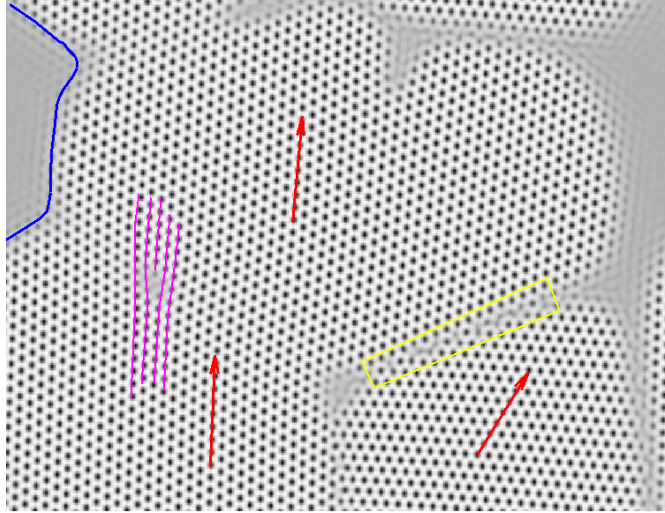


Figure 8.1: Atomic number density field of a partially solidified supercooled melt. The grey scale corresponds to the atomic number density field which is uniform (hexagonal) in liquid (solid) regions. Red arrows indicate the orientation of three grains, the blue line highlights the liquid/solid interface, the purple lines show a single dislocation between two grains of similar (but different) orientation. The yellow box encloses a grain boundary between two grains of with a large orientational mismatch.

8.1 Generic Properties of Periodic Systems

Periodic structures arise in many different physical systems, such as crystals, block co-polymer films, charge density waves, magnetic films, superconducting vortex lattices and Rayleigh-Bénard convection. In some cases these patterns can be characterized by free energy functionals, while in others the systems are constantly driven far out of equilibrium and the patterns cannot be described by such functionals. For the purposes of this chapter it will be assumed that such functionals exist. While the physical mechanisms that give rise to these patterns are significantly different there are some generic (perhaps obvious) features that are worth discussing. First in a periodic system there is a specific length scale (or set of length scales) that characterizes the equilibrium or stationary states. For example a crystalline state can be characterized by the principle reciprocal lattice vectors, while a block co-polymer system might be characterized by a stripe width. For illustrative purposes consider a system characterized in equilibrium by one length scale, a_{eq} . The energy associated with a stretch or compression of the system can be obtained by expanding \mathcal{F} around a_{eq} , i.e.,

$$\mathcal{F}(a) = \mathcal{F}(a_{eq}) + \underbrace{\frac{\partial \mathcal{F}}{\partial a} \Big|_{a_{eq}}}_{=0} (a - a_{eq}) + \frac{1}{2} \frac{\partial^2 \mathcal{F}}{\partial a^2} \Big|_{a_{eq}} (a - a_{eq})^2 + \dots \quad (8.1)$$

The second term is zero since \mathcal{F} is a minimum when $a = a_{eq}$, thus to leading order in Δa ,

$$\Delta \mathcal{F} = \frac{k}{2} (\Delta a)^2 \quad \text{Hooke's Law!} \quad (8.2)$$

where $\Delta\mathcal{F} \equiv \mathcal{F} - \mathcal{F}(a_{eq})$, $k \equiv (\partial^2\mathcal{F}/\partial a^2)|_{a_{eq}}$ and $\Delta a \equiv a - a_{eq}$. This result is identical to the potential energy of a spring, i.e., Hooke's Law. This illustrates the fact that elastic energy, as defined as the gain in free energy upon deformation, is naturally incorporated by free energies that are minimized by periodic functions.

The second important feature of periodic systems is the nature and interactions of the defects. In general the *type* of defects are controlled by the nature of the fields (eg., real, complex, periodic, uniform) that create the patterns. For example, in systems defined by uniform scalar fields (such as concentration or magnetization) the defects are interfaces. In periodic systems such as block-copolymer films and crystals, line or point defects typically emerge. For periodic systems the precise type of defects depends on the symmetry of the periodic state, in essence geometry completely controls the topological defects that can form. Thus a rotationally invariant free energy functional that produces an FCC pattern can naturally give rise all possible defects associated with FCC crystal lattices. In addition, by construction, such a model will have the anisotropies associated with the FCC lattice. The free energy must be rotationally invariant since the free energy should not be a function of the orientation of the crystalline lattice. If such a free energy can be constructed then it naturally allows for multiple crystal orientations since they all have equivalent energy. Finally coexistence between, for example, uniform (i.e., liquid) and periodic (i.e., crystalline) phases, can occur if the periodically varying field is conserved, since a Maxwell equal area construction (also called the "common tangent construction") will be required to obtain the equilibrium states. In the next section perhaps the simplest continuum model describing periodic structures will be presented and analyzed before the PFC model is introduced and detailed.

8.2 Periodic Free Energies and The Swift-Hohenberg Equation

The central topic of this section is on how to construct free energy functionals that are minimized by periodic patterns. It turns out this is quite simple and can be illustrated by considering the usual ' ϕ^4 ' free energy functional, with a slight modification to the spatial gradients, i.e.,

$$\mathcal{F} = \int d\vec{r} \left(\psi \frac{G}{2} \psi + \frac{u}{4} \psi^4 \right). \quad (8.3)$$

Similar to Model A or B the free energy will have a single well if $G > 0$ and two wells if $G < 0$. Thus periodic structures can be produced if G is negative when ψ is periodic and positive when ψ is uniform. In other words G is an operator constructed such that \mathcal{F} is minimized by a periodic function, such as $A \sin(qx)$. For simplicity consider expanding G in one dimension as follows,

$$G = g_0 + g_2 \frac{d^2}{dx^2} + g_4 \frac{d^4}{dx^4} + g_6 \frac{d^6}{dx^6} + \dots \quad (8.4)$$

where odd derivatives are not included as that would imply that the free energy depends on the direction of the gradient. If $\psi = A \sin(qx)$ then,

$$G\psi = (g_0 - q^2 g_2 + q^4 g_4 - q^6 g_6 + \dots) \psi = \hat{G}(q)\psi, \quad (8.5)$$

where $\hat{G}(q) \equiv g_0 + q^2 g_2 + q^4 g_4 - q^6 g_6 + \dots$. This implies that the free energy functional becomes,

$$\mathcal{F} = \int d\vec{r} \left(\hat{G}(q) \frac{\psi^2}{2} + \frac{u}{4} \psi^4 \right). \quad (8.6)$$

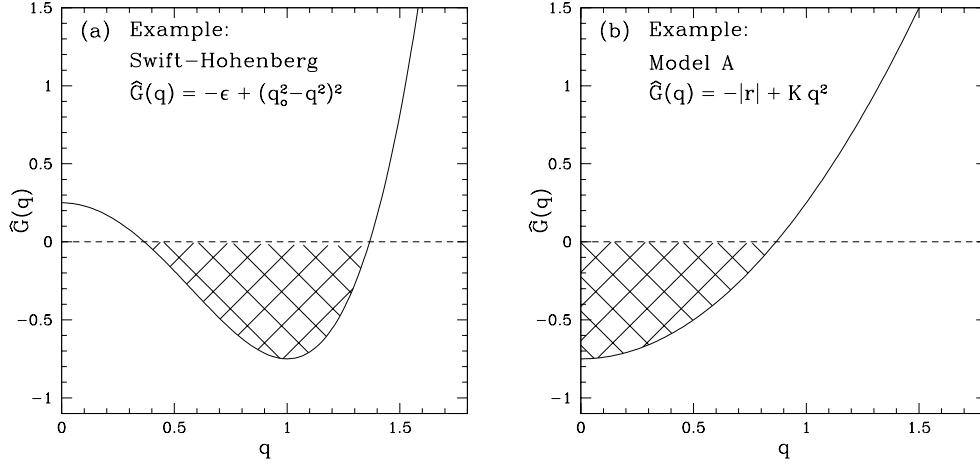


Figure 8.2: Examples of function $\hat{G}(q)$. In figure (a) the Swift-Hohenberg \hat{G} is plotted for $\epsilon = 3/4$ and $q_o = 1$. In figure (b) the standard ‘Model A’ \hat{G} is plotted as a function of q for $K = 1$ and $|r| = 3/4$. The interesting feature of this plot is that in the Swift-Hohenberg case \hat{G} is a minimum at a finite q , while for Model A, \hat{G} is a minimum at $q = 0$, corresponding to a uniform (infinite wavelength) case.

Equation (8.6) shows that when $\hat{G}(q)$ is positive \mathcal{F} has one well (at $\psi = 0$) and when $\hat{G}(q)$ is negative \mathcal{F} has two wells. In the latter case the periodicity is largely determined by the value of q that minimizes \hat{G} (corrections due to higher order fourier components can alter this periodicity). If \hat{G} is most negative at $q = 0$ then the two phase states consists of spatially uniform phases as in standard phase field models of solidification. In contrast when the minimum of \hat{G} occurs at a finite value of q (say at q_{min}) then typically \mathcal{F} will be minimized by a periodic patterns with periodicity close to $2\pi/q_{min}$. For example, in Model A (or B) \hat{G} is equal to $-r + Kq^2$, where $r \propto T - T_c$. In contrast, for the so-called Swift-Hohenberg (SH) free energy functional [193] $\hat{G}(q) = -\epsilon + (q_o^2 - q^2)^2$ (or $G = -\epsilon + (q_o^2 + \nabla^2)^2$), where ϵ is a control parameter related to the Rayleigh number. Both these functions are plotted in Fig. (8.2) and illustrate that \hat{G} is a minimum at a finite value of q for the SH model and zero for Model A.

Mathematically the simplest functional form for $\hat{G}(q)$ that produces a minima at a finite q occurs when g_0, g_2 and g_4 are finite and all other coefficients are zero. For instance in the SH equation $g_0 = -\epsilon + q_o^4$, $g_2 = 2q_o^2$ and $g_4 = 1$. In this case the specific wavelength chosen is essentially a competition between g_2 and g_4 . Before considering the contribution of the non-linear term it is interesting to illustrate the g_2 part of the free energy functional by integrating by parts, i.e.,

$$\frac{g_2}{2} \int dx \psi \frac{d^2}{dx^2} \psi = \frac{g_2}{2} \int dx \psi \frac{d}{dx} \left(\frac{d\psi}{dx} \right) = \frac{g_2}{2} \left(\psi \frac{d^2\psi}{dx^2} \Big|_S - \int dx \left(\frac{d\psi}{dx} \right)^2 \right). \quad (8.7)$$

In many cases the surface term is zero (as in periodic systems, or zero flux boundary conditions) so that

$$\frac{g_2}{2} \int dx \psi \frac{d^2}{dx^2} \psi = \frac{g_2}{2} \int dx \left(- \left(\frac{d\psi}{dx} \right)^2 \right) = \frac{g_2}{2} \int dx \left(-|\vec{\nabla}\psi|^2 \right). \quad (8.8)$$

Notice that is precisely the term that appears in Model A (or B), except that the sign is negative. This highlight the obvious fact that in periodic system, some spatial gradients are energetically favorable. This term alone would be insufficient as it implies the lowest energy state contains infinite gradients. The g_4 term is included to suppress very large gradients.

The Swift-Hohenberg model introduced above [193] equation was derived for the phenomena of Rayleigh-Bénard convection in which a fluid (or gas) is trapped between a hot and cold plate. If the difference in temperature between the two plates is large enough (or more precisely if the Rayleigh number is large enough) a convective instability occurs in which convective roles form to transport the hot fluid to the cold plate and cold fluid to the hot plate. The SH model can be considered as the ‘Model A’ of periodic systems and is written,

$$\mathcal{F} = \int d\vec{r} \left[\frac{1}{2} \psi (-\epsilon + (q_o^2 + \nabla^2)^2) \psi + \frac{\psi^4}{4} \right], \quad (8.9)$$

where the field ψ is a two dimensional scalar field that is commensurate with the convective rolls that form at high Rayleigh number. The dimensionless parameter, ϵ , is proportional to deviations of the Rayleigh number from the critical value at which the convective instability occurs. The dynamics of the field ψ are assumed to be dissipative and driven to minimize the free energy functional in the usual way, i.e.,

$$\frac{\partial \psi}{\partial t} = -\Gamma \frac{\delta \mathcal{F}}{\delta \psi} + \eta = \Gamma [(\epsilon - (q_o^2 + \nabla^2)^2) \psi - \psi^3] + \eta, \quad (8.10)$$

where Γ is a phenomenological parameter that can be scaled out, η is a Gaussian random noise term with correlations $\langle \eta \rangle = 0$ and $\langle \eta(\vec{r}, t) \eta(\vec{r}', t') \rangle = 2\Gamma D \delta(\vec{r} - \vec{r}') \delta(t - t')$ and D is the noise strength.

Before continuing, it will prove useful to re-case Eq. (8.10) in dimensionless units. Noting that while Eq. (8.10) contains four parameters (ϵ , q_o , Γ and D) it is effectively a two parameter model since q_0 and Γ can be eliminated by a simple change of variables. For example if the following definitions are made $\vec{r} = \vec{x}/q_o$, $\psi = q_o^2 \phi$, $\epsilon = q_o^4 \mathcal{E}$ and $t = \tau/q_o^4 \Gamma$, then Eq. (8.10) becomes,

$$\frac{\partial \phi}{\partial \tau} = -\frac{\delta \mathcal{F}'}{\delta \phi} + \zeta = (\mathcal{E} - (1 + \nabla_x^2)^2) \phi - \phi^3 + \zeta, \quad (8.11)$$

where,

$$\mathcal{F}' = \int d\vec{x} \left[\frac{1}{2} \phi (-\mathcal{E} + (1 + \nabla_x^2)^2) \phi + \frac{\phi^4}{4} \right] \quad (8.12)$$

and $\langle \zeta \rangle = 0$ and $\langle \zeta(\vec{x}, \tau) \zeta(\vec{x}', \tau') \rangle = 2D' \delta(\vec{x} - \vec{x}') \delta(\tau - \tau')$ and $D' \equiv Dq_o^{d-8}$.

Equations (8.9) and (8.10) provide a relatively simple mathematical system that gives rise to periodic solutions for ψ . In the next several subsections the static (i.e., equilibrium) and dynamic properties of this model in one dimensions will be discussed. In Section II a very similar equation will be used to model another periodic systems, i.e., crystals. In crystals the field ψ is proportional to the ensemble average of the atomic number density and is a conserved quantity. The conservation law changes both static and dynamics solutions and makes things a bit more complicated. Nevertheless it is instructive to consider the simpler case as will be done in the next few paragraphs.

8.2.1 Static Analysis of the SH Equation

The form of the SH free energy functional is symmetric in ψ , i.e., it only depends on ψ^2 . This symmetry leads to equilibrium solutions that are stripes in two-dimensions and planes in three dimensional. As will

be seen in following sections when this symmetry is broken (by adding asymmetric terms such as ψ^3) other periodic symmetries can form such as triangular in two dimensions and BCC in three dimensions. The mathematical form of the equilibrium solutions can be found by expanding ψ in a Fourier series and then minimizing the free energy per unit length with respect to the Fourier coefficients and wavevector, q . More specifically ψ can be written as,

$$\psi = \sum_{n=1} (A_n e^{inqx} + A_n^* e^{-inqx}). \quad (8.13)$$

where A_n is an amplitude associated with the wave mode n . Substituting this form into Eq. (8.9) and averaging over one wavelength gives,

$$\begin{aligned} F &\equiv \frac{\mathcal{F}}{2\pi/q} = \frac{q}{2\pi} \int_0^{\frac{2\pi}{q}} dx \left(\frac{\psi}{2} (-\epsilon + (q_o^2 + \nabla^2)^2) \psi + \frac{\psi^4}{4} \right) \\ &= -\sum_n \omega_n |A_n|^2 + \sum_{n,i,j} \left(A_{i+j+n}^* A_i A_j A_n + \frac{3}{2} A_{i+j-n}^* A_i A_j A_n^* + A_{i-j-n}^* A_i A_j^* A_n^* \right) \end{aligned} \quad (8.14)$$

where $\omega_n \equiv \epsilon - (q_o^2 - (nq)^2)^2$. To find the lowest energy state F must be simultaneously minimized with respect to A_n for all n and q , i.e., the equations, $dF/dA_n = 0$ and $dF/dq = 0$ must be solved. To simplify the task it is useful to consider a finite number of fourier components. For example the simplest approximation is to retain only one mode, A_1 , which is equivalent to the approximation $\psi \approx (A_1 + A_1^*) \cos(qx)$. In this limit the free energy per unit length becomes,

$$F = -\omega_1 |A_1|^2 + \frac{3}{2} |A_1|^4 \quad (8.15)$$

Minimizing with respect to A_1 gives, $\partial F/\partial(|A_1|^2) = 0 = -\omega_1 + 3|A_1|^2$, with solutions

$$|A_1|_{min} = \begin{cases} 0 & \omega_1 < 0 \\ \pm\sqrt{\omega_1/3} & \omega_1 > 0 \end{cases} \quad (8.16)$$

Substituting the non-trivial solution back into F gives,

$$F = -\frac{1}{6} \omega_1^2 = -\frac{1}{6} (\epsilon - (q_o^2 - q^2)^2)^2 \quad (8.17)$$

The value of q that minimizes F is found by solving, $dF/dq = 0$, which gives, $q_{eq} = q_o$ and in turn,

$$|A_1|_{eq} = |A_1|_{min}(q_o) = \sqrt{\epsilon/3}. \quad (8.18)$$

Thus the solution that minimizes the free energy is,

$$\psi_{eq} = 2\sqrt{\frac{\epsilon}{3}} \cos(q_o x). \quad (8.19)$$

and the minimum free energy/length is

$$F_{stripe} = -\epsilon^2/6. \quad (8.20)$$

Before discussing the dynamic behaviour of the SH model, it is interesting to examine Eq. (8.17), which describes the free energy as a function of wavevector (or wavelength) and can be used to derive

an expression for the ‘elastic’ energy associated with a stretch or compression of the striped phase. Expanding Eq. (8.17) in $\Delta a \equiv (a - a_{eq})/a_{eq}$, where a is the stripe wavelength (i.e., $2\pi/q$) and a_{eq} is the equilibrium stripe wavelength (i.e., $2\pi/q_o$) gives,

$$\Delta F \equiv F - F_{stripe} = \frac{64\pi^4\epsilon}{3a_{eq}^4} \left(\frac{\Delta a}{a_{eq}}\right)^2 + \dots = 4(q_o^2 |A_1|_{eq})^2 \left(\frac{\Delta a}{a_{eq}}\right)^2 + \dots \quad (8.21)$$

The above equation shows a number of interesting features. To lowest order in Δa this model obeys Hooke’s law (i.e., $\Delta F = k(\Delta x)^2/2$), with an effective ‘spring constant’ of $8(q_o^2 |A_1|_{eq})^2$. The spring constant is thus proportional to the amplitude $|A_1|$, which is in turn in proportional to ϵ . In the next section a model almost identical to the SH model will be used to describe crystal growth in which the parameter ϵ is related to temperature. In that context the crystal becomes ‘stiffer’ (i.e., k increases) as the temperature is lowered. In the above expansion $\Delta a/a_{eq}$ was considered to be small compared to unity, however for large $\Delta a/a_{eq}$ a periodic solution may not even exist. Consider for example the solution for A_{min} given in Eq. (8.16), i.e.,

$$|A_1|_{min}(q) = \sqrt{\frac{\omega_1}{3}} = \sqrt{\frac{(\epsilon - (q_o^2 - q^2)^2)}{3}}. \quad (8.22)$$

Since A is a real quantity (at least for this phenomena) there are no periodic solutions for A if

$$\epsilon < (q_o^2 - q^2)^2. \quad (8.23)$$

Or solutions only exist when

$$\sqrt{q_o^2 - \sqrt{\epsilon}} < q < \sqrt{q_o^2 + \sqrt{\epsilon}}. \quad (8.24)$$

The implication is that if the system is compressed or stretched too much a periodic solution no longer exists (i.e., the lowest energy state is $\psi = 0$). As will be discussed in the next section even when solutions exist they can be dynamically unstable (an Eckhaus instability). In Fig. (8.3) the regions where periodic solutions exist are depicted as a function of q and ϵ . The dynamical behaviour of the SH equation is examined next.

8.2.2 Dynamical analysis of the SH equation

Equation (8.10) describes dissipative dynamics that drive the system towards the equilibrium solution. While it is very difficult to obtain exact analytic solutions for arbitrary initial conditions, insight can be gained by considering a simple linear stability analysis about a) an initially uniform state and b) a periodic equilibrium state. (Consider $\Gamma = 1$ for simplicity). The stability of the uniform $\psi = 0$ state can be determined by linearizing Eq. (8.10) around $\psi = 0$, i.e.,

$$\frac{\partial \psi}{\partial t} = (\epsilon - (q_o^2 + \nabla^2)^2) \psi. \quad (8.25)$$

where here ψ represents a small deviation away from the uniform solution. Equation 8.25 can be solved by making the Ansatz for ψ ,

$$\psi(x, t) = A_q(t) \cos(qx). \quad (8.26)$$

where A_q is the amplitude of the perturbation. Substituting Eq. (8.26) into Eq. (8.25) gives,

$$\frac{dA_q(t)}{dt} = \omega_1 A_q(t) \quad (8.27)$$

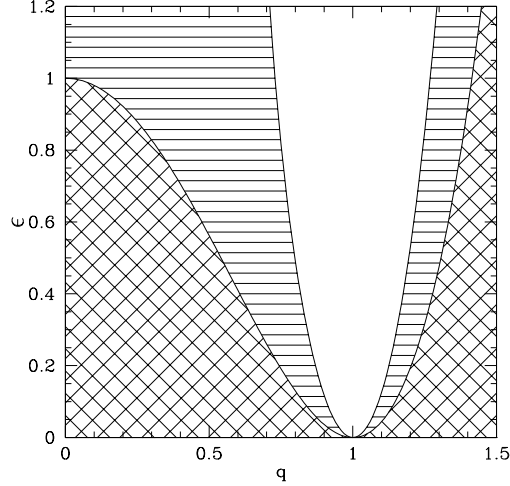


Figure 8.3: Phase diagram of one dimensional Swift-Hohenberg Equation. The diagonally hatched region corresponds to regions for which periodic solutions do not exist in the one mode approximation. The horizontally hatched region corresponds to regions for which periodic solution are dynamically unstable (Eckhaus instability).

which has solution,

$$A_q = e^{\omega_1 t} A_q \quad (8.28)$$

where as usual ($\omega_1 \equiv (\epsilon - (q_o^2 - q^2)^2)$). If $\omega_1 > 0$ (< 0), ψ will grow (decay) exponential in time. Since $(q_o^2 - q^2)^2$ is always positive this implies unstable (stable) growth for $\epsilon > 0$ ($\epsilon < 0$). Since $(q_o^2 - q^2)^2$ is a minimum when $q = q_o$ the system is most unstable (i.e., fastest exponential growth) when $q = q_o$. This is the primary instability that gives rise to the periodic structure and is somewhat similar to Model B, in that a finite wavelength is initially selected. However in the Swift-Hohenberg equation the wavelength doesn't change significantly since the equilibrium solution has a wavevector quite close to q_o .

Perhaps a more interesting case is the stability of the periodic stationary solution (i.e., for $\epsilon > 0$). Expanding around $\psi = \psi_{eq}(x) + \delta\psi$ gives,

$$\frac{\partial \delta\psi}{\partial t} = (\epsilon - 3\psi_{eq}^2 - (q_o^2 + \nabla^2)^2) \delta\psi + \mathcal{O}(\delta\psi)^2 + \dots, \quad (8.29)$$

where for the sake of generality the equilibrium solution are represented as $\psi_{eq} = \sum_n (A_n e^{iqnx} + A_n^* e^{-inqx})$. To solve this linear equation, $\delta\psi$ expanded in the following Fourier series,

$$\delta\psi = \sum_{n=-N}^{n=N} b_n(t) e^{i(nq+Q)x}. \quad (8.30)$$

where N is in principle infinite, but for practical purposes will be set to one. The task is now to solve for $b_n(t)$ in terms of q and Q (a procedure known as Bloch-Floquet theory). Substituting $\delta\psi$ in Eq. (8.29)

gives

$$\sum_n \frac{\partial b_n}{\partial t} e^{inqx} = \sum_n \omega_{nq+Q} b_n e^{inqx} - 3 \sum_{n,m,p} b_n \left(A_m A_p e^{i(n+m+p)qx} + 2A_m^* A_p e^{i(n-m+p)qx} + A_m^* A_p^* e^{i(n-m-p)qx} \right), \quad (8.31)$$

where $\omega_{nq+Q} \equiv \epsilon - (q_0^2 - (nq + Q)^2)^2$. Integrating over $(q/2\pi) \int_0^{2\pi/q} dx e^{-ijqx}$ then gives;

$$\begin{aligned} \sum_n \frac{\partial b_n}{\partial t} \delta_{n,j} &= \sum_n \omega_{nq+Q} b_n \delta_{n,j} - 3 \sum_{n,m,p} b_n \left(A_m A_p \delta_{n+m+p,j} + 2A_m^* A_p \delta_{n-m+p,j} + A_m^* A_p^* \delta_{n-m-p,j} \right) \\ \frac{\partial b_j}{\partial t} &= \omega_{jq+Q} b_j - 3 \sum_{m,p} \left(b_{j-m-p} A_m A_p + 2b_{j+m-p} A_m^* A_p + b_{j+m+p} A_m^* A_p^* \right) \end{aligned} \quad (8.32)$$

which utilizes the following identities,

$$\frac{q}{2\pi} \int_0^{2\pi/q} dx e^{i(n-m)qx} = \delta_{n,m} = \begin{cases} 1 & n = m \\ 0 & n \neq m \end{cases} \quad (8.33)$$

To simplify calculations consider a one mode approximation, i.e., $|A_1| = \sqrt{\omega_q/3}$, and $A_n = 0$ for $n = 2, 3, \dots$. At this level of approximation Eq. (8.32) becomes,

$$\frac{\partial b_j}{\partial t} = \omega_{jq+Q} b_j - 3(b_{j-2} A_1^2 + 2b_j |A_1|^2 + b_{j+2} (A_1^*)^2). \quad (8.34)$$

Making a similar one mode approximation for b_n (i.e., $b_n = 0$ for $n = 2, 3, \dots$) gives,

$$\begin{aligned} \frac{\partial b_1}{\partial t} &= (\omega_{Q+q} - 6|A_1|^2) b_1 - 3b_{-1} A_1^2 = (\omega_{Q+q} - 2\omega_q) b_1 - b_{-1} \omega_q \\ \frac{\partial b_0}{\partial t} &= (\omega_Q - 6|A_1|^2) b_0 = (\omega_Q - 2\omega_q) b_0 \\ \frac{\partial b_{-1}}{\partial t} &= (\omega_{Q-q} - 6|A_1|^2) b_{-1} - 3b_1 (A_1^*)^2 = (\omega_{Q-q} - 2\omega_q) b_{-1} - b_1 \omega_q \end{aligned} \quad (8.35)$$

Notice that b_0 is conveniently decoupled from b_1 and b_{-1} . Thus the solution for b_0 is,

$$b_0(t) = e^{-(2\omega_q - \omega_Q)t} b_0(0), \quad (8.36)$$

where $2\omega_q - \omega_Q < 0$ for small Q and thus b_0 decays exponentially to zero and can be ignored. Making the ansatz, $b_n \sim \exp(\lambda t)$ gives rise to an eigenvalue problem, i.e.,

$$\begin{bmatrix} \lambda - (\omega_{Q+q} - 2\omega_q) & \omega_q \\ \omega_q & \lambda - (\omega_{Q-q} - 2\omega_q) \end{bmatrix} \begin{bmatrix} b_1 \\ b_{-1} \end{bmatrix} = 0 \quad (8.37)$$

The eigenvalues (λ) are determined by setting the determinate of the matrix in Eq. (8.37) to zero, which gives the solutions,

$$\lambda_{\pm} = \frac{1}{2} \left(\omega_{Q+q} + \omega_{Q-q} - 4\omega_q \pm \sqrt{(\omega_{Q+q} - \omega_{Q-q})^2 + 4\omega_q^2} \right). \quad (8.38)$$

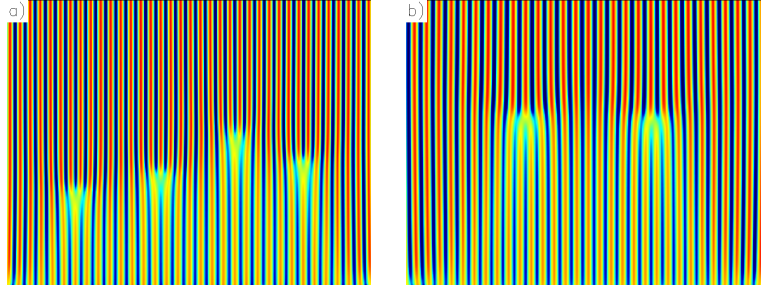


Figure 8.4: Eckhaus instability in the one dimensional Swift Hohenberg equation. In this figure the color corresponds to the magnitude of ψ and the horizontal and vertical scales correspond to space and time respectively. In both instances the initial state was $\psi = 2\sqrt{(\epsilon - (1 - q^2)^2)/3} \cos(qx) + \eta$, where η was random gaussian noise of amplitude 0.05. In Figs. a) and b) $q = 0.88$ and 1.115 respectively.

Since $b_n \sim e^{\lambda t}$ the solutions are unstable if either eigenvalue is positive. For $q \approx q_0$ both eigenvalues are negative and the system is stable. When q is much larger or smaller than q_0 one eigenvalues (λ_+) become positive and an instability occurs. This implies that if the initial state is periodic, but the periodicity is far away from the equilibrium solution, then any small perturbation will grow and the system will evolve into another periodicity closer to the equilibrium one. This is known as an Eckhaus instability. When such an instability occurs the wavelength (or q) will spontaneously change by either creating an extra wavelength or deleting one.

To better understand the Eckhaus instability, it is instructive to expand λ_{\pm} to lowest order in Q gives,

$$\lambda_+ = -2 \left(3q^2 - q_0^2 - \frac{4(q_0^2 - q^2)^2 q^2}{\omega_q} \right) Q^2 + \dots \quad (8.39)$$

$$\lambda_- = -2\omega_q - 2 \left(3q^2 - q_0^2 + \frac{4(q_0^2 - q^2)^2 q^2}{\omega_q} \right) Q^2 + \dots \quad (8.40)$$

The eigenvalue λ_- is always negative or zero and thus not of much interest, however the coefficient of Q^2 in Eq. (8.39) can be positive for some values of q . The boundary between a negative and positive value occurs when $\epsilon = \epsilon_{Eck}(q)$ where,

$$\epsilon_{Eck} = \frac{(7q^2 - q_0^2)(q_0^2 - q^2)^2}{3q^2 - q_0^2}. \quad (8.41)$$

This solution determines the boundary between periodic solutions that are stable and unstable. In Fig. (8.3) the regions where periodic solutions are dynamically unstable are shown. When this instability occurs the perturbations initially grow exponentially until a *phase slip* occurs in which one or more periods is gained or lost, depending whether or not the wavelength of the initial state was too small or large. Examples of such processes are shown in Fig. (8.4). In the next section a similar model will be introduced to model crystal growth. For crystal growth the corresponding Eckhaus instability can be associated with the nucleation of dislocations.

An additional interesting feature of this calculation is that it can be used to determine an effective diffusion constant of the system. For perturbations around the lowest energy state ($q = q_0$ in one-dimension and $w_{q_0} = \epsilon$) Eq. (8.39) becomes

$$\lambda_+ = -4q_0^2 Q^2 + \mathcal{O}(Q)^4 + \dots \quad (8.42)$$

Or in other words the perturbations satisfy a diffusion equation (in the long wavelength limit) with diffusion constant

$$D_v = 4q_o^2. \quad (8.43)$$

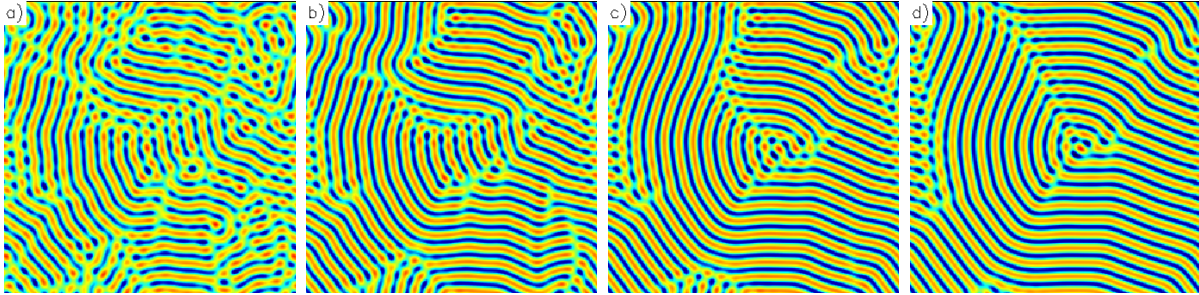


Figure 8.5: Two dimensional ordering in the Swift-Hohenberg model in Eq. (8.10). In this figure the color corresponds to the magnitude of ψ . These simulations were conducted for $(\epsilon, q_o, \Gamma, D) = (0.1, 1, 1, 0)$, in a system of size (128×128) and Figs a), b) c), d) correspond to times $t = 100, 200, 400$ and 800 respectively.

The discussion in this subsection has thus far focussed on the one dimensional properties of the SH equation. In two dimensions the mean field equilibrium solutions remain the same (i.e., stripes), however the dynamics are significantly more complex since the stripes can form in any orientation. A sample two dimensional simulation is shown in Fig. (8.5). Ordering or coarsening of stripe patterns has been the subject of many studies [69, 68, 55, 94, 30]. Earlier studies [69, 68, 55, 94] indicated a dynamic growth exponent of $n = 1/5$ without noise and $n = 1/4$ with noise. Later studies showed that the exponent changes with the magnitude of the noise and frozen glassy states emerge at zero noise strength [30].

The Swift-Hohenberg equation is a simple model system for studying the formation and ordering of modulated or striped phases. While the original SH equation is minimized by one-dimensional stripes it is straight forward to extend the model to hexagonal patterns (in two dimensions) by simply adding a cubic term to the free energy functional show in Eq. (8.9), i.e.,

$$\mathcal{F} = \int d\vec{r} \left[\frac{1}{2} \psi (-\epsilon + (q_o^2 + \nabla^2)^2) \psi + \alpha \frac{\psi^3}{3} + \frac{\psi^4}{4} \right]. \quad (8.44)$$

The additional term breaks the \pm symmetry of ψ such that (for positive α) the energy is smaller for negative ψ . For small α the stripe solutions still exist, however the width of the positive portion shrinks and the negative portion grows. For large enough α the stripes break apart and form dots or mounds as shown in Fig. (8.6). Energetically it is most favorable for these dots to order into a triangular pattern. Notably grains of arbitrary orientation naturally emerge and form grain boundaries when two grains hit. It is precisely these features that lead to the idea that such models could be used to model crystal growth.

8.3 Phase Field Crystal (PFC) Modeling

As discussed in the preceding sections, and illustrated with the SH equation, continuum models that are minimized by periodic structures contain much of the generic ingredients, such as elasticity, dislocations, multiple crystal orientations and anisotropy, needed for modeling crystal growth, as illustrated in the

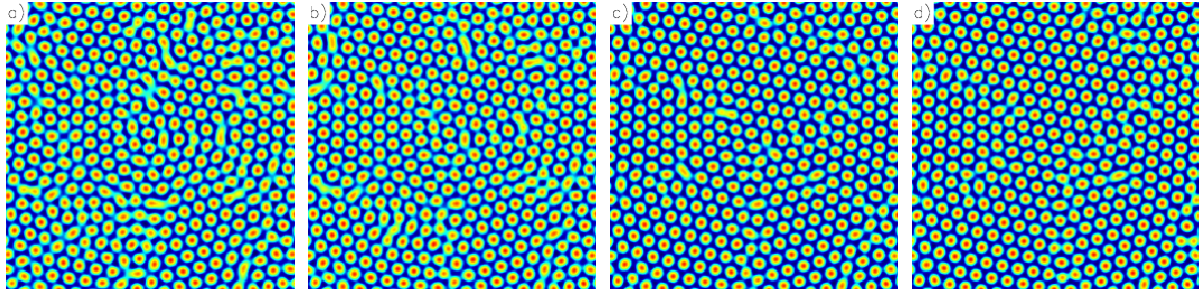


Figure 8.6: Two dimensional ordering in the Swift-Hohenberg equation with extra cubic term in free energy functional (see Eq. (8.44)). In this figure the color corresponds to the magnitude of ψ . These simulations were conducted for $(\epsilon, q_o, \Gamma, D, \alpha) = (0.1, 1, 1, 0, 1/2)$, in a system of size (128×128) and Figs a), b) c), d) correspond to times $t = 100, 200, 400$ and 800 respectively.

preceding section. It was this observation that motivated the development of the so-called phase field crystal (PFC) model [61, 66], which is simply a conserved version of the SH equation, i.e., Eq. (8.10) with the right hand side multiplied by $-\nabla^2$. This modification fixes the average value of ψ ($\bar{\psi}$) and effectively adds a cubic term to the free energy functional when $\bar{\psi}$ is non-zero. As seen in the last section, cubic terms can give rise more interesting solutions such as triangular and BCC patterns in two and three dimensions respectively. In addition to altering the equilibrium solutions, the conservation law also makes a significant impact on the dynamics. For example in the SH equation a defect, such as an extra stripe randomly inserted into an equilibrium pattern, can spontaneously disappear. However when the dynamics are conserved, defect motion such as climb, can only occur by vacancy diffusion [25]. In other words an extra row of atoms cannot simply disappear, they must diffuse away. While the SH free energy functional was originally proposed for modeling crystal growth it was later recognized that this model could be derived from classical density functional theory (CDFT). This derivation involves many crude approximations, but does give some physical insight into the parameters that enter the model. In the next few paragraphs this derivation will be outlined.

The derivation begins from the CDFT of freezing as proposed by Ramakrishnan and Yussouff [176] and reviewed by Singh [187]. It should also be possible to connect the PFC model to the atomic density theory of Jin and Khachatryan, which was recently proposed [110]. A nice description of CDFT can also be found in Chaiken and Lubensky [43]. In this theory the Helmholtz free energy, \mathcal{F} , is derived by expanding around the properties of a liquid that is in coexistence with a crystalline phase. In this formulation \mathcal{F} is a functional of the local number density, $\rho(\vec{r})$ of atoms in the system. Formally the solution is

$$\frac{\Delta\mathcal{F}}{k_B T} = \int d\vec{r} \left. \frac{\delta\mathcal{F}}{\delta\rho} \right|_{\ell} \delta\rho + \frac{1}{2!} \int d\vec{r}_1 d\vec{r}_2 d\vec{r}_3 \left. \frac{\delta^2\mathcal{F}}{\delta\rho_1\delta\rho_2} \right|_{\ell} \delta\rho_1\delta\rho_2 + \frac{1}{3!} \int d\vec{r}_1 d\vec{r}_2 \left. \frac{\delta^3\mathcal{F}}{\delta\rho_1\delta\rho_2\delta\rho_3} \right|_{\ell} \delta\rho_1\delta\rho_2\delta\rho_3 + \dots \quad (8.45)$$

where, the subscript ℓ refers to the reference liquid state, $\delta\rho \equiv \rho - \rho_{\ell}$ and $\Delta\mathcal{F} \equiv \mathcal{F} - \mathcal{F}_{\ell}$. The above expression is a functional Taylor series expansion. Ramakrishnan and Yussouff showed that the second term is equivalent the entropy of an ideal gas, i.e.,

$$\left. \frac{\delta\mathcal{F}}{\delta\rho} \right|_{\ell} \delta\rho = \rho \ln \left(\frac{\rho}{\rho_{\ell}} \right) - \delta\rho \quad (8.46)$$

and that the higher order terms are directly related to direct correlation functions, i.e.,

$$\frac{\delta^n F}{\delta\rho_1\delta\rho_2\dots\delta\rho_n} = -C_n(\vec{r}_1, \vec{r}_2, \vec{r}_3, \dots, \vec{r}_n) \quad (8.47)$$

where C_n are direct correlation functions. These functions measure correlations between the atomic number density at various points in space. For example C_2 gives a measure of the probability that if an atom exists at point \vec{r}_1 that another particle also exists at point \vec{r}_2 . The advantage of expanding around the liquid state is that liquids are typically isotropic and have short range order. This implies that the correlation functions are also isotropic and short-ranged. In the crystalline state the correlations functions are anisotropic, mimicking the symmetry of the crystalline lattice, and long-ranged (i.e., Bragg peaks in Fourier space). Thus it would not be possible to expand around the solid-state correlation functions since this would lead to free energy functionals that are not rotationally invariant. In what follows it will be assumed that C_2 is only dependent on the distance between the two points, i.e., $C_2(\vec{r}_1, \vec{r}_2) = C_2(r)$, where $r \equiv |\vec{r}_1 - \vec{r}_2|$. Reiterating, this is a key approximation that can only be made in the liquid state and ensures that the free energy functional is invariant under a global rotation of the density field.

Using Eq. (8.47) the CDFT free energy functional can be written

$$\frac{\Delta\mathcal{F}}{k_B T} = \int d\vec{r} \left[\rho \ln \left(\frac{\rho}{\rho_\ell} \right) - \delta\rho \right] - \frac{1}{2!} \int d\vec{r}_1 d\vec{r}_2 C_2(\vec{r}_1, \vec{r}_2) \delta\rho_1 \delta\rho_2 - \frac{1}{3!} \int d\vec{r}_1 d\vec{r}_2 d\vec{r}_3 C_3(\vec{r}_1, \vec{r}_2, \vec{r}_3) \delta\rho_1 \delta\rho_2 \delta\rho_3 + \dots \quad (8.48)$$

While this free energy has been used to study freezing transitions in a wide variety of systems [176, 187], it is inconvenient for numerical calculations of non-equilibrium phenomena. Typically the solutions for ρ that minimize \mathcal{F} are very sharply peaked in space and consequently require a high degree of spatial resolution such that it may require 100^d (where d is dimension) mesh points to resolve a single atomic number density peak.

In the next few pages several simplification will be introduced to develop a model that, while retaining the essential features of crystals, is much easier to numerically simulate. It should be noted that the simplifications are quite drastic, resulting in a model that is a poor approximation to the CDFT. The goal is not to reproduce CDFT but to motivate a phase field scheme that incorporates the ‘essential physics’. Despite the inaccuracy of the resulting model it is an interesting exercise as the parameters of the simple model can be directly related to the correlation functions that enter CDFT and thus give some interesting insight. To match the resulting model with an experimental system a more pragmatic approach should be taken, as discussed in section 8.7.

To begin the derivation, it is convenient to introduce the dimensionless number density field, n , defined such that

$$n \equiv (\rho - \bar{\rho})/\bar{\rho}, \quad (8.49)$$

where $\bar{\rho}$ is constant reference density (usually taken to be the density of the liquid at coexistence). In the following calculations n will be assumed to be a small parameter and the free energy functional will be expanded to order n^4 . It should be noted that in the full CDFT solution, n is not small. For example, in Fe at $T = 1772K$ and $\bar{\rho} = 0.09\text{\AA}^{-3}$ (i.e., close to the melting temperature) n can be on the order of forty or fifty near the center of lattice sites [105]. Further simplifications are made by truncating the density functional series in Eq. (8.48) at C_2 and expanding C_2 in fourier space upto k^4 , i.e.,

$$\hat{C}(k) \approx -\hat{C}_0 + \hat{C}_2 k^2 - \hat{C}_4 k^4 \quad (8.50)$$

where for convenience the subscript ‘2’ has been dropped. It is useful to note that the fourier transform of this function ($\hat{C}(\vec{k})$) is related to the structure factor ($S(k) = \langle |\delta\hat{\rho}(k)|^2 \rangle$) as follows $S(k) = 1/(1 - \bar{\rho}\hat{C})$.

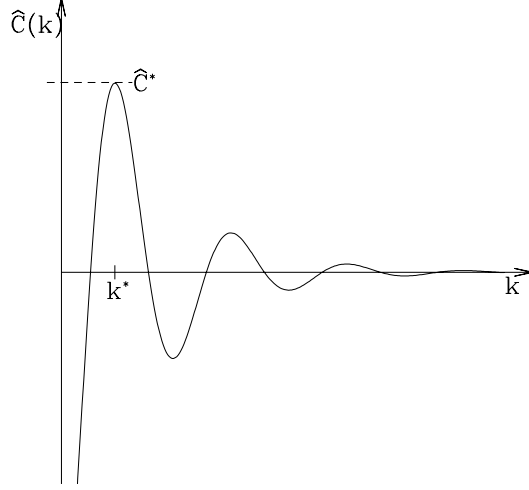


Figure 8.7: Sketch of two point direct correlation function in Fourier space.

In this approximation $\hat{C}(k)$ has been expanded to the lowest possible order that captures the periodic nature of crystalline systems. A sample sketch of such a function is given in Fig. (8.7). Essentially the parameters \hat{C}_0 , \hat{C}_2 and \hat{C}_4 can be used to fit the first peak in the \hat{C} . From a more practical point of view these parameters can be used to fit various physical features of the material as discussed in references [213, 198, 105] and in Sec. (8.7). Substituting $\hat{C}(k)$ into Eq. (8.48) gives ¹

$$\frac{\Delta\mathcal{F}}{k_BTV\bar{\rho}} \approx \ln\left(\frac{\bar{\rho}}{\rho_\ell}\right) + \frac{\rho_\ell - \bar{\rho}}{\bar{\rho}} + \frac{1}{V} \int d\vec{x} \left[\frac{B^\ell}{2} n^2 + \frac{B^x}{2} n (2R^2\nabla^2 + R^4\nabla^4) n - t\frac{n^3}{3} + v\frac{n^4}{4} \right] \quad (8.51)$$

where $t = 1/2$, $v = 1/3$, $B^\ell \equiv 1 + \bar{\rho}\hat{C}_0$, $B^x \equiv \bar{\rho}(\hat{C}_2)^2/4\hat{C}_4$, $R \equiv \sqrt{2|\hat{C}_4|/\hat{C}_2}$ and $V \equiv \int d\vec{x} \equiv \int dx dy dz$. Since only one length scale (R) appears in Eq. (8.51) it can be eliminated by a simple length rescaling, i.e.,

$$\frac{\Delta\mathcal{F}}{k_BTV\bar{\rho}} \approx \ln\left(\frac{\bar{\rho}}{\rho_\ell}\right) + \frac{\rho_\ell - \bar{\rho}}{\bar{\rho}} + \frac{R^d}{V} \int d\vec{r} \left[\frac{n}{2} (\Delta B + B^x(1 + \nabla^2)^2) n - t\frac{n^3}{3} + v\frac{n^4}{4} \right] \quad (8.52)$$

where $\vec{r} \equiv \vec{x}/R$ and $\Delta B \equiv B^\ell - B^x$. This form is of course remarkably similar to the SH equation (see Eq. (8.44)).

The free energy in Eq. (8.52) contains only two parameters, B^ℓ and B^x . The parameter B^ℓ is the inverse liquid state isothermal compressibility ² (in dimensionless units) and as will be shown, B^x is proportional to the magnitude of the elastic constants. In physical terms the three parameters control, the length scale and the energies scales of the liquid and solid states. To relate this to the Swift-Hohenberg

¹In real space variables, the expression in Eq. (8.50) becomes $C(\vec{r}_1, \vec{r}_2) = C(|\vec{r}_1 - \vec{r}_2|) = (-\hat{C}_0 - \hat{C}_2\nabla^2 - \hat{C}_4\nabla^4) \delta(\vec{r}_1 - \vec{r}_2)$.

²In Ref. [62], B^ℓ was mistakenly referred to as the isothermal compressibility, instead of its inverse.

description a simple change of variables can be made, i.e., $\vec{r} = \vec{x}/R$, $B^\ell = B^x(1 + \epsilon)$ and $\phi = n\sqrt{v/B^x}$ gives,

$$\frac{\Delta\mathcal{F}}{k_BTV\bar{\rho}} = \ln\left(\frac{\bar{\rho}}{\rho_\ell}\right) + \frac{\rho_\ell - \bar{\rho}}{\bar{\rho}} + \frac{R^d(B^x)^2}{vV} \int d\vec{r} \left[\frac{\epsilon}{2}\phi^2 + \frac{\phi}{2}(1 + \nabla^2)^2\phi - g\frac{\phi^3}{3} + \frac{\phi^4}{4} \right] \quad (8.53)$$

where $g \equiv t/\sqrt{vB^x}$. Similar to the SH free energy functional the transition from a liquid (i.e., $n = \text{constant}$) to a solid (n periodic) occurs roughly when ϵ changes sign. Since the field n is a conserved field the thermodynamics are different from the SH model and the transition changes from being a second order (in mean field theory [1, 93]) to first order as expected for a liquid solid transition. In this context ϵ becomes negative as the temperature lowered or as the density increases. To evaluate the properties of this very simple model various equilibrium and non-equilibrium properties will be derived in the next few sections.

8.4 Equilibrium Properties in a One Mode Approximation

To evaluate various properties of this model it is useful to analytically determine the minimum energy states of the free energy functional in mean field theory. Assuming that the system is in a crystalline state and the reference density ($\bar{\rho}$) is the average value of the density, the functional form of a periodic density can be written down in terms of the reciprocal lattice vectors, \vec{G} , i.e.,

$$n = \sum_{\vec{G}} \eta_{\vec{G}} e^{i\vec{G}\cdot\vec{r}} + \text{c.c.} \quad (8.54)$$

where c.c. is the complex conjugate and $\eta_{\vec{G}}$ represent the amplitudes of a given reciprocal lattice vector mode. As discussed in section (5.1) these amplitudes can be interpreted as complex order parameters of the crystal. In three dimensions, \vec{G} can be written $\vec{G} = n_1\vec{q}_1 + n_2\vec{q}_2 + n_3\vec{q}_3$, where $(\vec{q}_1, \vec{q}_2, \vec{q}_3)$ are the principle reciprocal lattice vectors describing a specific crystalline symmetry, (n_1, n_2, n_3) are integers and the summation in Eq. (8.54) refers to a summation over all n_1, n_2 and n_3 . The convenience of this description is that the amplitudes are constant in a perfectly periodic state. If the amplitudes are allowed to vary in space and time then this description is quite useful for generating complex order parameter models that describe multiple crystal orientations, elastic deformations, defects, etc. This was explored in detail by Goldenfeld *et al.* [78] and touched upon in Sec. (5.2).

In the following sections the simplest approximation will be made for the equilibrium solid phase, that of a perfect single crystal in a ‘one mode approximation’. For the purpose of this book a ‘one-mode approximation’ will refer to an approximation in which the summation only includes (n_1, n_2, n_3) values that correspond to the lowest order (i.e., smallest) values of \vec{G} needed to reconstruct a given crystal symmetry. While this approximation cannot be used to describe the mean field equilibrium functional forms for n in CDFT it is reasonably accurate for the PFC model and exact in the limit $\epsilon \sim (B^\ell - B^x)/B^x \rightarrow 0$. In the following sections this approximation will be used to derive the phase diagram in one, two and three dimensions.

8.4.1 Three dimensions: BCC lattice

To evaluate the equilibrium states of the PFC model in three dimensions the free energy of various crystalline symmetries must be compared. In a one mode approximation it turns out that a BCC

symmetry minimizes the free energy functional. For a BCC crystal \vec{G} can be written in terms of the following set of principle reciprocal lattice vectors,

$$\vec{q}_1 = \frac{2\pi}{a} \left(\frac{\hat{x} + \hat{y}}{\sqrt{2}} \right), \quad \vec{q}_2 = \frac{2\pi}{a} \left(\frac{\hat{x} + \hat{z}}{\sqrt{2}} \right) \quad \text{and} \quad \vec{q}_3 = \frac{2\pi}{a} \left(\frac{\hat{y} + \hat{z}}{\sqrt{2}} \right), \quad (8.55)$$

where a is the lattice constant. The values of (n_1, n_2, n_3) in Eq. (8.54) that correspond to a ‘one-mode approximation’ are then $(n_1, n_2, n_3) = (1, 0, 0), (0, 1, 0), (0, 0, 1), (1, -1, 0), (0, 1, -1),$ and $(-1, 0, 1)$. Each of the corresponding $\vec{G} = n_1\vec{q}_1 + n_2\vec{q}_2 + n_3\vec{q}_3$ vectors has magnitude, $2\pi/a$. Substituting these reciprocal lattice vectors into Eq. (8.54) and assuming all the amplitudes are equivalent, (i.e., $\eta_{\vec{G}} = \phi/4$, where the factor of 4 is for convenience) gives,

$$n = \phi [\cos(qx) \cos(qy) + \cos(qx) \cos(qz) + \cos(qy) \cos(qz)], \quad (8.56)$$

where $q = 2\pi/(\sqrt{2}a)$. This functional form can now be used to calculate various equilibrium properties.

To determine the equilibrium states, the next step is to determine the values of ϕ and q that minimize the dimensionless free energy difference, F , which is defined to be

$$F(q, \phi) \equiv \frac{1}{a^3} \int_0^a dx \int_0^a dy \int_0^a dz \left[\frac{B^\ell}{2} n^2 + \frac{B^x}{2} n (2\nabla^2 + \nabla^4) n - t \frac{n^3}{3} + v \frac{n^4}{4} \right] \quad (8.57)$$

where for convenience the constant terms in Eq. (8.52) have been subtracted. Substitution of Eq. (8.56) gives,

$$F(q, \phi) = \frac{3}{8} [B^\ell - 4B^x (q^2 - q^4)] \phi^2 - \frac{t}{4} \phi^3 + \frac{135v}{256} \phi^4. \quad (8.58)$$

The value of q (and the lattice constant a) can now be obtained by minimizing with respect to q (i.e., $dF/dq = 3B^x(-q + 2q^3) = 0$), which gives,

$$q_{eq} = 1/\sqrt{2} \quad (8.59)$$

or $a = 2\pi/q = 2\pi$ (in dimensionless units). Substitution of this expression into F gives,

$$F(q_{eq}, \phi) = \frac{3}{8} \Delta B \phi^2 - \frac{t}{4} \phi^3 + \frac{135v}{256} \phi^4. \quad (8.60)$$

where $\Delta B \equiv B^\ell - B^x$. For illustrative purposes $F(q_{eq}, \phi)$ is plotted as a function of ϕ in Fig. (8.8a) for several values of ΔB to highlight the first order phase transition from a liquid ($\phi = 0$) to solid ($\phi \neq 0$) state. The value of ΔB at which the transition occurs (i.e., when the two minima are equal) can be obtained by first minimizing F with respect to ϕ , i.e., $dF/d\phi = 0$, gives,

$$\phi_{eq} = \frac{4}{45v} \left(2t + \sqrt{4t^2 - 45v\Delta B} \right) \quad (8.61)$$

(note three solutions of $dF/d\phi = 0$ exist, $\phi = 0$ corresponds to the liquid state and $\phi = 4(2t - \sqrt{4t^2 - 45v\Delta B})/45v$ an inflection point). Substituting this expression back into the free energy density, and solving the equation $F(q_{eq}, \phi_{eq}) = 0$, for ΔB gives the melting value, ΔB_{ls} , since $F = 0$ is the energy density of the liquid state. The solution is,

$$\Delta B_{ls} = 32t^2/(405v). \quad (8.62)$$

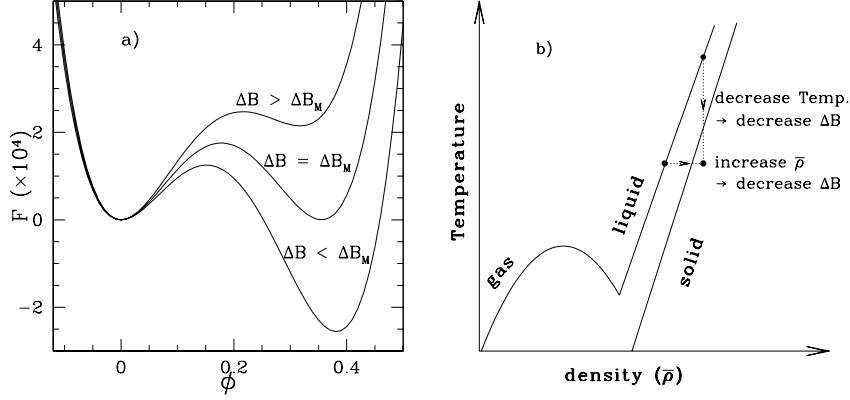


Figure 8.8: (a) Free energy density as a function of ϕ at three values of $\Delta B = B^\ell - B^x$ with $(t, v) = (1/2, 1/3)$. The top, middle and bottom curves correspond to $\Delta B = \Delta B_{ls} + 0.005$, ΔB_{ls} and $\Delta B_{ls} - 0.005$. (b) Sketch of typical gas/liquid/solid phase diagram. As illustrated in this figure the parameter ΔB will decrease when the density is increased or the temperature is decreased.

This calculation shows that a first order phase transition from a liquid to solid state occurs at $\Delta B = \Delta B_M$ and the order parameter for the transition is ϕ . From this point of view the “phase” field that is usually introduced in traditional phase field models to describe liquid/solid transition is not an arbitrary field introduced for convenience. As discussed in earlier chapters, this field is the amplitude of the number density field. It is also probe the physical significance of the parameter ΔB_M . Intuitively one expects that this parameter is related to temperature, which it is. To see this it is useful to substitute the definitions of B^ℓ and B^x (i.e., $B^\ell = 1 + \bar{\rho}\hat{C}_0$ and $B^x = \bar{\rho}\hat{C}_2^2/4\hat{C}_4$) into ΔB to obtain,

$$\Delta B = 1 + \bar{\rho} (\hat{C}_0 - \hat{C}_2^2/4\hat{C}_4). \quad (8.63)$$

Next noting that the maximum of \hat{C} occurs when $k^2 = \hat{C}_2/2\hat{C}_4$ or when $\hat{C}^* = -\hat{C}_0 + \hat{C}_2^2/4\hat{C}_4$ (see Fig. (8.7)) gives,

$$\Delta B = 1 - \bar{\rho}\hat{C}^* = 1/S(k^*). \quad (8.64)$$

where $S(k^*)$ is the maximum of the structure factor. Thus as the peak in $S(k)$ increases (which is increasing the nearest neighbour correlations) a transition to a crystalline state is triggered. Additionally as the average number density ($\bar{\rho}$) increases ΔB decreases and a transition to the crystalline state occurs as expected. Recalling that \hat{C}^* is the peak in \hat{C} along the liquid coexistence line, and noting that it is roughly constant along this line indicates that ΔB decreases with increasing density or decreasing temperature as illustrated in Fig. (8.8b). Thus changing ΔB is equivalent to changing the temperature or the average density.

In the preceding calculations it was explicitly assumed that a single phase state was formed (a crystalline phase) and it was convenient to expand the n around $\bar{n} = 0$. However, there exists the possibility of phase coexistence between the liquid and crystalline phases. In order to account for this possibility (and to derive the liquid/crystal coexistence lines) a specific $\bar{\rho}$ must be chosen to expand around. The most convenient (and consistent) value to expand around is the density along the liquid coexistence line,

i.e., $\bar{\rho} = \rho_\ell$. In this instance the constant terms in Eq. (8.51) disappear and the coefficients are evaluated at ρ_ℓ , i.e., $B^\ell \equiv 1 + \rho_\ell \hat{C}_0$ and $B^x = \rho_\ell \hat{C}_2^2 / 4\hat{C}_4$. As will be seen the transition to the crystalline phase occurs as the average value of n (which is now not zero) is increased consistent with the earlier discussion. To determine the equilibrium states, for BCC symmetry, n_o must be added to Eq. (8.56), i.e.,

$$n = n_o + \phi [\cos(qx) \cos(qy) + \cos(qx) \cos(qz) + \cos(qy) \cos(qz)], \quad (8.65)$$

Substituting this expression into Eq. (8.57) and minimizing with respect to q gives $q_{eq} = 1/\sqrt{2}$ as before and,

$$F(q_{eq}, \phi, n_o) = \frac{B^\ell}{2} n_o^2 - t \frac{n_o^3}{3} + v \frac{n_o^4}{4} + \frac{3}{8} [\Delta B - n_o(2t - 3vn_o)] \phi^2 - \frac{1}{4} [t - 3vn_o] \phi^3 + \frac{135v}{256} \phi^4. \quad (8.66)$$

For illustrative purposes this free energy is plotted as a function of n_o and ϕ in Fig. (8.9). For the parameters used in this figure the free energy has two minima, one corresponding to liquid at $(n_o, \phi) = (0, 0)$ and one for a crystal at $(n_o, \phi) \approx (0.03811, 0.3870)$.³

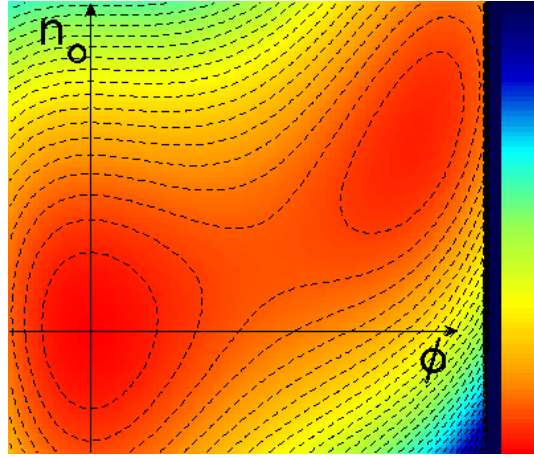


Figure 8.9: Free energy as a function of n_o and ϕ as described by Eq. (8.60) for $B^\ell = 1$, $B^x = 0.925$, and $(t, v) = (1/2, 1/3)$.

The coexisting equilibrium densities of the solid and liquid phases can be found by first minimizing F with respect to ϕ as before to obtain,

$$\phi_{bcc} = \frac{4}{45v} \left(2t - 6vn_o + \sqrt{4t^2 - 45v\Delta B + 33vn_o(2t - 3vn_o)} \right) \quad (8.67)$$

Equation (8.67) is then substituted into Eq. (8.66) to obtain the free energy of the crystal as a function of n_o . To obtain the equilibrium coexistence lines this free energy must be compared with the liquid state

³As an aside the reader may notice that the coefficient of ϕ^2 contains the term $-n_o(2t - 3vn_o)$. The implication is that for large n_o this coefficient is positive which in term implies this term favors a liquid state. This unphysical result is simply a consequence of the small n expansion. If done more carefully it can be shown that these terms are just the lowest order expansion of $1/(1 + n_o) - 1$ which always decreases as n_o increases.

free energy (i.e., Eq. (8.66) at $\phi = 0$),

$$F^{liq} = \frac{B^\ell}{2}n_o^2 - t\frac{n_o^3}{3} + v\frac{n_o^4}{4}. \quad (8.68)$$

A sample plot of the liquid and crystal free energy densities is shown in Fig. (8.10a) at $B^\ell = 1$ and $B^x = 0.925$. The equilibrium liquid (n_ℓ) and crystal (n_x) densities can be obtained in the usual manner, i.e., by the common tangent rule (see Fig. (8.10a)) or by the Maxwell equal area construction rule (see Fig. (8.10b)). To perform the common tangent construction, it is useful to expand the solid and liquid

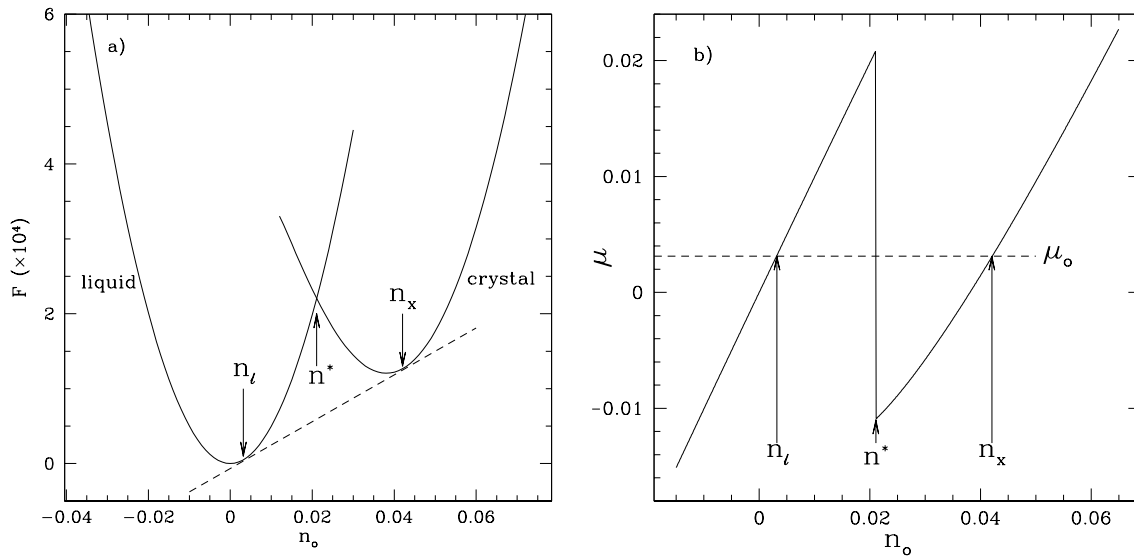


Figure 8.10: Comparison of liquid and crystal free energy densities (a) and chemical potentials (b) for $B^\ell = 1$, $B^x = 0.925$ and $(t, v) = (1/2, 1/3)$. In (a) the dashed line is the common tangent that determines the equilibrium liquid and crystal densities, n_ℓ and n_x . In (b) the dashed line corresponds to the chemical potential at which the upper triangle has the same area as the lower triangle.

free energies about the density where the liquid and crystal free energies are equal. This density is given by

$$n^* = (t - 3\sqrt{1545t^2 - 4635v\Delta B/103})/3v. \quad (8.69)$$

Repeating these calculations for various values of B^ℓ and B^x leads to liquid/crystal coexistence lines show in Fig. (8.11) for three values of B^ℓ as a function of ΔB . As can be seen in these figures increasing B^ℓ and B^x , with ΔB fixed, decreases the miscibility gap (i.e., the density difference between the liquid and solid phases). As will be shown in Section (8.4.4) elastic moduli tend to increase with increasing B^x . This has the effect of reducing the liquid/crystal interfacial thicknesses.

The preceding calculations implicitly assume small n (and small n_o). For small n_o the relevant phases are the liquid and BCC phases. However for larger positive values of n_o other structures minimize the free energy density, such as a two-dimensional triangular lattice of rods or at even larger values of n_o a one-dimensional ordering of planes or stripes. Thus to obtain the complete phase diagram between all

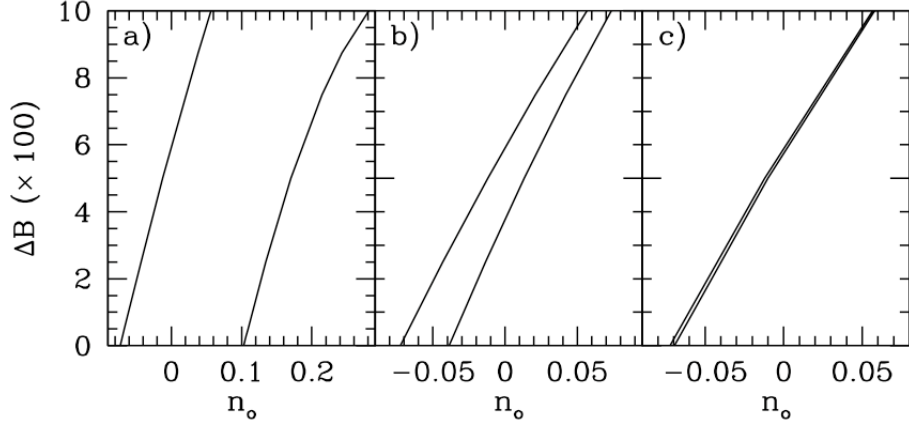


Figure 8.11: Sample liquid/crystal coexistence lines. In all figures the lines on the left (right) are the liquid (crystal) coexistence lines. The value of B^ℓ is a), b) and c) are 0.1, 1.0 and 10.0 respectively.

phases, the free energy for an array of triangular rods and striped planes must be evaluated. A similar procedure to that used in this subsection can be then used to construct coexistence lines between these various phases. The next two subsections work through the steps required to calculate the the free energy of rods and stripe phases in a simple one-mode approximation.

8.4.2 Two dimensions triangular rods

It is straightforward to extend the calculations in the preceding section to a two dimensional system with triangular symmetry. For a triangular system the principle reciprocal lattice vector are

$$\vec{q}_1 = -\frac{2\pi}{a} \left(\frac{\sqrt{3}}{2} \hat{x} + \frac{1}{2} \hat{y} \right) \quad \text{and} \quad \vec{q}_2 = \frac{2\pi}{a} (\hat{y}). \quad (8.70)$$

In a ‘one-mode’ approximation the lowest order reciprocal lattice vectors ($\vec{G} = n_1 \vec{q}_1 + n_2 \vec{q}_2$) correspond to $(n_1, n_2) = (1, 0), (0, 1)$ and $(-1, -1)$. Assuming the amplitudes (i.e., $\eta_{\vec{G}}$) are constant this lowest order set of vectors leads to the following approximation for n ,

$$n = n_o + \phi \left(\frac{1}{2} \cos \left(\frac{2q}{\sqrt{3}} y \right) - \cos(qx) \cos \left(\frac{q}{\sqrt{3}} y \right) \right), \quad (8.71)$$

where $q = (2\pi/a)(\sqrt{3}/2)$ and $-\eta_1 = -\eta_2 = \eta_3 = \phi/4$. Substitution of this form into the free energy and minimizing with respect to q gives $q_{eq} = \sqrt{3}/2$ and

$$F(q_{eq}, \phi, n_o) = \frac{B^\ell}{2} n_o^2 - t \frac{n_o^3}{3} + v \frac{n_o^4}{4} + \frac{3}{16} [\Delta B - n_o(2t - 3vn_o)] \phi^2 - \frac{1}{16} [t - 3vn_o] \phi^3 + \frac{45v}{512} \phi^4. \quad (8.72)$$

Minimizing F with respect to ϕ gives,

$$\phi_{tri} = \frac{4}{15v} \left(t - 3vn_o + \sqrt{t^2 - 15v\Delta B + 12n_ov(2t - 3vn_o)} \right) \quad (8.73)$$

The liquid has the same free energy as in the BCC case and the density at which the liquid and solid free energies are equal occurs when,

$$n_o = n^* = (t - 3\sqrt{185t^2 - 555v\Delta B/37})/3v \quad (8.74)$$

A two dimensional phase diagram of the liquid phase with the triangular phase is obtained by comparing the minimized free energy of the triangular (Eq. (8.72) and liquid (Eq. (8.68)) phases. An example of such a phase coexistence is shown in Fig. (8.12). As noted in the last section different solutions arise for

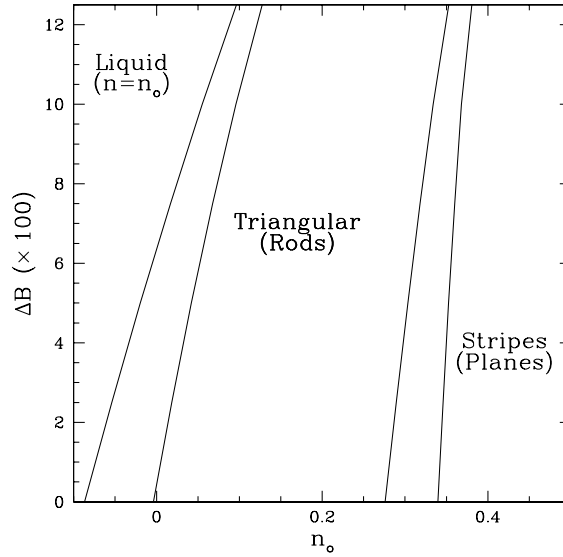


Figure 8.12: Sample phase diagram for a two dimensional system for $B^\ell = 1$. The labels indicate the equilibrium phases and the unlabeled regions are coexistence regions.

large values of n_o . Increasing n_o further gives rise to a striped phase and the coexistence of the stripes with the triangular phase should then be considered.

8.4.3 One dimensional planes

In one dimension the one mode approximation for n is simply

$$n = n_o + \phi \cos(qx) \quad (8.75)$$

Substitution of this form into the free energy leads gives and minimizing with respect to q gives $q_{eq} = 1$ and

$$F(q_{eq}, \phi, n_o) = \frac{B^\ell}{2} n_o^2 - t \frac{n_o^3}{3} + v \frac{n_o^4}{4} + \frac{1}{4} [\Delta B - n_o(2t - 3vn_o)] \phi^2 + v \frac{3}{32} \phi^4. \quad (8.76)$$

Minimizing Eq. (8.76) with respect to ϕ gives,

$$\phi_{eq} = 2\sqrt{-3v\Delta B + 3vn_o(2t - 3vn_o)}/3v \quad (8.77)$$

The liquid has the same free energy as in the BCC case and the density at which the liquid and solid free energies are equal occurs when,

$$n^* = (t - \sqrt{t^2 - 3v\Delta B})/3v \quad (8.78)$$

When the free energy of this state is compared with the 2D triangular rods and 3D BCC phases it is found that the 1d planes are the lowest energy state for large values of n_o and a coexistence between triangular rods and stripes can occur. This coexistence is also shown in Fig. (8.12). The complete phase diagram that includes all phases studied is shown in Fig. (8.13). A similar phase diagram of the original

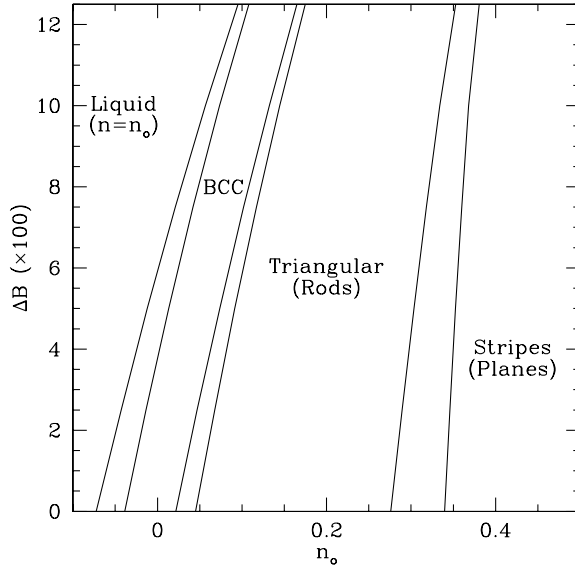


Figure 8.13: Sample phase diagram for a three dimensional system for $B^\ell = 1$. The labels indicate the equilibrium phases and the unlabeled regions are coexistence regions.

SH parameter set can be found in the thesis of Wu [212].

8.4.4 Elastic Constants of PFC Model

One of the motivations for studying a phase field model that resolves the atomic scale is that it natural contains elastic energy. In general the elastic energy contained in the free energy functional can be evaluated by considering an expansion around an unstrained state, i.e.,

$$n(\vec{r}) = n_{eq}(\vec{r} + \vec{u}) \quad (8.79)$$

where \vec{u} is a displacement vector and n_{eq} is an unstrained equilibrium state. The free energy can now be formally expanded in the strain tensor, $U_{ij} = (\partial u_i / \partial x_j + \partial u_j / \partial x_i) / 2$, i.e.,

$$F(n_{eq}(\vec{r} + \vec{u})) = \frac{1}{V} \int_V d\vec{r} \left[f_{eq} + \left(\frac{\partial f}{\partial U_{ij}} \right)_{eq} U_{ij} + \frac{1}{2} \left(\frac{\partial^2 f}{\partial U_{kl} \partial U_{ij}} \right)_{eq} U_{kl} U_{ij} + \dots \right] \quad (8.80)$$

where the Einstein summation convention over like indices has been adopted and f for the example free energy given in Eq. (8.51) is $f \equiv B^\ell n^2/2 + B^x/2n(2\nabla^2 + \nabla^4)n - n^3/6 + n^4/12$. By definition f_{eq} is a minimum at n_{eq} thus

$$\left(\frac{\partial f}{\partial U_{ij}} \right)_{eq} = 0. \quad (8.81)$$

This leads to the following result,

$$\Delta F = \frac{1}{V} \int_V d\vec{r} \left[\frac{1}{2} \left(\frac{\partial^2 f}{\partial U_{kl} \partial U_{ij}} \right)_{eq} U_{kl} U_{ij} + \dots \right] \quad (8.82)$$

where $\Delta F \equiv F(n_{eq}(\vec{r} + \vec{u})) - F(n_{eq}(\vec{r}))$ is the increase in energy due to the deformation. This implies that the elastic constants can be formally written,

$$K_{ijkl} = \frac{1}{V} \int_V d\vec{r} \left(\frac{\partial^2 f}{\partial U_{ij} \partial U_{kl}} \right)_{eq}. \quad (8.83)$$

and in turn that the elastic constants will automatically have the symmetry of the equilibrium state. To evaluate the coefficients for a specific crystalline system the most convenient representation is the amplitude expansion, i.e, Eg. (8.54). In this representation deformations of lattice are represented by $\eta_{\vec{G}} \rightarrow \eta_{eq} \exp(i\vec{G} \cdot \vec{u})$, where \vec{u} is the displacement vector. Details of these calculations will be given in Section (8.6).

8.5 PFC Dynamics

The dynamics of the dimensionless number density difference, n , is assumed to be dissipative and driven to minimize the free energy functional. Since n is a conserved field one would expect the dynamics to obey the following equation of motion

$$\frac{\partial n}{\partial t} = \Gamma \nabla^2 \frac{\delta F}{\delta n} + \eta = \Gamma \nabla^2 [(B^\ell + B^x (2\nabla^2 + \nabla^4)) n - tn^2 + vn^3] + \eta. \quad (8.84)$$

A more detailed derivation of this equation can be obtained using Poisson bracket relationships as discussed in general by Chaiken and Lubinsky [43] and specifically by Majaniemi and Grant [147] and Khachatryan [117]. These calculations imply that the dynamics are more accurately written as

$$\frac{\partial^2 \rho}{\partial t^2} + \beta \frac{\partial \rho}{\partial t} = \vec{\nabla} \rho \cdot \vec{\nabla} \frac{\delta F}{\delta n} + \zeta \quad (8.85)$$

where β is a friction coefficient and ζ is a Gaussianly correct random noise term. This form was first proposed by Stefanovic, Haataja and Provatas [188]. The form without the inertial term (second order time derivative) was proposed by Evans [71] and Archer [11]. Equation (8.85) can be reduced to

$$\frac{\partial^2 n}{\partial t^2} + \beta \frac{\partial n}{\partial t} = \frac{1}{k_B T V \rho_\ell^2} \vec{\nabla} (1+n) \cdot \vec{\nabla} [(B^\ell + B^x (2\nabla^2 + \nabla^4)) n - tn^2 + vn^3] + \frac{\zeta}{\rho_\ell} \quad (8.86)$$

or, simplifying for small n ,

$$\frac{1}{\beta} \frac{\partial^2 n}{\partial t^2} + \frac{\partial n}{\partial t} \approx \Gamma \nabla^2 [(B^\ell + B^x (2\nabla^2 + \nabla^4)) n - tn^2 + vn^3] + \eta \quad (8.87)$$

where

$$\Gamma \equiv \frac{1}{\beta k_B T V \rho_\ell^2}, \quad (8.88)$$

$$\langle \eta \rangle = 0 \text{ and } \langle \eta(\vec{r}_1, t_1) \eta(\vec{r}_2, t_2) \rangle = -2k_B T \rho_\ell \nabla^2 \delta(\vec{r}_1 - \vec{r}_2) \delta(t_1 - t_2).$$

Most of the calculations presented in next sections only consider the limit in which $\beta \rightarrow \infty$, i.e.,

$$\frac{\partial n}{\partial t} \approx \Gamma \nabla^2 [(B^\ell + B^x (2\nabla^2 + \nabla^4)) n - tn^2 + vn^3] + \eta \quad (8.89)$$

A full treatment of the computational subtleties of the extra second order time derivative in Eq. (8.87) is beyond the scope of this book.

8.5.1 Vacancy Diffusion

Consider a perfect lattice with one ‘atom’ taken out. On atomic length and time scales the vacancy created by the missing atom will jump from site to site and eventually diffuse throughout the lattice. In the PFC model the density at the vacancy slowly fills in and the density at neighbouring sites slowly decreases as the vacancy diffuses throughout the lattice. A simulation of the PFC for this phenomena is shown in Fig. (8.14). To highlight the diffusion of the vacancy, the configurations shown have been

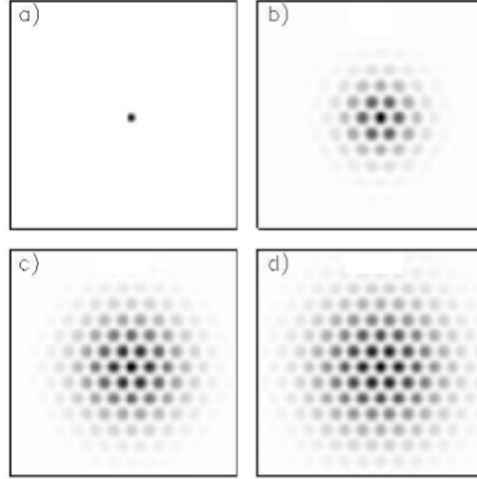


Figure 8.14: Vacancy diffusion. In this figure the grey scale corresponds to $\rho(x, y, t) - \rho_{eq}(x, y)$, where $\rho(x, y, 0)$ corresponded to $\rho_{eq}(x, y)$ with one ‘atom’ missing.

subtracted from a perfect lattice.

To determine the time scales for vacancy diffusion it is useful to perform a Floquet analysis or a linear stability analysis around a periodic state (as was done for the Swift-Hohenberg Equation). The two dimensional state equilibrium state can be written in the usual manner, i.e.,

$$n_{eq} = n_o + \sum \eta_j e^{i\vec{G}_j \cdot \vec{r}} + c.c. \quad (8.90)$$

where \vec{G}_j are the reciprocal lattice vectors for the equilibrium state and η_j is complex amplitudes associated with wave mode j . The field n is now perturbed around a equilibrium crystal phase (n_{eq}), such that $n = n_{eq} + \delta n$, and in turn the PFC model to order δn becomes,

$$\frac{\partial \delta n}{\partial t} = \Gamma \nabla^2 [B^\ell + B^x (2\nabla^2 + \nabla^4) - 2tn_{eq} + 3vn_{eq}^2] \delta n. \quad (8.91)$$

The perturbation can be written as,

$$\delta n = \sum_j B_j(t) e^{i(\vec{G}_j + \vec{Q}) \cdot \vec{r}} + \text{c.c.} \quad (8.92)$$

It turns out that the largest eigenvalue can be obtained by keeping by the $j = 0$ term, i.e., $\delta n = B_0 e^{i\vec{Q} \cdot \vec{r}} + \text{c.c.}$. Substitution of δn into Eq. (8.91) and average over the unit cell gives

$$\begin{aligned} \frac{dB_0}{dt} &= -\Gamma Q^2 \left(B^\ell - 2tn_o + 3vn_o^2 + 3v \sum |\eta_j|^2 + B^x (-2Q^2 + Q^4) \right) B_0 \\ &\approx -\Gamma Q^2 \left(B^\ell - 2tn_o + 3vn_o^2 + 3v \sum |\eta_j|^2 \right) B_0, \end{aligned} \quad (8.93)$$

where a one mode approximation was assumed for the amplitudes and a small Q expansion was made to arrive at the last line. Since a diffusion equation has the form $dc/dt = D_v \nabla^2 c$ (or $dc/dt = -D_v Q^2 c$ in fourier space), the diffusion constant can be immediately written down and is

$$D_v = \Gamma \left(B^\ell - 2tn_o + 3vn_o^2 + 3v \sum |\eta_j|^2 \right), \quad (8.94)$$

For a BCC state in a one mode approximation $\sum |\eta_j|^2 = 6|\eta_1|^2 = 3\phi_{bcc}^2/8$, where ϕ_{bcc} is given in Eq. (8.67). Similarly for the two dimensional triangular state $\sum |\eta_j|^2 = 3|\eta_1|^2 = 3\phi_{tri}^2/16$, where ϕ_{tri} is given in Eq. (8.73).

For a comparison with molecular dynamics simulations it is useful to consider the number of time steps needed to simulate some characteristic scale such as the time needed for a vacancy to diffuse one lattice space, i.e.,

$$\tau_D = a^2/D_v. \quad (8.95)$$

Numerically it takes roughly 500 to 1000 time steps to simulate one diffusion time using the PFC model. In MD simulations the time step is roughly a femto second ($10^{-15}s$). In the table below the number of time steps needed to simulate one diffusion time in MD simulations of Gold and Copper is shown for several temperatures. The number of time steps varies from 10^9 to 10^{11} implying that PFC is from 10^6 to 10^8 times faster. While this is a great advantage (and in fact the reason for using this approach) it is important to note that the dynamics are inappropriate in some instances. For example in brittle fracture, cracks tips move at velocities similar to the speed of sound, clearly much faster than diffusive time scales. In constrast at low temperatures the vacancy diffusion time may be years or decades, many times slower than the time scale for a particular experimental measurement or material process. Several extension of to the dynamics have been conducted to address both issues by adding higher order time derivatives in the former case [188] and by introducing an energy cost for vacancies to dissapper [46]. In addition in a study of solidification in colloidal systems other dynamical forms that are more faithful to dynamic

density functional theory were examined [198].

Material	Temperature	Diffusion time	# MD steps	
Copper	650°C	0.20 ms	$\sim 10^{11}$	
($T_{\text{melt}} = 1083^\circ\text{C}$)	850°C	2.51 μs	$\sim 10^9$	
	1030°C	0.23 μs	$\sim 10^8$	(8.96)
Gold	800°C	0.26 ms	$\sim 10^{11}$	
($T_{\text{melt}} = 1063^\circ\text{C}$)	900°C	33.2 μs	$\sim 10^{10}$	
	1020°C	5.53 μs	$\sim 10^9$	

8.6 Multi-scale Modeling: Amplitude Expansions (Optional)

In Section (8.4) the dimensionless number density field was expanded in terms of the amplitudes (or complex order parameters) of the periodic structure of interest (i.e., BCC in Section (8.4.1) and hexagonal in Section (8.4.2)). The calculations performed in those sections assume that the amplitude of each mode was constant (e.g., $|\eta_{\vec{G}}(\vec{r})| = \phi/4$). This approximation is quite reasonable in an equilibrium state and can be exploited to calculate phase diagrams and elastic constants. However, much more information can be retained if the amplitudes are allowed to vary in both space and time. As studied previously, liquid/solid interfaces can be described by a scalar amplitude (or order parameter) that is finite in the solid phase and decreases continuously to zero in the liquid phase as depicted in Fig. (8.15). Similarly a dislocation can be modeled by a rapid change in the amplitude.

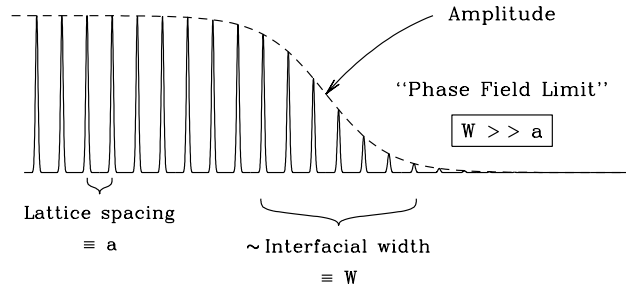


Figure 8.15: Schematic of liquid solid interface. In this figure the solid line corresponds to the number density profile and the dashed line to the amplitude of this profile.

A simple change in the magnitude of a scalar amplitudes does not, however, capture the local deformations in the lattice that give rise to long range elastic fields associated with dislocations. In traditional continuum elasticity theory, this lattice distortion is represented by a displacement field (\vec{u}) that describes the distance an atom is from some idea equilibrium lattice position. In the amplitude description this displacement can be reconstructed by allowing the amplitudes to be complex. Complex numbers can be written $\sim \phi e^{i\theta}$, where the spatial dependence of the phase ($\theta = \vec{G} \cdot \vec{u}$) can allow for local displacements as will be highlighted in the next few pages.

A key question to be addressed is how can equations of motion for the complex amplitudes be systematically constructed? For the PFC model, Goldenfeld *et al.* [78, 79] have published a number of papers that discuss various methods (so-called “quick and dirty”, renormalization group and multiple scales

analysis) for answering this question. While the mathematics behind these calculations can be lengthy, the basic physical assumptions and ideas underlying these calculations is relatively straightforward. To begin the calculations the number density field is represented in the usual fashion, i.e.,

$$n = \sum_{\vec{G}} \left(\eta_{\vec{G}} \exp \left[i\vec{G} \cdot \vec{r} \right] + \eta_{\vec{G}}^* \exp \left[-i\vec{G} \cdot \vec{r} \right] \right) \quad (8.97)$$

where $\eta_{\vec{G}}$ is a complex variable that is assumed to vary on length scales much larger than the density field itself as depicted in Fig. (8.15). Next consider substituting Eq. (8.97) into the PFC model (Eq. (8.89)), multiplying both sides of the resulting equation by $\exp[-i\vec{G} \cdot \vec{r}]$ and integrating over a unit cell. Schematically this is depicted in one dimension as

$$\int_x^{x+a} dx e^{-iGx} \frac{\partial n}{\partial t} = \dots \quad (8.98)$$

This integration can only be performed if it is assumed that $\eta_{\vec{G}}$ is constant over the integration range (i.e., from x to $x+a$). This is the essential approximation that assumes the existence of two well separated length scales; a “fast” length scale associated with rapid variations on the atomic scales (i.e., a in Fig. (8.15)) and a “slow” length scale associated with variations of the amplitude around interfaces (i.e., W in Fig. (8.15)) and dislocations. In some sense this multiple-scales approximation ($W \gg a$) can be thought of as the ‘phase field limit’, since traditional phase field models implicitly assume interfaces are much larger than atomic spacing, as discussed in previous chapters. For the PFC model this limit is equivalent to the limit in which $(B_0^\ell - B_0^x)/B_0^x$ (or ϵ in the Swift-Hohenberg equation) goes to zero. For a detailed discussion of the various formal perturbation theories dealing with this issues, the reader is referred to references [54, 78, 80, 79].

Despite the complexities of constructing a formal perturbation theory to justify multiple-scales expansion it is relatively straightforward to derive equations for the amplitudes that incorporates the essential physics of crystallization, elasticity and plasticity. Considering that the PFC equation is itself a relatively poor approximation to classical DFT, it is perhaps not that important to develop amplitude models that are accurate descriptions of the PFC model. From this point of view, equations of motion for the amplitudes can be thought of as fundamentally motivated phenomenological models in themselves. In the following few pages a simple derivation of amplitude equations will be presented.

When Eq. (8.97) is directly substituted in Eq. (8.89) the following expression is obtained,

$$\begin{aligned} \sum_j e^{i\vec{G}_j \cdot \vec{r}} \frac{\partial \eta_j}{\partial t} + c.c. &= \sum_j e^{i\vec{G}_j \cdot \vec{r}} \mathcal{L}_j [B^\ell + B^x(2\mathcal{L}_j + \mathcal{L}_j^2)] \eta_j + c.c. \\ &- t \sum_{j,k} \left[e^{i(\vec{G}_j + \vec{G}_k) \cdot \vec{r}} \mathcal{L}_{i+j} \eta_j \eta_k + e^{i(-\vec{G}_j + \vec{G}_k) \cdot \vec{r}} \mathcal{L}_{-i+j} \eta_j^* \eta_k + c.c. \right] \\ &+ v \sum_{j,k,l} \left[e^{i(\vec{G}_j + \vec{G}_k + \vec{G}_l) \cdot \vec{r}} \mathcal{L}_{j+k+l} \eta_j \eta_k \eta_l + e^{i(\vec{G}_j + \vec{G}_k - \vec{G}_l) \cdot \vec{r}} \mathcal{L}_{j+k-l} \eta_j \eta_k \eta_l^* \right. \\ &\left. + e^{i(\vec{G}_j - \vec{G}_k + \vec{G}_l) \cdot \vec{r}} \mathcal{L}_{j-k+l} \eta_j \eta_k^* \eta_l + e^{i(-\vec{G}_j + \vec{G}_k + \vec{G}_l) \cdot \vec{r}} \mathcal{L}_{-j+k+l} \eta_j^* \eta_k \eta_l \right. \\ &\left. + c.c. \right] \end{aligned} \quad (8.99)$$

where \mathcal{L} is an operator such that $\mathcal{L}_j \equiv -G_j^2 + 2i\vec{G}_j \cdot \vec{\nabla} + \nabla^2$ and the notation is such that $\mathcal{L}_{j+k} \equiv -|\vec{G}_j + \vec{G}_k|^2 + 2i(\vec{G}_j + \vec{G}_k) \cdot \vec{\nabla} + \nabla^2$ or $\mathcal{L}_{j-k} \equiv -|\vec{G}_j - \vec{G}_k|^2 + 2i(\vec{G}_j - \vec{G}_k) \cdot \vec{\nabla} + \nabla^2$, etc.. For convenience

the subscript j has been used to represent a given reciprocal lattice vector. It will be useful in what follows to note that the operator $2\mathcal{L}_j + \mathcal{L}_j^2$ that appears in the linear term reduces in a one-mode approximation to

$$2\mathcal{L}_j + \mathcal{L}_j^2 = (-1 + \mathcal{G}_j)(2 - 1 + \mathcal{G}_j) = -1 + \mathcal{G}_j^2 \quad (8.100)$$

where $\mathcal{G} \equiv \nabla^2 + 2i\vec{G}_j \cdot \vec{\nabla}$ and in dimensionless units $|\vec{G}_j| = 1$. Multiplying Eq. (8.99) by $\int d\vec{r} \exp[-i\vec{G}_m \cdot \vec{r}]$ and integrating over one unit cell in the limit $W \gg a$ gives,

$$\begin{aligned} \frac{\partial \eta_m}{\partial t} = & (-1 + \mathcal{G}_m) \left\{ [\Delta B + B^x \mathcal{G}_m^2] \eta_m - t \sum_{j,k} [\delta_{m,j+k} \eta_j \eta_k + \delta_{m,-j+k} \eta_j^* \eta_k + c.c.] \right. \\ & \left. + v \sum_{j,k,l} [\delta_{m,j+k+l} \eta_j \eta_k \eta_l + \delta_{m,j+k-l} \eta_j \eta_k \eta_l^* + \delta_{m,j-k+l} \eta_j \eta_k^* \eta_l + \delta_{m,j-k+l} \eta_j^* \eta_k \eta_l + c.c.] \right\} \end{aligned} \quad (8.101)$$

where, $\Delta B \equiv B^\ell - B^x$ and the delta functions in the above expression are actually Kronecker delta functions for reciprocal lattice vectors, i.e.,

$$\delta_{m,j+k+l} \equiv \begin{cases} 0 & \vec{G}_m \neq \vec{G}_j + \vec{G}_k + \vec{G}_l \\ 1 & \vec{G}_m = \vec{G}_j + \vec{G}_k + \vec{G}_l \end{cases} \quad (8.102)$$

and $\delta_{m,j}^* = \delta_{m,-j}$, etc.. To continue the discussion a set of reciprocal lattice vectors must be specified. In the following several subsections reciprocal lattice vectors in one, two and three dimensional cases are considered.

8.6.1 One dimensions

In one dimension it is sufficient to make $\vec{G} = 1$ (in dimensionless units), i.e.,

$$n = \eta(x, t) e^{ix} + \eta^*(x, t) e^{-ix}, \quad (8.103)$$

and thus Eq. (8.101) reduces to

$$\frac{\partial \eta}{\partial t} = (-1 + \mathcal{G}) \frac{\delta \mathcal{F}_{1d}}{\delta \eta^*} = (-1 + \mathcal{G}) \{ [\Delta B + B^x \mathcal{G}^2] \eta + 3v |\eta|^2 \eta \} \quad (8.104)$$

where $\mathcal{G} \equiv \partial_x^2 + 2i\partial_x$, and

$$\mathcal{F}_{1d} = \int dx [\Delta B |\eta|^2 + B^x |\mathcal{G}\eta|^2 + 3v |\eta|^4 / 2]. \quad (8.105)$$

To gain more insight into this result it is useful to consider a small deformation, i.e., $\rho(\vec{r}) \rightarrow \rho(\vec{r} + \vec{u})$ or in terms of the amplitude,

$$\eta = \phi \exp[i\vec{G} \cdot \vec{u}]. \quad (8.106)$$

Substituting this expression into Eq. (8.105) and expanding to the lowest order gradients in ϕ and u gives,

$$\mathcal{F}_{1d} = 2 \int dx \left[\frac{\Delta B}{2} \phi^2 + \frac{3v}{4} \phi^4 + 2B^x \left| \frac{\partial \phi}{\partial x} \right|^2 + 2B^x \phi^2 U_{xx}^2 + \dots \right] \quad (8.107)$$

where U_{xx} is the linear strain tensor (i.e., $U_{xx} = \partial u_x / \partial x$) and “...” represents higher order derivatives. The result is quite interesting, the first three terms are identical in form to Model A and the last term is the just the linear elastic energy. Essentially this model describes a phase transition with elasticity. The elastic constant is proportional to ϕ so that elastic energy self-consistently disappears in the liquid state which is defined to be $\phi = 0$.

Before continuing to higher dimensions it should be noted that the approximation given in Eq. (8.103) does not allow for the average value of n to vary in space. This approximation does not allow for coexistence between liquid and crystal phases over a range of average densities, i.e., there is no miscibility gap or volume expansion upon melting. This feature can be taken into account as shown in one-dimensions by Matthews and Cox [149] for the conserved SH equation and by Yeon *et al.* [217] for the PFC model in two and three dimensions. For these calculations the field n is written,

$$n = n_o(x, t) + \eta(x, t)e^{ix} + \eta^*(x, t)e^{-ix}, \quad (8.108)$$

where now both η and n_o are “slow” variables in space, i.e., it is assumed that they both vary on length scales much larger than the atomic spacing. Substitution of this expression into Eq. (8.89) gives and integrating over $e^{-iq_o x}$ gives;

$$\frac{\partial \eta}{\partial t} = (-1 + \mathcal{G}) [B^\ell + B^x \mathcal{G}^2 - 2tn_o + 3vn_o^2 + 3v|\eta|^2] \eta = (-1 + \mathcal{G}) \frac{\delta F'}{\delta \eta^*} \quad (8.109)$$

and over 1 gives ⁴

$$\frac{\partial n_o}{\partial t} = \Gamma \nabla^2 [(B^\ell + B^x(2\nabla^2 + \nabla^4) + 6v|\eta|^2) n_o - tn_o^2 + vn_o^3 - 2t|\eta|^2] = \nabla^2 \frac{\delta F'}{\delta n_o} \quad (8.110)$$

The effective free energy functional F' appearing in Eqs. (8.109) and (8.110) is given by

$$F' = \int dx \left[\left(\Delta B |\eta|^2 + B^x |\mathcal{G}\eta|^2 + \frac{3v}{2} |\eta|^4 \right) - n_o(2t - 3vn_o) |\eta|^2 + \left(n_o \frac{G_{n_o}}{2} n_o - t \frac{n_o^3}{3} + v \frac{n_o^4}{4} \right) \right] \quad (8.111)$$

and $G_{n_o} \equiv B^\ell + B^x(2\nabla^2 + \nabla^4)$. In long wavelength limit it is possible to replace $-1 + \mathcal{G}$ with -1 in Eq. (8.109) and G_{n_o} by B^ℓ as is discussed in some detail by Yeon *et al.* [217].

8.6.2 Two Dimensions

In two dimensions the equilibrium state of the PFC model is triangular and the principle reciprocal lattice are vectors are

$$\vec{q}_1 = -\frac{1}{2} (\sqrt{3}\hat{x} + \hat{y}) \quad ; \quad \vec{q}_2 = \hat{y} \quad (8.112)$$

In a one mode approximation all the reciprocal lattice vectors (i.e., $\vec{G} = l\vec{q}_1 + m\vec{q}_2$) with length one must be included. The full one-mode set is then corresponds to $(l, m) = (1, 0), (0, 1), (-1, -1)$ and are depicted in Fig. (8.16). For this two dimensional system the atomic density field n becomes,

⁴Think of this like e^{iGx} where $G = 0$ is the wave vector associated with the density change, which aries on long wavelengths.

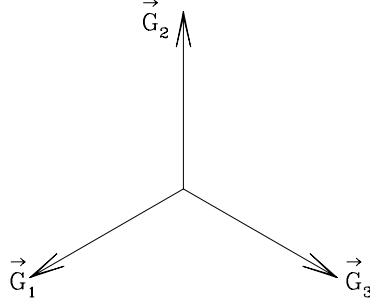


Figure 8.16: Reciprocal lattices vectors for one mode approximation to triangular lattice.

$$n = \sum_{j=1}^{j=3} \eta_j(\vec{r}, t) e^{i\vec{G}_j \cdot \vec{r}} + \sum_{j=1}^{j=3} \eta_j^*(\vec{r}, t) e^{-i\vec{G}_j \cdot \vec{r}}. \quad (8.113)$$

Repeating the steps outlined in the preceding section then gives,

$$\frac{\partial \eta_j}{\partial t} = (\mathcal{G}_j - 1) \frac{\delta \mathcal{F}_{2d}}{\delta \eta_j^*} = (\mathcal{G}_j - 1) \left[(\Delta B + B^x (\mathcal{G}_j)^2 + 3v (A^2 - |\eta_j|^2)) \eta_j - 2t \prod_{i \neq j} \eta_i^* \right] \quad (8.114)$$

where, $\mathcal{G}_j \equiv \nabla^2 + 2i\vec{G}_j \cdot \vec{\nabla}$ and

$$\mathcal{F}_{2d} = \int d\vec{r} \left[\frac{\Delta B}{2} A^2 + \frac{3v}{4} A^4 + \sum_{j=1}^3 \left\{ B^x |\mathcal{G}_j \eta_j|^2 - \frac{3v}{2} |\eta_j|^4 \right\} - 2t \left(\prod_{j=1}^3 \eta_j + \text{c.c.} \right) \right] \quad (8.115)$$

with the representation $A^2 \equiv \sum_i |\eta_i|^2$. Again, it turns out that the approximation $(\mathcal{G}_j - 1) \rightarrow -1$ can be made in Eq. (8.114)

As in the one dimensional case, it is interesting to consider a small deformation, which is represented in the complex amplitude by $\eta_j \equiv \phi \exp(i\vec{G}_j \cdot \vec{u})$. Substitution of this expression in Eq. (8.114) gives in the long wavelength limit,

$$\mathcal{F}_{2d} \approx \int d\vec{r} \left[3\Delta B \phi^2 - 4t\phi^3 + \frac{45}{2} v \phi^4 + 6B^x |\vec{\nabla} \phi|^2 + 3B^x \left\{ \sum_{i=1}^2 \frac{3}{2} U_{ii}^2 + U_{xx} U_{yy} + 2U_{xy}^2 \right\} \phi^2 \right] \quad (8.116)$$

where $U_{ij} \equiv (\partial_j u_i + \partial_i u_j)/2$ is the linear strain tensor. The first three terms in \mathcal{F}_{2d} describe a double-well potential with an odd term to generate a tilt between the wells. This leads to a first order phase transition from a liquid state ($\phi = 0$) at large ΔB to a crystalline phase ($\phi \neq 0$) at low or negative ΔB . This is precisely analogous to the phase field free energy functional that was discussed in section (2.2.5). The fourth term is the usual surface energy contribution that appears in nearly all traditional phase field

models. The last set of terms are the elastic energy (which as before is negligible in the liquid state). Written in this form the independent elastic constant can be immediately read off (see for example reference [134], pages 32 to 35) and are $C_{11} = 9B^x\phi^2$, $C_{12} = C_{44} = C_{11}/3$. As in the one dimensional case, this calculation can be extended to include a miscibility gap in the density field [217].

8.6.3 Three Dimensions

In three dimensions the equilibrium crystal state of the PFC model has BCC symmetry, for small undercooling. For large undercooling FCC and HCP symmetries are possible [106]. For BCC crystals the principle reciprocal lattice vectors are

$$\vec{q}_1 = (\hat{x} + \hat{y})/\sqrt{2} ; \quad \vec{q}_2 = (\hat{x} + \hat{z})\sqrt{2} ; \quad \vec{q}_3 = (\hat{y} + \hat{z})\sqrt{2} \quad (8.117)$$

In a one mode approximation the lowest order reciprocal lattice vectors ($\vec{G} = l\vec{q}_1 + m\vec{q}_2 + n\vec{q}_3$) correspond to $(l, m, n) = (1, 0, 0), (0, 1, 0), (0, 0, 1), (1, -1, 0), (0, 1, -1), (-1, 0, 1)$ or

$$\begin{aligned} \vec{G}_1 &= (\hat{x} + \hat{y})/\sqrt{2}, & \vec{G}_2 &= (\hat{x} + \hat{z})/\sqrt{2}, & \vec{G}_3 &= (\hat{y} + \hat{z})/\sqrt{2}, \\ \vec{G}_4 &= (\hat{y} - \hat{z})/\sqrt{2}, & \vec{G}_5 &= (\hat{x} - \hat{y})/\sqrt{2}, & \vec{G}_6 &= (\hat{z} - \hat{x})/\sqrt{2}. \end{aligned} \quad (8.118)$$

Substitution of n into the equation of motion and integrating as before then gives,

$$\frac{\partial\eta_1}{\partial t} = (\mathcal{G}_1 - 1) [(\Delta B + B^x\mathcal{G}_1^2 + 3v(A^2 - |\eta_1|^2))\eta_1 - 2t(\eta_3\eta_6^* + \eta_2\eta_4) + 6v(\eta_3\eta_4\eta_5 + \eta_2\eta_5^*\eta_6^*)] \quad (8.119)$$

$$\frac{\partial\eta_4}{\partial t} = (\mathcal{G}_4 - 1) [(\Delta B + B^x\mathcal{G}_4^2 + 3v(A^2 - |\eta_4|^2))\eta_4 - 2t(\eta_5^*\eta_6^* + \eta_1\eta_2^*) + 6v(\eta_1\eta_3^*\eta_5^* + \eta_3\eta_2^*\eta_6^*)] \quad (8.120)$$

where the equations of motion for η_2 and η_3 are obtained by cyclic permutations on the groups (1,2,3) and (4,5,6) from Eq. (8.119). Similarly equations for η_5 and η_6 can be obtained by cyclic permutations of Eq. (8.120). As with the one and two dimensional cases these equations can be written in the form,

$$\frac{\partial\eta_j}{\partial t} = (\mathcal{G}_j - 1) \frac{\delta\mathcal{F}_{3d}}{\delta\eta_j^*} \quad (8.121)$$

where

$$\begin{aligned} \mathcal{F}_{3d} &= \int d\vec{r} \left[\frac{\Delta B}{2} A^2 + \frac{3v}{4} A^4 + \sum_{j=1}^3 \left\{ B^x |\mathcal{G}_j \eta_j|^2 - \frac{3v}{2} |\eta_j|^4 \right\} \right. \\ &\quad + 6v (\eta_1\eta_3^*\eta_4^*\eta_5^* + \eta_2\eta_1^*\eta_5^*\eta_6^* + \eta_3\eta_2^*\eta_6^*\eta_4^* + \text{C.C.}) \\ &\quad \left. - 2t (\eta_1^*\eta_2\eta_4 + \eta_2^*\eta_3\eta_5 + \eta_3^*\eta_1\eta_6 + \text{C.C.}) \right] \end{aligned} \quad (8.122)$$

In the small deformation and long wavelength limit this reduces to

$$\begin{aligned} \mathcal{F}_{3d} &\approx \int d\vec{r} \left[6\Delta B\phi^2 - 16t\phi^3 + 135v\phi^4 + 8B^x |\vec{\nabla}\phi|^2 \right. \\ &\quad \left. + 4B^x \left\{ \left(\sum_{i=1}^3 U_{ii}^2 + \frac{1}{2} \sum_{j \neq i} U_{ii} U_{jj} \right) + 2 \sum_{i=1}^4 U_{ii}^2 \right\} \phi^2 \right]. \end{aligned} \quad (8.123)$$

This free energy is essentially equivalent to the two dimensional case except for the coefficients. The three elastic constants for this model are then $C_{11} = 8B^x\phi^2$, $C_{12} = C_{44} = C_{11}/2$ as expected for a BCC lattice.

8.6.4 Rotational Invariance

While all the equations derived for the amplitudes are rotationally invariant, trouble will arise if two angles are used to describe the same crystal orientation. For a better understanding of this it is useful to consider a simple rotation of the two dimensional system as depicted in Fig. (8.17). To describe this

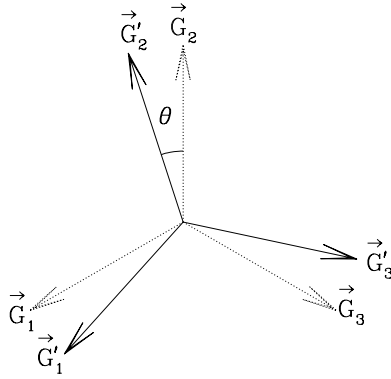


Figure 8.17: Reciprocal lattices vectors for one mode approximation to triangular lattice under rotation.

rotation the amplitudes would be transformed as,

$$\eta_j \rightarrow \eta_j \exp(i \delta \vec{G}_j \cdot \vec{r}), \quad (8.124)$$

where $\delta \vec{G}_j \equiv \vec{G}'_j - \vec{G}_j$ and $\vec{G}'_j = (G_j^x \cos(\theta) - G_j^y \sin(\theta))\hat{x} + (G_j^x \sin(\theta) + G_j^y \cos(\theta))\hat{y}$. When Eq.(8.124) is substituted into Eq. (8.115) it is easy to show that all dependence on θ disappears. As expected the free energy is invariant under rotation. However there is a problem when two ‘identical crystals’ impinge on one another. Consider for example a rotation of $\pi/6$ for the two dimensional reciprocal lattice set which turns $\vec{G}'_1 \rightarrow -\vec{G}_2$, $\eta_1 \rightarrow \eta_2^*$ and similarly for other modes. Under the rotation the exact same crystal structure is represented as for $\theta = 0$. However, for $\theta = 0$ the amplitudes are constant, while for $\theta = \pi/6$ the amplitudes are oscillating in space according to Eq. (8.124). If these two crystal come into contact a domain wall with forms between them since the amplitudes are not constant across the interface. Clearly a domain wall between two identical crystals is unphysical. Thus when using the amplitude expansions for the two dimensional case the condition $-\pi/6 < \theta < \pi/6$ must be maintained. Similar care must be taken when considering the three dimensional BCC amplitude equations. Curiously, this limitation is similar to that encountered in all multi-phase field models where separate scalar order parameters are associated with each rotation.

8.7 Parameter fitting

The approximations used in the derivation of PFC from CDFT are extremely crude and lead to a model that is not a good approximation of classical DFT. From a computational point of view this is a good thing since CDFT solutions for n are sharply peaked at each lattice sites and may require on the order of $\sim 100^d$ mesh points (where d is dimension) to resolve. In contrast, solutions of the PFC are much smoother and require on the order of $\sim 10^d$ mesh points which leads to a significant computational saving. Unfortunately the PFC model as derived from CDFT (i.e., Eq. 8.51 with $t = 1/2$ and $v = 1/3$) gives poor predictions for many physical quantities. This leads to an important questions: Can parameters for the PFC model be chosen such that n is smooth and reasonable predictions are made for key physical quantities such as the liquid/solid surface energy and anisotropy, liquid and solid elastic moduli, magnitude of volume expansion upon melting, etc..

At the time of writing this text, the only metallic system that has been studied in some detail is Fe. The first study was initiated by Wu and Karma [213]. In their study the authors fit the width, height and position of the first peak in $\hat{C}(k)$ to predict B^ℓ , B^x and R (although in a different notation) and the parameters t and v were chosen to match the amplitude (ϕ) of the density fluctuations of molecular dynamics studies and to ensure the liquid and solid phases have the same energy at coexistence. This scheme did quite well to predict the liquid/solid surface energy and anisotropy. Unfortunately predictions for the elastic moduli, volume expansion upon melting and the isothermal compressibility of the liquid phase were not very accurate. The main difficulty lies in simultaneously fitting the first peak in \hat{C}_k and \hat{C}_0 using only three parameters. In a later study Jaatinen *et al.* [105] added one more parameter to the PFC free energy so that both the first peak and $k = 0$ mode of \hat{C}_k were fit reasonably well. By adding this one extra parameter the models predictions for the volume expansion of upon melting, the bulk moduli of liquid and solid phases and as before the liquid/solid surface energy and anisotropy, closely match experimental numbers. Whether the general procedure outlined in this study will work for other metals/materials needs to be examined in more detail.

In another study, an examination of the velocity of solidifying front in a colloidal system was examined by van Teeffeen *et al.* [198]. In this work the authors fit the peak of \hat{C}_k with the form $A + B(k^2 - (k^*)^2) + C(k^2 - (k^*)^2)^2$ where k^* is the peak position of the first peak in \hat{C}_k and scaled the total free energy by a constant. The authors found reasonable agreement between for the front velocity and classical dynamic density functional theory and also examined a dynamical model that is more faithful to dynamical density functional theory.

Chapter 9

Phase Field Crystal Modeling of Binary Alloys

This Chapter extends the ideas discussed in the previous Chapter and develops a PFC model for binary. As in section (8), the starting point is a classical density functional theory for a two-component mixture. This formal approach is used to motivate the origins of the alloy PFC model. As in the case of the pure materials, the formalism merely serves as a guide to assure that the correct basic physics is included in the underlying phenomenology that is subsequently developed. Following the derivation of the PFC alloy equations, alloy model's potential is demonstrated in a suite of applications.

9.1 A Two-Component PFC Model For Alloys

The free energy functional for a binary alloy to order C_2 can be written as the sum of the free energy functional for two pure systems plus a coupling term that introduces the direct correlation function between the two species that make up the alloy. More specifically the free energy functional of an alloy consisting of A and B atoms to order C_2 reads,

$$\frac{\mathcal{F}}{k_B T} = \frac{\mathcal{F}_A}{k_B T} + \frac{\mathcal{F}_B}{k_B T} - \int d\vec{r}_1 d\vec{r}_2 \delta\rho_A(\vec{r}_1) C_{AB}(\vec{r}_1, \vec{r}_2) \delta\rho_B(\vec{r}_2) + \dots \quad (9.1)$$

where C_{AB} is the direct two point correlation function between the A and B atoms, \mathcal{F}_A and \mathcal{F}_B are the free energy given by Eq. (8.48) and the $+\dots$ represent higher order A/B correlations. To make a connection with conventional phase field models of binary alloys (i.e., Models A, B, C ,....) it is useful to introduce a total density field, and concentration

$$\rho \equiv \rho_A + \rho_B \quad ; \quad c \equiv \rho_A / \rho, \quad (9.2)$$

such that $\rho_A = c\rho$ and $\rho_B = \rho(1 - c)$. The free energy given in Eq. (9.1) can now be written in terms of ρ and c , i.e.,

$$\begin{aligned} \frac{\mathcal{F}'}{k_B T} = & \int d\vec{r} \left[\rho \ln \frac{\rho}{\rho_l} - \delta\rho - \frac{\rho}{2} (c^2 C^{AA} + (1 - c)^2 C^{BB} + 2c(1 - c) C^{AB}) \rho + \rho [(1 - c) \ln(1 - c) + c \ln c] \right. \\ & \left. + \rho c \left((C^{AA} - C^{AB}) \rho_{lA} + (C^{AB} - C^{BB}) \rho_{lB} + \ln \frac{\rho_{lB}}{\rho_{lA}} \right) \right] \quad (9.3) \end{aligned}$$

where a new notation, C^{IJ} ($I, J = A, B$), has been introduced. In this notation, C^{IJ} is an operator that acts on the function immediately to its right. For example, $C^{IJ}\rho$ is written explicitly as

$$C^{IJ}\rho \equiv \int C_{IJ}(|\vec{r} - \vec{r}'|) \rho(\vec{r}') d\vec{r}' \quad (9.4)$$

In Eq. (9.3) $\rho_l \equiv \rho_{lA} + \rho_{lB}$ and ρ_{lA} , ρ_{lB} are the densities of the A and B atoms respectively in a reference liquid state and as in the pure case the series has been truncated at C_2 . In addition a constant ($A \equiv \int d\vec{r} \rho (\ln(\rho_l/\rho_{lB}) + C^{BB}\rho_{lB} + C^{AB}\rho_{lA}(1 - \rho_{lB})) - (C^{BB}\rho_{lB}^2 + C^{AA}\rho_{lA}^2)/2$) has been subtracted such that $\mathcal{F}' \equiv \mathcal{F} - k_B T A$

Before developing a simple model for simulating binary systems with elasticity, plasticity etc., it is instructive to consider two simple cases, one in which the density is constant (i.e., a liquid with $\rho = \rho_l$) and the other in which the concentration is constant in the solid phase. While these are obviously not the most general cases they offer some physical insight into the expansion.

9.1.1 Constant density approximation: liquid

Consider a liquid in which the density is approximately constant, i.e., $\rho = \rho_l$ (although setting $\rho = \rho_l$ is just for convenience it could be set to any constant density). In this case the interesting part of the free energy functional reduces to;

$$\frac{\mathcal{F}'}{k_B T \rho_l} \approx \int d\vec{r} \left[[(1-c)\ln(1-c) + c\ln c] - \frac{\rho_l}{2} \Delta C \delta c^2 + \left(\ln \frac{\rho_{lB}}{\rho_{lA}} - \frac{1}{2} (\rho_{lA} - \rho_{lB}) \Delta C \right) \delta c \right] \quad (9.5)$$

where $\delta c = c - 1/2$,

$$\Delta C \equiv C^{AA} + C^{BB} - 2C^{AB}. \quad (9.6)$$

and all terms not containing c or δc were dropped for simplicity. Next the direct correlation functions are expanded in the usual fashion in fourier space, i.e., $\hat{C}_{AA} = -\hat{C}_0^{AA} + \hat{C}_2^{AA} k^2 + \dots$ or more explicitly for ΔC ,

$$\Delta \hat{C} = -\Delta \hat{C}_0 - \Delta \hat{C}_2 k^2 + \dots \quad (9.7)$$

Note that in the above expansion it was explicitly assumed that $2\hat{C}_2^{AB} > \hat{C}_2^{AA} + \hat{C}_2^{BB}$. As will be seen this assumption is explicitly needed to ensure the gradient energy coefficient is positive. Substituting these expressions for ΔC and expanding to order δc^4 gives,

$$\frac{\Delta \mathcal{F}}{k_B T \rho_l} = \int d\vec{r} \left[\gamma \delta c + \omega \frac{\delta c^2}{2} + \frac{16}{3} \frac{\delta c^4}{4} + K \frac{|\vec{\nabla} \delta c|^2}{2} \right] \quad (9.8)$$

where $\Delta \mathcal{F}' = \mathcal{F}'(\delta c) - \mathcal{F}'(0)$, $\gamma \equiv \ln(\rho_{lB}/\rho_{lA}) + \Delta \hat{C}_0(\rho_{lA} - \rho_{lB})/2$, $\omega \equiv 4 + \rho_l \Delta \hat{C}_0$ and $K = \rho_l \Delta \hat{C}_2$. Equation (9.8) is the standard Cahn-Hilliard model (or Model B) of phase segregation, where the parameters that enter that model can be identified in terms of the liquid state correlation functions. More specifically the parameter that enters the quadratic term (ω) are the inverse isothermal compressibilities of the liquids not “interaction” potentials as normally identified. An interesting feature of this free energy is that the gradient energy coefficient can be negative. If this was the case higher order terms in the direct correlation functions would be required and may lead to sublattice ordering.

9.1.2 Constant concentration approximation: solid

If the concentration is constant then the model simplifies to the form,

$$\frac{\Delta\mathcal{F}}{k_B T} = \int d\vec{r} \left[\rho \ln \frac{\rho}{\rho_l} - \delta\rho \right] - \frac{1}{2!} \int d\vec{r}_1 d\vec{r}_2 C^e \delta\rho_1 \delta\rho_2 \quad (9.9)$$

where all terms linear in ρ have been included in $\Delta\mathcal{F}$ and the effective direct two point correlation function is given by

$$C^e = c^2 C^{AA} + (1-c)^2 C^{BB} + 2c(1-c)C^{AB}. \quad (9.10)$$

This free energy is identical to the free energy of a pure system (i.e., Eq. (8.48)) to order C_2 . Thus prediction made in earlier chapters for elastic, lattice and diffusion constants, can be immediately extended to include concentration, i.e., the concentration dependence of these constants can now be predicted. For example for a BCC lattice the equilibrium wavevector was $q_{eq} = 1/\sqrt{2}$ in dimensionless units, or $q_{eq} = 1/\sqrt{2}R$ which implies a lattice constant of $a_{eq} = 2\pi/q_{eq} = 2\sqrt{2}\pi R$, where $R \equiv (2\hat{C}_4/\hat{C}_2)^{1/2}$. The implication is that,

$$a_{eq}(c) = 2\sqrt{2}\pi \sqrt{2\hat{C}_4^e/\hat{C}_2^e} \quad (9.11)$$

where C^e has been expanded in fourier space as was before, i.e.,

$$\hat{C}^e = -\hat{C}_0^e + \hat{C}_2^e k^2 - \hat{C}_4^e k^4 + \dots \quad (9.12)$$

where $\hat{C}_n^e = c^2 \hat{C}_n^{AA} + (1-c)^2 \hat{C}_n^{BB} + c(1-c)\hat{C}_n^{AB}$. This implies the concentration dependence of the lattice constant can be written,

$$a_{eq}(c) = 4\pi \sqrt{\frac{c^2 \hat{C}_4^{AA} + (1-c)^2 \hat{C}_4^{BB} + 2c(1-c)\hat{C}_4^{AB}}{c^2 \hat{C}_2^{AA} + (1-c)^2 \hat{C}_2^{BB} + 2c(1-c)\hat{C}_2^{AB}}}. \quad (9.13)$$

Expanding around $c = 1/2$ gives,

$$a_{eq}(\delta c) = a_{eq}(0)(1 + \eta\delta c + \dots) \quad (9.14)$$

where η is the solute expansion coefficient given by

$$\eta = \frac{1}{2} \left(\frac{\delta \hat{C}_4}{\hat{C}_4} - \frac{\delta \hat{C}_2}{\hat{C}_2} \right), \quad (9.15)$$

where

$$\begin{aligned} \bar{C} &\equiv (C^{AA} + C^{BB} + 2C^{AB})/4 \\ \delta C &\equiv C^{AA} - C^{BB} \end{aligned} \quad (9.16)$$

such that $\hat{C}_n = (\hat{C}_n^{AA} + \hat{C}_n^{BB} + 2\hat{C}_n^{AB})/4$ and $\delta \hat{C}_n = \hat{C}_n^{AA} - \hat{C}_n^{BB}$. Similar calculations can be made for the elastic constants.

9.2 Simplification of Binary Model

In the preceding two sections some properties of a binary CDFT model (to order C_2) were examined in two specific limits. In the limit of constant density it was shown that the model naturally includes phase segregation, while in the limit of constant concentration it was shown that the model naturally includes the concentration dependence of the lattice and elastic constants and the liquid/solid phase transition. In this section a simplified binary PFC model that incorporates all these features (in addition to elasticity, plasticity, multiple crystal orientations) is presented. Similar to the simple PFC model of a pure system, the goal is to develop the simplest possible model that includes the correct physical features, not to reproduce CDFT.

The first step in the calculation is to expand the free energy given in Eq. 9.3 and around $\psi = 2c - 1$ and $n = (\rho - \rho_l)/\rho_l$. To further simplify the calculations it will be assumed that terms of order n^1 can be neglected since the average value of n (i.e. its integral over space) is zero. Additionally n is assumed to vary in space much more rapidly than c . In this limit the expansion to order ψ^4 and n^4 of Eq. (9.3) becomes,

$$\begin{aligned} \frac{\Delta\mathcal{F}}{k_B T \rho_l} &= \int d\vec{r} \left[\frac{n}{2} \left(1 - \rho_l \left(\bar{C} + \frac{\delta C}{2} \psi + \frac{\Delta C}{4} \psi^2 \right) \right) n - \frac{1}{6} n^3 + \frac{1}{12} n^4 \right. \\ &\quad \left. + \left(\ln \frac{\rho_{lB}}{\rho_{lA}} - \frac{1}{2} (\rho_{lA} - \rho_{lB}) \Delta C \right) \frac{\psi}{2} + \frac{\psi}{2} \left(1 - \rho_l \frac{\Delta C}{4} \right) \psi + \frac{1}{12} \psi^4 \right] \end{aligned} \quad (9.17)$$

where $\Delta\mathcal{F} \equiv \mathcal{F}(\psi, n) - \mathcal{F}(0, 0)$.

The next step is to expand the correlation functions (i.e., \bar{C} , ΔC and δC) in fourier space up to order k^4 , as was done for the pure material (see Eq. (8.50)). After some straightforward but tedious algebra, this reduces $\Delta\mathcal{F}$ to

$$\frac{\Delta\mathcal{F}}{k_B T \rho_l} = \int d\vec{r} \left[\frac{B^\ell}{2} n^2 + B^x \frac{n}{2} (2R^2 \nabla^2 + R^4 \nabla^4) n - \frac{t}{3} n^3 + \frac{v}{4} n^4 + \gamma \psi + \frac{\omega}{2} \psi^2 + \frac{u}{4} \psi^4 + \frac{K}{2} |\vec{\nabla} \psi|^2 \right] \quad (9.18)$$

where $t = 1/2$, $v = 1/3$ and

$$\begin{aligned} \tilde{C}_i &\equiv \hat{C}_i + \delta \hat{C}_i \psi / 2 + \Delta \hat{C}_i \psi^2 / 4 \\ \omega &\equiv 1 + \rho_l \Delta \hat{C}_0 / 4 \\ \gamma &\equiv \ln(\rho_{lB} / \rho_{lA}) / 2 + \Delta \hat{C}_0 (\rho_{lA} - \rho_{lB}) / 4 \\ K &= \rho_l \Delta \hat{C}_2 / 4 \\ B^\ell &= 1 + \rho_l \hat{C}_0 + \delta \hat{C}_0 \psi / 2 + \Delta \hat{C}_0 \psi^2 / 4 \\ B^x &= \rho_l \frac{\hat{C}_2^2}{\hat{C}_4} = \rho_l \frac{\hat{C}_2^2}{\hat{C}_4} \left(1 - \left(\frac{\delta \hat{C}_2}{\hat{C}_2} - \frac{\delta \hat{C}_4}{2 \hat{C}_4} \right) \psi + \mathcal{O}(\psi)^2 + \dots \right) \equiv B_0^x + B_1^x \psi + B_2^x \psi^2 + \dots \\ R &= \sqrt{\frac{2 \hat{C}_4}{\hat{C}_2}} = \sqrt{\frac{2 \hat{C}_4}{\hat{C}_2}} \left(1 + \frac{1}{2} \left(\frac{\delta \hat{C}_2}{\hat{C}_2} - \frac{\delta \hat{C}_4}{\hat{C}_4} \right) \psi / 2 + \mathcal{O}(\psi)^2 + \dots \right) = R_0 + R_1 \psi + R_2 \psi^2 + \dots \end{aligned} \quad (9.19)$$

Equation (9.18) is a relatively simple model that can be used to simulate solidification, phase segregation and elasticity/plasticity. In the next several section some basic properties of this model will be discussed.

9.2.1 Equilibrium Properties: Two dimensions

To determine the equilibrium properties of the model in Eq. (9.18), specific choices for various parameters must be made. For simplicity the ψ dependence of B^ℓ and B^x will be given as $B^\ell = B_0^\ell + B_2^\ell \psi^2$, $B^x = B_0^x$ and γ will be set to zero. With these choices the phase diagram is symmetric about $\psi = 0$. In addition it will be assumed that the parameter K is “large” such that the concentration field (ψ) varies on ‘slow’ scales compared with n . With these simplifications n can be integrated out of the free energy by in a one mode approximation. Substituting the standard one mode approximation for n (i.e., $\phi[\cos(2qy/\sqrt{3})/2 - \cos(qx) \cos(qy/\sqrt{3})]$ for 2D HCP) into Eq. (9.18), integrating over one unit cell and minimizing the resulting expression with respect to ϕ and q gives,

$$q_{tri} = \sqrt{3}/(2R) \quad (9.20)$$

$$\phi_{tri}(\psi) = 4 \left(t + \sqrt{t^2 - 15v(\Delta B_0 + B_2^\ell \psi^2)} \right) / (15v) \quad (9.21)$$

where $\Delta B = B^\ell - B^x$ and $\Delta B_0 = B_0^\ell - B_0^x$. The free energy per unit area (a_{eq}^2) is then

$$\frac{\Delta \mathcal{F}_{Xtal}}{k_B T \rho_l a_{eq}^2} = \frac{\omega}{2} \psi^2 + \frac{u}{4} \psi^4 + \frac{3}{16} \Delta B \phi_{tri}^2 - \frac{t}{16} \phi_{tri}^3 + \frac{45v}{512} \phi_{tri}^4. \quad (9.22)$$

Equation (9.22) is now only a function of ψ and can be used to construct the phase diagram as a function of $\bar{\psi}$ (i.e., concentration) and ΔB (i.e., temperature). To simplify calculations it is useful to expand \mathcal{F}_{Xtal} to lowest order in ψ , i.e.,

$$\begin{aligned} \frac{\Delta \mathcal{F}_{Xtal}(\psi)}{k_B T \rho_l a_{eq}^2} &= \frac{\Delta \mathcal{F}_{Xtal}(0)}{k_B T \rho_l a_{eq}^2} + \frac{1}{2} \left(\omega + \frac{3}{8} B_2^\ell \phi_{tri}^2(0) \right) \psi^2 + \frac{1}{4} \left(u - \frac{6(B_2^\ell)^2 \phi_{tri}(0)}{15v \phi_{tri}(0) - 4t} \right) \psi^4 + \dots \\ &\equiv F_0 + \frac{a}{2} \psi^2 + \frac{b}{4} \psi^4 + \dots \end{aligned} \quad (9.23)$$

where F_0 , a and b are defined by matching the two equations.

If the coefficient of ψ^4 , (i.e., b) in Eq. (9.23) is negative then higher order terms in the expansion must be included so that the solution does not diverge. In what follows it is assumed that b is positive. If the coefficient of ψ^2 , (i.e., a), is positive then a single phase homogeneous state emerges. If a is negative then a two phase heterogeneous state emerges with coexisting concentrations (obtained by solving minimizing $\Delta \mathcal{F}_{Xtal}$ with respect to ψ),

$$\psi_{coex} = \pm \sqrt{|a|/b} \quad (9.24)$$

The critical temperature (or critical ΔB_0^c) separating the single phase and two-phase region is obtained by setting $\psi_{coex} = 0$ and solving for ΔB_0 . This calculation gives,

$$\Delta B_0^c = \frac{15\omega v - 2t \sqrt{-6B_2^\ell \omega}}{6B_2^\ell} \quad (9.25)$$

Liquid/solid coexistence also requires the free energy density of the liquid. This can be calculated by assuming that the liquid state is defined by $n = n_0$, which for simplicity will be assumed to be zero. In this limit the free energy per unit area of the liquid state is,

$$\frac{\Delta \mathcal{F}_{Liquid}(\psi)}{k_B T \rho_l a_{eq}^2} = \frac{\omega}{2} \psi^2 + \frac{u}{4} \psi^4 \quad (9.26)$$

While an exact calculation of the coexistence lines is difficult, to a good approximation the lines can be obtained by first determining the concentration (ψ_{ls}) at which the free energies of the liquid and solid are equal and then expanding about \mathcal{F}_{liquid} and \mathcal{F}_{Xtal} around ψ_{ls} to order $(\psi - \psi_{ls})^2$. Using this simple approximation for the liquid and crystal free energies allows for an exact solution of the common tangent construction (or, Maxwell's equal area construction) to obtain the liquid/crystal coexistence lines. Specifically, setting Eq. (9.26) equal to Eq. (9.22) and solving for ψ gives the value of ψ (denoted ψ_{ls}) at which the liquid and solid have the same energy per unit area gives,

$$\psi_{ls}^2 = \frac{\Delta B_0^{ls} - \Delta B_0}{B_2^l} \quad (9.27)$$

where ΔB_0^{ls} is the lowest value of ΔB_0 at which a liquid can coexist with a solid and is given by

$$\Delta B_0^{ls} = \frac{8t^2}{135v} \quad (9.28)$$

Next, the liquid and solid free energies are expanded about ψ_{ls}^2 to second order, i.e.,

$$F^l = F_0^l + F_1^l(\psi - \psi_{ls}) + F_2^l(\psi - \psi_{ls})^2/2 \quad (9.29)$$

and

$$F^s = F_0^s + F_1^s(\psi - \psi_{ls}) + F_2^s(\psi - \psi_{ls})^2/2 \quad (9.30)$$

These equations give the following chemical potentials for each phase,

$$\mu^l = F_1^l + F_2^l(\psi - \psi_{ls}) \quad (9.31)$$

and

$$\mu^s = F_1^s + F_2^s(\psi - \psi_{ls}). \quad (9.32)$$

If the equilibrium chemical potential is denoted μ_{ls} , then the liquid (ψ_l) and solid (ψ_s) concentrations can be expressed as

$$\begin{aligned} \psi_l &= \psi_{ls} + (\mu_{ls} - F_1^l)/F_2^l \\ \psi_s &= \psi_{ls} + (\mu_{ls} - F_1^s)/F_2^s \end{aligned} \quad (9.33)$$

Maxwell's equal area construction rule can be used to calculate μ_{ls} according to

$$\int_{\psi_l}^{\psi_{ls}} d\psi (\mu_l - \mu_{ls}) + \int_{\psi_{ls}}^{\psi_s} d\psi (\mu_s - \mu_{ls}) = 0. \quad (9.34)$$

Solving the above expression for μ_{ls} thus gives,

$$\mu_{ls} = \frac{F_1^s F_2^l - F_1^l F_2^s + (F_1^l - F_1^s) \sqrt{F_2^l F_2^s}}{F_2^l - F_2^s} \quad (9.35)$$

Thus if $(F_1^l, F_2^l, F_1^s, F_2^s)$ are known then μ_{ls} is known and in turn ψ_l and ψ_s are known from Eq. (9.33). Straightforward expansions of the liquid and solid free energy functionals around $\psi = \psi_{ls}$ gives,

$$F_1^l = w\psi_{ls} + u\psi_{ls}^3, \quad F_2^l = w + 3u\psi_{ls}^2, \quad F_1^s = \frac{4B_2^l}{5v} \Delta B_{ls} \psi_{ls} + F_1^l, \quad F_2^s = \frac{4B_2^l}{5v} (4\Delta B_0 - 3\Delta B_0^{ls}) + F_2^l. \quad (9.36)$$

Equation (9.33) can now be used to construct the liquid/solid part of the phase diagram. A sample phase diagram as shown in Fig. (9.1) ¹.

¹Note that the parameter $w = -0.04$ reported in the corresponding figure in Ref. [62] is a typo.

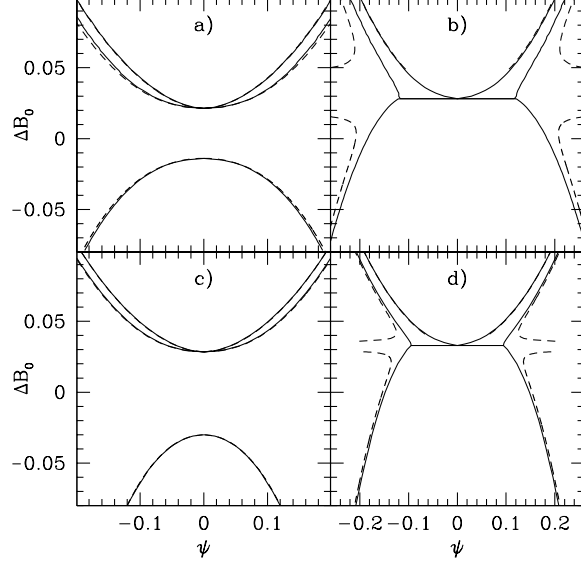


Figure 9.1: Phase diagrams in two (a,b) and three (c,d) dimensions. In all figures the parameters are $t = 0.6$, $v = 1$, $u = 4$, $B^\ell = B_0^\ell - 1.8\psi^2$ (i.e., $B_1^\ell = 0$, $B_2^\ell = -1.8$), $B^x = 1$. The parameter w is 0.088 in (a) and (c), and 0.008 in (b) and (d). The solid lines are exact one-mode solutions and the dashed lines are approximate solutions as described by Eqns. (9.24) and (9.33).

9.2.2 Equilibrium Properties: Three dimensions (BCC)

The calculations presented in previous section can easily be extended to a three dimensional BCC crystal structure. For these calculations a one mode approximation for n is,

$$n = \phi (\cos(qx) \cos(qy) + \cos(qy) \cos(qz) + \cos(qz) \cos(qx)). \quad (9.37)$$

Substituting this one mode BCC approximation for n into the free energy, averaging over one unit cell and minimizing with respect to q and ϕ gives,

$$q_{bcc} = 1/(\sqrt{2}R) \quad (9.38)$$

and

$$\phi_{bcc}(\psi) = 4 \left(2t + \sqrt{4t^2 - 45v(\Delta B_0 + B_2^\ell \psi^2)} \right) / (45v). \quad (9.39)$$

The free energy per unit volume (a_{eq}^3) is then

$$\frac{\mathcal{F}_{Xtal}}{k_B T \rho_l a_{eq}^3} = \frac{\omega}{2} \psi^2 + \frac{u}{4} \psi^4 + \frac{3}{8} \Delta B \phi_{bcc}^2 - \frac{t}{4} \phi_{bcc}^3 + \frac{135v}{256} \phi_{bcc}^4 \quad (9.40)$$

Expanding \mathcal{F}_{Xtal} as before gives,

$$\frac{\Delta \mathcal{F}_{Xtal}(\psi)}{k_B T \rho_l a_{eq}^3} = \frac{\Delta \mathcal{F}_{Xtal}(0)}{k_B T \rho_l a_{eq}^3} + \frac{1}{2} \left(\omega + \frac{3}{4} B_2^\ell \phi_{bcc}^2(0) \right) \psi^2 + \frac{1}{4} \left(u - \frac{12(B_2^\ell)^2 \phi_{bcc}(0)}{45v \phi_{bcc}(0) - 8t} \right) \psi^4 + \dots$$

$$\equiv F_0 + \frac{a}{2}\psi^2 + \frac{b}{4}\psi^4 + \dots \quad (9.41)$$

For positive a the equilibrium state is homogeneous, while for negative a a two phase heterogeneous state emerges with coexisting concentrations again at $\psi_{coex} = \pm\sqrt{|a|/b}$. The critical temperature (or critical ΔB_0^c) can be obtained by setting $\psi_{coex} = 0$ and solving for ΔB_0 . This calculation gives,

$$\Delta B_0^c = \frac{45\omega v - 8t\sqrt{-3B_2^\ell\omega}}{12B_2^\ell} \quad (9.42)$$

Setting Eq. (9.40) equal to Eq. (9.26) and solving for ψ gives the value of ψ (ψ_{ls}) at which the liquid and solid have the same energy per unit area. This occurs when

$$\psi_{ls}^2 = \frac{\Delta B_0^{ls} - \Delta B_0}{B_2^\ell} \quad (9.43)$$

where ΔB_0^{ls} is the lowest value of ΔB_0 at which a liquid can coexist with a solid and is given by

$$\Delta B_0^{ls} = \frac{32t^2}{405v} \quad (9.44)$$

Proceeding precisely as in the two dimensional case and expanding of the liquid and solid free energy functionals around $\psi = \psi_{ls}$ gives

$$F_1^l = w\psi_{ls} + u\psi_{ls}^3, \quad F_2^l = w + 3u\psi_{ls}^2, \quad F_1^s = \frac{8B_2^l}{15v}\psi_{ls} + F_1^l, \quad F_2^s = \frac{8B_2^l}{15v}(4\Delta B_0 - 3\Delta B_0^{ls}) + F_2^l \quad (9.45)$$

The same steps as in the two dimensional case can be used once more to calculate the phase diagram. Sample phase diagram are given in Fig. (9.1).

9.3 PFC Alloy Dynamics

As with the phase field crystal model of a pure system it is assumed that the dynamics is driven to minimize the free energy, i.e.,

$$\begin{aligned} \frac{\partial \rho_A}{\partial t} &= \vec{\nabla} \cdot \left(M_A \vec{\nabla} \frac{\delta F}{\delta \rho_A} \right) + \zeta_A \\ \frac{\partial \rho_B}{\partial t} &= \vec{\nabla} \cdot \left(M_B \vec{\nabla} \frac{\delta F}{\delta \rho_B} \right) + \zeta_B \end{aligned} \quad (9.46)$$

where M_A and M_B are the mobilities of each atomic species, which in general depend on density. The variables ζ_A and ζ_B are conserved Gaussianly correlated noise due to thermal fluctuations of species A and B respectively and satisfy the fluctuation dissipation theorem, i.e., $\langle \zeta_i(\vec{r}, t) \zeta_j(\vec{r}', t') \rangle = -2k_B T M_i \nabla^2 \delta(\vec{r} - \vec{r}') \delta(t - t') \delta_{i,j}$

A useful approximation that can be made to Eqs. (9.46) is to assume that the concentration field ψ can be approximated as follows,

$$\psi = 2c - 1 = 2\rho_A/\rho = (\rho_A - \rho_B)/\rho = (\rho_A - \rho_B)/[\rho_l(n+1)] \approx (\rho_A - \rho_B)/\rho_l. \quad (9.47)$$

This assumptions leads to the following equation of motion for n and ψ ,

$$\begin{aligned}\frac{\partial n}{\partial t} &= \vec{\nabla} \cdot M_1 \vec{\nabla} \frac{\delta \mathcal{F}}{\delta n} + \vec{\nabla} \cdot M_2 \vec{\nabla} \frac{\delta \mathcal{F}}{\delta \psi} + (\zeta_A + \zeta_B)/\rho_l \\ \frac{\partial \psi}{\partial t} &= \vec{\nabla} \cdot M_2 \vec{\nabla} \frac{\delta \mathcal{F}}{\delta n} + \vec{\nabla} \cdot M_1 \vec{\nabla} \frac{\delta \mathcal{F}}{\delta \psi} + (\zeta_A - \zeta_B)/\rho_l\end{aligned}\quad (9.48)$$

where $M_1 \equiv (M_A + M_B)/\rho_l^2$ and $M_2 \equiv (M_A - M_B)/\rho_l^2$. The derivation of Eqs. (9.48) will not shown here. The reader is referred to Ref. [62].

Applying the relevant functional derivatives to Eqs. (9.48) gives the following equations of motion for the fields n and ψ ,

$$\begin{aligned}\frac{\delta \mathcal{F}}{\delta n} &= B^l n + \frac{B^x}{2} (2R^2 \nabla^2 + R^4 \nabla^4) n + \nabla^2 (B^x R^2 n) + \frac{1}{2} \nabla^4 (B^x R^4 n) - tn^2 + vn^3 \\ \frac{\delta \mathcal{F}}{\delta \psi} &= \frac{\partial B^\ell}{\partial \psi} \frac{n^2}{2} + \frac{\partial (B^x R^2)}{\partial \psi} n \nabla^2 n + \frac{1}{2} \frac{\partial (B^x R^4)}{\partial \psi} n \nabla^4 n + w\psi + u\psi^3 - K \nabla^2 \psi.\end{aligned}\quad (9.49)$$

Two representative simulations of Eqs. (9.49) using $M_A = M_B$, $B^\ell = B_0^\ell + B_2^\ell \psi^2$, $B^x = B_0^x$ and $R = R_0 + R_1 \psi$ are shown in Fig. (9.2). The figure on the left illustrates the flexibility of the approach to simultaneously model liquid/solid transitions, phase segregation, grain boundaries, multiple crystal orientations and different size atoms in a single simulation. The figure on the right illustrate that the model can reproduce known structures such as dendrites and eutectic crystals resolved down to the atomic scale.

In instances when the mobilities are equal and the difference in atomic size is modest a slightly simpler version of this model can be used. Using, once again, the parameterization $B^\ell = B_0^\ell + B_2^\ell \psi^2$, $B^x = B_0^x$ and $R = R_0 + R_1 \psi$, and taking the limit of small solute in these parameters, leads to,

$$\begin{aligned}\frac{\partial n}{\partial t} &= M_1 \nabla^2 (B^l n + B^x \mathcal{A} n + 2\eta B^x (\psi \mathcal{B} n + \mathcal{B} \psi n) - tn^2 + vn^3) \\ \frac{\partial \psi}{\partial t} &= M_1 \nabla^2 (2B^x \eta n \mathcal{B} n + (w + B_2^\ell n^2) \psi + u\psi^3 - K \nabla^2 \psi)\end{aligned}\quad (9.50)$$

where $\mathcal{A} \equiv 2\nabla^2 + \nabla^4$ and $\mathcal{B} \equiv \nabla^2 + \nabla^4$. This version is a little more convenient for numerical simulations.

The alloy PFC model of Eqs. (9.48) can be explored numerically using a Fortran 90 code that accompanies this book in the directory ‘‘PFC_alloy’’ in CD that accompanies this book. The algorithm very closely follows the approach of the model C codes studies in connection with solidification of pure materials and alloys in previous chapters and will not be explicitly discussed here

9.4 Applications of PFC models

The PFC models studied in this book can be applied to a many different physical phenomena in which elasticity, plasticity and multiple crystal orientations play a role. In this section some of the applications that can be address by this modeling paradigm are briefly outlined. For more details of implementation, the reader is referred to the original publications for the details.

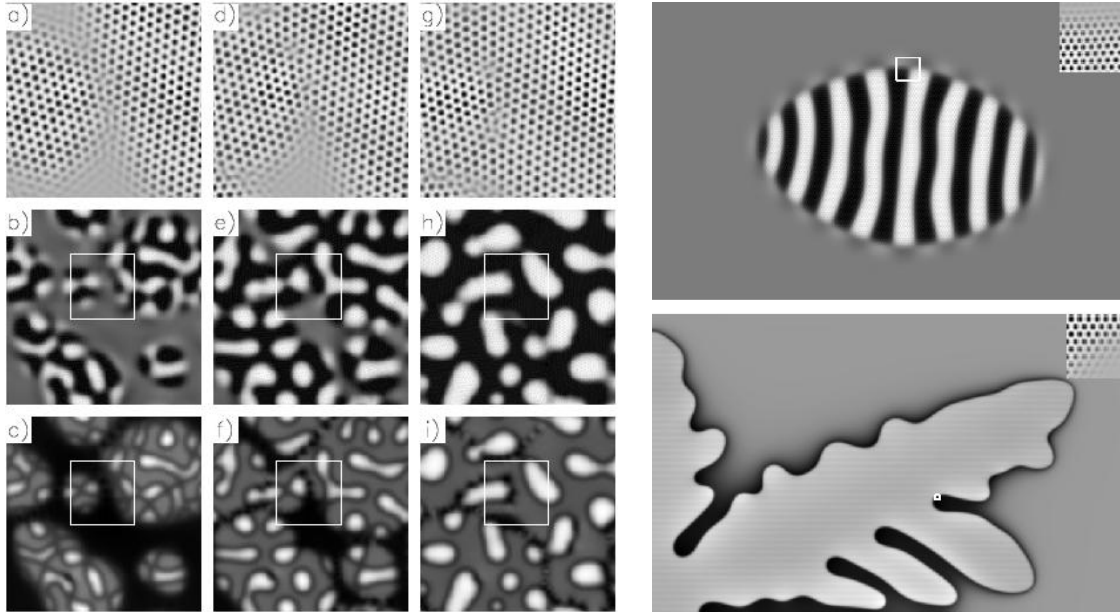


Figure 9.2: Eutectic and Dendritic solidification phenomena. In the figure on the left the grey scale represents ρ in the top row, ψ in the middle row and the smoothed local free energy density in the bottom row. The left, middle and right columns corresponds to times $t/\tau_D = 106, 260$ and 801 respectively. In figs. (a,d,g) only a portion of the simulation cell is shown corresponding to the region enclosed by the white squares shown in the other figures. In the figure on the right the top illustrates the ψ for a eutectic crystal grown from a supercooled liquid and in the bottom figure a dendrite is grown from a supercooled liquid. In the top right of each figure a small portion of the structures is blown up to show the atomistic resolution of the simulations.

A natural area for exploration using the PFC model is **grain boundaries** since the model can describe crystals of arbitrary orientations and the dislocations that comprise the boundaries. Initial PFC studies of the energy of such boundaries [67, 66] confirmed the well know Read-Shockley equation [180] for low angle grain boundaries and were consistent with experiments for large angle boundaries. These results were reconfirmed in other studies of the PFC model [153] and of the amplitude representation [78]. Other work focussed on **premelting** of grain boundaries [24, 153] in which regions close to grain boundaries or even single dislocations were shown to melt before the bulk melting temperature is reached. It would be interesting to use the binary PFC model to such solute trapping and drag at grain boundaries and surface, although no studies have been published to date.

One of the applications that motivated the development of the PFC model was **epitaxial growth**, or the growth of a thin film on a substrate with a similar but different crystal structure. The mismatch of the film/substrate lattice structures gives rise to the growth of strained coherent films, which often undergo morphological changes to reduce the strain. Common mechanisms for strain relaxation are surface buckling or mound formation (i.e., an Asaro-Tiller, Grinfeld instability) or the nucleation of defects within the film. Several studies have been conducted to study these mechanisms using both pure and binary models and even amplitude expansions [61, 60, 66, 62, 98, 214, 99].

In other contexts the interaction of substrates (or surfaces) with films or single layers can be easily modeled by the PFC model as shown in number of studies by Achim *et al.* [4, 178, 6]. In these studies a two dimensional substrate was modeled by incorporating an effective surface potential into the PFC free energy. By implementing a surface potential with for example square symmetry the model can be used to study **commensurate/incommensurate transitions** as a function of interaction strength between the surface layer and substrate. In addition when a driving force is added the model can model **pinning and sliding friction** of single layers [5, 179].

The PFC models ability to incorporate elastic and plastic deformations makes it useful for the study of the **material hardness** of polycrystalline (or nano-crystalline) materials. An initial study [25] of single dislocations reveal the existence of Peierls barriers and show that climb and glide follow viscous equations such that the effective mobility for glide is an order of magnitude faster than climb. Other studies of the deformation of polycrystalline material have been conducted using the basic PFC model [67, 66], the modified PFC model [188] and with a novel numerical algorithms for modeling compression and tension [91]. These studies have been able to reproduce the reverse Hall-Petch effect in which the yield strength increases as a function of grain size as observed in experiments on nano-crystalline materials [218].

Appendix A

Thin-Interface Limit of a Binary Alloy Phase Field Model

This appendix derives the thin interface limit of the "model C" type phase field models, comprising one order parameter equation coupled to one diffusion equation. This notation is based on the alloy model discussed in Chapter (6), although it is adaptable to that model C describing solidification of a pure material also, as studied in Chapter (5).

The following analysis derives the behavior of a generalized alloy phase field model in the limit when the interface width W_ϕ is formally smaller than the capillary length d_o . Solutions are expanded to second order accuracy in the small parameter $\epsilon = W_\phi/d_o$. The effective sharp interface relations derived in the analysis still hold for diffuse interfaces (i.e. for $W_\phi \sim d_o$) so long as the thermodynamic driving force that drives microstructure formation is small. The analysis treats an isotropic interface energy for simplicity. Because it is performed in interface local coordinates, the results of the isotropic case carry over essentially unchanged to anisotropic case. The calculations of this appendix follow the standard matched asymptotic analysis methods [158] and generalize the approach first developed by Almgren [8] and later extended by Karma and co workers [113, 112, 57] to the case of a generalized alloy free energy and to two-sided diffusion.

Readers wishing only a summary of the results of part (1) discussed above should become familiar with section (A.1), which defines the form of phase field models being studied, and jump to section (A.8), which summarizes the main results of the main asymptotic analysis, covered in sections (A.2)-(A.7). Section (A.9) covers part (2) discussed above.

A.1 Phase Field Model

The alloy free energy considered here considers one order parameter (or phase field) ϕ , an impurity concentration c and a temperature T , considered isothermal at present. The paradigm alloy phase field model free energy considered is of the form

$$F = \int_V \left\{ \frac{|\epsilon_c \nabla c|^2}{2} + \frac{|\epsilon_\phi \nabla \phi|^2}{2} + wg(\phi) + \bar{f}_{AB}^{\text{mix}}(\phi, c, T) \right\} dV \quad (\text{A.1})$$

where $\epsilon_\phi \equiv \sqrt{w}W_\phi$ and $\epsilon_c \equiv \sqrt{w}W_c$ are constants that set the scale of the solid-liquid interface and compositional domain interface energy, respectively. Their units are $[J/m]^{1/2}$. The constant w is the nucleation barrier between the solid and liquid phase of component A, and has units of $[J/m^3]$. The constants W_ϕ and W_c thus set the length scale of the solid-liquid interface and a compositional boundary. The inverse of w is also defined herein by $w \equiv 1/\lambda$. The function $g(\phi)$ is the double-well potential, which models the solid-liquid free energy of the component A at its melting temperature T_m . It has two minima for ϕ_s and ϕ_L , corresponding to the order parameters for the solid and liquid phases, respectively, and a barrier between the two phases. The function $\bar{f}_{AB}^{\text{mix}}(\phi, c, T)$ is the bulk free energy of mixing of the alloy, and determined the phase diagram of the alloy.

Equations of motion for the fields c and ϕ are given by

$$\begin{aligned}\tau \frac{\partial \phi}{\partial t} &= -\frac{\delta F}{\delta \phi} = W_\phi^2 \nabla^2 \phi - \frac{dg}{d\phi} - \frac{\partial f_{AB}}{\partial \phi} \\ \frac{\partial c}{\partial t} &= \nabla \cdot \{M(\phi, c) \nabla \mu\} \\ \mu &= \frac{\delta F}{\delta c} = \frac{\partial \bar{f}_{AB}^{\text{mix}}}{\partial c} - \epsilon_c^2 \nabla^2 c\end{aligned}\tag{A.2}$$

where the definition

$$f_{AB} \equiv \bar{f}_{AB}^{\text{mix}}/w\tag{A.3}$$

has been made, while $\tau \equiv 1/(wM_L)$ controls the time of attachment of atoms to the solid interface from the liquid, governed formally by the atomic mobility in the liquid M_L . The mobility function $M(\phi, c)$ is given by

$$\begin{aligned}M(\phi, c) &= D_L q(\phi, c) \\ q(\phi, c) &\equiv Q(\phi) / \frac{\partial^2 \bar{f}_{AB}^{\text{mix}}}{\partial c^2}\end{aligned}\tag{A.4}$$

where the function $Q(\phi)$ is an interpolation function whose that is to be used to interpolate the diffusion through the solid-liquid interface. Its has limits $Q(\phi \rightarrow \phi_L) = 1$ and $Q(\phi \rightarrow \phi_s) = D_s/D_L$ where D_s is the solid phase impurity diffusion constant. For example, for the regular solution model of a binary alloy, $\partial^2 \bar{f}_{AB}^{\text{mix}}/\partial c^2 \equiv \partial \mu^{\text{bulk}}/\partial c = (RT_m/v_o)/c(1-c)$, where v_o , R and T_m are the molar volume of the material, the natural gas constant and the melting point of A, respectively. Through Eq. (A.4) the mobility in the liquid phase is identified as

$$M_L = D_L q(\phi = \phi_L, c = c_L^{\text{eq}}) = D_L / \left(\frac{\partial \mu}{\partial c} \right)_{c_L^{\text{eq}}}\tag{A.5}$$

A.2 Curvi-linear Coordinate Transformations

The phase field equations are considered here with respect to a set of curvi-linear co-ordinates, denoted (u, s) and illustrated in Fig. (A.1). In this coordinate system, distances are measured with respect to a curvilinear co-ordinate system which is anchored to a position along the solid-liquid interface, where the interface is defined by the locus of points satisfying

$$I = \{(x, y) | \phi(x, y) = \phi_c\}\tag{A.6}$$

where ϕ_c is a constant ¹. The co-ordinate u in this system measures the distance from the interface to a point (x, y) , along a line normal to the interface. The co-ordinate s measures the arclength from a reference position on the interface to the position on the interface coinciding with the normal direction along which u is measured.

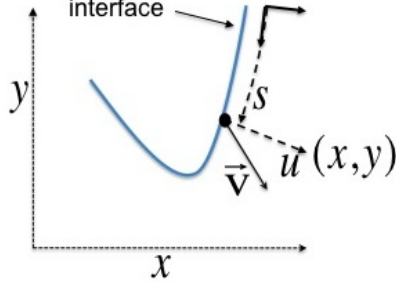


Figure A.1: Schematic of the (u, s) co-ordinates relative to an orthogonal co-ordinate system anchored onto the interface. The co-ordinate u measures distances normal to the interface while s measure the arclength long the interface. The vector \vec{v} denotes the velocity of the interface at the point indicated by the dot, which is situated at co-ordinates $(0, s)$. See also Fig. (C.1) for further details.

Transforming to a co-ordinate system moving with a velocity \vec{v} transforms the time derivative according to

$$\frac{\partial}{\partial t} \rightarrow \frac{\partial}{\partial t} - \vec{v} \cdot \nabla \quad (\text{A.7})$$

where \vec{v} is the velocity vector at the reference point on the interface. As shown in section (C.2), in the (u, s) co-ordinates Eq. (A.7) becomes

$$\frac{\partial}{\partial t} \rightarrow \frac{\partial}{\partial t} - (-u_t \hat{n} - s_t \hat{\tau}) \cdot \left(\hat{n} \frac{\partial}{\partial u} + \frac{1}{1 + u\kappa} \hat{\tau} \frac{\partial}{\partial s} \right) \approx \frac{\partial}{\partial t} - v_n \frac{\partial}{\partial u} + s_{,t} \frac{\partial}{\partial s} \quad (\text{A.8})$$

where $-u_t (\equiv v_n)$ and $-s_{,t} (\equiv v_t)$ define the components of \vec{v} projected onto the normal \hat{n} and transverse (s) directions, respectively, and κ is the local interface curvature at the point $(0, s)$ on the interface. (It is noted that the notation " $f_{,x}$ " will often be used to denote partial differentiation of a function f with respect to x). The $(1 + u\kappa)$ term in the second equality was dropped as it will be seen later to be of lower order than required in this analysis. ²

The ∇ and ∇^2 operators are similarly be transformed into (u, s) co-ordinates. Applying Eq. (C.15) derived in section (C.2), it is found –after some algebra– that the Laplacian operator (∇^2) becomes,

$$\nabla^2 \rightarrow \frac{\partial^2}{\partial u^2} + \frac{\kappa}{(1 + u\kappa)} \frac{\partial}{\partial u} + \frac{1}{(1 + u\kappa)^2} \frac{\partial^2}{\partial s^2} - \frac{u}{(1 + u\kappa)^3} \frac{\partial \kappa}{\partial s} \frac{\partial}{\partial s} \quad (\text{A.9})$$

¹It should be noted the location of the interface defined through $\phi(x, y)$, typically found in many papers, is not unique. The most consistent choice of ϕ_c is that which defines the Gibb's dividing surface. In this calculation $\phi_c = 0$ will be chosen such that a 1D solution of the ϕ field is even about the interface position.

²This will become clearer in section (A.6). When the re-scaled phase field equations are expanded in a small parameter ϵ (defined below) time derivatives become of order ϵ^2 , while the expression $(1 + u\kappa)^{-1} \approx 1 + \mathcal{O}(\epsilon)$ (e.g. see Eqs. (A.36)), making any contribution from the $u\kappa$ term of order ϵ^3 , which is not being considered here.

while the "sandwiched" ∇ operator $\nabla \cdot (q\nabla)$, arising from the diffusion equation, becomes

$$\nabla \cdot (q\nabla) \rightarrow \frac{\partial}{\partial u} \left(q \frac{\partial}{\partial u} \right) + \frac{q\kappa}{(1+u\kappa)} \frac{\partial}{\partial u} + \frac{1}{(1+u\kappa)^2} \frac{\partial}{\partial s} \left(q \frac{\partial}{\partial s} \right) - \frac{uq}{(1+u\kappa)^3} \frac{\partial \kappa}{\partial s} \frac{\partial}{\partial s} \quad (\text{A.10})$$

A.3 Length and Time Scales

As discussed in the text, matched asymptotic analysis is a multiple scales analysis that matches solutions of the phase field equations at distances much smaller than the interface width to those far outside the interface. Before proceeding, it is instructive to define some useful expressions and the characteristic length and time scales that will be used to non-dimensionalise the phase field equations in the following analysis.

The "inner region" of the phase field model is defined by the length scale W_ϕ , the interface width. The "outer region" of the model is defined by scales much larger than that of the capillary length d_o . In terms of phase field parameters, the capillary length d_o will turn out to scale with the interface width W_ϕ and the nucleation barrier $1/\lambda$. It is thus expressed as

$$d_o \equiv \frac{W_\phi}{\alpha\lambda} \quad (\text{A.11})$$

where α is a constant that will be determined later in the analysis³.

The asymptotic analysis will be done by solving the field equations order by order (to second order) in the small variable defined by $\epsilon \equiv W_\phi v_s / D_L \ll 1$, where v_s is a characteristic velocity. In this analysis $v_s = D_L / d_o$, which characterizes the speed with which atoms diffuse across the solid-liquid, whose scale is set by d_o [57]. These definitions imply that $\epsilon = W_\phi / d_o$. It will also be assumed that the interface width is small compared to the local interface curvature of the interface. Specifically, in most practical situations the radius of curvature of the interface $R \sim 1/\kappa$ is much larger than the capillary length d_o . This leads to the condition $W_\phi \kappa \ll 1$. Finally, the characteristic time scale with which time in the model will be re-scaled, both in inner and outer domain is $t_c = D_L / v_s^2$. To summarize,

$$\begin{aligned} \text{inner region : } x &\ll W_\phi \\ \text{outer region : } x &\gg D_L / v_s = d_o \\ \text{characteristic time : } t_c &= D_L / v_s = d_o / D_L \\ \text{expansion parameter : } \epsilon &= W_\phi v_s / D_L = W_\phi / d_o \ll 1 \\ \text{curvature : } W_\phi \kappa &\sim \epsilon \end{aligned} \quad (\text{A.12})$$

From the definitions in Eqs. (A.12), the free energy of mixing f_{AB} can be re-scaled according to

$$f_{AB} \equiv \frac{\bar{f}_{AB}^{\text{mix}}}{w} = \epsilon \frac{\bar{f}_{AB}^{\text{mix}}}{\alpha} = \epsilon f \quad (\text{A.13})$$

where the definition

$$f(\phi, c) \equiv \bar{f}_{AB}^{\text{mix}}(\phi, c) / \alpha \quad (\text{A.14})$$

³It will be determined by comparing the effective phase field capillary length, which is derived from the final result in Eq. (A.130) with Eq. (A.11). For example, for a binary alloy, Eq. (6.73) and shows that $\alpha \propto RT/\Omega$, where here Ω is the molar volume of the material.

in the last equality has been made for convenience of notation in the algebra that follows.

It should be noted that while the analysis presented herein is in the small parameter $\epsilon = W_\phi/d_o$, the results derived will be valid so long as $\epsilon f \ll 1$. This implies that W_ϕ can be of order d_o so long as the thermodynamic driving force f is small or if the microstructure growth rates are small. This is motivated empirically by noting, through Eq. (A.13), that the coupling of the ϕ and c disappears when $\epsilon \rightarrow 0$, i.e. the classical sharp interface limit, or when $|f| \rightarrow 0$. The latter situation corresponds to very small interface velocities, v_n . Examination of the final results of this analysis, summarized in section (A.8), show that the $v_n \rightarrow 0$ limit leads, to lowest order, to essentially the same effective sharp interface model as the $W_\phi/d_o \rightarrow 0$ limit (subject always to the Eq. (A.11) and the condition $W_\phi \kappa \ll 1$).

A.4 Matching Conditions Between Outer and Inner Solutions

After solving the phase field equations in the inner and outer regions, their respective solutions will be matched in the intermediate region. This processes will make it possible to extract the Gibbs-Thomson and flux conservation equations acting at an effective solid-liquid interface of the corresponding phase field model. The solutions in the outer regions are denoted by ϕ^o while in the inner region they are denoted by ϕ^i . It will be assumed that the solutions of the outer region can be expressed in an asymptotic series as

$$\begin{aligned}\phi^o &= \phi_0^o + \epsilon\phi_1^o + \epsilon^2\phi_2^o + \dots \\ c^o &= c_0^o + \epsilon c_1^o + \epsilon^2 c_2^o + \dots \\ \mu^o &= \mu_0^o + \epsilon\mu_1^o + \epsilon^2\mu_2^o + \dots\end{aligned}\tag{A.15}$$

and while the solution in inner region are given by

$$\begin{aligned}\phi^{\text{in}} &= \phi_0^{\text{in}} + \epsilon\phi_1^{\text{in}} + \epsilon^2\phi_2^{\text{in}} + \dots \\ c^{\text{in}} &= c_0^{\text{in}} + \epsilon c_1^{\text{in}} + \epsilon^2 c_2^{\text{in}} + \dots \\ \mu^{\text{in}} &= \mu_0^{\text{in}} + \epsilon\mu_1^{\text{in}} + \epsilon^2\mu_2^{\text{in}} + \dots \\ v_n &= v_{n0} + \epsilon v_{n1} + \epsilon^2 v_{n2} + \dots\end{aligned}\tag{A.16}$$

where v_n is the normal velocity, which will play an important role when analyzing the inner behaviour of the phase field equations.

The inner and outer solutions are matched by comparing the inner solutions in the limit of $\xi \equiv u/W_\phi \rightarrow \infty$ with the outer solutions in the limit in the limit $\eta = u/(D_L/v_s) \rightarrow 0$ [8]. This leads to the following matching conditions.

For the concentration field c :

$$\begin{aligned}\lim_{\xi \rightarrow \pm\infty} c_0^{\text{in}}(\xi) &= \lim_{\eta \rightarrow 0^\pm} c_0^o(\eta) = c_0^o(0^\pm) \\ \lim_{\xi \rightarrow \pm\infty} c_1^{\text{in}}(\xi) &= \lim_{\eta \rightarrow 0^\pm} \left(c_1^o(\eta) + \frac{\partial c_0^o(\eta)}{\partial \eta} \xi \right) = c_1^o(0^\pm) + \frac{\partial c_0^o(0^\pm)}{\partial \eta} \xi \\ \lim_{\xi \rightarrow \pm\infty} \frac{\partial c_2^{\text{in}}(\xi)}{\partial \xi} &= \lim_{\eta \rightarrow 0^\pm} \left(\frac{\partial c_1^o(\eta)}{\partial \eta} + \frac{\partial^2 c_0^o(\eta)}{\partial \eta^2} \xi \right) = \frac{\partial c_1^o(0^\pm)}{\partial \eta} + \frac{\partial^2 c_0^o(0^\pm)}{\partial \eta^2} \xi\end{aligned}\tag{A.17}$$

For the chemical potential μ :

$$\lim_{\xi \rightarrow \pm\infty} \mu_0^{\text{in}}(\xi) = \lim_{\eta \rightarrow 0^\pm} \mu_0^o(\eta) = \mu_0^o(0^\pm)$$

$$\begin{aligned}
\lim_{\xi \rightarrow \pm\infty} \mu_1^{\text{in}}(\xi) &= \lim_{\eta \rightarrow 0^\pm} \left(\mu_1^o(\eta) + \frac{\partial \mu_0^o(\eta)}{\partial \eta} \xi \right) = \mu_1^o(0^\pm) + \frac{\partial \mu_0^o(0^\pm)}{\partial \eta} \xi \\
\lim_{\xi \rightarrow \pm\infty} \frac{\partial \mu_2^{\text{in}}(\xi)}{\partial \xi} &= \lim_{\eta \rightarrow 0^\pm} \left(\frac{\partial \mu_1^o(\eta)}{\partial \eta} + \frac{\partial^2 \mu_0^o(\eta)}{\partial \eta^2} \xi \right) = \frac{\partial \mu_1^o(0^\pm)}{\partial \eta} + \frac{\partial^2 \mu_0^o(0^\pm)}{\partial \eta^2} \xi
\end{aligned} \tag{A.18}$$

For the phase field ϕ :

$$\begin{aligned}
\lim_{\xi \rightarrow -\infty} \phi_0^{\text{in}}(\xi) &= \phi_s = \lim_{\eta \rightarrow 0^+} \phi_0^o(\eta) \\
\lim_{\xi \rightarrow \infty} \phi_0^{\text{in}}(\xi) &= \phi_L = \lim_{\eta \rightarrow 0^-} \phi_0^o(\eta) \\
\lim_{\xi \rightarrow \pm\infty} \phi_j^{\text{in}}(\xi) &= 0, \quad \forall j = 1, 2, 3, \dots \\
\phi_j^o(\eta) &= 0, \quad \forall j = 1, 2, 3, \dots
\end{aligned} \tag{A.19}$$

where ϕ_s and ϕ_L denote the steady state order parameter of the bulk solid and liquid. These are determined by the specific form of the free energy. The simplest free energies to work with are such that bulk phase field values are uniform constants.

Velocity is dependent only of the arclength s and does not require matching in the transverse coordinate.

A.5 Outer Equations Satisfied by Phase Field Model

To examine the phase field equations Eqs. (A.2) in the outer region, the following re-scaling of space and time are made: $\eta = v_s u / D_L$, $\bar{s} = v_s s / D_L$ and $\bar{t} = t / (D_L / v_s^2)$. This leads to the following dimensionless version of Eqs. (A.2),

$$\bar{D} \epsilon^2 \frac{\partial \phi}{\partial \bar{t}} = \epsilon^2 \bar{\nabla}^2 \phi - \frac{dg}{d\phi} - \epsilon \frac{\partial f}{\partial \phi} \tag{A.20}$$

$$\frac{\partial c}{\partial \bar{t}} = \bar{\nabla} \cdot \{q(\phi, c) \bar{\nabla} \mu\} \tag{A.21}$$

where $\bar{D} = D_L \tau / W_\phi^2$ and $\bar{\nabla}$ denotes gradients with respect to *dimensionless* length scales.

The next step is to substitute Eqs. (A.15) into Eqs. (A.20) and (A.21) and expand all non-linear terms up order ϵ^2 . This is referred to a "second order expansion" in ϵ . Expanding first the phase field equation Eq. (A.20) to second order gives

$$\begin{aligned}
\bar{D} \epsilon^2 \frac{\partial \phi_0^o}{\partial \bar{t}} &= \epsilon^2 \bar{\nabla}^2 \phi_0^o - g'(\phi_0^o) \\
&- \epsilon \left(f_{,\phi}(\phi_0^o, c_0^o) + g''(\phi_0^o) \phi_1^o \right) \\
&- \epsilon^2 \left(f_{,\phi\phi}(\phi_0^o, c_0^o) \phi_1^o + f_{,\phi c}(\phi_0^o, c_0^o) c_1^o + g''(\phi_0^o) \phi_2^o + g'''(\phi_0^o) (\phi_1^o)^2 / 2 \right) - \dots
\end{aligned} \tag{A.22}$$

To make the notation compact, ordinary derivatives with respect to the order parameter are denoted by primes, while mixed partial derivatives are denoted with commas. Thus $f_{,\phi c}$ denotes partial differentiation of f with respect to ϕ , then c . The idea behind matched asymptotic analysis is to separate Eq. (A.22)

into a series of separate equations, each of which contains terms of the same order in ϵ . In this case the equations at each order are given by

$$\mathcal{O}(1) : g'(\phi_0^o) = 0 \quad (\text{A.23})$$

$$\mathcal{O}(\epsilon) : f_{,\phi}(\phi_0^o, c_0^o) + g''(\phi_0^o)\phi_1^o = 0 \quad (\text{A.24})$$

$$\mathcal{O}(\epsilon^2) : \bar{D} \frac{\partial \phi_0^o}{\partial \bar{t}} - \bar{\nabla}^2 \phi_0^o + \left(f_{,\phi\phi}(\phi_0^o, c_0^o)\phi_1^o + f_{,\phi c}(\phi_0^o, c_0^o)c_1^o + g''(\phi_0^o)\phi_2^o + g'''(\phi_0^o)(\phi_1^o)^2/2 \right) = 0 \quad (\text{A.25})$$

The solutions of Eq. (A.23) define the minima of the double well potential function $g(\phi)$, which denote the equilibrium values of the order parameter in the liquid ($\phi_0^o = \phi_s$) and the solid ($\phi_0^o = \phi_L$). These values must remain constant in the solid and liquid far from the interface since no solidification takes place there. The bulk free energy of mixing is constructed such that the order parameter does not change far away from the interface where no phase change is occurring, regardless of the concentration. This requirement is expressed as $f_{,\phi}(\phi_0^o \equiv \{\phi_s, \phi_L\}, c_0^o) = 0$, which implies that $\phi_1^o = 0$ in Eq. (A.24). It is similarly required that the far field chemical potential not depend on the order parameter, i.e. $f_{,\phi c}(\phi_0^o \equiv \{\phi_s, \phi_L\}, c_0^o) = f_{,c\phi}(\phi_0^o \equiv \{\phi_s, \phi_L\}, c_0^o) = 0$. This leads to $\phi_2^o = 0$ in Eq. (A.25). To summarize, the stated constraints on $f(\phi, c)$ lead to:

$$\phi_0^o = \phi_L, \phi_s \quad \eta \rightarrow \pm\infty \quad (\text{A.26})$$

$$\phi_1^o = 0 \quad (\text{A.27})$$

$$\phi_2^o = 0 \quad (\text{A.28})$$

The solutions ϕ_L and ϕ_s will be matched below to the inner solutions of the phase field equation.

Expanding the concentration equation Eq. (A.21) to second order gives the same diffusion equation to all orders in ϵ , namely,

$$\frac{\partial c_j^o}{\partial \bar{t}} = \bar{\nabla} \cdot \{q(\phi_0^o, c_0^o) \bar{\nabla} \mu_j^o\} \quad (\text{A.29})$$

Putting this back in dimensional units (using the scaling for \bar{t} and η given at the beginning of this subsection) and using the fact that $Q(\phi_0^o = \phi_L) = 1$ and $Q(\phi_0^o = \phi_s) = D_s/D_L$ gives

$$\frac{\partial c_j^o}{\partial t} = \nabla \cdot \{M_{L,s} \nabla \mu_j^o\}, \quad \forall j = 0, 1, 2, \dots \quad (\text{A.30})$$

i.e. the usual Fick's law of diffusion in either phase. To summarize, the outer solutions of the phase field Eqs. (A.2) describe standard solute diffusion in the bulk solid and liquid phases and reduce to a constant order parameter far from the interface in either phase.

A.6 Inner Expansion of Phase Field Equations

To perform the inner expansion of Eqs. (A.2), it is instructive to transform these into the curvilinear co-ordinates defined in section (A.2). Substituting Eqs. (A.8), (A.9) and (A.10) into Eqs. (A.2) gives,

$$\begin{aligned} \tau \left(\frac{\partial \phi}{\partial t} - v_n \frac{\partial \phi}{\partial u} + s_{,t} \frac{\partial \phi}{\partial s} \right) &= W_\phi^2 \left(\frac{\partial^2 \phi}{\partial u^2} + \frac{\kappa}{(1+u\kappa)} \frac{\partial \phi}{\partial u} + \frac{1}{(1+u\kappa)^2} \frac{\partial^2 \phi}{\partial s^2} - \frac{u\kappa_{,s}}{(1+u\kappa)^3} \frac{\partial \phi}{\partial s} \right) \\ &- \frac{dg(\phi)}{d\phi} - \epsilon \frac{df(\phi, c)}{d\phi} \end{aligned} \quad (\text{A.31})$$

$$\begin{aligned}
\frac{\partial c}{\partial t} - v_n \frac{\partial c}{\partial u} + s, t \frac{\partial c}{\partial s} &= \frac{\partial}{\partial u} \left(q \frac{\partial \mu}{\partial u} \right) + \frac{q\kappa}{(1+u\kappa)} \frac{\partial \mu}{\partial u} + \frac{1}{(1+u\kappa)^2} \frac{\partial}{\partial s} \left(q \frac{\partial \mu}{\partial s} \right) \\
&- \frac{qu}{(1+u\kappa)^3} \frac{\partial \kappa}{\partial s} \frac{\partial \mu}{\partial s}
\end{aligned} \tag{A.32}$$

To examine the phase field equations Eqs. (A.31) and (A.32) in the inner region, the following re-scaling of space and time are made: $\xi = u/W_\phi$, $\bar{t} = t/(D_L/v_s^2)$. Distance along the arclength is re-scaled according to $\sigma = s/(D_L/v_s)$, since variations along the interface should be more gradual than through the model interface. The dimensionless normal velocity is likewise defined by $\bar{v}_n = v_n/v_s$. These scalings lead to the following relations between some of the other variables which will be used often below in going through the derivations:

$$\begin{aligned}
s &= \frac{W_\phi}{\epsilon} \sigma \\
\kappa &= \frac{\partial \theta}{\partial s} = \frac{\epsilon}{W_\phi} \bar{\kappa} \\
u\kappa &= \epsilon \xi \bar{\kappa} \\
u\kappa, s \frac{\partial}{\partial s} &\equiv u \frac{\partial \kappa}{\partial s} \frac{\partial}{\partial s} = \frac{\epsilon^3}{W_\phi^2} \xi \bar{\kappa}, \sigma \frac{\partial}{\partial \sigma}
\end{aligned} \tag{A.33}$$

where $\bar{\kappa}$ is the dimensionless curvature. Using Eqs. (A.33) to re-scale variables in Eqs. (A.31) and (A.32) gives (retaining terms only to second order in ϵ),

$$\begin{aligned}
\bar{D}\epsilon^2 \frac{\partial \phi}{\partial \bar{t}} - \bar{D}\epsilon \bar{v}_n \frac{\partial \phi}{\partial \xi} + \bar{D}\epsilon^2 \sigma, \bar{t} \frac{\partial \phi}{\partial \sigma} &= \left(\frac{\partial^2 \phi}{\partial \xi^2} + \frac{\epsilon \bar{\kappa}}{(1+\epsilon \xi \bar{\kappa})} \frac{\partial \phi}{\partial \xi} + \frac{\epsilon^2}{(1+\epsilon \xi \bar{\kappa})^2} \frac{\partial^2 \phi}{\partial \sigma^2} \right) \\
&- \frac{dg(\phi)}{d\phi} - \epsilon \frac{df(\phi, c)}{d\phi}
\end{aligned} \tag{A.34}$$

$$\epsilon^2 \frac{\partial c}{\partial \bar{t}} - \epsilon \bar{v}_n \frac{\partial c}{\partial \xi} + \epsilon^2 \sigma, \bar{t} \frac{\partial c}{\partial \sigma} = \frac{\partial c}{\partial \xi} \left(q \frac{\partial \mu}{\partial \xi} \right) + \frac{\epsilon q \bar{\kappa}}{(1+\epsilon \xi \bar{\kappa})} \frac{\partial \mu}{\partial \xi} + \frac{\epsilon^2}{(1+\epsilon \xi \bar{\kappa})^2} \frac{\partial}{\partial \sigma} \left(q \frac{\partial \mu}{\partial \sigma} \right) \tag{A.35}$$

where, again, the a subscript preceded by a comma denotes differentiation with respect to that variable. Note that the last terms in the laplacian expansions of Eqs. (A.9) and (A.10) have been dropped in Eq. (A.34) and Eq. (A.35), respectively, as they are of order ϵ^3 in the re-scaled co-ordinates.

Further simplification can be made to the inner equations by expanding some of the non-linear term in Eqs. (A.34) and (A.35) to order $\mathcal{O}(\epsilon^2)$. Specifically,

$$\begin{aligned}
\frac{\epsilon \bar{\kappa}}{1+\epsilon \xi \bar{\kappa}} &\approx \epsilon \bar{\kappa} - \epsilon^2 \xi \bar{\kappa}^2 \\
\frac{\epsilon^2}{(1+\epsilon \xi \bar{\kappa})^2} &\approx \epsilon^2 (1 - 2\epsilon \xi \bar{\kappa}) \approx \epsilon^2
\end{aligned} \tag{A.36}$$

This gives,

$$\begin{aligned}
\bar{D}\epsilon^2 \frac{\partial \phi}{\partial \bar{t}} - \bar{D}\epsilon \bar{v}_n \frac{\partial \phi}{\partial \xi} + \bar{D}\epsilon^2 \sigma, \bar{t} \frac{\partial \phi}{\partial \sigma} &= \left(\frac{\partial^2 \phi}{\partial \xi^2} + \epsilon \bar{\kappa} \frac{\partial \phi}{\partial \xi} - \epsilon^2 \xi \bar{\kappa}^2 \frac{\partial \phi}{\partial \xi} + \epsilon^2 \frac{\partial^2 \phi}{\partial \sigma^2} \right) \\
&- \frac{dg(\phi)}{d\phi} - \epsilon \frac{df(\phi, c)}{d\phi}
\end{aligned} \tag{A.37}$$

$$\epsilon^2 \frac{\partial c}{\partial t} - \epsilon \bar{v}_n \frac{\partial c}{\partial \xi} + \epsilon^2 \sigma_{,\bar{t}} \frac{\partial c}{\partial \sigma} = \frac{\partial c}{\partial \xi} \left(q \frac{\partial \mu}{\partial \xi} \right) + \epsilon q \bar{\kappa} \frac{\partial \mu}{\partial \xi} - \epsilon^2 \xi \bar{\kappa}^2 q \frac{\partial \mu}{\partial \xi} + \epsilon^2 \frac{\partial}{\partial \sigma} \left(q \frac{\partial \mu}{\partial \sigma} \right) \quad (\text{A.38})$$

The next step arriving at the order by order inner equations for the phase and concentration equations is to; (1) substitute Eqs. (A.16) into the phase and concentration evolution equations (A.37) and (A.38); (2) expand the remaining non-linear terms ($q(\phi, c)$, $g(\phi)$ and $f(\phi, c)$) to order $\mathcal{O}(\epsilon^2)$; (3) collect terms, order by order in ϵ , into separate equations. The second order expansion of $g_{,\phi}(\phi) + \epsilon f_{,\phi}(\phi, c)$ is given by

$$\begin{aligned} -\frac{\partial g(\phi_0^{\text{in}} + \delta\phi^{\text{in}})}{\partial \phi} &= \epsilon \frac{\partial f(\phi_0^{\text{in}} + \delta\phi^{\text{in}}, c_0^{\text{in}} + \delta c^{\text{in}})}{\partial \phi} = -g'(\phi_0^{\circ}) - \epsilon \left(f_{,\phi}(\phi_0^{\circ}, c_0^{\circ}) + g''(\phi_0^{\circ}) \phi_1^{\circ} \right) \\ &- \epsilon^2 \left(f_{,\phi\phi}(\phi_0^{\circ}, c_0^{\circ}) \phi_1^{\circ} + f_{,\phi c}(\phi_0^{\circ}, c_0^{\circ}) c_1^{\circ} + g''(\phi_0^{\circ}) \phi_2^{\circ} + g'''(\phi_0^{\circ}) (\phi_1^{\circ})^2 / 2 \right) \end{aligned} \quad (\text{A.39})$$

where $\delta\phi^{\text{in}} = \epsilon\phi_1^{\text{in}} + \epsilon\phi_2^{\text{in}} + \dots$ and $\delta c^{\text{in}} = \epsilon c_1^{\text{in}} + \epsilon c_2^{\text{in}} + \dots$. Substituting Eq. (A.39) into Eqs. (A.37) and substituting the expansions (A.16) into Eqs. (A.37) and (A.38) gives two lengthy equations, each of which has terms of different powers of ϵ . Equations for ϕ^{in} and c^{in} are given, order by order, as follows:

A.6.1 Inner Expansion of phase field equation A.37 at different orders

$$\mathcal{O}(1) : \quad \frac{\partial^2 \phi_0^{\text{in}}}{\partial \xi^2} - g'(\phi_0^{\text{in}}) = 0 \quad (\text{A.40})$$

$$\mathcal{O}(\epsilon) : \quad \frac{\partial^2 \phi_1^{\text{in}}}{\partial \xi^2} - g''(\phi_0^{\text{in}}) \phi_1^{\text{in}} = -(\bar{D}\bar{v}_0 + \bar{\kappa}) \frac{\partial \phi_0^{\text{in}}}{\partial \xi} + f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \quad (\text{A.41})$$

$$\begin{aligned} \mathcal{O}(\epsilon^2) : \quad \frac{\partial^2 \phi_2^{\text{in}}}{\partial \xi^2} - g''(\phi_0^{\text{in}}) \phi_2^{\text{in}} &= \bar{D} \frac{\partial \phi_0^{\text{in}}}{\partial t} - \frac{\partial^2 \phi_0^{\text{in}}}{\partial \sigma^2} - (\bar{D}\bar{v}_0 + \bar{\kappa}) \frac{\partial \phi_1^{\text{in}}}{\partial \xi} - (\bar{D}\bar{v}_1 - \xi \bar{\kappa}^2) \frac{\partial \phi_0^{\text{in}}}{\partial \xi} \\ &+ f_{,\phi\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} + g'''(\phi_0^{\text{in}}) \frac{(\phi_1^{\text{in}})^2}{2} + f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} \end{aligned} \quad (\text{A.42})$$

Note that the subscript "n" (for normal) has been dropped from the velocity normal to the interface, v_n , to simplify notation.

A.6.2 Inner expansion of concentration equation A.38 at different orders

$$\mathcal{O}(1) : \quad \frac{\partial}{\partial \xi} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_0^{\text{in}}}{\partial \xi} \right) = 0 \quad (\text{A.43})$$

$$\begin{aligned} \mathcal{O}(\epsilon) : \quad \frac{\partial}{\partial \xi} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) &= -\frac{\partial}{\partial \xi} \left(\{ q_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} + q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} \} \frac{\partial \mu_0^{\text{in}}}{\partial \xi} \right) - \bar{v}_0 \frac{\partial c_0^{\text{in}}}{\partial \xi} \\ &- \bar{\kappa} q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_0^{\text{in}}}{\partial \xi} \end{aligned} \quad (\text{A.44})$$

$$\begin{aligned} \mathcal{O}(\epsilon^2) : \quad \frac{\partial}{\partial \xi} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_2^{\text{in}}}{\partial \xi} \right) &= \frac{\partial c_0^{\text{in}}}{\partial t} - \bar{v}_1 \frac{\partial c_0^{\text{in}}}{\partial \xi} + \sigma_{,\bar{t}} \frac{\partial c_0^{\text{in}}}{\partial \sigma} + \xi \bar{\kappa}^2 q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_0^{\text{in}}}{\partial \xi} - \bar{v}_0 \frac{\partial c_1^{\text{in}}}{\partial \xi} \\ &- \bar{\kappa} q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} - \frac{\partial}{\partial \sigma} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_0^{\text{in}}}{\partial \sigma} \right) - \bar{\kappa} \{ q_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} + q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} \} \frac{\partial \mu_0^{\text{in}}}{\partial \xi} \end{aligned} \quad (\text{A.45})$$

$$\begin{aligned}
& -\frac{\partial}{\partial \xi} \left(q_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) - \frac{\partial}{\partial \xi} \left(\left[q_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_2^{\text{in}} + \frac{q_{,\phi\phi}(\phi_0^{\text{in}}, c_0^{\text{in}})}{2} (\phi_1^{\text{in}})^2 \right] \frac{\partial \mu_0^{\text{in}}}{\partial \xi} \right) \\
& -\frac{\partial}{\partial \xi} \left(q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) - \frac{\partial}{\partial \xi} \left(\left[q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_2^{\text{in}} + \frac{q_{,cc}(\phi_0^{\text{in}}, c_0^{\text{in}})}{2} (c_1^{\text{in}})^2 \right] \frac{\partial \mu_0^{\text{in}}}{\partial \xi} \right) \\
& + \partial_\xi \left(q_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} c_1^{\text{in}} \frac{\partial \mu_0^{\text{in}}}{\partial \xi} \right)
\end{aligned}$$

While the last equation looks daunting, it will turn out that most of the terms involving derivatives of μ_0^{in} will vanish when matching the inner and outer equation.

A.6.3 Inner Chemical potential expansion

To proceed further the different order of the chemical potential must also be expanded in terms of the inner concentration and phase fields. The chemical potential is given by

$$\mu = -\epsilon_c^2 \nabla^2 c + \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c)}{\partial c} \quad (\text{A.46})$$

$$\Rightarrow \frac{\mu}{w} = \epsilon \frac{\mu}{\alpha} = -\delta \left(\frac{\partial^2 c}{\partial \xi^2} + \frac{\epsilon \bar{\kappa}}{(1 + \epsilon \xi \bar{\kappa})} \frac{\partial c}{\partial \xi} + \frac{\epsilon^2}{(1 + \epsilon \xi \bar{\kappa})^2} \frac{\partial^2 c}{\partial \sigma^2} \right) + \epsilon \frac{\partial f(\phi, c)}{\partial c} \quad (\text{A.47})$$

where $\epsilon_c = \sqrt{w} W_c$ was used to define $\delta \equiv (W_c/W_\phi)^2$. The term $\nabla^2 c$ in Eq. (A.46) was expressed in (u, s) co-ordinates by using Eq. (A.9), then re-scaled in terms of inner co-ordinates (ξ, σ) using Eqs. (A.33). As with Eq. (A.34), the last term in Eq. (A.9) was dropped as it is of order ϵ^3 . Simplifying Eq. (A.47) using Eq. (A.36) and, once again, retaining only terms up to second order in ϵ , gives,

$$\frac{\mu}{\alpha} = \bar{\delta} \left(-\frac{\partial^2 c}{\partial \xi^2} - \epsilon \bar{\kappa} \frac{\partial c}{\partial \xi} + \epsilon^2 \xi \bar{\kappa}^2 \frac{\partial^2 c}{\partial \xi^2} + \epsilon^2 \frac{\partial^2 c}{\partial \sigma^2} \right) + \frac{\partial f(\phi, c)}{\partial c} \quad (\text{A.48})$$

where $\bar{\delta} \equiv \delta/\epsilon$, which will be assumed, without loss of generality, to be of order unity. Substituting from Eq. (A.16) the expansion for μ^{in} on the left hand side of Eq. (A.47) and $c^{\text{in}}, \phi^{\text{in}}$ on the right hand side, expanding $f(\phi_0^{\text{in}} + \delta \phi^{\text{in}}, c_0^{\text{in}} + \delta c^{\text{in}})$ and collecting terms with like powers of ϵ into separate equations gives,

$$\mathcal{O}(1) : \quad \frac{\mu_0^{\text{in}}}{\alpha} = -\bar{\delta} \frac{\partial^2 c_0^{\text{in}}}{\partial \xi^2} + f_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) \quad (\text{A.49})$$

$$\mathcal{O}(\epsilon) : \quad \frac{\mu_1^{\text{in}}}{\alpha} = -\bar{\delta} \frac{\partial^2 c_1^{\text{in}}}{\partial \xi^2} - \bar{\delta} \bar{\kappa} \frac{\partial c_0^{\text{in}}}{\partial \xi} + f_{,c\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} + f_{,cc}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} \quad (\text{A.50})$$

The $\mathcal{O}(\epsilon^2)$ term for μ is not shown as it will not be required.

A few words are in order about the parameter $\delta \sim W_c^2$, which originates from the term $|\epsilon_c \nabla c|^2$, in the free energy. This term can be used to account for compositional gradients across an interface, while the $|\epsilon_\phi \nabla \phi|^2$ accounts for changes in solid-liquid order [64]. Some phase field theories [14] treat the phase field interface as an artificial construct and rely entirely on W_c (or equivalently ϵ_c) to capture the properties of solute trapping predicted by experiments and sharp-interface models at rapid solidification rates [16]. The work of Ref. [14] assumes that W_c is larger than W_ϕ , although the precise values for W_c are not known. In more recent multi-phase field models [75, 17, 74], multiple phases are modeled using different order parameters (or volume fraction fields), $\{\phi_i\}$. In this case, only terms comprising gradients of the

phase fields are required to fully capture the sharp interface kinetics of solidification at low solidification rates. In what follows both compositional and order parameter gradients will be retained, and $\bar{\delta}$ will be assumed to be of order one, making $W_c/W_\phi \sim \sqrt{\epsilon}$.

A.7 Analysis of Inner Equations and Matching to Outer Fields

The next step in the matched asymptotic analysis is to solve the inner equations for ϕ^{in} , c^{in} and μ^{in} (Eqs. (A.40)-(A.42), Eqs. (A.43)-(A.45) and Eqs. (A.49)-(A.50)) at each order and match their solutions, order by order, to the outer fields ϕ^o and c^o (Eqs. (A.26)-(A.28) and solutions of Eqs. (A.30)) using the matching conditions in Eqs. (A.17), (A.18) and (A.19). The aim of this exercise is to obtain the appropriate boundary conditions that the outer phase field model solutions of satisfy when projected into a hypothetical sharp interface.

A.7.1 $\mathcal{O}(1)$ phase field equation (A.40)

Equation (A.40) can be solved analytically by multiplying both sides of the equation by the $d\phi_0^{\text{in}}/d\xi$ and integrating from a position ξ to ∞ gives,

$$\begin{aligned} \frac{1}{2} \int_{\xi}^{\infty} \frac{\partial}{\partial \xi'} \left(\frac{\partial \phi_0^{\text{in}}}{\partial \xi'} \right)^2 d\xi' - \int_{\xi}^{\infty} \frac{\partial \phi_0^{\text{in}}}{\partial \xi'} \frac{\partial g}{\partial \phi_0^{\text{in}}} d\xi' &= 0 \\ \frac{1}{2} \left(\frac{\partial \phi_0^{\text{in}}}{\partial \xi} \right)^2 - (g(\phi_0^{\text{in}}(\xi)) - g(\phi_0^{\text{in}}(\infty))) &= 0 \end{aligned} \quad (\text{A.51})$$

Inverting Eq. (A.51) gives ϕ_0^{in} through the solution of

$$\int_{\phi_c}^{\phi_0^{\text{in}}} \frac{d\phi_0^{\text{in}}}{\sqrt{2(g(\phi_0^{\text{in}}) - g(\infty))}} = \xi \quad (\text{A.52})$$

where ϕ_c is an integration constant that defines the position of the interface as in Eq. (A.6). It can be chosen to shift the origin of co-ordinates in the boundary layer such that ϕ_0^{in} is an odd function about the origin. The far field (i.e. bulk phase) values of ϕ_0^{in} are determined by the properties of $g(\phi)$ and satisfy, according to the boundary conditions in Eq. (A.19), $\lim_{\xi \rightarrow -\infty} \phi_0^{\text{in}}(\xi) = \phi_s$ and $\lim_{\xi \rightarrow \infty} \phi_0^{\text{in}}(\xi) = \phi_L$.

As an example, consider the choice of $g(\phi) = -\phi^2/2 + \phi^4/4$. Equation (A.52) gives

$$\tanh^{-1}(\phi_0^{\text{in}}) - \tanh^{-1}(\phi_c) = -\frac{\xi}{\sqrt{2}} \quad (\text{A.53})$$

or

$$\phi_0^{\text{in}} = -\tanh\left(\frac{\xi - \xi_0}{\sqrt{2}}\right) \quad (\text{A.54})$$

where

$$\xi_0 = \sqrt{2} \tanh^{-1}(\phi_c) \quad (\text{A.55})$$

For ϕ_0^{in} to be odd about $\xi = 0$, ξ_0 must be zero, which requires that $\phi_c = 0$ (picking ϕ_c such that ϕ_0^{in} be odd about the origin will be required below). In the example considered above, the far field values of the hyperbolic tangent function are $\phi_s = 1$ and $\phi_L = -1$, which define the minima of $g(\phi)$.

A.7.2 $\mathcal{O}(1)$ diffusion equation (A.43)

Integrating Eq. (A.43) gives,

$$\frac{\partial \mu_0^{\text{in}}}{\partial \xi} = \frac{B}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \quad (\text{A.56})$$

where B is an integration constant that may depend of the arclength σ . Integrating Eq. (A.56) once more gives,

$$\mu_0^{\text{in}} = \mu_{\text{E}}(\sigma) + B \int_{-\infty}^{\xi} \frac{d\xi}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \quad (\text{A.57})$$

where $\mu_{\text{E}}(\sigma)$ is a second integration constant, also dependent on the [scaled] arclength σ since integration is with respect to ξ . Since $q(\phi_0^{\text{in}}, c_0^{\text{in}})$ becomes a constant in the liquid, i.e. as $\xi \rightarrow \infty$, the limit $\lim_{\xi \rightarrow \pm\infty} \mu_0^{\text{in}}(\xi) = \mu_{\text{E}} + \lim_{\xi \rightarrow \infty} \int_{-\infty}^{\xi} 1/q(\phi_0^{\text{in}}, c_0^{\text{in}}) d\xi$ will diverge unless $B = 0$. Taking these considerations into account allows the $\mathcal{O}(1)$ expression for the the chemical potential expansion from Eq. (A.49) to be expressed as

$$-\alpha \bar{\delta} \frac{\partial^2 c_0^{\text{in}}}{\partial \xi^2} + \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_0^{\text{in}}, c_0^{\text{in}})}{\partial c} = \mu_0^{\text{in}}(\sigma) \quad (\text{A.58})$$

where the notation $\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_0^{\text{in}}, c_0^{\text{in}})/\partial c \equiv \partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c)/\partial c|_{\phi_0^{\text{in}}, c_0^{\text{in}}}$ will be used hereafter. The lowest order chemical potential in the interface is thus a constant dependent on curvature. Equation (A.58) can be solved (or inverted if $\bar{\delta} = 0$) to give the spatial dependent of $c_0^{\text{in}}(\xi)$ through the interface once $\mu_0^{\text{in}}(\sigma)$ and the far field –bulk– values of $c_0^{\text{in}}(\pm\infty)$ are determined.

The far-field values of $c_0^{\text{in}}(\xi)$ are determined as follows. Consider Eqs. (A.17) and define $c_L \equiv \lim_{\eta \rightarrow 0^+} c_0^o(\eta)$, and $c_s \equiv \lim_{\eta \rightarrow 0^-} c_0^o(\eta)$, where $c_L(c_s)$ correspond to the lowest order outer concentration field, $c_0^o(\eta)$, projected onto the liquid/ 0^+ (solid/ 0^-) sides of the interface defined by $\phi = 0$. The first of Eqs. (A.17) implies that $\lim_{\xi \rightarrow \infty} c_0^{\text{in}}(\xi) = c_L$ and $\lim_{\xi \rightarrow -\infty} c_0^{\text{in}}(\xi) = c_s$. Moreover, since $c_0^{\text{in}}(\xi)$ asymptotes to constant far field values far from the interface, $\partial^2 c_0^{\text{in}}/\partial \xi^2 \rightarrow 0$ and $\partial c_0^{\text{in}}/\partial \xi \rightarrow 0$ as $\xi \rightarrow \mp\infty$. Similarly, the first of Eqs. (A.18) requires that

$$\lim_{\xi \rightarrow \pm\infty} \mu_0^{\text{in}} \equiv \mu_0^{\text{in}}(\sigma) = \lim_{\eta \rightarrow 0^\pm} \mu_0^o(\eta) \equiv \mu_0^o(0^\pm), \quad (\text{A.59})$$

where $\mu_0^o(0^\pm)$ is the lowest order chemical potential of the outer field projected onto the solid/liquid sides of the sharp interface; it is a constant that depends on the local curvature. Implementing these considerations in the $\xi \rightarrow \pm\infty$ limits of Eq. (A.58) gives,

$$\frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s)}{\partial c} = \mu_0^{\text{in}}(\sigma) = \mu_0^o(0^\pm) \quad (\text{A.60})$$

$$\frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L)}{\partial c} = \mu_0^{\text{in}}(\sigma) = \mu_0^o(0^\pm) \quad (\text{A.61})$$

Once $\mu_0^o(0^\pm)$ is known, c_s and c_L can be determined. In the case of a flat stationary interface $\mu^o(0^\pm) \rightarrow \mu_{\text{eq}}^{\text{F}}$, which can be determined from equilibrium thermodynamics. For Eqs. (A.60)-(A.61) to be self consistent for curved and moving interfaces, they must be supplemented by an additional equation, which relates $\mu_0^o(0^\pm)$ to $\bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s)$, $\bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L)$ and curvature [181, 175]. This is given by the lowest order Gibbs-Thomson condition, derived in the next subsection (see Eq. (A.68) or, equivalently, Eq. (A.72)).

A.7.3 $\mathcal{O}(\epsilon)$ phase field equation (A.41)

The $\mathcal{O}(\epsilon)$ equation for ϕ^{in} is simplified by first multiplied by $\partial\phi_0^{\text{in}}/d\xi$ and integrated from $\xi \rightarrow -\infty$ to ∞ , giving

$$\int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} \mathcal{L}(\phi_1^{\text{in}}) d\xi = -(\bar{D}\bar{v}_0 + \bar{\kappa}) \int_{-\infty}^{\infty} \left(\frac{\partial\phi_0^{\text{in}}}{\partial\xi} \right)^2 d\xi + \int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) d\xi \quad (\text{A.62})$$

where $\mathcal{L} \equiv \partial_{\xi\xi} - g''(\phi_0^{\text{in}})$ and the double prime on $g(\phi)$ denotes a double derivative with respect to ϕ . Integrating the integral on the left hand side of Eq. (A.62) by parts to give

$$\int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} \mathcal{L}(\phi_1^{\text{in}}) d\xi = \int_{-\infty}^{\infty} \frac{\partial\phi_1^{\text{in}}}{\partial\xi} \left(\frac{\partial^2\phi_0^{\text{in}}}{\partial\xi^2} - g'(\phi_0^{\text{in}}) \right) d\xi = 0 \quad (\text{A.63})$$

where the last equality comes from Eq. (A.40). The first integral on the right hand side of Eq. (A.62) will prove to hold a special significance and is denoted as

$$\sigma_{\phi} \equiv \int_{-\infty}^{\infty} \left(\frac{\partial\phi_0^{\text{in}}}{\partial\xi} \right)^2 d\xi \quad (\text{A.64})$$

The second integral on the right hand side of Eq. (A.62) can be simplified by re-writing it as

$$\int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) d\xi = \int_{-\infty}^{\infty} \frac{\partial f(\phi_0^{\text{in}}, c_0^{\text{in}})}{\partial\xi} - \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial\xi} f_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) d\xi \quad (\text{A.65})$$

$$= \frac{\{\bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L) - \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s)\}}{\alpha} - \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial\xi} \left\{ \frac{\mu_0^{\text{in}}}{\alpha} + \bar{\delta} \frac{\partial^2 c_0^{\text{in}}}{\partial\xi^2} \right\} d\xi \quad (\text{A.66})$$

where Eq. (A.49) was used to substitute $f_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}})$ in the second integral on the right hand side of Eq. (A.65). The last integral in Eq. (A.66) gives

$$\bar{\delta} \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial\xi} \frac{\partial^2 c_0^{\text{in}}}{\partial\xi^2} d\xi = 0 \quad (\text{A.67})$$

as can be seen by integrating once by parts and using far field values of $\partial c_0^{\text{in}}/\partial\xi = 0$. The results of Eqs. (A.64), (A.66) and (A.67) reduce Eq. (A.62) to

$$\frac{\mu_0^o(0^{\pm})}{\alpha} = \frac{\{\bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L) - \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s)\}}{\alpha\Delta c} - (\bar{D}\bar{v}_0 + \bar{\kappa}) \frac{\sigma_{\phi}}{\Delta c} \quad (\text{A.68})$$

where $\Delta c \equiv (c_L - c_s)$ and the first of the matching conditions in Eqs. (A.18) was used to replace $\mu_0^{\text{in}} = \mu_0^o(0^{\pm})$. Equations (A.60), (A.61) and (A.68) comprise a closed system of non-linear equations that can be solved for $\{c_s, c_L, \mu_0^o(0^{\pm})\}$.

Equation (A.68) can be simplified into the lowest order form of the Gibb's Thomson condition, which relates the deviation of $\mu_0^o(0^{\pm})$ from its equilibrium value due to curvature and velocity. This is done by first expanding $\bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L)$ and $\bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s)$, respectively, in a Taylor series about $c_L = c_L^{\text{F}}$ and $c_s = c_s^{\text{F}}$, the respective equilibrium liquid and solid concentrations corresponding to a flat stationary interface. These expansions lead to

$$\bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L) - \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s) \approx \left\{ \bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L^{\text{F}}) + \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L^{\text{F}})}{\partial c} (c_L - c_L^{\text{F}}) \right\} - \left\{ \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s^{\text{F}}) + \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s^{\text{F}})}{\partial c} (c_s - c_s^{\text{F}}) \right\} \quad (\text{A.69})$$

Use is then made of equilibrium conditions

$$\mu_{\text{eq}}^{\text{F}} = \frac{\bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L^{\text{F}}) - \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s^{\text{F}})}{c_L^{\text{F}} - c_s^{\text{F}}} = \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s^{\text{F}})}{\partial c} = \frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L^{\text{F}})}{\partial c} \quad (\text{A.70})$$

where $\mu_{\text{eq}}^{\text{F}}$ is the chemical potential of a flat stationary interface. Substituting Eq. (A.69) and Eq. (A.70) into Eq. (A.68) gives

$$\mu_0^o(0^\pm) = \mu_{\text{eq}}^{\text{F}} - \frac{\bar{D}\alpha\sigma_\phi}{\Delta c}\bar{v}_0 - \frac{\sigma_\phi\alpha}{\Delta c}\bar{\kappa} \quad (\text{A.71})$$

Equation (A.71) is put into dimensional form by utilizing the scalings and definitions found in Eqs. (A.11), (A.12), (A.13) and (A.33); first write velocity as $\bar{v}_0 = (d_o/D_L)v_0^{\text{dim}}$ (where "dim" implies dimensional) and curvature by $\bar{\kappa} = (W_\phi/\epsilon)\kappa^{\text{dim}}$. Then use the definition of the length scale d_o from Eq. (A.11) and note that $\alpha/\epsilon = w = 1/\lambda$ (deduced from Eq. (A.13)). This finally gives,

$$\mu_0^o(0^\pm) = \mu_{\text{eq}}^{\text{F}} - \left(\frac{\sigma_\phi}{\Delta c}\right)\left(\frac{W_\phi}{\lambda}\right)\kappa - \left(\frac{\sigma_\phi}{\Delta c}\right)\left(\frac{\tau}{\lambda W_\phi}\right)v_0 \quad (\text{A.72})$$

where the superscript "dim" are implied in Eq. (A.72). It should be noted that the concentration jump Δc is related to that of a flat stationary interface by $\Delta c = \Delta c_F(1 + \delta c)$ where $\delta c \equiv \Delta c/\Delta c_F - 1$ with $\Delta c_F \equiv c_L^{\text{F}} - c_s^{\text{F}}$. The deviation of Δc from Δc_F is on the order of $W_\phi\kappa \sim \epsilon \ll 1$. As a result, to $\mathcal{O}(\epsilon)$ it is reasonable to approximate $\Delta c \approx \Delta c_F$. Equation (A.72) is the first order Gibbs-Thomson condition satisfied by the outer chemical potential field at the interface. The second order correction to this expression is derived below.

A.7.4 $\mathcal{O}(\epsilon)$ diffusion equation (A.44)

Equation (A.44) is greatly simplified by observing that the μ_0^{in} dependence vanished as it does not depend on ξ . The surviving equation is thus

$$\frac{\partial}{\partial \xi} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) = -\bar{v}_0 \frac{\partial c_0^{\text{in}}}{\partial \xi} \quad (\text{A.73})$$

Integrating Eq. (A.73) from $\xi \rightarrow -\infty$ to ξ gives,

$$q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} = -\bar{v}_0 c_0^{\text{in}}(\xi) + A \quad (\text{A.74})$$

The integration constant A is found by considering the $\xi \rightarrow -\infty$ limit of Eq. (A.74) and by assuming that $Q(\phi(\xi \rightarrow -\infty)) = Q(\phi_s) = D_s/D_L \approx 0$. With this assumption the boundary condition

$$\lim_{\xi \rightarrow -\infty} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) = 0 = -\bar{v}_0 c_0^{\text{in}}(-\infty) + A \quad (\text{A.75})$$

gives $A = \bar{v}_0 c_s$ where $\lim_{\xi \rightarrow -\infty} c_0^{\text{in}}(\xi) = c_s$ has been used. Integrating Equation (A.74) once thus gives

$$\mu_1^{\text{in}} = -\bar{v}_0 \int_0^\xi \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx + \bar{\mu} \quad (\text{A.76})$$

where $\bar{\mu}$ is an integration constant to be determined below. It should be noted that that D_s/D_L actually ranges from $10^{-4} - 10^{-2}$ for most metals during solidification. However, what matters is that diffusion in the solid over most of the relevant solidification time behaves as if it was zero. This situation can be practically emulated by setting $D_s/D_L = 0$ throughout. Of course, in this case, the solution of μ_1^{in} may diverge if the numerator in the integral of Eq. (A.76) vanishes more slowly than $q(\phi_0^{\text{in}}, c_0^{\text{in}})$ in the overlap region (i.e. $1 \ll \xi \ll 1/\epsilon$). It will thus be assumed that $q(\phi_0^{\text{in}}, c_0^{\text{in}})$ can be chosen such that as $\xi \rightarrow -\infty$, the function $[c_0^{\text{in}}(\xi) - c_s]$ vanishes more quickly than $q(\phi_0^{\text{in}}, c_0^{\text{in}}) \rightarrow q(\phi_s, c_s) \equiv q^- \approx 0$. It will also be shown later that certain classes of phase field models that use a so-called *anti-trapping flux* in the mass transport equations can be constructed so as to assure this condition [57].

It is instructive to split Eq. (A.76) into two pieces, one valid for $\xi < 0$ and the other for $\xi > 0$,

$$\mu_1^{\text{in}} = -\bar{v}_0 \int_0^\xi \left\{ \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} - \frac{[c_L - c_s]}{q^+} \right\} dx - \frac{\bar{v}_0(c_L - c_s)}{q^+} \xi + \bar{\mu}, \quad \xi > 0 \quad (\text{A.77})$$

$$\mu_1^{\text{in}} = \bar{v}_0 \int_\xi^0 \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx + \bar{\mu}, \quad \xi < 0 \quad (\text{A.78})$$

where the notation

$$q^+ \equiv q(\phi_L, c_L) \quad (\text{A.79})$$

has been defined to simplify the notation. In terms of Eqs. (A.77) and (A.78), the far field ($|\xi| \gg 1$) limits of Eq. (A.76) become,

$$\lim_{\xi \rightarrow \infty} \mu_1^{\text{in}} = \bar{v}_0 \int_0^\infty \left\{ \frac{\Delta c}{q^+} - \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \right\} dx - \frac{\bar{v}_0 \Delta c}{q^+} \xi + \bar{\mu} \quad (\text{A.80})$$

$$\lim_{\xi \rightarrow -\infty} \mu_1^{\text{in}} = \bar{v} \int_{-\infty}^0 \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx + \bar{\mu} \quad (\text{A.81})$$

Using Eqs. (A.80) and (A.81) in the second matching condition of Eqs. (A.18) gives

$$\mu_1^o(0^+) + \frac{\partial \mu_0^o(0^+)}{\partial \eta} \xi = \bar{\mu} + \bar{v}_0 F^+ - \frac{\bar{v}_0 \Delta c}{q^+} \xi \quad (\text{A.82})$$

$$\mu_1^o(0^-) + \frac{\partial \mu_0^o(0^-)}{\partial \eta} \xi = \bar{\mu} + \bar{v}_0 F^- \quad (\text{A.83})$$

where the definitions

$$F^+ = \int_0^\infty \left\{ \frac{\Delta c}{q^+} - \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \right\} dx$$

$$F^- = \int_{-\infty}^0 \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx \quad (\text{A.84})$$

have been made to further simplify notation.

Subtracting Equation (A.83) from Eq. (A.82) and comparing powers of ξ^0 of the result gives,

$$\mu_1^o(0^+) - \mu_1^o(0^-) = (F^+ - F^-)\bar{v}_0 \quad (\text{A.85})$$

Equation (A.85) can be made more illuminating by expressing $\mu^o \approx \mu_0^o + \epsilon\mu_1^o + \dots$ with $\mu_0^o(0^-) = \mu_0^o(0^-)$ and replacing $\epsilon = W_\phi v_s/D_L$ and $\bar{v}_0 = v_0/v_s$. This gives,

$$\epsilon\mu_1^o(0^+) - \epsilon\mu_1^o(0^-) = \frac{W_\phi}{D_L}(F^+ - F^-)v_0 \quad (\text{A.86})$$

Equation (A.85) predicts that to an error of $\mathcal{O}(\epsilon^2)$, a finite size of interface thickness (W_ϕ) gives rise to a jump discontinuity in the chemical potential for moving interfaces. This effect lies at the heart of solute trapping.

Comparing powers of ξ in Eq. (A.83) and Eq. (A.82) gives,

$$q^+ \frac{\partial \mu_0^o(0^+)}{\partial \eta} = -\bar{v}_0 \Delta c \quad (\text{A.87})$$

and $\partial_\eta \mu_0^o(0^-) = 0$. Equation (A.87) is cast into dimensional units by substituting $\bar{v}_0 = v_0/v_s$ and $\eta = v_s u/D_L$, which leads to

$$D_L q^+ \frac{\partial \mu_0^o(0^+)}{\partial u} = -\Delta c v_0 \quad (\text{A.88})$$

Equation (A.88) is the usual condition of mass flux conservation across the solid-liquid interface, to first order in ϵ . This equation will be augmented with additional terms that appear at order ϵ^2 below.

It is instructive to conclude this section with a few words about the case of a finite q^- . It is straightforward to re-work the steps in this subsection to show that in this situation the flux conservation condition becomes,

$$q^- \frac{\partial \mu_0^o(0^-)}{\partial \eta} - q^+ \frac{\partial \mu_0^o(0^+)}{\partial \eta} = \bar{v}_0 \Delta c \quad (\text{A.89})$$

In the limit $q^- \ll 1$, Eq. (A.87) is again recovered. The $q^- \neq 0$ case now introduces an additional correction term in chemical potential jump in Eq. (A.85), which depends on the gradient of the chemical potential arising from the boundary condition in Eq. (A.75). Namely,

$$\mu_1^o(0^+) - \mu_1^o(0^-) = (F^+ - F^-)\bar{v}_0 - q^- \frac{\partial \mu_0^o(0^-)}{\partial \eta} (G^+ - G^-) \quad (\text{A.90})$$

where G^+ and G^- are defined by

$$\begin{aligned} G^+ &= \int_{-\infty}^0 \left(\frac{1}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} - \frac{1}{q^+} \right) dx \\ G^- &= \int_{-\infty}^0 \left(\frac{1}{q^-} - \frac{1}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \right) dx \end{aligned} \quad (\text{A.91})$$

As in Eq. (A.86), both correction terms vanish as $W_\phi \rightarrow 0$. To eliminate the chemical potential mismatch for a diffuse W_ϕ , it is necessary to simultaneously make $\Delta F \equiv F^+ - F^-$ and $\Delta G \equiv G^+ - G^-$ vanish, in general a very difficult task⁴. For simpler to consider the limit of the one-sided model $q^- \partial_\eta \mu_0^o(0^-) \rightarrow 0$, making the second term on the right hand side of Eq. (A.90) vanish.

⁴These "corrections" actually represent physical deviations from the usual interface equilibrium that become manifest at high solidification rates, since W_ϕ is small in reality. At low solidification rates, however, where an artificially enlarged W_ϕ is used for numerical expediency, these terms can cause spurious effects and, hence, need to be eliminated.

A.7.5 $\mathcal{O}(\epsilon^2)$ phase field equation (A.42)

Equation (A.42) is simplified, analogously with Eq. (A.41), by multiplying by $\partial\phi_0^{\text{in}}/\partial\xi$ and integrating from $\xi = -\infty$ to $\xi = \infty$. Dropping the ϕ_0^{in} terms dependent on \bar{t} and σ gives,

$$\begin{aligned} \int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} \mathcal{L}(\phi_2^{\text{in}}) dx &= -\bar{D}\bar{v}_1 \int_{-\infty}^{\infty} \left(\frac{\partial\phi_0^{\text{in}}}{\partial\xi} \right)^2 dx + \int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} \{f_{,\phi\phi}(\phi_0^{\text{in}}, c_0^{\text{in}})\phi_1^{\text{in}} + f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}})c_1^{\text{in}}\} d\xi \quad (\text{A.92}) \\ &- (\bar{D}\bar{v}_0 + \bar{\kappa}) \int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} \frac{\partial\phi_1^{\text{in}}}{\partial\xi} + \bar{\kappa}^2 \int_{-\infty}^{\infty} \xi \left(\frac{\partial\phi_0^{\text{in}}}{\partial\xi} \right)^2 d\xi + \frac{1}{2} \int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} g'''(\phi_0^{\text{in}})(\phi_1^{\text{in}})^2 d\xi \end{aligned}$$

As in Section (A.41), the left hand side of Eq. (A.92) is zero as the integrand can be converted through integration by parts to $\phi_2^{\text{in}}\mathcal{L}(\phi_0^{\text{in}}) = 0$. All terms on the second line of Eq. (A.92) also vanish. To see this it is first instructive investigate the properties of ϕ_1^{in} from the $\mathcal{O}(\epsilon)$ phase field equation

$$\mathcal{L}(\phi_1^{\text{in}}) = -(\bar{D}\bar{v}_0 + \bar{\kappa}) \frac{\partial\phi_0^{\text{in}}}{\partial\xi} + f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \quad (\text{A.93})$$

The requirement that ϕ_0^{in} be anti-symmetric or odd in ξ about the origin –which can be done through the choice of ϕ_{c-} guarantees that $\partial\phi_0^{\text{in}}/\partial\xi$ is an even function in ξ . Moreover, in following the approaches used in quantitative phase field modeling [120, 112, 57, 221, 118], the bulk free energies considered here will be assumed to satisfy $f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) = GP_{,\phi}(\phi_0^{\text{in}})$, where G is independent of ξ and $P(\phi)$ is chosen to be an odd function of ϕ ⁵. Choosing $g(\phi)$ to be an even function of ϕ , makes the operator \mathcal{L} even in ξ since $g''(\phi_0^{\text{in}}(\xi))$ is even in ξ . Since both sides of Eq (A.93) are even in ξ , $\phi_1^{\text{in}}(\xi)$ must thus be an even function of ξ . These considerations imply that the third and fourth integrals on the right hand side of Eq. (A.92) are zero as they are integrals of an even functions multiplied by an odd function. Similarly the last integral on the right hand side of Eq (A.92) vanishes, as its integrand is odd in ξ (i.e., even function \times odd function \times even function). With these simplifications, Eq. (A.92) thus reduces to

$$-\bar{D}\sigma_\phi\bar{v}_1 + \int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} \{f_{,\phi\phi}(\phi_0^{\text{in}}, c_0^{\text{in}})\phi_1^{\text{in}} + f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}})c_1^{\text{in}}\} d\xi = 0 \quad (\text{A.94})$$

The integral term in Eq. (A.94) can be further simplified. Consider, first, the expression

$$T_1 \equiv \int_{-\infty}^{\infty} \left(\frac{\partial\phi_0^{\text{in}}}{\partial\xi} f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}})c_1^{\text{in}} - \frac{\partial c_0^{\text{in}}}{\partial\xi} f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}})\phi_1^{\text{in}} \right) d\xi \quad (\text{A.95})$$

Equation (A.50) can be used to eliminate the $f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}})\phi_1^{\text{in}}$ term from the second term on the right hand side of Eq. (A.95). This gives,

$$\begin{aligned} T_1 &= \int_{-\infty}^{\infty} \frac{\partial\phi_0^{\text{in}}}{\partial\xi} f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}})c_1^{\text{in}} d\xi - \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial\xi} \frac{\mu_1^{\text{in}}}{\alpha} d\xi - \bar{\delta}\bar{\kappa}\sigma_c \\ &- \bar{\delta} \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial\xi} \frac{\partial^2 c_1^{\text{in}}}{\partial\xi^2} c_1^{\text{in}} d\xi + \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial\xi} f_{,cc}(\phi_0^{\text{in}}, c_0^{\text{in}})c_1^{\text{in}} \xi d\xi \quad (\text{A.96}) \end{aligned}$$

⁵This restriction can still accommodate a large class of models. It also is quite convenient feature for quantitative phase field modeling since for flat stationary interfaces, where c_0^{in} becomes independent of curvature and interface velocity, it makes the function $f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}})$ vanish. Thus, for this class of free energies, the concentration and phase field completely decouple at steady state.

were

$$\sigma_c \equiv \int_{-\infty}^{\infty} \left(\frac{\partial c_0^{\text{in}}}{\partial \xi} \right)^2 d\xi \quad (\text{A.97})$$

Integrating the last two terms in Eq. (A.96) by parts once yields, for the first,

$$-\bar{\delta} \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial \xi} \frac{\partial^2 c_1^{\text{in}}}{\partial \xi^2} d\xi = \bar{\delta} \int_{-\infty}^{\infty} \frac{\partial c_1^{\text{in}}}{\partial \xi} \frac{\partial^2 c_0^{\text{in}}}{\partial \xi^2} d\xi \quad (\text{A.98})$$

while the second term becomes,

$$\begin{aligned} \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial \xi} f_{,cc}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} d\xi &= \int_{-\infty}^{\infty} c_1^{\text{in}} \frac{\partial f_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}})}{\partial \xi} d\xi - \int_{-\infty}^{\infty} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} d\xi \\ &= [c_1^{\text{in}}(\infty) f_{,c}(\phi_L, c_L) - c_1^{\text{in}}(-\infty) f_{,c}(\phi_s, c_s)] - \int_{-\infty}^{\infty} \frac{\partial c_1^{\text{in}}}{\partial \xi} f_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) d\xi \\ &\quad - \int_{-\infty}^{\infty} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} d\xi \end{aligned} \quad (\text{A.99})$$

Substituting Eqs. (A.98) and (A.99) back into Eq. (A.96) and making the replacement $f_{,c}(\phi_L, c_L) = f_{,c}(\phi_s, c_s) = \mu_0^o(0^\pm)/\alpha = (-\bar{\delta} \partial^2 c_0^{\text{in}}/\partial \xi^2 + f_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}))$ gives

$$T_1 = - \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial \xi} \frac{\mu_1^{\text{in}}}{\alpha} d\xi - \bar{\delta} \sigma_c \bar{\kappa} \quad (\text{A.100})$$

Comparing T_1 in Eq. (A.100) with that in Eq. (A.95) gives,

$$\int_{-\infty}^{\infty} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} = - \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial \xi} \frac{\mu_1^{\text{in}}}{\alpha} d\xi - \bar{\delta} \sigma_c \bar{\kappa} + \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial \xi} f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} d\xi \quad (\text{A.101})$$

Substituting the left hand side of Eq. (A.101) into Eq. (A.94) gives,

$$-\bar{D} \sigma_\phi \bar{v}_1 - \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial \xi} \frac{\mu_1^{\text{in}}}{\alpha} d\xi - \bar{\delta} \sigma_c \bar{\kappa} + \int_{-\infty}^{\infty} \frac{\partial f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}})}{\partial \xi} \phi_1^{\text{in}} d\xi = 0 \quad (\text{A.102})$$

where the decomposition $\partial f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}})/\partial \xi = (\partial \phi_0^{\text{in}}/\partial \xi) f_{,\phi\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) + (\partial c_0^{\text{in}}/\partial \xi) f_{,\phi c}(\phi_0^{\text{in}}, c_0^{\text{in}})$ was used in arriving at Eq. (A.102).

Proceeding further, Eq. (A.76) is used to eliminate μ_1^{in} in Eq. (A.102). Moreover, from the discussion of the symmetry properties of ϕ_0^{in} and ϕ_1^{in} , the last term vanishes. With these simplification, Eq. (A.102) reduces to

$$\bar{D} \sigma_\phi \bar{v}_1 + \bar{\delta} \sigma_c \bar{\kappa} - \frac{\bar{v}_0}{\alpha} K + \frac{\bar{\mu}}{\alpha} \Delta c = 0 \quad (\text{A.103})$$

where

$$K = \int_{-\infty}^{\infty} \frac{\partial c_0^{\text{in}}}{\partial \xi} \left\{ \int_0^\xi \frac{c_0^{\text{in}}(x) - c_s}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx \right\} d\xi \quad (\text{A.104})$$

Using Eq. (A.82) and Eq. (A.83) to eliminate $\bar{\mu}$ finally leads to

$$\mu_1^o(0^\pm) = - \frac{\alpha \bar{\delta} \sigma_c}{\Delta c} \bar{\kappa} - \frac{\alpha \bar{D} \sigma_\phi}{\Delta c} \bar{v}_1 + \frac{K + F^\pm \Delta c}{\Delta c} \bar{v}_0 \quad (\text{A.105})$$

It is noteworthy that $\mu_1^o(0)$, unlike $\mu_0^o(0)$, is *not* the same on either side of the interface, i.e. there is a chemical potential jump proportional to $\Delta F \equiv F^+ - F^-$ at the interface. This is a direct consequence of the finite size of the interface (W_ϕ) and leads to the physical phenomenon of solute trapping.

It is instructive to re-cast $\epsilon\mu_1^o$ into dimensional form by utilizing the scalings and definitions found in Eqs. (A.11), (A.12), (A.13) and (A.33), giving

$$\epsilon\mu_1^o(0^\pm) = -\frac{\delta\sigma_c W_\phi}{\Delta c} \kappa + \frac{K + F^\pm \Delta c}{\Delta c} \frac{W_\phi}{D_L} v_0 - \frac{\tau\sigma_\phi}{W_\phi \lambda \Delta c} \epsilon v_1 \quad (\text{A.106})$$

Since $\mu^o \approx \mu_0^o + \epsilon\mu_1^o + \mathcal{O}(\epsilon^3)$, Eq. (A.106) and Eq. (A.72) can be combined to obtain the $\mathcal{O}(\epsilon^2)$ correction to Gibbs-Thomson correction,

$$\delta\mu^o(0^\pm) \equiv \mu^o(0^\pm) - \mu_{\text{eq}}^F = -\frac{(\sigma_\phi + \delta\sigma_c) W_\phi}{\Delta c} \frac{1}{\lambda} \kappa - \frac{\tau\sigma_\phi}{W_\phi \lambda \Delta c} \left\{ 1 - \frac{(K + F^\pm \Delta c) \lambda}{\sigma_\phi \bar{D}} \right\} v_0 - \frac{\tau\sigma_\phi}{W_\phi \lambda \Delta c} \epsilon v_1 \quad (\text{A.107})$$

Note that the last $\mathcal{O}(\epsilon)$ term should receive a second contribution identical to the $(K + F^\pm \Delta c)$ term of the v_0 term if the asymptotic expansion is carried out to $\mathcal{O}(\epsilon^3)$. It appeared because the interface velocity $v_n(s, t)$ was expanded as in Ref. ([8]).

For the case $q^- \neq 0$ the Gibbs-Thomson Eq. (A.107) will contain an additional correction brought about by the additional G^+ and G^- corrections to μ_1^{in} , discussed in section (A.7.4). Working out and substituting the revised form of μ_1^{in} into Eq. (A.102), it is straightforward to show that Eq. (A.107) will contain the extra term

$$\mu_{\text{extra}}^o = \left\{ \frac{\Delta F}{\Delta c} + [G^+ - G^\pm] \right\} q^- \frac{\partial \mu_0^o(0^-)}{\partial \eta} \quad (\text{A.108})$$

on the right hand side. As discussed above, things become simpler, without losing generality, if the one-sided diffusion is considered, where $q^- \partial_{,\eta} \mu_0^o \rightarrow 0$ is considered, making this extra correction term negligible.

A.7.6 $\mathcal{O}(\epsilon^2)$ diffusion equation (A.45)

The final phase in the asymptotic expansion is to extend the flux conservation condition, Eq. (A.88) to include second order ϵ corrections, as was done for the Gibbs-Thomson condition in the last subsection. Using what has been determined about μ_0^{in} , ϕ_0^{in} and c_0^{in} , the $\mathcal{O}(\epsilon^2)$ concentration equation (A.45) reads

$$\begin{aligned} \frac{\partial}{\partial \xi} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_2^{\text{in}}}{\partial \xi} \right) &= -\bar{v}_1 \frac{\partial c_0^{\text{in}}}{\partial \xi} - \bar{v}_0 \frac{\partial c_1^{\text{in}}}{\partial \xi} - \bar{\kappa} q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} - \frac{\partial}{\partial \sigma} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_0^{\text{in}}}{\partial \sigma} \right) \\ &\quad - \frac{\partial}{\partial \xi} \left(q_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) - \frac{\partial}{\partial \xi} \left(q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) \end{aligned} \quad (\text{A.109})$$

Substituting $q(\phi_0^{\text{in}}, c_0^{\text{in}}) \partial \mu_1^{\text{in}} / \partial \xi = -\bar{v}_0 (c_0^{\text{in}}(\xi) - c_s)$ from Eq. (A.76) (for the $q^- = 0$ case) and integrating once with respect to ξ gives,

$$\begin{aligned} q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_2^{\text{in}}}{\partial \xi} &= -\bar{v}_1 c_0^{\text{in}}(\xi) - \bar{v}_0 c_1^{\text{in}}(\xi) + \bar{\kappa} \bar{v}_0 \int_0^\xi [c_0^{\text{in}}(\xi) - c_s] dx - \frac{\partial^2 \mu_0^{\text{in}}}{\partial \sigma^2} \int_0^\xi q(\phi_0^{\text{in}}, c_0^{\text{in}}) dx \\ &\quad - \{ q_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} + q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} \} \frac{\partial \mu_1^{\text{in}}}{\partial \xi} + B(\sigma) \end{aligned} \quad (\text{A.110})$$

Where $B(\sigma)$ is an integration constant that depends on the [scaled] arc-length variable σ .

It is not necessary to explicitly determine μ_2^{in} . Instead the $\xi \rightarrow \pm\infty$ limits (i.e. solid/liquid) limits of Eq. (A.110) only need be considered. Several terms in Eq. (A.110) can be greatly simplified in this limit. From the definition of $q(\phi, c)$ (Eq. (A.4)), the expression $q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) = -Z(c_0^{\text{in}})q(\phi_0^{\text{in}}, c_0^{\text{in}})$, where $Z(c) \equiv \partial_{,cc}\mu/\partial_{,c}\mu$ where $\mu \equiv \partial f_{\text{AB}}^{\text{mix}}/\partial c$ ⁶. This implies, using Eq. (A.75), that $q_{,c}\partial\mu_1^{\text{in}}/\partial\xi \rightarrow 0$ as $\xi \rightarrow -\infty$ since $\lim_{\xi \rightarrow -\infty} q(\phi_0^{\text{in}}, c_0^{\text{in}}) \rightarrow q^- = 0$. Also, from the matching conditions between the inner and out phase field solutions, $\lim_{\xi \rightarrow \pm\infty} \phi_1^{\text{in}}(\xi) = 0$. With these simplifications the $\xi \rightarrow -\infty$ limit of Eq. (A.110) becomes

$$\begin{aligned} \lim_{\xi \rightarrow -\infty} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial\mu_2^{\text{in}}}{\partial\xi} \right) = 0 &= -\bar{v}_1 c_s - \bar{v}_0 \left\{ \lim_{\xi \rightarrow -\infty} c_1^{\text{in}}(\xi) \right\} - \bar{\kappa}\bar{v}_0 \int_{-\infty}^0 (c_0^{\text{in}}(x) - c_s) dx \\ &+ \frac{\partial^2\mu_0^{\text{in}}}{\partial\sigma^2} \int_{-\infty}^0 dx q(\phi_0^{\text{in}}, c_0^{\text{in}}) + B(\sigma) \end{aligned} \quad (\text{A.111})$$

Analogously, the $\xi \rightarrow \infty$ limit is

$$\begin{aligned} \lim_{\xi \rightarrow \infty} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial\mu_2^{\text{in}}}{\partial\xi} \right) &= q^+ \frac{\partial\mu_1^o(0^+)}{\partial\eta} + q^+ \frac{\partial^2\mu_0^o(0^+)}{\partial\eta^2} \xi \\ &= -\bar{v}_1 c_L - \lim_{\xi \rightarrow \infty} [\{\bar{v}_0 - Z(c_L)q^+\partial_{,\eta}\mu_0^o(0^+)\} c_1^{\text{in}}(\xi)] + \bar{\kappa}\bar{v}_0 \int_0^\infty dx (c_0^{\text{in}}(x) - c_L) \\ &+ \bar{\kappa}\bar{v}_0 \Delta c \xi - \frac{\partial^2\mu_0^{\text{in}}}{\partial\sigma^2} \left\{ \int_0^\infty dx (q(\phi_0^{\text{in}}, c_0^{\text{in}}) - q^+) + q^+ \xi \right\} + B(\sigma) \end{aligned} \quad (\text{A.112})$$

where the last of Eqs. (A.18) was used on the first line of Eq. (A.112) and the second of Eqs. (A.18) was used to express $\lim_{\xi \rightarrow \infty} \partial_{,\xi}\mu_2^{\text{in}}$ in terms of outer solutions.

Subtracting Eq. (A.112) from Eq. (A.111), using the second of Eqs. (A.17) to express the limits of $c_1^{\text{in}}(\xi)$ at $\pm\infty$ and noting from Eq. (A.87) that $q^+\partial_{,\eta}\mu_0^o(0^+) = -\bar{v}_0\Delta c$ (for $q^- = 0$), gives

$$\begin{aligned} -q^+ \frac{\partial\mu_1^o(0^+)}{\partial\eta} - q^+ \frac{\partial^2\mu_0^o(0^+)}{\partial\eta^2} \xi &= \bar{v}_1 \Delta c + \bar{v}_0 \Delta c_1 + \bar{\kappa}\bar{v}_0 \Delta H + \frac{\partial^2\mu_0^{\text{in}}}{\partial\sigma^2} \Delta J + \Delta c \bar{v}_0 Z(c_L) c_1^o(0^+) \\ &+ \left\{ \Delta c \bar{v}_0 Z(c_L) \frac{\partial c_0^o(0^+)}{\partial\eta} - \bar{v}_0 \left(\frac{\partial c_0^o(0^-)}{\partial\eta} + \frac{\partial c_0^o(0^+)}{\partial\eta} \right) + q^+ \frac{\partial^2\mu_0^{\text{in}}}{\partial\sigma^2} - \bar{\kappa}\bar{v}_0 \Delta c \right\} \xi \end{aligned} \quad (\text{A.113})$$

where $\Delta c_1 \equiv c_1^o(0^+) - c_1^o(0^-)$ has been defined for simplicity, while $\Delta H \equiv H^+ - H^-$ and $\Delta J \equiv J^+ - J^-$, where

$$H^+ = \int_0^\infty dx (c_L - c_0^{\text{in}}(x)), \quad H^- = \int_{-\infty}^0 dx (c_0^{\text{in}}(x) - c_s), \quad (\text{A.114})$$

$$J^+ = \int_0^\infty dx (q(\phi_0^{\text{in}}, c_0^{\text{in}}) - q^+), \quad J^- = \int_{-\infty}^0 dx (q^- - q(\phi_0^{\text{in}}, c_0^{\text{in}})) \quad (\text{A.115})$$

(note that for one-sided diffusion considered here q^- vanishes identically and is merely put in the J^- integral for completeness). Collecting the terms Eq. (A.113) corresponding to ξ^0 into one equation gives

⁶ Z is strictly also a function of ϕ . However in the limits studied below, it will only be evaluated in the far field where ϕ_0^{in} becomes constant, and thus it is written as a function of c_0^{in} to simplify the notation.

the remaining, $\mathcal{O}(\epsilon^2)$, contribution to the flux conservation condition for the case of one-sided diffusion. Namely,

$$q^+ \frac{\partial \mu_1^{\text{in}}(0^+)}{\partial \eta} = -\bar{v}_1 \Delta c - \bar{\kappa} \bar{v}_0 \Delta H - \frac{\partial^2 \mu_0^{\text{in}}}{\partial \sigma^2} \Delta J - \bar{v}_0 \Delta c_1 - \Delta c \bar{v}_0 Z(c_L) c_1^o(0^+) \quad (\text{A.116})$$

Equation (A.116) is reverted to dimensional units by multiplying both sides by ϵ and using $\eta = v_s u / D_L$, $\bar{\kappa} = (W_\phi / \epsilon) \kappa$, $\bar{v}_j = v_j / v_s$, ($j = 1, 2$) and $\sigma = (\epsilon / W_\phi) s$. This gives

$$D_L q^+ \frac{\partial (\epsilon \mu_1^o(0^+))}{\partial u} = -(\epsilon v_1) \Delta c - [\Delta H v_0 + D_L \Delta J \partial_\theta (\kappa \partial_\theta \mu_0^o(0^\pm))] W_\phi \kappa - v_0 (\epsilon \Delta c_1) - \Delta c \bar{v}_0 Z(c_L) (\epsilon c_1^o(0^+)) \quad (\text{A.117})$$

where the chain rule has been used to write $\partial_{ss} \mu_0^{\text{in}} \equiv \partial_{ss} \mu_0^o(0^\pm)$ in terms of the angle θ of the local interface normal by using the relation $\kappa = \partial \theta / \partial s$. Adding the first order flux conservation condition from Eq. (A.88) to Eq. (A.117) gives

$$D_L q^+ \frac{\partial (\mu_0^o(0^+) + \epsilon \mu_1^o(0^+))}{\partial u} = -\Delta c (v_0 + \epsilon v_1) - [\Delta H v_0 + D_L \Delta J \partial_\theta (\kappa \partial_\theta \mu_0^o(0^\pm))] W_\phi \kappa - (\epsilon \Delta c_1) v_0 - \Delta c \bar{v}_0 Z(c_L) (\epsilon c_1^o(0^+)) \quad (\text{A.118})$$

The final stage of this subsection is to show that the last two terms on the right hand side of Eq. (A.118) are related to the chemical potential jump, proportional to ΔF . To see this, note that since $\mu^{\text{out}} = \mu_0^o + \epsilon \mu_1^o$, then $\mu^{\text{out}}(0^+) - \mu^{\text{out}}(0^-) = \epsilon \mu_1^o(0^+) - \epsilon \mu_1^o(0^-)$, which, from Eq. (A.86), gives

$$\epsilon \mu_1^o(0^+) - \epsilon \mu_1^o(0^-) \equiv \delta \mu_1^o(0^+) - \delta \mu_1^o(0^-) = \frac{\Delta F W_\phi}{D_L} v_0 \quad (\text{A.119})$$

The assumption of an asymptotic series expansion implies that the chemical potential jumps, $\delta \mu_1^o(0^\pm) \equiv \epsilon \mu_1^o(0^\pm)$, can be related to the corresponding concentration changes, $\delta c_1^o(0^\pm) \equiv \epsilon c_1^o(0^\pm)$. Thus, the $\delta \mu_1^o(0^\pm)$ can be Taylor expanded to lowest order in terms of $\delta c_1^o(0^\pm)$, making Eq. (A.119)

$$\frac{\partial \mu_0^o(c_L)}{\partial c} \delta c_1^o(0^+) - \frac{\partial \mu_0^o(c_s)}{\partial c} \delta c_1^o(0^-) = \Lambda_L \epsilon c_1^o(0^+) - \Lambda_s \epsilon c_1^o(0^-) = \frac{\Delta F W_\phi}{D_L} v_0 \quad (\text{A.120})$$

where the definitions $\Lambda_L \equiv \partial_c \mu_0^o(c_L) = \partial_{cc} \bar{f}_{\text{AB}}^{\text{mix}}(c_L)$ and $\Lambda_s \equiv \partial_c \mu_0^o(c_s) = \partial_{cc} \bar{f}_{\text{AB}}^{\text{mix}}(c_s)$ have been made. Recalling the definition of $Z(c_L)$, the last two terms of Eq. (A.118) can be written as

$$-(\epsilon \Delta c_1) v_0 - \Delta c \bar{v}_0 Z(c_L) (\epsilon c_1^o(0^+)) = - \left\{ 1 + \frac{\partial_{,cc} \mu(c_L)}{(\partial_{,c} \mu(c_L))^2} \partial_{,c} \mu(c_L) \Delta c \right\} v_0 \epsilon c_1^o(0^+) + v_0 \epsilon c_1^o(0^-) \quad (\text{A.121})$$

For a bulk free energy $\bar{f}_{\text{AB}}^{\text{mix}}$ corresponding to an ideal, dilute alloy, it is straightforward to show that $\partial_{,cc} \mu(c_L) / (\partial_{,c} \mu(c_L))^2 = -1$, exactly, for all c_L . This is also the leading order behaviour for a wide class of alloys described by regular or sub-regular solution type models, particularly at low concentrations. Moreover, to leading order dilute alloys also satisfy $\partial_{,cc} \bar{f}_{\text{AB}}^{\text{mix}}(c_L) c_L \approx \partial_{,cc} \bar{f}_{\text{AB}}^{\text{mix}}(c_s) c_s$ (exact for ideal alloys), making it possible to approximate the solute partition or segregation coefficient⁷ between solid and liquid phases by

$$k \equiv \frac{c_s}{c_L} \approx \frac{\Lambda_L}{\Lambda_s} = \frac{\partial_{,cc} \bar{f}_{\text{AB}}^{\text{mix}}(c_L)}{\partial_{,cc} \bar{f}_{\text{AB}}^{\text{mix}}(c_s)} \quad (\text{A.122})$$

⁷This is the same as the equilibrium partition coefficient, k_e , only for a flat stationary interface. Recall from sections (A.7.2) and (A.7.3) that c_s and c_L involve curvature

Substituting Eqs. (A.122) into Eq. (A.121), then using Eq. (A.120) and noting that $\Delta c = (1 - k)c_L$, simplifies Eq. (A.121) to

$$-(\epsilon\Delta c_1)v_0 - \Delta c\bar{v}_0 Z(c_L)(\epsilon c_1^o(0^+)) \approx -v_0 [k\epsilon c_1^o(0^+) - \epsilon c_1^o(0^-)] = -\frac{k\Delta F W_\phi}{\Lambda_L D_L} v_0^2 \quad (\text{A.123})$$

The final form of the mass flux conservation condition at the interface is given by substituting Eq. (A.123) into Eq. (A.118), gives, to order $\mathcal{O}(\epsilon^2)$,

$$D_L q^+ \frac{\partial(\mu_0^o(0^+) + \epsilon\mu_1^o(0^+))}{\partial u} = -\Delta c v_n - [\Delta H v_0 + D_L \Delta J \partial_\theta (\kappa \partial_\theta \mu_0^o(0^\pm))] W_\phi \kappa - \frac{k\Delta F}{\Lambda_L D_L} W_\phi v_0^2 \quad (\text{A.124})$$

where $v_n = v_0 + \epsilon v_1 + \dots$ is the second order expansion of velocity. Note that the other terms that scale with v_0 at this order of expansion would acquire v_1 contributions if a higher order velocity expansion is used [8].

As in previous sections, it is instructive to discuss the case of $q^- \neq 0$ on the flux conservation equation at order ϵ^2 . In this situation, the left hand side of Eq. (A.124) is altered to

$$D_L q^+ \frac{\partial(\mu_0^o(0^+) + \epsilon\mu_1^o(0^+))}{\partial u} - D_L q^- \frac{\partial(\mu_0^o(0^-) + \epsilon\mu_1^o(0^-))}{\partial u} \quad (\text{A.125})$$

and the additional term

$$\left(q^- \frac{\partial \mu_0^o(0^-)}{\partial u} \right) W_\phi \Delta F v_0 \quad (\text{A.126})$$

appears at the end of Eq. (A.124). This correction also vanishes for specific classes of phase field models constructed such that $\Delta F = 0$, a condition required to make contact with traditional sharp interface kinetics at low undercooling. As has been done throughout, it is most convenient to consider one-sided diffusion, where $q^- = 0$ identically, where Eq. (A.124) is recovered.

A.8 Summary of Results of Appendix Sections (A.2)-(A.7)

It is useful at this point to summarize the relevant results of the asymptotic analysis performed up to this point in this Appendix, and to interpret the physical significance of the results obtained in the context of traditional sharp interface models for alloy solidification.

A.8.1 Effective sharp Interface limit of Eqs. (A.2)

The asymptotic analysis derived in Appendix (A) derives the effective sharp interface model corresponding to the phase field model described by equations (A.2)-(A.5). The main results that were explicitly derived covered the case of zero or very small diffusion in the solid – a metallurgical situation closely obeyed by substitutional diffusion. Specifically, on length scales larger than the interface width W_ϕ , the diffusion of solute impurities is governed by the standard diffusion equation and phases are described by a uniform (i.e, mean field) order parameter. Moreover, the outer concentration (c), chemical potential (μ) and phase (ϕ) fields evolve such that their asymptotic behaviour (i.e. their projection onto an interface defined by the surface $\phi(\vec{x}) = \phi_c$, where ϕ_c is chosen to make $\phi_o(x)$ an odd function) is consistent with the following sharp interface boundary conditions:

- The lowest order (in ϵ) of the phase field profile, ϕ_0^{in} , is given by Eq. (A.52). Its values far from the interface are denoted ϕ_s/ϕ_L in the solid/liquid phases. The lowest order concentration field, c_0^{in} , is given by Eq (A.58)
- Equations (A.60), (A.61) and (A.72) collectively determine lowest order concentrations on the liquid (c_L) and solid (c_s) side of the interface, corrected for curvature and interface velocity:

$$\frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_s, c_s)}{\partial c} = \mu_0^o(0^\pm) \quad (\text{A.127})$$

$$\frac{\partial \bar{f}_{\text{AB}}^{\text{mix}}(\phi_L, c_L)}{\partial c} = \mu_0^o(0^\pm) \quad (\text{A.128})$$

where the lowest order chemical potential through the interface is given by

$$\mu_0^o(0^\pm) = \mu_{\text{eq}}^{\text{F}} - \left(\frac{\sigma_\phi}{\Delta c}\right) \left(\frac{W_\phi}{\lambda}\right) \kappa - \left(\frac{\sigma_\phi}{\Delta c}\right) \left(\frac{\tau}{\lambda W_\phi}\right) v_0 \quad (\text{A.129})$$

with $\mu_{\text{eq}}^{\text{F}}$ being the equilibrium chemical potential between bulk solid and liquid, $\Delta c \equiv c_L - c_s$ and σ_ϕ is defined in Eq. (A.64). It is recalled that v_0 is the lowest order normal interface velocity ⁸ and κ is curvature. Other constants are phase field model parameters defined at the beginning of Appendix (A).

- Equation (A.107) describes the second order Gibbs-Thomson correction to the equilibrium chemical potential on either side of the effective sharp interface:

$$\delta\mu^o(0^\pm) \equiv \mu^o(0^\pm) - \mu_{\text{eq}}^{\text{F}} = - \underbrace{\frac{(\sigma_\phi + \delta\sigma_c) W_\phi}{\Delta c \lambda}}_{\propto d_o} \kappa - \underbrace{\frac{\tau \sigma_\phi}{W_\phi \lambda \Delta c} \left\{ 1 - \frac{(K + F^\pm \Delta c) \lambda}{\sigma_\phi \bar{D}} \right\}}_{\propto \beta^\pm} v_0 \quad (\text{A.130})$$

where σ_c is given by Eq. (A.64), F^+ , F^- are given by Eqs. (A.84), K by Eq. (A.104) and $\bar{D} = D_L \tau / W_\phi^2$. The underlined terms are the effective capillary length and kinetic coefficient of the corresponding sharp interface model. Note that $\beta^+ \neq \beta^-$ since $F^+ \neq F^-$ in general.

- Equation (A.124) describes the conservation of mass flux conservation across the effective sharp interface:

$$D_L q^+ \frac{\partial (\mu_0^o(0^+) + \epsilon \mu_1^o(0^+))}{\partial u} = -\Delta c v_0 - [\Delta H v_0 + D_L \Delta J \partial_\theta (\kappa \partial_\theta \mu_0^o(0^\pm))] W_\phi \kappa - \frac{k \Delta F}{\Lambda_L D_L} W_\phi v_0^2 \quad (\text{A.131})$$

where ΔH and ΔJ are given by Eqs. (A.114), (A.115), respectively, while $\Delta F = F^+ - F^-$ and the variables k and Λ_L are defined in Eq. (A.122).

A.8.2 Interpretation of thin interface limit correction terms

It is clear that the effective sharp interface limit of the phase field model *is not* the same as the traditional sharp interface model, in the limit of a diffuse W_ϕ . There are two main differences: The chemical

⁸A higher order correction v_1 to the velocity is not written here, which is equivalent to assuming that $v_n = v_0$. Also, Δc can be substituted for Δc_{F} throughout, as this will only lead to negligible, higher order curvature and velocity corrections.

potential experiences a jump at the interface proportional to ΔF as shown by Eq. (A.107). Moreover the flux conservation condition, Eq. (A.124), has three "extra" terms not traditionally seen when describing sharp interface kinetics of solidification and analogous free boundary problems. It is instructive to consider their physical origin. The chemical potential jump (ΔF) arises when solute diffuses through a finite sized interface with a finite mobility. If the solidification rate is too fast or, alternatively, if the physical interface of the phase boundary is too large, it is not possible for atoms to remain in local equilibrium at the interface –one of the quintessential assumptions of traditional sharp interface models. As a result, the interface maintains a two-sided chemical potential. The ΔH term arises because of the arclength of the interface being slightly longer one side than the other. That effectively serves to create a source of solute at locations of high curvature. The ΔJ term arises because solute diffusion at the interface can occur across (i.e. normal to) the interface as well as laterally, along the interface. Again, this is a feature that, by construction, traditional sharp interface models do not incorporate.

How can the differences between the traditional sharp interface model of alloy solidification and that predicted by the above phase field analysis be reconciled? This is done by noting that all so-called "correction terms" (first coined as such in [112]) described above scale with the interface width W_ϕ and the interface speed v_0 . That implies that if a material has a perfectly sharp phase boundary ($W_\phi \rightarrow 0$) during solidification, all three "corrections" vanish. In reality $W_\phi \sim 10^{-9}m$, not zero. It will also be noted that the ΔF and ΔH corrections also scale with the interface speed v_0 . For most solidification problems associated with thin slab or continuous casting the rates of solidification are sufficiently low that the correction terms associated with ΔF and ΔH are so small that they can be neglected. It should be remarked that while the ΔJ term does not couple to v_0 its magnitude, $W_\phi \kappa \ll 1$ for nearly all microstructures of interest and can thus be neglected, even for modest values of W_ϕ .

Of course, conducting simulations of Eqs. (A.2) with W_ϕ on the order of nanometers and at an undercooling that emulates realistic (i.e., slow) solidification rates would lead to impractically long CPU times (see section (B.3) below). One way to avoid this dilemma is to simulate with an artificially diffuse interface width W_ϕ , which reduces simulation times. This, however, leads to results that are quantitatively different from the standard sharp interface kinetics expected for alloy solidification. This is due to the amplification of the correction terms proportional to ΔF , ΔH and ΔJ discussed above. Until recently this was a problem for most single order parameter phase field models, multiple order parameters models and models incorporating an orientation field. The work of Karma and co-workers [113, 112, 57] recently changed this –at least for ideal, dilute alloys– by using a so-called anti-trapping flux source in the solute diffusion equation. This was then extended by other researchers to multi-phase solidification [74], non-ideal alloys [194] and multi-component alloys [118]. The anti-trapping formalism is discussed in detail in the section (A.9).

A.9 Elimination of Thin Interface Correction Terms

This, the last, section of the Appendix (A) modifies the phase field model of Eqs. (A.2) so as to make it possible to eliminate the so-called correction terms ΔF , ΔH and ΔJ discussed in the previous sections. These modifications will involve two changes. The first is to introduce a so-called *anti-trapping* flux term in the concentration equation. The second is to make the ϕ -dependent interpolation functions in the phase field and concentration equations independent. In so doing the "fundamental" origin of the phase field model will be abandoned in favour for a mathematical "trick" that serves to endow the [modified] phase field equations with extra degrees of freedom that make it possible to match the sharp interface model. The idea of adding an anti-trapping flux was first developed for an ideal, dilute binary alloy model

by Karma and co-workers [112, 57]. It has since been extended to non-ideal binary alloys for single phase [194] and three-phase solidification [74] and to multi-component solidification [118].

A.9.1 Modifying the phase field equations

Consider the following two modifications to the phase field equations (A.2):

- Let the $\tilde{g}(\phi)$ denote the function that interpolates $\mu \equiv \partial_c \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c)$ between bulk solid and bulk liquid. Define a new function $h(\phi)$, where $h(\phi)$ and $\partial_\phi h(\phi)$ have the same limits as $\tilde{g}(\phi)$ and $\partial_\phi \tilde{g}(\phi)$, respectively, at $\phi = \phi_s$ and $\phi = \phi_L$. Redefine the chemical potential appearing in both phase field equations by

$$\mu(\phi, c) \rightarrow \partial_c \bar{f}_{\text{AB}}^{\text{mix}}(h(\phi), c) \quad (\text{A.132})$$

- Add a new source of flux is subtracted from the traditional gradient flux in the solute diffusion equation. This flux is given by

$$\vec{J}_a = -W_\phi a(\phi) U(\phi, c) \partial_t \phi \frac{\nabla \phi}{|\nabla \phi|} \quad (\text{A.133})$$

and is referred to as an *anti-trapping current*, after Karma [112]. The functions $a(\phi)$ and $U(\phi, c)$ are as yet unspecified functions of ϕ and c .

It is further assumed that the bulk free energy $\bar{f}_{\text{AB}}^{\text{mix}}(\phi, c)$ (or equivalently $f(\phi, c) \equiv \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c)/\alpha$) can be cast into the general form

$$\partial_\phi \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c) = \Delta c G(\mu - \mu_0^o(0^\pm), \mu_0^o(0^\pm) - \mu_{\text{Eq}}^{\text{F}}) P'(\phi) \quad (\text{A.134})$$

where $\mu(\phi, c) \equiv \partial_c \bar{f}_{\text{AB}}^{\text{mix}}(\phi, c)$, while $\mu_0^o(0^\pm)$ is the lowest order outer solution of the chemical potential through the interface, $\mu_{\text{Eq}}^{\text{F}}$ is the chemical potential of a flat stationary interface, $\Delta c = (c_L - c_s)$ and $P'(\phi) \equiv dP(\phi)/d\phi$. The function $G(x, y)$ satisfies: $G(0, 0) = 0$, $G(0, y) = y$, $\partial_x G(x = 0, y) = 1$. Also, the function $P(\phi)$ is odd in ϕ and interpolates between two constants in the bulk solid and liquid. Here, $P(\phi_L) - P(\phi_s) = -1$.

The addition of $h(\phi)$ and \vec{J}_a provide additional degrees of freedom to the original phase field equations so as to be able to eliminate the correction terms ΔF , ΔH and ΔJ from the effective sharp interface limit of the phase field equations derived above. The consequences of these modification to the asymptotic analysis are considered next. For simplicity only the case $\delta = 0$ is considered.

A.9.2 Changes due to the altered form of bulk chemical potential

The section re-traces the relevant algebra of the previous asymptotic analysis to demonstrate how the first two modifications of section (A.9.1) alter the effective equilibrium and sharp interface properties of the phase field equations from those summarized in section (A.8). The effect of the anti-trapping will be considered in the next subsection.

- $\mathcal{O}(1)$ phase field equation: This clearly stays unaltered. Moreover, Eq. (A.134) implies that the lowest order ϕ_0^{in} equation will also solve for the steady state ϕ field.

- $\mathcal{O}(1)$ concentration equation: Equation (A.58) follows exactly as before except that $h(\phi)$ is used,

$$\partial_c \bar{f}_{\text{AB}}^{\text{mix}}(\phi_0^{\text{in}}, c_0^{\text{in}}) = \mu_0^o(0^\pm) \rightarrow \partial_c \bar{f}_{\text{AB}}^{\text{mix}}(h(\phi_0^{\text{in}}), c_0^{\text{in}}) = \mu_0^o(0^\pm) \quad (\text{A.135})$$

Since $h(\phi)$ and $g(\phi)$ have the same limits, the modified conditions in Eqs. (A.60) and (A.61) will remain unchanged. The lowest order concentration profile through the interface will now be interpolated by $h(\phi)$.

- $\mathcal{O}(\epsilon)$ phase field equation: Using Eqs. (A.134), the last term in Eq. (A.62) can be written as

$$\int_{-\infty}^{\infty} \frac{\partial \phi_0^{\text{in}}}{d\xi} f_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) dx \rightarrow \frac{\Delta c}{\alpha} \int_{-\infty}^{\infty} \frac{\partial \phi_0^{\text{in}}}{d\xi} G(\mu(\phi_0^{\text{in}}, c_0^{\text{in}}) - \mu_0^o(0^\pm), \mu_0^o(0^\pm) - \mu_{\text{Eq}}^{\text{F}}) P'(\phi) dx \quad (\text{A.136})$$

However, from Eqs. (A.58) and (A.59), $\mu(\phi_0^{\text{in}}, c_0^{\text{in}}) = \bar{f}_{\text{AB}}^{\text{mix}}(h(\phi_0^{\text{in}}), c_0^{\text{in}}) = \mu_0^o(0^\pm)$ giving

$$G(\mu(\phi_0^{\text{in}}, c_0^{\text{in}}) - \mu_0^o(0^\pm), \mu_0^o(0^\pm) - \mu_{\text{Eq}}^{\text{F}}) = G(0, \mu_0^o(0^\pm) - \mu_{\text{E}}^{\text{F}}) = \mu_0^o(0^\pm) - \mu_{\text{E}}^{\text{F}} \quad (\text{A.137})$$

Using Eq. (A.137) in Eq. (A.136) leads to Eq. (A.72).

- $\mathcal{O}(\epsilon)$ concentration equation: This is unaffected as the differential equation solves directly for the chemical potential and does not make explicit reference to the constitutive relation between μ , ϕ and c . Only c_0^{in} is related –implicitly– to $h(\phi_0^{\text{in}})$ via Eq. (A.135).
- $\mathcal{O}(\epsilon^2)$ phase field equation: Picking up the calculation at Eq. (A.94) and substituting $f_{,\phi\phi}(\phi, c) = (\Delta c/\alpha) [G(\mu - \mu_0^o(0^\pm), \mu_0^o(0^\pm) - \mu_{\text{Eq}}^{\text{F}}) P''(\phi) + G_{,x}(\mu - \mu_0^o(0^\pm), \mu_0^o(0^\pm) - \mu_{\text{Eq}}^{\text{F}}) \partial_\phi \mu P'(\phi)]$ and $f_{,\phi c}(\phi, c) = (\Delta c/\alpha) G_{,x}(\mu - \mu_0^o(0^\pm), \mu_0^o(0^\pm) - \mu_{\text{Eq}}^{\text{F}}) \partial_c \mu P'(\phi)$ yields

$$\begin{aligned} 0 = & -\bar{D}\sigma_\phi \bar{v}_1 + \frac{\Delta c}{\alpha} G(0, \mu_0^o(0^\pm) - \mu_{\text{Eq}}^{\text{F}}) \int_{-\infty}^{\infty} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} P''(\phi_0^{\text{in}}) \phi_1^{\text{in}} d\xi \\ & + \frac{\Delta c}{\alpha} \int_{-\infty}^{\infty} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} P'(\phi_0^{\text{in}}) \{ \partial_c \mu(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} + \partial_\phi \mu(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} \} d\xi \end{aligned} \quad (\text{A.138})$$

where $G_{,x}$ denotes differentiation with respect to the first argument of G . Equation (A.50) is used to substitute the expression in the curly brackets of the last term in Eq. (A.138) by μ_1^{in} , the explicit form of which is still given by Eq. (A.76). Moreover, the first integral in Eq. (A.138) vanishes due to the symmetry of ϕ_0^{in} and ϕ_1^{in} . These simplifications reduce Eq. (A.138) to

$$\bar{D}\sigma_\phi \bar{v}_1 - \frac{\bar{v}_0}{\alpha} K + \frac{\bar{\mu}}{\alpha} \Delta c = 0 \quad (\text{A.139})$$

which is exactly of the same form as Eq. (A.103), except that K is now defined by

$$K = \Delta c \int_{-\infty}^{\infty} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} P'(\phi_0^{\text{in}}) \left\{ \int_0^\xi \frac{c_s - c_0^{\text{in}}(x)}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx \right\} d\xi \quad (\text{A.140})$$

Using Eq. (A.82) and Eq. (A.83) and repeating the steps in section (A.7.5) following Eq. (A.103) leads to the Gibbs-Thomson condition in Eq. (A.107).

- $\mathcal{O}(\epsilon^2)$ concentration equation: As with the $\mathcal{O}(\epsilon)$ concentration equation, This is unaffected as the differential equation solves directly for the chemical potential and does not make explicit reference to the constitutive relation between μ , ϕ and c . The final form of the flux conservation condition is still described by Eq. (A.124).

A.9.3 Changes due to the addition of anti-trapping flux

This section examines how the addition of an anti-trapping flux, introduced in in section (A.9.1), further alters the asymptotic analysis of the concentration equation, which is now written as

$$\frac{\partial c}{\partial t} = \nabla \cdot (M(\phi, c) \nabla \mu(h(\phi), c)) - \nabla \cdot \vec{J}_a \quad (\text{A.141})$$

where the function $h(\phi)$ is indicated to emphasize that $\mu = f_{,c}(\phi, c)$ is now interpolated using $h(\phi)$. The idea of the anti-trapping flux \vec{J}_a is to correct or "kick out" any excess solute trapped through the interface as a results of its finite width W_ϕ . It thus scales directly with W_ϕ as well as the rate of interface advance, controlled by $\partial_t \phi \hat{n}$. The remainder of this section examines how $\nabla \cdot \vec{J}_a$ in Eq. (A.141) alters the previous asymptotic analysis.

Re-scaing the diffusion equation as was done in arriving at Eq. (A.35), the dimensionless version of Eq. (A.141) for the inner concentration field c becomes

$$\epsilon^2 \frac{\partial c}{\partial \bar{t}} - \epsilon \bar{v}_n \frac{\partial c}{\partial \xi} + \epsilon^2 \sigma_{,i} \frac{\partial c}{\partial \sigma} = \nabla_{\xi, \sigma} (q(\phi, c) \nabla_{\xi, \sigma} \mu) - \frac{W_\phi^2}{D_L} \left[\nabla \cdot \vec{J}_a \right]_{\xi, \sigma, \bar{t}} \quad (\text{A.142})$$

where the subscripts ξ, σ, \bar{t} denote transformation to scaled curvi-linear coordinates (ξ, σ) and time \bar{t} . (Note that for this subsection, the usual "in" superscript for the fields is dropped to simplify notation). To modify the equations for the inner concentration field at different orders in ϵ it therefore suffices to examine the last term in Eq. (A.142) containing the anti-trapping flux.

The expression for $\nabla \cdot \vec{J}_a$ is written with respect to (ξ, σ) with the aid of Eq. (C.17), where Eq. (C.18) is used to write $-\nabla \phi / |\nabla \phi|$ and Eq. (A.8) is used to write $\partial / \partial t$ in curvi-linear coordinates as

$$\frac{\partial}{\partial \bar{t}} = \frac{v_s^2}{D_L} \frac{\partial}{\partial \bar{t}} - \frac{v_s}{W_\phi} \bar{v} \frac{\partial}{\partial \xi} + \frac{v_s^2}{D_L} \sigma_{\bar{t}} \frac{\partial}{\partial \sigma} \quad (\text{A.143})$$

(where it is recalled that $\bar{t} \rightarrow t/D_K/v_s^2$). Substituting these expressions into Eq. (C.17) gives, after a little straightforward –and boring– algebra, an expression for the last term in Eq. (A.142). Retaining only terms up to order $\mathcal{O}(\epsilon^2)$, as has been done throughout the asymptotic analysis, leads to

$$\begin{aligned} -\frac{W_\phi^2}{D_L} \left[\nabla \cdot \vec{J}_a \right]_{\xi, \sigma} &= \epsilon \frac{\partial}{\partial \xi} \left(a(\phi) U \bar{v}_n \frac{\partial \phi}{\partial \xi} \right) \\ &- \epsilon^2 \left\{ \frac{\partial}{\partial \xi} \left(a(\phi) U \frac{\partial \phi}{\partial \bar{t}} \right) + \frac{\partial}{\partial \xi} \left(a(\phi) U \partial_\sigma \frac{\partial \phi}{\partial \sigma} \right) - \bar{\kappa} a(\phi) U \bar{v}_n \frac{\partial \phi}{\partial \xi} \right\} \end{aligned} \quad (\text{A.144})$$

It is seen that Eq. (A.144) explicitly modifies only the $\mathcal{O}(\epsilon)$ and $\mathcal{O}(\epsilon^2)$ equations of the inner concentration expansion. Substituting the inner expansions of ϕ and c given by Eqs. (A.16) into Eq. (A.144), expanding $a(\phi)$ and $U(\phi, c)$ and collecting the $\mathcal{O}(\epsilon)$ terms modifies Eq. (A.73) to

$$\mathcal{O}(\epsilon) : \frac{\partial}{\partial \xi} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) = -\bar{v}_0 \frac{\partial c_0^{\text{in}}}{\partial \xi} - \frac{\partial}{\partial \xi} \left(a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_0 \frac{\partial \phi_0^{\text{in}}}{\partial \xi} \right) \quad (\text{A.145})$$

Similarly collecting the $\mathcal{O}(\epsilon^2)$ terms modifies Eq. (A.109) to

$$\mathcal{O}(\epsilon^2) : \frac{\partial}{\partial \xi} \left(q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_2^{\text{in}}}{\partial \xi} \right) = -\bar{v}_1 \frac{\partial c_0^{\text{in}}}{\partial \xi} - \bar{v}_0 \frac{\partial c_1^{\text{in}}}{\partial \xi} - \bar{\kappa} q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} - q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial^2 \mu_0^{\text{in}}}{\partial \sigma^2} \quad (\text{A.146})$$

$$\begin{aligned}
& - \frac{\partial}{\partial \xi} \left(q_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) - \frac{\partial}{\partial \xi} \left(q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}} \frac{\partial \mu_1^{\text{in}}}{\partial \xi} \right) \\
& - \bar{\kappa} a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_0 \frac{\partial \phi_0^{\text{in}}}{\partial \xi} - \frac{\partial}{\partial \xi} \left(a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_0 \frac{\partial \phi_1^{\text{in}}}{\partial \xi} \right) \\
& - \frac{\partial}{\partial \xi} \left([a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_1 + a(\phi_0^{\text{in}}) \bar{v}_0 \delta U_1 + a'(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_0 \phi_1^{\text{in}}] \frac{\partial \phi_0^{\text{in}}}{\partial \xi} \right)
\end{aligned}$$

where $\delta U_1 \equiv U_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} + U_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}}$, $a'(\phi) \equiv \partial_\phi a(\phi)$ and it is recalled that that ϕ_0^{in} and c_0^{in} do not depend explicitly on σ and \bar{t} . It is seen that only the $\mathcal{O}(\epsilon)$ and $\mathcal{O}(\epsilon^2)$ concentration equations are potentially affected by the anti-trapping flux.

A.9.4 Analysis of modified $\mathcal{O}(\epsilon)$ inner diffusion equation

Integrating Eq. (A.145) once gives

$$q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_1^{\text{in}}}{\partial \xi} = -\bar{v}_0 c_0^{\text{in}}(\xi) - a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_0 \frac{\partial \phi_0^{\text{in}}}{\partial \xi} + A(s) \quad (\text{A.147})$$

Applying, as before, the boundary condition $q(\phi_0^{\text{in}}, c_0^{\text{in}}) \rightarrow q^{-1} = 0$ and $\partial \phi_0^{\text{in}} = 0$ as $\xi \rightarrow -\infty$, gives

$$\mu_1^{\text{in}} = -\bar{v}_0 \int_0^\xi \frac{[c_0^{\text{in}}(x) - c_s]}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx - \bar{v}_0 \int_0^\xi \frac{U(\phi_0^{\text{in}}, c_0^{\text{in}}) a(\phi_0^{\text{in}})}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} dx + \bar{\mu} \quad (\text{A.148})$$

Re-tracing the steps of section (A.7.4) again will lead to exactly the same form of the $\mathcal{O}(\epsilon)$ flux conservation condition given by Eqs. (A.87) or (A.88). However, the chemical potential jump at the interface given by Eq. (A.85) is now modified to

$$\mu_1^o(0^+) - \mu_1^o(0^-) = (\mathcal{F}^+ - \mathcal{F}^-) \bar{v}_0 \quad (\text{A.149})$$

where

$$\begin{aligned}
\mathcal{F}^+ &= F^+ - \int_0^\infty \frac{U(\phi_0^{\text{in}}, c_0^{\text{in}}) a(\phi_0^{\text{in}})}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} dx \\
\mathcal{F}^- &= F^- + \int_{-\infty}^0 \frac{U(\phi_0^{\text{in}}, c_0^{\text{in}}) a(\phi_0^{\text{in}})}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} dx
\end{aligned} \quad (\text{A.150})$$

where F^+ and F^- are given by the expression in Eqs. (A.84). It is recalled that the lowest order concentration field $c_0^{\text{in}}(\xi)$ is modified by $h(\phi_0^{\text{in}})$ as discussed in the previous section.

A.9.5 Analysis of modified $\mathcal{O}(\epsilon^2)$ inner phase field equation

It was noted in section (A.7.5) that Eq. (A.76) is used to eliminate μ_1^{in} in Eq. (A.102). This lead to Eq. (A.103), where K given by Eq. (A.104). Similarly retracing the steps of the $\mathcal{O}(\epsilon^2)$ phase field equation analysis of section (A.9.2) with the explicit form of μ_1^{in} given by Eq. (A.148) leads to the following modified definition of K ,

$$K = \Delta c \int_{-\infty}^\infty \frac{\partial \phi_0^{\text{in}}}{\partial \xi} P'(\phi_0^{\text{in}}) \left\{ \int_0^\xi \frac{c_s - c_0^{\text{in}}(x)}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} dx - \frac{a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}})}{q(\phi_0^{\text{in}}, c_0^{\text{in}})} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} \right\} d\xi, \quad (\text{A.151})$$

which is like Eq. (A.140) modified by the anti-trapping flux. This definition of K and $F^\pm \rightarrow \mathcal{F}^\pm$ replace their previous versions in Eq. (A.107).

A.9.6 Analysis of modified $\mathcal{O}(\epsilon^2)$ inner diffusion equation

Proceeding analogously to section (A.7.6), the expression in Eq. (A.147)) is substituted into the third term on the right hand side of Eq. (A.146) and the result is integrated once, yielding

$$\begin{aligned}
q(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \mu_2^{\text{in}}}{\partial \xi} &= -\bar{v}_1 c_0^{\text{in}}(\xi) - \bar{v}_0 c_1^{\text{in}}(\xi) + \bar{\kappa} \bar{v}_0 \int_0^\xi [c_0^{\text{in}}(\xi) - c_s] dx + \bar{\kappa} \bar{v}_0 \int_0^\xi a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \phi_0^{\text{in}}}{\partial \xi} dx \\
&\quad - \frac{\partial^2 \mu_0^{\text{in}}}{\partial \sigma^2} \int_0^\xi q(\phi_0^{\text{in}}, c_0^{\text{in}}) dx - \{q_{,\phi}(\phi_0^{\text{in}}, c_0^{\text{in}}) \phi_1^{\text{in}} + q_{,c}(\phi_0^{\text{in}}, c_0^{\text{in}}) c_1^{\text{in}}\} \frac{\partial \mu_1^{\text{in}}}{\partial \xi} - a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_0 \frac{\partial \phi_1^{\text{in}}}{\partial \xi} \\
&\quad - \{a(\phi_0^{\text{in}}) \bar{v}_0 \delta U_1 + a'(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_0 \phi_1^{\text{in}} + a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \bar{v}_1\} \frac{\partial \phi_0^{\text{in}}}{\partial \xi} \\
&\quad - \bar{\kappa} \bar{v}_0 \int_0^\xi a(\phi_0^{\text{in}}) U(\phi_0^{\text{in}}, c_0^{\text{in}}) \frac{\partial \phi_0^{\text{in}}}{\partial \xi} dx + B(\sigma)
\end{aligned} \tag{A.152}$$

It is noted that the fourth and second to last terms on the right hand side of Eq. (A.152) exactly cancel. As in section (A.7.6) the $\mathcal{O}(\epsilon^2)$ flux conservation condition is obtained by examining Eq. (A.152) in the limits $\xi \rightarrow \pm\infty$. In those limits, both the large bracketed term multiplying $\partial_\xi \phi_0^{\text{in}}(\xi)$ and the term multiplying $\partial_\xi \phi_1^{\text{in}}(\xi)$ vanish. As a result, Eq. (A.152) reduces to Eq. (A.111) in the limit $\xi \rightarrow -\infty$ and Eq. (A.112) in the limit $\xi \rightarrow \infty$. Therefore, all manipulation encountered in section (A.7.6) follow in the same way and anti-trapping does not enter explicitly into the $\mathcal{O}(\epsilon^2)$ flux condition. The one difference is that the ΔF expression that appears after Eq. (A.119) is now replaced by $\Delta \mathcal{F} \equiv \mathcal{F}^+ - \mathcal{F}^-$, where the modified \mathcal{F}^+ and \mathcal{F}^- are defined in Eqs. (A.150). The corrections ΔH and ΔJ remain the same as in section (A.7.6).

To summarize, the introduction of the interpolation function $h(\phi)$, the anti-trapping function $a(\phi)$ and the freedom to choose $q(\phi, c)$ (within limits) provide three degrees of freedom with which $\Delta \mathcal{F}$, ΔH and ΔJ can be simultaneously eliminated from the effective sharp interface model emulated by the phase field model in Eqs. (A.2). In this approach, the usual diffusion equation is swapped for Eq. (A.141), with \vec{J}_a given by Eq. (A.133) and the interpolation function $g(\phi)$ appearing in μ (via $f_{\text{AB}}^{\text{mix}}$) is swapped for $h(\phi)$.

Appendix B

Basic Numerical Algorithms for Phase Field Equations

This section describes the basic ideas of finite difference, finite volume and finite element methods for discretizing and numerically solving phase field and related partial differential equations. It discusses explicit time marching as a simple way for evolving such equations forward in time. It also points out the main differences between explicit and implicit methods. For a detailed discussion of implicit methods and other numerical methods, the reader is referred to the many texts available on this topic (e.g. [168]). The material in this appendix compliments the discussions on numerical algorithms presented in the text. The reader new to numerical modeling is thus encouraged to read this appendix first in order to better understand the numerical algorithms presented in the text and the Fortran 90 codes provided in the CD that accompanies the book.

B.1 Explicit Finite Difference Method for Model A

The simplest phase field equation examined in this book is the model A type equation examined previously. This equation serves as a paradigm for for magnetic domain growth in a ferromagnet. It is of the form

$$\tau \frac{\partial \phi}{\partial t} = W_\phi^2 \nabla^2 \phi - \frac{\partial f_{\text{bulk}}(\phi, c)}{\partial \phi} \quad (\text{B.1})$$

where $f_{\text{bulk}}(\phi, c)$ can be assumed to be some non-linear function of space and τ and W_ϕ are constants. Also, an isotropic gradient energy term is assumed here for simplicity. Equation (B.1) also serves as a paradigm for many non-linear reaction-diffusion equations. A computer can only represent a continuum at discrete set of points (i, j) ((i, j, k) in 3D) that are physically separated by some length scale Δx , Δy , Δz . Similarly, time can only march along in discrete units of a small time step Δt . As a result continuum fields go over to discrete arrays defined at these discrete points in space and time, i.e. $\phi(x, y, t) \rightarrow \phi^n(i, j)$, where $x = i\Delta x$, $y = j\Delta y$, $t = n\Delta t$ and the discrete indices satisfy $i = 0, 1, 2, 3, \dots, N$, $j = 0, 1, 2, 3, \dots, N$ and $n = 0, 1, 2, \dots$, where N is such that $(N - 1)\Delta x = L$ and L is the size of the physical domain, assumed here to be square. Here it is assumed that N is the same in each spatial direction, although it is straightforward to generalize all conclusions below to different N in each direction ¹.

¹The function c can also be discretized as $c(x, y, t) \rightarrow c^n(i, j)$

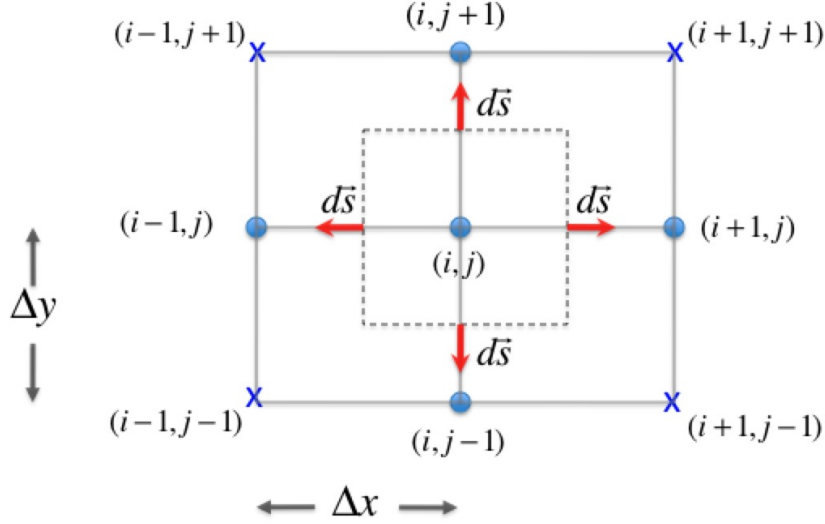


Figure B.1: Schematic of the uniform rectangular grid (solid lines) neighboring a pint (i, j) on the grid. The dashed box denotes the finite volume associated with the grid point (i, j) .

The layout of a uniform numerical mesh around a discrete coordinate $P = (i, j)$ is shown in Fig. (B.1). Points to the right and left, top and bottom of $P = (i, j)$ are referred to as *nearest neighbours*. Points at the diagonals of the square surrounding P are referred to as *next nearest neighbours*.

B.1.1 Spatial derivatives

There are several ways the to express the laplacian operator (i.e. ∇^2) in Eq.(B.1) on a discrete mesh in terms of $\phi(i, j)$ (dropping the n for now). The starting point is to relate $\phi(i, j)$ to its value at the nearest and next nearest neighbours of $P \equiv (i, j)$ (see Fig. (B.1)). This can be done using a Taylor series since the neighbours are on the order of $dx \sim dy \ll 1$ from P . Expanding $\phi(i, j)$ around P thus gives,

$$\phi(i \pm 1, j) = \phi(i, j) \pm \frac{\partial \phi(i, j)}{\partial x} \Delta x + \frac{1}{2} \frac{\partial^2 \phi(i, j)}{\partial x^2} \Delta x^2 \quad (\text{B.2})$$

$$\phi(i, j \pm 1) = \phi(i, j) \pm \frac{\partial \phi(i, j)}{\partial y} \Delta y + \frac{1}{2} \frac{\partial^2 \phi(i, j)}{\partial y^2} \Delta y^2 \quad (\text{B.3})$$

$$\phi(i \pm 1, j \pm 1) = \phi(i, j) \pm \frac{\partial \phi(i, j)}{\partial x} \Delta x + \frac{1}{2} \frac{\partial^2 \phi(i, j)}{\partial x^2} \Delta x^2 \pm \frac{\partial \phi(i, j)}{\partial y} \Delta y + \frac{1}{2} \frac{\partial^2 \phi(i, j)}{\partial y^2} \Delta y^2 \quad (\text{B.4})$$

The \pm versions of Eqs (B.2)-(B.4) describe expansions of ϕ about P using information from right/left or top/bottom neighbours of the point (i, j) . The simplest form of the discrete laplacian operator is obtained by considering information only from the top/bottom and left/right neighbours of (i, j) . Assuming for simplicity that $\Delta x = \Delta y$ and adding the $+$ and $-$ versions of Eq. (B.2) to the sums of the $+$ and $-$

versions of Eq. (B.3) yields, after re-arranging,

$$\begin{aligned}
\nabla^2 \phi(i, j) &= \frac{1}{\Delta x} \left(\frac{\{\phi(i+1, j) - \phi(i, j)\} - \{\phi(i, j) - \phi(i-1, j)\}}{\Delta x} \right. \\
&+ \left. \frac{\{\phi(i, j+1) - \phi(i, j)\} - \{\phi(i, j) - \phi(i, j-1)\}}{\Delta x} \right) + \mathcal{O}(\Delta x)^2 \\
&\approx \frac{1}{\Delta x^2} (\phi(i+1, j) + \phi(i-1, j) + \phi(i, j+1) + \phi(i, j-1) - 4\phi(i, j)) \quad (\text{B.5})
\end{aligned}$$

To highlight the intuitive nature Eq. (B.5), it is suggestively couched in the form of a finite difference of the right and left finite differenced one-sided derivatives.

Equation (B.5) is inherently anisotropic and is useful for very smoothly varying fields. For equations with rapidly varying solutions, such as those encountered in phase field and phase field crystal modeling a more stable and isotropic form of the laplacian operator is required. This is obtained by incorporating information from the next nearest neighbors. Once again, the + and - versions of Eq. (B.2) are added to the sums of the + and - versions of Eq. (B.3). To the resulting equation is now added the sum of the four equations generated by Eqs. (B.4), each weighted by 1/2. The result is

$$\begin{aligned}
\nabla^2 \phi(i, j) &= \frac{1}{\Delta x^2} \left(\frac{1}{2} [\phi(i+1, j) + \phi(i-1, j) + \phi(i, j+1) + \phi(i, j-1)] \right. \\
&+ \frac{1}{4} [\phi(i+1, j+1) + \phi(i-1, j+1) + \phi(i+1, j-1) + \phi(i-1, j-1)] \\
&- \left. 3\phi(i, j) \right) + \mathcal{O}(\Delta x)^2 \quad (\text{B.6})
\end{aligned}$$

This form of the discrete Laplacian was first used by Oono and Puri [163].

Weighting of the contribution from the next nearest neighbours by 1/2 implies that their contribution is less important to the laplacian at (i, j) than is that of the nearest neighbours. Many other such averaging schemes are possible. In the limit of small Δx , they all become equivalent.

B.1.2 Time marching

The simplest way Eq. (B.1) can evolved in discrete time on the discrete mesh illustrated in Fig. (B.1), is by applying a simple forward differencing scheme to the time derivative given by

$$\frac{\partial \phi}{\partial t} \approx \frac{\phi^{n+1}(i, j) - \phi^n(i, j)}{\Delta t} \quad (\text{B.7})$$

Equation (B.7), in conjunction with one of the second order accurate discretization schemes for the laplacian yield the following algorithm for numerical time integration of $\phi^n(i, j)$,

$$\tau \frac{\phi^{n+1}(i, j) - \phi^n(i, j)}{\Delta t} = W_\phi^2 \Delta^2 \phi^n(i, j) - N(\phi^n(i, j), c^n(i, j)), \quad (\text{B.8})$$

where Δ^2 represents the discrete Laplacian and

$$N(\phi, c) \equiv \frac{\partial f_{\text{bulk}}(\phi, c)}{\partial \phi} \quad (\text{B.9})$$

In the example of Eq. (B.1) f_{bulk} is the thermodynamic free energy of the system. In general, $N(\phi, c)$ will hereafter represent the non-gradient terms on of a reaction-diffusion type equation.

Equation (B.8) is a coupled map lattice that allows for solutions of ϕ at a future time $t = (n+1)\Delta t$ to be computed based simply on information of the field ϕ at a past time $t = n\Delta t$ according to the simple, so-called, Euler scheme

$$\phi^{n+1}(i, j) = \phi^n(i, j) + \frac{W_\phi^2 \Delta t}{\tau \Delta x^2} \bar{\Delta}^2 \phi^n(i, j) - \frac{\Delta t}{\tau} N(\phi^n(i, j), c^n(i, j)) \quad (\text{B.10})$$

where $\bar{\Delta}^2$ denotes either Eqs. (B.5) and (B.6) with the Δx^2 removed. The algorithm in Eq. (B.10) is known as an *explicit* because all quantities on the right hand side are evaluated at time $t = n\Delta t$. A major disadvantage of explicit methods is that they are numerically stable *only* for very small Δt . For the case of two spacial dimensions it will be shown below (see Eq. (B.33)) that Eq. (B.10) converges for time steps that satisfy $\Delta t < \Delta x^2 / (4W_\phi^2 / \tau)$. This restriction of the time step can make make explicit simulations very impractical since both W_ϕ and τ are microscopic parameters and thus W_ϕ^2 / τ represents a characteristic time to diffuse across a microscopic scale. A large number of time steps are thus required to span an experimentally relevant time scale. The nature of this explicit time restriction is discussed further in section (B.3).

B.2 Explicit Finite Volume Method for Model B

The Cahn-Hilliard equation ("model B"), the heat or mass diffusion equations of model C phase field models, as well as the phase field crystal equation are all examples of flux conserving equations. They have the form

$$\frac{\partial c}{\partial t} = -\nabla \cdot \vec{J} \quad (\text{B.11})$$

where \vec{J} is a flux of some quantity (e.g. heat, mass, density, etc). The flux \vec{J} is typically related to the gradient of the field $c(\vec{x}, t)$ (e.g. $\vec{J} = -M\nabla\mu(c(\vec{x}, t))$, where μ is a chemical potential). It is important when integrating such equations to use a method accurate enough to respect the conservation law of the quantity that these equations are meant to evolve. This particularly true for the mass diffusion equation encountered in phase field modeling of binary alloys. The flux balance required to conserve solute in the case of two-sided diffusivity, as well as the sharp boundary layers over which gradients must be resolved can lead to oscillatory instabilities when using simple finite difference schemes. A better way to discretize flux conserving equations is using the finite volume method.

B.2.1 Discrete volume integration

The finite volume method begins with a rectangular grid of volumes, at the centre of which lies the grid point " (i, j) " of the usual finite difference mesh used in the previous sub-section (see Fig. (B.1)). The idea behind the method is to integrate both sides of the conservation Eq. (B.11) over the area (volume in 3D) of the finite volume in the dashed lines in Fig. (B.1). This gives

$$\int_{\text{vol}} \frac{\partial c}{\partial t} d^3 \vec{x} = - \int_{\text{vol}} \nabla \cdot \vec{J} d^3 \vec{x} = - \int_{\text{surf}} \vec{J} \cdot d\vec{s} \quad (\text{B.12})$$

The last equality in Eq. (B.12) uses Gauus theorem to convert the volume integral of a divergence of flux into a surface integral of the normal flux through the surface (perimeter in 2D) enclosing the volume. The next step is to approximate the integrals in Eq. (B.12) to lowest order, which gives

$$\frac{dc(i, j, t)}{dt} dxdy = - \left\{ \vec{J}_{\text{right}} \cdot \hat{i} dy + \vec{J}_{\text{top}} \cdot \hat{j} dx - \vec{J}_{\text{left}} \cdot \hat{i} dy - \vec{J}_{\text{bot}} \cdot \hat{j} dx \right\} \quad (\text{B.13})$$

where \vec{J}_{right} is the flux evaluated at the centre of the right hand edge (face in 3D) of the volume depicted by a dashed line in Fig. (B.1), and $\hat{i} dy \equiv d\vec{s}$ is the distance (area in 3D) vector on the right face of the finite volume. Similar definitions apply for the other directions in the volume. The finite volume is assumed to be small enough that both the flux and area vectors can be assumed to be approximately constant along the length (area) of the control volume. The volume integral on the left hand side of Eq. (B.13) is analogously approximated by taking $\partial_t c$ out of the integral. This so-called one-point rule can easily be replaced by a more accurate integration rule that uses information from corner nodes. For compactness of notation the symbol $\vec{J}_{\text{right}} \cdot \hat{i} = \left(\vec{J}_{\text{right}} \right)_x \equiv J_R$ is used. Similarly J_T , J_L and J_B represent the the top, left and bottom terms, respectively, of the right hand side of Eq. (B.13).

B.2.2 Time and space discretization

The time derivative on the left hand side of Eq. (B.13) is computed using Eq. (B.7) and evaluating the fluxes on the right hand side of Eq. (B.13) at time $t = n\Delta t$ gives,

$$\frac{c^{n+1}(i, j) - c^n(i, j)}{\Delta t} dxdy = - \{ (J_R^n - J_L^n) dy + (J_T^n - J_B^n) dx \} \quad (\text{B.14})$$

Equation (B.14) provides another type of explicit scheme for updating update $c^n(i, j)$. Note that if Eq (B.11) contains a source term of the form $N(c(\vec{x}, t))$ on the right hand side, then Eq. (B.14) will contain an extra term

$$- \int_{\text{vol}} N(c(\vec{x}, t)) d^3\vec{x} \approx -N(c^n(i, j)) dxdy \quad (\text{B.15})$$

on the right hand side. Assuming that $\Delta x = \Delta y$ and that the flux can be written as a i.e. $\vec{J} = -MQ(c^n(i, j))\nabla\mu[c] \equiv -MQ^n\nabla\mu[c]$ gives,

$$c^{n+1}(i, j) = c^n(i, j) + \frac{M\Delta t}{\Delta x} \left\{ \left([Q^n\nabla\mu^n]_R - [Q^n\nabla\mu^n]_L \right) + \left([Q^n\nabla\mu^n]_T - [Q^n\nabla\mu^n]_B \right) \right\} - \Delta t N(c^n(i, j)) \quad (\text{B.16})$$

where the notation $[Q^n\nabla\mu^n]_R$ denotes the component of flux evaluated at the centre of the right edge (face 3D) of the dashed volume element in Fig. (B.1), and pointing along the normal to the same edge (see red arrows in Fig. (B.1)). Similarly for the other directions (L, R, T, B). It should be noted that quantities requiring evaluation at the centres of the dashed lines in the finite volume depicted in Fig. (B.1) must be interpolated from the corresponding quantities at the mesh points indicated, which are the ones actually being stored in the computer at any time step.

It is noted that for the special case where $Q(c) = 1$, centered differences about the finite volume faces are used to evaluate fluxes, and $\mu = c$, Eq. (B.16) reduces to the form of Eq. (B.10) and there is no difference between finite volume and finite differencing. However, when the diffusion coefficient is spatially dependent, it is preferable and easier to use Eq. (B.16).

As with all explicit methods, the time marching algorithm of Eq. (B.16) is only stable with a sufficiently small value of Δt . The precise formula for the restriction of Δt for this case depends on the form of the chemical potential μ . For the special case of $\mu = c$, the criterion is once again of the form $\Delta t < \Delta x^2/4M$ (in 2D). For more complex chemical potential, where μ contains a square gradient of the concentration (e.g. the Cahn-Hilliard model), the stability criterion becomes $\Delta t < \Delta x^4/(32M)$ in two dimensions. These stability formulae for explicit methods are discussed in more detail in section (B.3).

B.3 Stability of Time Marching Schemes

This section discusses in detail the stability criteria for explicit time integration methods. It also discusses *implicit* time marching methods, which typically permit Δt to be much larger than that possible in explicit methods. Unlike explicit methods, implicit time integration schemes evaluate quantities on the right hand side of an discretized equation (e.g. the laplacian and non-linear term) at the time $t = (n + 1)\Delta$, rather than at $t = n\Delta t$. So-called semi-implicit methods evaluate one the spatial gradients at $t = (n + 1)\Delta t$ but leave the non-linear terms at $t = n\Delta t$. This difference makes implicit methods amenable to the use of much larger values of Δt than in explicit methods. On the other hand, implicit methods can often required a very large amount of overhead, so much so that it can sometimes negate any advantage afforded by the much larger time step.

B.3.1 Linear stability of explicit methods

Explicit time stepping schemes such as Eq. (B.10) and Eq. (B.16) utilize information from the previous time (n) to propagate a field (labelled here a ϕ or c) one time step into the future (i.e. from $n \rightarrow n + 1$). Their main advantage is that they require minimal overhead in terms of memory allocation and are very easy to program on a computer. Their main disadvantage is that they are limited to small time steps Δt before their numerical integration becomes highly inaccurate and ultimately fails to converge. To illustrate the nature of this time step limitation, the linearized version of the discrete Equation (B.10) will be analyzed below for various versions of the numerical laplacian operator and for the case where

$$N(\phi, c) = -\phi \tag{B.17}$$

To keep notation simple, assume that space is in dimensions of W_ϕ and time in units of τ .

Considering first one dimension, the discrete solution $\phi^n(j)$ ($j = 1, 2, 3, \dots N$) is expanded in a discrete Fourier series as

$$\phi^n(j) = \frac{1}{\sqrt{N}} \sum_{k=1}^N \hat{\phi}^n(k) e^{-i(2\pi j k)/N} \tag{B.18}$$

where $\hat{\phi}^n(k)$ is the discrete Fourier component k , which corresponds to the continuum wave vector

$$q \equiv \frac{2\pi k}{N\Delta x} \tag{B.19}$$

This is obtained by comparing $\exp(2\pi j k/N)$ to $\exp(qx)$, the latter being the factor appearing in the continuous Fourier transform. Substituting Eq. (B.18) into the 1D version of Eq. (B.10) (i.e. ignore all i terms), and equating the coefficients of $\exp(-i(2\pi j k)/N)$ gives,

$$\hat{\phi}^{n+1}(k) = (1 + \gamma_k \Delta t) \hat{\phi}^n(k) \tag{B.20}$$

where

$$\gamma_k \equiv 1 - \Gamma_k = 1 - \frac{2}{\Delta x^2} \left[1 - \cos \left(\frac{2\pi k}{N} \right) \right] \quad (\text{B.21})$$

Comparing Eq. (B.20) with its continuum counterpart

$$\frac{\hat{\phi}^{n+1}(k) - \hat{\phi}^n(k)}{\Delta t} = (1 - q^2) \hat{\phi}^n(k) \quad (\text{B.22})$$

shows that Γ_k is the finite size, discrete laplacian. Indeed, in the limit of long wavelengths, or alternatively, infinite system size (i.e. $2\pi k/N \ll 1$), a Taylor series expansion of Γ_k gives

$$\Gamma_k \approx \left(\frac{2\pi k}{N\Delta x} \right)^2 - \frac{\Delta x^2}{12} \left(\frac{2\pi k}{N\Delta x} \right)^4 + \dots \quad (\text{B.23})$$

Thus, at long wavelengths $\Gamma_k \rightarrow q^2$.

The solution of Eq. (B.20) is found by substituting the trial function $\hat{\phi}^n(k) = a_o A^n$ which yields

$$[A - (1 + \gamma_k \Delta t)] a_o A^n = 0 \quad (\text{B.24})$$

which gives $A = (1 + \gamma_k \Delta t)^n a_o$. From the initial conditions $\hat{\phi}^0(k)$, a_o is determined and thus

$$A = (1 + \gamma_k \Delta t)^n \hat{\phi}^0(k) \quad (\text{B.25})$$

It is clear from inspection of Eq. (B.25) that two conditions for a divergent, discrete solution, to exist:

$$\begin{aligned} 1 + \gamma_k \Delta t &> 1 \\ 1 + \gamma_k \Delta t &< -1 \end{aligned} \quad (\text{B.26})$$

The first case corresponds to $\gamma_k > 0$ or $1 - \Gamma_k > 1$, which will always occur for some sufficiently large wavelengths or at a given wavelength for sufficiently large system. This divergence also occurs in the exact solution of the diffusion equation, $\hat{\phi}(k) = e^{(1-q^2)t}$, for $q^2 < 1$. It is a physical linear instability that leads to a growing solutions (e.g. the start of phase separation), which are ultimately bounded by the ϕ^3 or one of the other polynomial order terms of ϕ that occur in the non-linear terms $N(\phi)$. This will be discussed further below. The second criterion for a divergent solution in Eq. (B.26) requires that $\gamma_k \Delta t < 2$, which imposes a time step constrain on the diffusion equation of the form

$$\Delta t < \frac{-2}{1 - \Gamma_k} \quad (\text{B.27})$$

The most stringent condition on Δt occurs when Γ_k is a maximum, which occurs at the wave vector $k = N/2$, which gives, from Eq. (B.21), $\gamma_k = 1 - 4/\Delta x^2$. Thus, the stability criterion of Eq. (B.27) in one spatial dimension becomes

$$\Delta t < \frac{2\Delta x^2}{4 - \Delta x^2} \approx \frac{\Delta x^2}{2} \quad (\text{B.28})$$

where the second equality assumes, as is usual, that $\Delta x \ll 1$ in numerical simulations.

The arguments above can be applied to two and three dimensions as well. For example, in 2D, the analogue of the expansion in Eq. (B.18) is

$$\phi^n(i, j) = \frac{1}{N} \sum_{k_x=1}^N \sum_{k_y=1}^N \hat{\phi}^n(k_x, k_y) e^{-I2\pi(i k_x + j k_y)/N} \quad (\text{B.29})$$

(where $I = \sqrt{-1}$ is used here to avoid confusion with i , the lattice index.) Substituting Eq. (B.29) into Eq. (B.10), with Laplacian given by Eq. (B.5), gives

$$\hat{\phi}^{n+1}(k_x, k_y) = (1 + \gamma_k \Delta t) \hat{\phi}^n(k_x, k_y) \quad (\text{B.30})$$

where now

$$\gamma_{k_x, k_y} \equiv 1 - \Gamma_{k_x, k_y} = 1 - \frac{2}{\Delta x^2} \left[2 - \cos\left(\frac{2\pi k_x}{N}\right) - \cos\left(\frac{2\pi k_y}{N}\right) \right] \quad (\text{B.31})$$

Proceeding exactly as the 1D case yields

$$A = (1 + \gamma_{k_x, k_y} \Delta t)^n \hat{\phi}^0(k_x, k_y) \quad (\text{B.32})$$

The same stability considerations considered previously now yield the time step constraint

$$\Delta t < \frac{2\Delta x^2}{8 - \Delta x^2} \approx \frac{\Delta x^2}{4} \quad (\text{B.33})$$

The one dimensional and two dimensional stability thus differ by a factor of 1/2.

The same considerations can similarly be applied to model A with the more isotropic laplacian of Eq. (B.6). It is left to the reader to work through the stability analysis to find that the stability criterion corresponding to the numerical laplacian operator in Eq. (B.6) is given by

$$\Delta t < \frac{2\Delta x^2}{4 - \Delta x^2} \approx \frac{\Delta x^2}{2} \quad (\text{B.34})$$

which is a significant improvement over the 2D stability achieved by using the laplacian of Eq. (B.5).

Equations (B.28), (B.33) and (B.34) all imply that information cannot be propagated –numerically or otherwise– over the length scale Δx faster than the diffusion time inherent in the original equation. When the full non-linear form of N is implemented maximum on Δt is typically reduced even further, depending on the strength of the non-linearity.

Model B type equations, such as Eq. (B.16), can contain higher order gradients. For example, the diffusion of chemical impurities in a dilute phase is described by $\partial_t c = M \nabla^2 \mu$ where $\mu = \partial f / \partial c - \nabla^2 c$. Using Eq. (B.5) to finite difference μ , the linear portion of the finite difference form of this diffusion equation becomes (in 1D for simplicity)

$$c^{n+1}(i) = c^n(i) - \frac{\Delta t}{\Delta x^2} \left[c^n(i+2) - 4c^n(i+1) + 6c^n(i) - 4c^n(i-1) + c^n(i-2) \right] \quad (\text{B.35})$$

Substituting the discrete Fourier expansion of the form Eq. (B.18) into Eq. (B.35) gives, after some algebraic manipulations, $\Delta t < \Delta x^4 / (8M)$. Generalizing this procedure to two and three dimensions is straightforward, and yield the following criterion time step limitation for model B –at least in the linear stability sense–

$$\Delta t < \frac{\Delta x^4}{2^{2d+1} M} \quad (\text{B.36})$$

B.3.2 Non-linear instability criterion for Δt

The biggest restriction to linear stability discussed in section (B.3.1) arises in the interface since Δx is usually small there to resolve the order parameter. As ϕ moves away from the interface, Δx can become larger as interface resolution issues do not arise in phase field simulations. It turns out, however, that even away from the interface, there is a restriction to the time step for explicit methods due to the non-linear terms in $N(\phi, c)$. This is shown here by investigating the effect of the non-linear terms at work in a Model A type equation the discrete form of which is given by

$$\phi^{n+1}(i) = \phi^n(i) - \Delta t N(\phi^n(i), U) \quad (\text{B.37})$$

where it is recalled that t is in units of τ and where U here represents an external field or a general coupling of the ϕ field to a dimensionless temperature or chemical driving force acting at the mesh point i . For simplicity, only one dimension is considered in this analysis. As usual, the extension to two and three dimensions is exactly analogous.

Eq. (B.37) is an iterative mapping whose stable or *fixed* points, at any mesh point i , are found by solving

$$\phi^* = \phi^* - \Delta t N(\phi^*, U) \quad (\text{B.38})$$

Consider as a concrete example the interpolation function for the order parameter equations in section (5.7.3) (where ϕ varies from -1 to $+1$). Equation (B.38) becomes

$$\phi^* - (\phi^*)^3 - \hat{\lambda}U(1 - (\phi^*)^2)^2 = 0, \quad (\text{B.39})$$

the solutions of which are

$$\begin{aligned} \phi^* &= \pm 1 \\ \phi^* &= \frac{1}{2\hat{\lambda}U} \left(-1 \pm \sqrt{1 + 4(\hat{\lambda}U)^2} \right) \end{aligned} \quad (\text{B.40})$$

The first two of these roots should be recognized as the bulk values of the order parameter in model C for the pure material or alloy models discussed in the main text. Typically, the driving force $\hat{\lambda}U$ is small and so one of two roots on the last line of Eq. (B.40) becomes $\phi^* \approx \hat{\lambda}U$, while the other satisfies $|\phi^*| > 1$ and will be ignored.

The root $\phi^* \approx \hat{\lambda}U$ is unstable as any perturbation at all from $\phi = \phi^*$ causes ϕ to flow away from it. The roots $\phi^* = \pm 1$, on the other hand, can be stable or unstable depending on the size of Δt . This is illustrated in Fig. (B.2). For small enough Δt , $\phi^* = \pm 1$ becomes a stable attractive fixed point. That means that the sequence of iterates $\{\phi^n(i)\}$ asymptotically goes to $\phi^* = 1$. As Δt increases, the sequence of iterates $\{\phi^n(i)\}$ will eventually become locked in a so-called limit cycle around the $\phi^* = 1$ fixed point, signaling the breakdown of stability².

The criterion separating stable from non-stable behaviour for a fixed point of the iterative map in Eq. (B.37) is given by

$$\begin{aligned} \frac{\partial \phi^{n+1}}{\partial \phi^n} \Big|_{\phi^n = \phi^*} &= 0 \\ \implies 1 + \Delta t \left(1 - 3(\phi^*)^2 + 4\hat{\lambda}U(1 - (\phi^*)^2)\phi^* \right) &= 0 \end{aligned} \quad (\text{B.41})$$

²(It is simplest to consider the physical case where all $\phi(i)$ values initially lie in the range $-1 \leq \phi^0(i) \leq 1$). Indeed, for $\phi^0(i)$ values lying too far from $\phi^* = \pm 1$, iterates $\phi^n(i)$ will diverge to $\pm\infty$

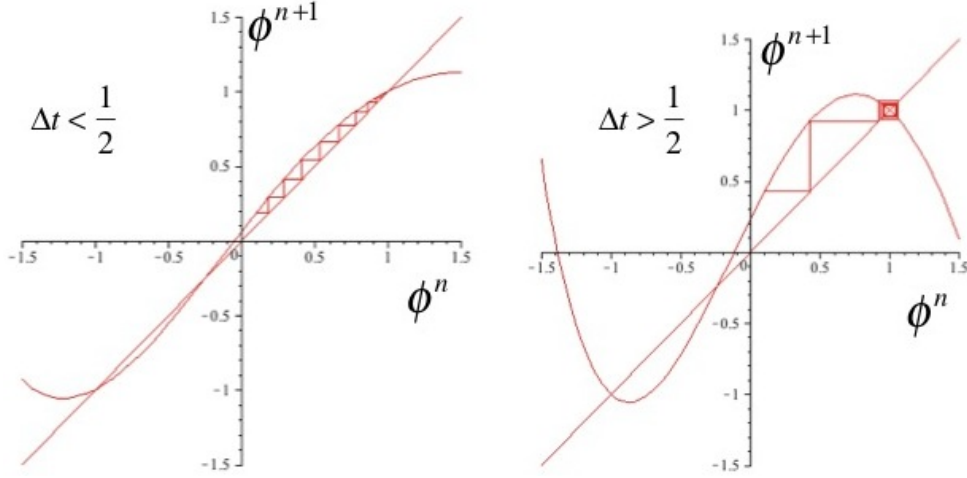


Figure B.2: Flow of iterates of the map $\phi^{n+1} = f(\phi^n)$ where $f(x) = x + \Delta t(x - x^3 - \hat{\lambda}U(1 - x^2)^2)$. (Left) for $\Delta t < 1/2$, iterates $\phi^{n+1}(i)$ flow to the fixed point $\phi^* = 1$. (Right) For $\Delta t > 1/2$ the fixed point generates a so-called limit cycle. Further increasing Δt will cause the iterates $\phi^{n+1}(i)$ to diverge. In this figure $\hat{\lambda}U = -0.25$.

Substituting $\phi^* = \pm 1$ into the last line of Eq. (B.41) sets the threshold on the maximum value of Δt as

$$\Delta t < \frac{1}{2} \quad (\text{B.42})$$

As mentioned at the beginning of this subsection, the non-linear conditions imposed by Eq. (B.42) is less restrictive than the linear condition imposed by Eq. (B.33), due to the fact that in most cases the mesh spacing should resolve the interface with some degree of accuracy, i.e. $\Delta x \leq 1$. To the extent that it is sufficient to very weakly resolve the interface, it is possible to let $\Delta x > 1$, thus allowing Δt to increase toward its ultimate cap imposed by Eq. (B.42). It turns out however, that there is also a constraint on how large Δx can be made in an explicit method before a grid-related instability sets in. This is examined next.

B.3.3 Non-linear instability criterion for Δx

This subsection continues with the example of section (B.3.2) and examines the effect of Δx on the stability of a model A type phase field equation. In particular, consider to linear order the structure of the steady state solution of the model A type equation studied in the previous section around one of its stable points, $\phi^* = \{\hat{\lambda}U, \pm 1\}$. Let the solution be expressed in the form $\phi = \phi^* + \delta\phi$. Substituting this expansion of ϕ into model A gives

$$\nabla^2 \delta\phi + \left(1 - 3(\phi^*)^2 + 4\hat{\lambda}U(1 - (\phi^*)^2)\phi^*\right) \delta\phi + \underbrace{\left\{\phi^* - (\phi^*)^3 - \hat{\lambda}U(1 - (\phi^*)^2)^2\right\}}_{=0, \text{ Eq. (B.39)}} = 0 \quad (\text{B.43})$$

The solution of Eq. (B.43) in 1D is of the form

$$\begin{aligned}\delta\phi &\sim e^{\pm\sqrt{2}x}, \quad \text{for } \phi^* = \pm 1 \\ \delta\phi &\sim e^{\pm i\sqrt{\beta}x}, \quad \text{for } \phi^* \approx \hat{\lambda}U,\end{aligned}\tag{B.44}$$

where

$$\beta = 1 - 3(\hat{\lambda}U)^2 + 4(\hat{\lambda}U)^2(1 - (\hat{\lambda}U)^2) \approx 1 + (\hat{\lambda}U)^2\tag{B.45}$$

The criterion determining how large Δx can now be made on the basis of how well the solution of the discretized equation corresponding to Eq. (B.43) reproduces the solution forms implied by Eqs. (B.44).

The discrete version of Eq. (B.43) is given by

$$\delta\phi^n(i+1) - 2\delta\phi^n(i) + \delta\phi^n(i-1) + \Delta x^2 \left(1 - 3(\phi^*)^2 + 4\hat{\lambda}U(1 - (\phi^*)^2)\phi^*\right) \delta\phi^n(i) = 0\tag{B.46}$$

where Eq. (B.5) is assumed for the square gradient operator. Consider first the case $\phi^* \approx \hat{\lambda}U$. Equation (B.46) is solved by a solution of the form

$$\delta\phi^n(i) = A\Lambda^i\tag{B.47}$$

if the constant Λ is equal to

$$\Lambda = \frac{\left(2 - \beta\Delta x^2 \pm \sqrt{(\beta\Delta x^2 - 2)^2 - 4}\right)}{2}\tag{B.48}$$

Similarly, the case $\phi^* = \pm 1$ is solved by a solution of the form Eq. (B.47), if Λ takes the form

$$\Lambda = \left(1 + \Delta x^2 \pm \sqrt{(\Delta x^2 + 1)^2 - 1}\right)\tag{B.49}$$

The $\phi^* = \pm 1$ roots in Eq. (B.49) are always real and this so in Eq. (B.49) can always be cast into the analytical form in second line of Eqs. (B.44). On the other hand, for the solution of the $\phi^* = \hat{\lambda}U$ solution of the order parameter can only be cast into the form of the first line in Eqs. (B.44) if the root Λ in Eq. (B.48) is complex. This implies that the radical must be negative, which requires

$$\begin{aligned}(\beta\Delta x^2 - 2)^2 - 4 &< 0 \\ \implies \Delta x &< \frac{2}{\sqrt{1 + (\hat{\lambda}U)^2}}\end{aligned}\tag{B.50}$$

Thus Eq. (B.50) puts a hard limit on how large Δx can be which, not very surprisingly perhaps, is very close to $\Delta x \approx 1$ when the local driving force is not too large, as suspected by physical considerations previously.

B.3.4 Implicit methods

The restriction on Δt imposed by explicit time marching can be overcome by using an *semi-implicit* time marching scheme, which allows for much larger time steps Δt to be used. Briefly, implicit methods express the fields on the right hand side of Eq. (B.8) in terms of the new time $n + 1$. This results in an *implicit* system of equations of the form $\mathbf{A}\bar{x}^{n+1} = \mathbf{b}(\bar{x}^n)$, where \bar{x}^{n+1} is the solution at all nodes at the new time $n + 1$, which depends on the solution at all nodes at the previous time step, n , and \mathbf{A} is a non-diagonal matrix of constants. This system of equations can formally be inverted to be solved. However, most straight inversion approaches require too many operations and are of little use to phase field modeling. For example, on an $N \times N$ mesh, matrix inversion of the above system of equations could take as long as N^6 operations. A simpler alternative is to solve this system of equations by iteration, however the simplest iterative methods (e.g. Jacobi, Conjugate gradient, Gauss-Seidel)³ require from $\mathcal{O}(N^3)$ to $\mathcal{O}(N^4)$ operations to converge. Contrast these to one time update of an explicit scheme which requires N^2 operations (i.e. one per node). Indeed, in most simple semi-implicit methods the gains of using a larger time step are nullified by their convergence time. As a result they are usually avoided in dynamical simulations requiring a very large number of time steps for the requisite physics to unfold. Two exceptions to this general rule are multi-grid methods and Fourier techniques both of which can require of order ($\mathcal{O}(N^2)$ steps) to converge. Implicit methods are beyond the scope of this book and the reader is referred to the abundant literature on this topic for more information.

Before closing this Appendix, it is noteworthy that the Cahn-Hilliard Eq. (4.14) can also be integrated numerically using finite differences –although as a conservation equation the finite volume technique presented below may be more accurate. Because of the conservation law there will be a $\Delta^4 \phi(i, j) \leftarrow \nabla^4 \phi$ term generated. The easiest way to handle this equation numerically is to compute $\Delta^2 \mathcal{M}^n(i, j)$, where $\mathcal{M}^n(i, j)$ is the right hand side of Eq. (B.8).

B.4 Semi-Implicit Fourier Space Method

This section describes the formulation of a Fourier-based semi-implicit method for solving phase field crystal type equations. A great advantage of working in Fourier methods is that in frequency space, even powers of gradients become even-powered algebraic expressions of the wave vector (or inverse wavelength). These methods are thus especially convenient to use with equations that exhibit periodic solutions such as those found in phase field crystal models.

The paradigm equation to be considered is of the form

$$\frac{\partial \rho}{\partial t} = \nabla^2 \left(\frac{\delta F[\rho]}{\delta \rho} \right) \quad (\text{B.51})$$

A commonly used form of $F[\rho]$ in phase field modeling is given by

$$F[\rho] = \int \left\{ \rho \frac{1 - C(\nabla)}{2} \rho + f(\rho) \right\} d\vec{x} \quad (\text{B.52})$$

³The simplest iterative schemes, Jacobi iteration, decomposes the system $\mathbf{A}\bar{x}^{n+1} = \mathbf{b}(\bar{x}^n)$ into $(\mathbf{A}_D + \mathbf{A}_o)\bar{x}^{n+1} = \mathbf{b}(\bar{x}^n)$, where \mathbf{A}_D is the diagonal portion of \mathbf{A} and \mathbf{A}_o is the off-diagonal portion. The original system is then written as $\mathbf{A}_D \bar{x}_{m+1}^{n+1} = \mathbf{b}(\bar{x}^n) - \mathbf{A}_o \bar{x}_m^{n+1}$ where m is an iteration index. An initial "guess" for \bar{x}_0^{n+1} leads to \bar{x}_1^{n+1} , which is substituted back into the right hand side, leading to \bar{x}_2^{n+1} , etc. The sequence $\{\bar{x}_m^{n+1}\}$ presumably converges to a fixed point, i.e. \bar{x}^{n+1} .

where the operator $C(\nabla)$ is in general a function of gradient operators, i.e.,

$$C(\nabla) = C_0 + C_2 \nabla^2 + C_4 \nabla^4 \quad (\text{B.53})$$

while $f(\rho)$ denotes any non-linear function of the field ρ . The generic free energy given by Eqs. (B.52)-(B.53) can be specialized to the case of the phase field crystal model by setting $1 - C(\nabla) = B_l + 2B_R^2 \nabla^2 + B_s R^4 \nabla^4$ (which would make the phase field crystal constants $B_l = 1 - C_0$, $B_s = C_2^2/(4|C_4|)$) and $f(\rho) = -\rho^3/6 + \rho^4/12$. This model can also be specialized to the Cahn-Hilliard equation used to study spinodal decomposition by setting $C_0 = -1$, $C_2 = 1$, $C_4 = 0$ and dropping the cubic term in $f(\rho)$.

Substituting Eq. (B.52) into Eq. (B.51) gives

$$\frac{\partial \rho}{\partial t} = \nabla^2 [(1 - C(\nabla))\rho + N(\rho)] \quad (\text{B.54})$$

where $N(\rho) \equiv \partial f(\rho)/\partial \rho$. Equation (B.54) can be efficiently solved numerically by taking the Fourier transforms of both sides of Eq. (B.51), which yields

$$\frac{\partial \hat{\rho}_k}{\partial t} = \Delta_k^2 (1 - \hat{C}(|k|)) \hat{\rho}_k + \Delta_k^2 \hat{N}_k[\rho] \quad (\text{B.55})$$

where $\hat{N}_k[\rho]$ is the Fourier transform of $N(\rho)$ and Δ_k^2 is the discrete Fourier space representation of the ∇^2 for a finite size system (which is algebraic in Fourier space). For example in a system of infinite size $\nabla^2 \rightarrow |\vec{k}|^2$. Finally, $\hat{C}(|\vec{k}|)$ is the Fourier transform of the operator $C(\nabla)\rho$.

Defining $w_k \equiv \Delta_k^2 (1 - \hat{C}(|k|))$, and $\hat{n}_k(t) \equiv \Delta_k^2 \hat{N}_k[\rho]$, we can formally invert Eq. (B.55)⁴, obtaining

$$\hat{\rho}_k(t) = e^{w_k t} \int_0^t e^{-w_k s} \hat{n}_k(s) ds + e^{w_k t} \hat{\rho}_k(0) \quad (\text{B.56})$$

can similarly write Eq. (B.56) at time $t + \Delta t$,

$$\begin{aligned} \hat{\rho}_k(t + \Delta t) &= e^{w_k(t+\Delta t)} \int_0^{t+\Delta t} e^{-w_k s} \hat{n}_k(s) ds + e^{w_k(t+\Delta t)} \hat{\rho}_k(0) \\ &= e^{w_k(t+\Delta t)} \left(\int_0^t e^{-w_k s} \hat{n}_k(s) ds + \int_t^{t+\Delta t} e^{-w_k s} \hat{n}_k(s) ds \right) + e^{w_k(t+\Delta t)} \hat{\rho}_k(0) \\ &= e^{w_k \Delta t} \hat{\rho}_k(t) + e^{w_k(t+\Delta t)} \int_t^{t+\Delta t} e^{-w_k s} \hat{n}_k(s) ds \end{aligned} \quad (\text{B.57})$$

The integral in the last line of Eq. (B.57) can be numerically approximated by expanding $\hat{n}_k(t + \Delta t)$ to second order, i.e. $\hat{n}_k(t + \Delta t) \approx \hat{n}_k(t) + (d\hat{n}_k(t)/dt) \Delta t$. This gives,

$$\int_t^{t+\Delta t} e^{-w_k s} \hat{n}_k(s) ds = \frac{1}{2} \left(e^{-w_k t} \hat{n}_k(t) \Delta t + e^{-w_k(t+\Delta t)} \hat{n}_k(t) \Delta t + O(\Delta t)^2 \right), \quad (\text{B.58})$$

⁴This utilizes the solution methodology for the first order ODE $y' + p(x)y = g(x)$ whose solution is given by $y = (\int^x \mu(s)g(s)ds) / \mu(x)$, where the integration factor $\mu(x) = \exp(-\int^x p(s)ds)$. In our case, $p(t) = -w_k$ and $g(t) = \hat{n}_k(t)$ as defined in the text.

which leads to

$$\begin{aligned}
\hat{\rho}_k(t + \Delta t) &\approx e^{w_k \Delta t} \hat{\rho}_k(t) + \frac{e^{w_k(t+\Delta t)}}{2} \left(e^{-w_k t} \hat{n}_k(t) \Delta t + e^{-w_k(t+\Delta t)} \hat{n}_k(t) \Delta t \right) \\
&= e^{w_k \Delta t} \hat{\rho}_k(t) + \frac{1}{2} \left(e^{w_k \Delta t} \hat{n}_k(t) \Delta t + \hat{n}_k(t) \Delta t \right) \\
&= e^{w_k \Delta t} \hat{\rho}_k(t) + \frac{1}{2} \left(\hat{n}_k(t) \Delta t + O(\Delta t)^2 + \hat{n}_k(t) \Delta t \right) \\
&= e^{w_k \Delta t} \hat{\rho}_k(t) + \Delta t \Delta_k^2 \hat{N}_k[\rho]
\end{aligned} \tag{B.59}$$

Recognizing that factor $\Delta_k^2 \Delta t$ in Eq. (B.59) can be approximated, for small Δt , as

$$\Delta_k^2 \Delta t \approx (e^{w_k \Delta t} - 1) / (1 - \hat{C}(|\vec{k}|)), \tag{B.60}$$

allows us to write Eq. (B.59) as

$$\hat{\rho}_k(t + \Delta t) \approx e^{[\Delta_k^2(1-\hat{C}(|k|))\Delta t]} \hat{\rho}_k(t) + \frac{e^{[\Delta_k^2(1-\hat{C}(|k|))\Delta t]} - 1}{(1 - \hat{C}(|k|))} \hat{N}_k[\rho(\vec{x}, t)] \tag{B.61}$$

Equation (B.61) formally constitutes numerical scheme for time marching Eq. (B.55). A higher order form of this scheme can be found in Ref. [153]. It becomes identical to traditional explicit time marching for $\Delta t \ll 1$. Its main advantage, however, arises from Eq. (B.60), which allows Eq. (B.61) to be advanced in time with *significantly larger* time steps than most traditional semi-implicit schemes. Moreover, unlike most semi-implicit methods, the one presented here requires only $\mathcal{O}(N^2)$ operations per time step. Of course, like semi-implicit methods, there is some upper bound to Δt . However, rather than the right hand side of Eq. (B.61) becoming unstable (i.e. "exploding") if $\Delta t \gg 1$, the solutions become inaccurate.

B.5 Finite Element Method

Since its introduction into main stream phase field modeling about 10 years ago, one of the most efficient numerical scheme for [accurately] simulating phase field models is the use of adaptive refinement (AMR). At the heart of AMR is the use of non-structured meshes, on which the physics of a particular model is played out using finite difference, finite volume or finite element methods. A separate section on adaptive re-meshing algorithm is beyond the scope of this book. (The interested reader can refer to one of [171, 173, 85] and references therein for details on AMR). The solvers in most AMR codes is the finite element method. Since most physics and materials science students have the least experience with finite elements, this section provides a basic tutorial on finite element theory. Specifically, it introduces the the *Galerkin* finite element approach and applies it in 1D and 2D to solve the Poisson equation.

B.5.1 The Diffusion Equation in 1D

Consider first a generic 1D reaction diffusion equation of the form

$$\frac{\partial \phi}{\partial t} = \nabla(\epsilon \nabla \phi) + \rho(x) \tag{B.62}$$

where here ϵ denotes the generalized diffusion constant. Consider a mesh as shown in Fig. B.3. The mesh has m elements of width "l" denoted by e_i , $i = 1, \dots, m$. These constitute a mesh of nodes labeled by

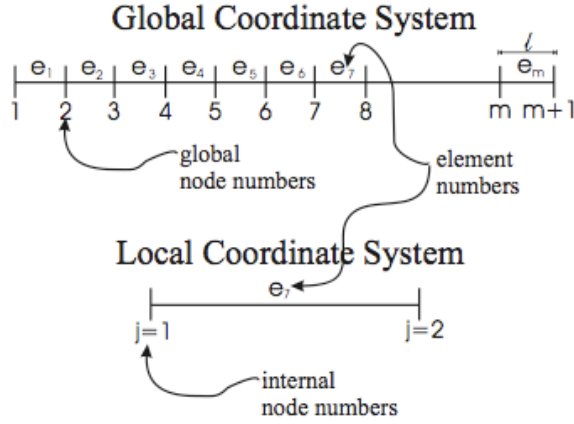


Figure B.3: Global versus local coordinates in 1-D used in the finite element method.

“global node numbers” running from $i = 1, \dots, m+1$. Each element has a set of “internal node numbers” $j = 1, \dots, n$, where n is the number of nodes in an element.

To proceed, define a family of *weight functions* $W_j(x)$ where $j = 1, \dots, n$. In addition, define a set of so-called “shape functions” $N_j(x)$ for $j = 1, \dots, n$, which are used to interpolate the field ϕ in the element as

$$\phi = \sum_{j=1}^n N_j(x) \phi_j \quad (\text{B.63})$$

where ϕ_j is the field at the node labelled internally by j . In this simple one dimensional example being considered here, $n = 2$ (see Fig B.3). The “weighted residual” approach to finite element analysis [53] forgoes the “exact” solution of Eq. (B.62) in each element, in favour of an approximate solution of the equation when weighted by each of the functions $W_j(x)$, $j = 1, \dots, n$.

$$\int_{(i-1)l}^{il} W_j(x) \frac{\partial \phi}{\partial t} - \int_{(i-1)l}^{il} W_j(x) \frac{\partial}{\partial x} \left(\epsilon(x) \frac{\partial \phi}{\partial x} \right) - \int_{(i-1)l}^{il} W_j(x) \rho_f(x) = 0, \quad \forall j = 1, 2, \dots, n \quad (\text{B.64})$$

In the *Galerkin* finite element approach, $W_j(x) \equiv N_j(x)$ for $j = 1 \dots n$, that is, the *weight functions* are the same as the *shape functions*. Equation (B.64) thus becomes

$$\int_{(i-1)l}^{il} N_j(x) \left\{ \frac{\partial \phi}{\partial t} - \nabla(\epsilon \nabla \phi) - \rho_f \right\} dx = 0, \quad \forall j = 1, 2, \dots, n \quad (\text{B.65})$$

which can be written in a more compact form as

$$\int_{(i-1)l}^{il} \begin{bmatrix} N_1(x) \\ N_2(x) \end{bmatrix} \left\{ \frac{\partial \phi}{\partial t} - \nabla(\epsilon \nabla \phi) - \rho_f \right\} dx = 0 \quad (\text{B.66})$$

The interpolation of the field ϕ within the domain of the element, Eq. (B.63), can similarly be expressed in this vector notation as

$$\phi = [N_1 N_2] \begin{bmatrix} \phi_{e_i}^1 \\ \phi_{e_i}^2 \end{bmatrix} = [N][\phi_{e_i}]^T \quad (\text{B.67})$$

where the shape functions N_1 and N_2 in the global coordinate frame are chosen for linear interpolation as

$$\begin{aligned} N_1(x) &= \frac{l-[x-(i-1)l]}{l} & (i-1) < x < il & & i = 1, \dots, m \\ N_2(x) &= \frac{x-(i-1)l}{l} & (i-1) < x < il & & i = 1, \dots, m \end{aligned} \quad (\text{B.68})$$

where l is the size of the element.

In what follows, it will be convenient (particularly in 2D below) to work in a *local coordinate system*, defined by a local variable ξ that spans the domain $0 < \xi < 1$. The transformation from local coordinates to global coordinate is made via

$$x_{global} = l\xi + (i-1)l = (i-1)l(1-\xi) + il\xi \quad (\text{B.69})$$

The Jacobian of this transformation between the local and global coordinates is

$$J = \frac{\partial x_{global}}{\partial \xi} = l \quad (\text{B.70})$$

In local coordinates, the shape functions thus become

$$N_1(\xi) = (1-\xi) \quad (\text{B.71})$$

$$N_2(\xi) = \xi \quad (\text{B.72})$$

Note that when the transformation from the local to the global coordinates uses the shape functions used to interpolate the field within an element, the finite element formulation is called *isoparametric*.

Substituting Eq. (B.67) into Eq. (B.66) gives rise to a matrix equation satisfied by the nodal field values in each element. Specifically, the first term in the matrix equation becomes

$$\int_{(i-1)l}^{il} [N]^T \frac{d}{dt} [N] [\phi_{e_i}]^T dx = \int_{(i-1)l}^{il} [N]^T [N] dx [\dot{\phi}_{e_i}] = \int_0^1 [N(\xi)]^T [N(\xi)] l d\xi [\dot{\phi}_{e_i}] \quad (\text{B.73})$$

where $[\phi_{e_i}]$ is shorthand matrix notation for the nodal field values, i.e.,

$$[\phi_{e_i}] = \begin{bmatrix} \phi_{e_i}^1 \\ \phi_{e_i}^2 \end{bmatrix} \quad (\text{B.74})$$

Note that the last equality is in element-local co-ordinates. The last integral is referred to as the "mass matrix", defined by

$$[C_{e_i}] \equiv \int_0^1 [N(\xi)]^T [N(\xi)] l d\xi \quad (\text{B.75})$$

The second term in the matrix version of Eq. (B.66) gives rise to

$$\int_{(i-1)l}^{il} [N] \frac{\partial}{\partial x} \left(\epsilon \frac{\partial}{\partial x} \phi \right) dx = \int_{(i-1)l}^{il} \left([N]^T \frac{\partial}{\partial x} \left(\epsilon \frac{\partial}{\partial x} ([N] [\phi_{e_i}]^T) \right) \right) dx \quad (\text{B.76})$$

Integrating by parts via

$$u = [N] \quad (\text{B.77})$$

$$du = [N_x] \quad (\text{B.78})$$

$$v = \epsilon \frac{\partial}{\partial x} ([N][\phi]^T) \quad (\text{B.79})$$

$$dv = \frac{\partial}{\partial x} \left(\epsilon \frac{\partial}{\partial x} [N][\phi]^T \right) dx, \quad (\text{B.80})$$

gives

$$\begin{aligned} \int_{(i-1)l}^{il} \{ [N]^T \frac{\partial}{\partial x} \left(\epsilon(\xi) \frac{\partial}{\partial x} ([N][\phi_{e_i}]^T) \right) \} dx &= [N]^T \epsilon(\xi) \frac{\partial}{\partial x} [N][\phi_{e_i}]^T \Big|_{(i-1)l}^{il} \\ &- \int_{(i-1)l}^{il} \epsilon(\xi) [N_x]^T \frac{\partial}{\partial x} [N][\phi_{e_i}]^T dx \end{aligned} \quad (\text{B.81})$$

which is equivalently expressed in local coordinates as

$$\begin{aligned} \frac{1}{l} \int_0^1 [N]^T \frac{\partial}{\partial \xi} \left(\epsilon \frac{\partial}{\partial \xi} [N][\phi_{e_i}]^T \right) d\xi &= \frac{1}{l} [N]^T \epsilon \frac{\partial}{\partial \xi} [N][\phi_{e_i}]^T \Big|_0^1 \\ &- \left(\frac{1}{l} \int_0^1 \frac{\partial}{\partial \xi} [N]^T \epsilon \frac{\partial}{\partial \xi} [N] l d\xi \right) [\phi_{e_i}]^T \end{aligned} \quad (\text{B.82})$$

The first term on the right hand side of Eq. (B.82) is a boundary term for all elements e_i , $i = 1, 2, 3, \dots, m$. It is straightforward to see that all terms arising from adjoining elements interior to the domain $0 \leq x \leq L$ cancel, except those from the two elements containing the left ($x = 0$) and right ($x = L$) domain boundaries [53]. These two surviving terms, from elements e_1 and e_m ($m + 1$ is the rightmost node in the domain), are given by

$$[BC_1]^T = -[N(\xi = 0)]^T \frac{\epsilon(x = 0)}{l} \frac{\partial}{\partial \xi} [N(\xi = 0)][\phi_{e_1}]^T, \quad (\text{B.83})$$

and

$$[BC_{m+1}]^T = [N(\xi = l)]^T \frac{\epsilon(x = L)}{l} \frac{\partial}{\partial \xi} [N(\xi = l)][\phi_{e_m}]^T \quad (\text{B.84})$$

Moreover, the second term on the right hand side of Eq. (B.82) can be written as

$$\left(\frac{1}{l} \int_0^1 \epsilon(\xi) \frac{\partial}{\partial \xi} [N]^T \frac{\partial [N]}{\partial \xi} d\xi \right) [\phi_{e_i}]^T = [K_{e_i}][\phi_{e_i}]^T \quad (\text{B.85})$$

where $[K_{e_i}]$ is referred to as the ‘‘stiffness matrix’’. The final term in Eq. (B.66) is the source term. This is written as

$$\int_{(i-1)l}^{il} [N]^T \rho_f(x) dx = \int_0^1 [N]^T \rho_f(\xi) l d\xi = [R_{e_i}]^T \quad (\text{B.86})$$

Collecting the terms in Eqs. (B.75), (B.85) and (B.86) and the boundary condition in Eq. (B.82), the following matrix equation is obtained for each element:

$$[C_{e_i}][\dot{\phi}_{e_i}] = [K_{e_i}][\phi_{e_i}] + [R_{e_i}]^T + [BC_{e_i}]^T \quad (\text{B.87})$$

where the boundary term $[BC_{e_i}]^T$ is formally written for each element, but is only non-zero in the elements e_1 and e_m via Eqs. (B.83) and (B.84). To obtain the global solution valid simultaneously

B.5.2 The 2D Poisson Equation

The method defined above can be generalized to 2D in a straightforward way. Consider a mesh of 4-noded square elements as shown in Fig. (B.4). The 2D Galerkin finite element analysis begins with

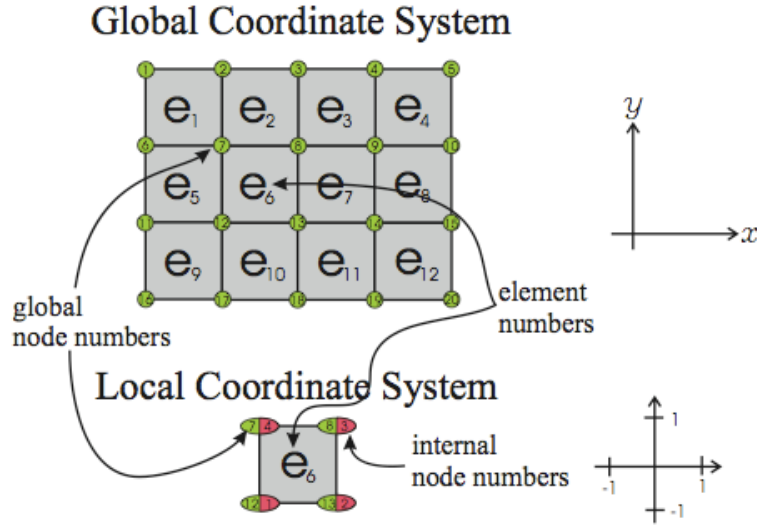


Figure B.4: Global versus local coordinates in 2D used in the finite element method.

the interpolating functions defined in the local coordinates of each element (See Fig. (B.4)). For linear interpolation based on the four noded elements, the shape functions are given explicitly as

$$N_1(\xi, \eta) = \frac{1}{4}(1 - \xi)(1 - \eta) \quad (\text{B.94})$$

$$N_2(\xi, \eta) = \frac{1}{4}(1 + \xi)(1 - \eta) \quad (\text{B.95})$$

$$N_3(\xi, \eta) = \frac{1}{4}(1 + \xi)(1 + \eta) \quad (\text{B.96})$$

$$N_4(\xi, \eta) = \frac{1}{4}(1 - \xi)(1 + \eta) \quad (\text{B.97})$$

The field being solved for is interpolated within the element as

$$\phi = [N][\phi_{e_i}]^T = [N_1(\xi, \eta) \ N_2(\xi, \eta) \ N_3(\xi, \eta) \ N_4(\xi, \eta)][\phi_{e_i}]^T \quad (\text{B.98})$$

In the isoparametric formulation, the transformation from internal to global coordinates is given by

$$X = N_1(\xi, \eta)X_1 + N_2(\xi, \eta)X_2 + N_3(\xi, \eta)X_3 + N_4(\xi, \eta)X_4 \quad (\text{B.99})$$

and

$$Y = N_1(\xi, \eta)Y_1 + N_2(\xi, \eta)Y_2 + N_3(\xi, \eta)Y_3 + N_4(\xi, \eta)Y_4 \quad (\text{B.100})$$

Where X_i and Y_i are the x and y co-ordinates of the 4 nodes of the elements. The Jacobian of the transformation is defined by the matrix

$$J = \begin{pmatrix} \frac{\partial x}{\partial \xi} & \frac{\partial y}{\partial \xi} \\ \frac{\partial x}{\partial \eta} & \frac{\partial y}{\partial \eta} \end{pmatrix} \quad (\text{B.101})$$

where

$$|J| = \frac{l_{xe} l_{ye}}{4}. \quad (\text{B.102})$$

Through these definitions, integrals on the 2D domain Ω_{e_i} of an element are transformed as

$$\int \int_{\Omega_{e_i}} f(x, y) dx dy = \int_{-1}^1 \int_{-1}^1 f(x(\xi, \eta), y(\xi, \eta)) |J| d\xi d\eta \quad (\text{B.103})$$

The Galerkin finite element residual of the 2D Poisson or diffusion type equation is written as

$$\int \int [N]^T \left\{ \frac{\partial \phi}{\partial t} - \nabla (\epsilon \cdot \nabla \phi) - \rho_f \right\} dx dy = 0 \quad (\text{B.104})$$

Working in local coordinates, the source term in Eq. (B.104) becomes

$$\begin{aligned} \int \int [N]^T \rho_f dx dy &= \int_{-1}^1 \int_{-1}^1 [N(\xi, \eta)]^T \rho(\xi, \eta) |J| d\xi d\eta \\ &= \frac{l_x l_y}{4} \int_{-1}^1 \int_{-1}^1 [N(\xi, \eta)]^T \rho(\xi, \eta) d\xi d\eta \equiv [R]_{e_i}^T \end{aligned} \quad (\text{B.105})$$

where the last equality assumes equal sized elements of dimensions $l_x \times l_y$. Using Green's theorem the gradient terms in Eq. (B.104) becomes

$$\begin{aligned} &\int \int_{\Omega_{e_i}} [N]^T \nabla (\epsilon \cdot \nabla \phi) dx dy = \\ &- \int \int_{\Omega_{e_i}} \frac{\partial}{\partial x} ([N]^T \epsilon) \frac{\partial \phi}{\partial x} dx dy + \oint [N]^T \epsilon \frac{\partial \phi}{\partial x} dl - \int \int_{\Omega_{e_i}} \frac{\partial}{\partial y} ([N]^T \epsilon) \frac{\partial \phi}{\partial y} dx dy + \oint [N]^T \epsilon \frac{\partial \phi}{\partial y} dl \end{aligned} \quad (\text{B.106})$$

where the field within the element is interpolated by

$$\phi = [N][\phi_{e_i}]^T \quad (\text{B.107})$$

The partial derivatives are expressed in local element coordinates as

$$\frac{\partial \phi}{\partial \xi} = [N_{,\xi}] [\phi_{e_i}]^T = \begin{bmatrix} \partial N_1 / \partial \xi & \partial N_2 / \partial \xi & \partial N_3 / \partial \xi & \partial N_4 / \partial \xi \end{bmatrix} \times \begin{pmatrix} \phi_1 \\ \phi_2 \\ \phi_3 \\ \phi_4 \end{pmatrix} \quad (\text{B.108})$$

and

$$\frac{\partial \phi}{\partial \eta} = [N_{,\eta}] [\phi_{e_i}]^T = \begin{bmatrix} \frac{\partial N_1}{\partial \eta} & \frac{\partial N_2}{\partial \eta} & \frac{\partial N_3}{\partial \eta} & \frac{\partial N_4}{\partial \eta} \end{bmatrix} \times \begin{pmatrix} \phi_1 \\ \phi_2 \\ \phi_3 \\ \phi_4 \end{pmatrix} \quad (\text{B.109})$$

Equations (B.108) and (B.109) are compactly expressed as

$$\begin{pmatrix} \phi_{l\xi} \\ \phi_{l\eta} \end{pmatrix} = \begin{bmatrix} N_{1l\xi} & N_{2l\xi} & N_{3l\xi} & N_{4l\xi} \\ N_{1l\eta} & N_{2l\eta} & N_{3l\eta} & N_{4l\eta} \end{bmatrix} \times \begin{pmatrix} \phi_1 \\ \phi_2 \\ \phi_3 \\ \phi_4 \end{pmatrix} \quad (\text{B.110})$$

The partial derivatives in the global frame are related to those in the local frame by

$$\begin{pmatrix} \phi_{lx} \\ \phi_{ly} \end{pmatrix} = J^{-1} \begin{bmatrix} N_{1l\xi} & N_{2l\xi} & N_{3l\xi} & N_{4l\xi} \\ N_{1l\eta} & N_{2l\eta} & N_{3l\eta} & N_{4l\eta} \end{bmatrix} [\phi_{e_i}]^T = [B][\phi_{e_i}]^T \quad (\text{B.111})$$

In terms of Eq. (B.111), the boundary terms in Eq. (B.106) become

$$\oint [N]^T \epsilon \frac{\partial \phi}{\partial x} dl = \left(\int_{-1}^1 [N]^T \epsilon(\xi, \eta) B(1 : |J| d\xi) \right) [\phi_{e_i}]^T = [BC_x]_{e_i} [\phi_{e_i}]^T \quad (\text{B.112})$$

$$\oint [N]^T \epsilon \frac{\partial \phi}{\partial y} dl = \left(\int_{-1}^1 [N]^T \epsilon(\xi, \eta) B(2 : |J| d\eta) \right) [\phi_{e_i}]^T = [BC_y]_{e_i} [\phi_{e_i}]^T \quad (\text{B.113})$$

where $B(1 :)$ and $B(2 :)$ denote the first and second rows of the matrix $[B]$, respectively. The area integrals in Eq. (B.106) are expressed as

$$I_1 = \frac{l_x l_y}{2} \left(\int_{-1}^1 \int_{-1}^1 [B(1, :)]^T \epsilon [B(1, :)] d\xi d\eta \right) [\phi_{e_i}]^T \quad (\text{B.114})$$

and

$$I_2 = \frac{l_x l_y}{2} \left(\int_{-1}^1 \int_{-1}^1 [B(2, :)]^T \epsilon [B(2, :)] d\xi d\eta \right) [\phi_{e_i}]^T \quad (\text{B.115})$$

which can be combined into one matrix as

$$\begin{aligned} I &= I_1 + I_2 \\ &= - \left(\int_{-1}^1 \int_{-1}^1 \{ [B(1, :)]^T [B(1, :)] + [B(2, :)]^T [B(2, :)] \} \epsilon(\xi, \eta) |J| d\xi d\eta \right) [\phi_{e_i}]^T \\ &\equiv - [K]_{e_i} [\phi_{e_i}]^T, \end{aligned} \quad (\text{B.116})$$

where $[K]_{e_i}$ is defined as the stiffness matrix. To solve the complete problem, it is necessary, as in the 1D case, to generate, or *assemble* a global matrix equation out of each of the element equations. The global finite element matrix becomes

$$\underbrace{\left(\sum_{e_i} [C]_{e_i} \right)}_{[C]} [\phi]^T = - \underbrace{\left(\sum_{e_i} [K]_{e_i} \right)}_{[K]} [\phi]^T + \underbrace{\sum_{e_i} [R]_{e_i}^T}_{[R]^T} + \underbrace{\sum_{e_i} \left([BC_x]_{e_i} + [BC_y]_{e_i} \right)}_{[BC]^T} [\phi]^T \quad (\text{B.117})$$

An explicit formulation for time integration of Eq. (B.117) is given by

$$[\phi_{n+1}] = [\phi_n] + \Delta t [C]^{-1} (-[K][\phi_n]^T + [R]^T + [BC]^T) \quad (\text{B.118})$$

Using the same principle of *consistent mass lumping* as in the 1D case, the corresponding 2D lumped mass matrix for each element becomes

$$[C_{e_i}] = \frac{l_x l_y}{4} \begin{bmatrix} 1 & 0 & 0 & 0 \\ 0 & 1 & 0 & 0 \\ 0 & 0 & 1 & 0 \\ 0 & 0 & 0 & 1 \end{bmatrix}_{e_i} \quad (\text{B.119})$$

The global mass matrix in the global frame is assembled in the usual way. The above formulation can also be used to solve the Poisson Equation, in which case time in Eq. (B.118) is fictitious. It serves as an iteration variable in a Jacobi iteration scheme for Eq. (B.118). At convergence ($\phi_{n+1} = \phi_n$), the solution is that of the Poisson Equation.

Appendix C

Miscellaneous Derivations

C.1 Structure Factor: Section (4.6.1)

The structure factor is formally defined by

$$S(\vec{q}, t) = \int d\vec{r} e^{i\vec{q}\cdot\vec{r}} \langle \langle \phi(\vec{r}^{\prime}, t) \phi(\vec{r} - \vec{r}^{\prime}, t) \rangle \rangle \quad (\text{C.1})$$

where $\phi(\vec{r}, t)$ is the order parameter and the inner double angled brackets represent volume averages over all space of the variable \vec{r}^{\prime} while the outer angled brackets represent averaging over an infinite number of configurations of the system. Representing $\phi(\vec{r}, t)$ by its Fourier representation

$$\phi(\vec{r}, t) = \int d\vec{k} \phi_{\vec{k}}(t) e^{-i\vec{k}\cdot\vec{r}} \quad (\text{C.2})$$

Eq. (C.1) becomes,

$$\begin{aligned} S(\vec{q}, t) &= \int d\vec{r}^{\prime} \langle \langle \left(\int d\vec{k} \phi_{\vec{k}} e^{-i\vec{k}\cdot\vec{r}^{\prime}} \right) \left(\int d\vec{k}^{\prime} \phi_{\vec{k}^{\prime}} e^{-i\vec{k}^{\prime}\cdot(\vec{r}-\vec{r}^{\prime})} \right) \rangle \rangle e^{i\vec{q}\cdot\vec{r}} \\ &= \langle \langle \int \int d\vec{k} d\vec{k}^{\prime} \phi_{\vec{k}} \phi_{\vec{k}^{\prime}} e^{-i(\vec{k}-\vec{k}^{\prime})\cdot\vec{r}^{\prime}} \left(\int d\vec{r} e^{-i(\vec{k}^{\prime}-\vec{q})\cdot\vec{r}} \right) \rangle \rangle \end{aligned} \quad (\text{C.3})$$

Where it has been assumed that the order of the integrations and averages (which is also an integration) can be changed. Using the definition of the delta function of the form

$$\int d\vec{r} e^{-i(\vec{k}^{\prime}-\vec{q})\cdot\vec{r}} \equiv \delta(\vec{k}^{\prime} - \vec{q}) \quad (\text{C.4})$$

makes it possible to eliminate the \vec{k}^{\prime} integral in Eq. (C.3), and making the replacement $\vec{k}^{\prime} = \vec{q}$. This gives,

$$S(\vec{q}, t) = \langle \langle \int \int d\vec{k} \phi_{\vec{k}} \phi_{\vec{q}} e^{-i(\vec{k}-\vec{q})\cdot\vec{r}^{\prime}} \rangle \rangle \quad (\text{C.5})$$

Implementing the inner angled brackets in Eq. (C.5) as a spatial average over \vec{r}' finally gives,

$$\begin{aligned} S(\vec{q}, t) &= \left\langle \int \int d\vec{k} \phi_{\vec{k}} \phi_{\vec{q}} \left(\int d\vec{r}' e^{-i(\vec{k}-\vec{q})\cdot\vec{r}'} \right) \right\rangle \\ &= \langle |\phi_{-\vec{q}}|^2 \rangle \end{aligned} \quad (\text{C.6})$$

where the expression in large round brackets in Eq. (C.5) is identified with $\delta(\vec{k} - \vec{q})$. Recall, once again, that the remaining angled brackets in Eq (C.6) denote different realization of the \vec{q} mode of the square of the Fourier transform of the order parameter.

C.2 Transformations from Cartesian to Curvilinear Co-ordinates: Section (A.2)

This section derives the transformation of the ∇ operator to its counterpart in the curvilinear coordinate system used in the matched asymptotic analysis of section (A) and elsewhere in the text. The starting point is Fig. (C.1) which illustrates how to represent a point P with cartesian coordinate (x, y) in curvilinear coordinates (u, s) which are local to the interface. In the figure, \hat{n} is a unit normal to the interface at point Q , while $\hat{\tau}$ is a unit tangent to the interface at the point Q . The variable θ measures the angle between the x -axis and a line parallel to $\hat{\tau}$, as shown in Fig. (C.1). The line PQ is parallel to \hat{n} and has length u . The distance s measures the arclength along the interface, from a reference point (star symbol) to point Q . The vector $\vec{R}(s)$ is the displacement from the origin to the point Q . It is clear that the quantities \hat{n} , $\hat{\tau}$, \vec{R} and θ associated with the point Q all depend on the arclength s .

In terms of the variables defined in Fig. (C.1), the cartesian coordinates of the unit vectors \hat{n} and $\hat{\tau}$ are given by

$$\begin{aligned} \hat{n} &= (\sin \theta, -\cos \theta) \\ \hat{\tau} &= -\frac{d\hat{n}}{d\theta} = (-\cos \theta, -\sin \theta) \end{aligned} \quad (\text{C.7})$$

The coordinates of P are thus expressed in terms of u and θ as

$$\begin{aligned} x &= R_x(s) + u\hat{n}_x = R_x(s) + u \sin \theta \\ y &= R_y(s) + u\hat{n}_y = R_y(s) - u \cos \theta \end{aligned} \quad (\text{C.8})$$

Moreover, θ and s are related via the local interface curvature κ at Q according to

$$\kappa = -\frac{d\theta}{ds} \quad (\text{C.9})$$

Using the above definition, the transformation of quantities between (x, y) and (u, s) can now be made.

Writing a the order parameter as $\phi(s(x, y), u(x, y))$ and using the chain rule gives

$$\begin{pmatrix} \frac{\partial \phi}{\partial x} \\ \frac{\partial \phi}{\partial y} \end{pmatrix} = \underbrace{\begin{pmatrix} \frac{\partial s}{\partial x} & \frac{\partial u}{\partial x} \\ \frac{\partial s}{\partial y} & \frac{\partial u}{\partial y} \end{pmatrix}}_{\mathbf{J}} \begin{pmatrix} \frac{\partial \phi}{\partial s} \\ \frac{\partial \phi}{\partial u} \end{pmatrix} \quad (\text{C.10})$$

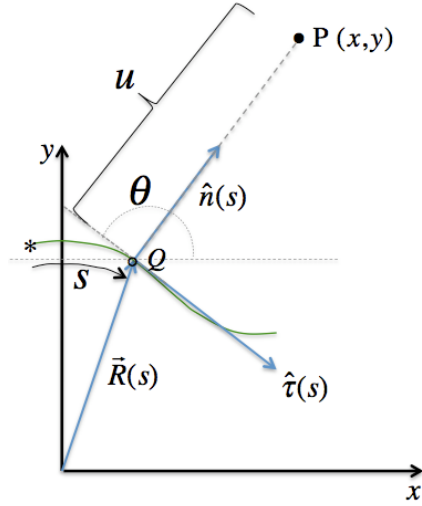


Figure C.1: Representation of a point P with cartesian coordinates (x, y) in curvi-linear co-ordinates (u, s) which are attached to the interface represented by the green curve. The vector \hat{n} is the unit normal to the interface at point Q and u is the length of QP (dotted line), which is parallel to \hat{n} . The vector $\hat{\tau}$ is perpendicular to \hat{n} and tangential to the interface at point Q . The distance s measures arclength along the interface, from a reference point (star symbol) to Q . The variable θ is the angle between the x -axis and a line parallel to $\hat{\tau}$. Other details described in the text

Where \mathbf{J} is the Jacobian matrix of the transformation from (u, s) derivatives to (x, y) derivatives. The inverse transformation is similarly defined via \mathbf{J}^{-1} as

$$\begin{pmatrix} \frac{\partial \phi}{\partial s} \\ \frac{\partial \phi}{\partial u} \end{pmatrix} = \underbrace{\begin{pmatrix} \frac{\partial x}{\partial s} & \frac{\partial y}{\partial s} \\ \frac{\partial x}{\partial u} & \frac{\partial y}{\partial u} \end{pmatrix}}_{\mathbf{J}^{-1}} \begin{pmatrix} \frac{\partial \phi}{\partial x} \\ \frac{\partial \phi}{\partial y} \end{pmatrix} \quad (\text{C.11})$$

Using Eq. (C.8) and (C.9) the partials dx and dy with respect to ds and du are found to be

$$\begin{aligned} dx &= \left[\frac{d\vec{R}_x}{ds} - u\kappa \cos \theta \right] ds + \sin \theta du \\ dy &= \left[\frac{d\vec{R}_y}{ds} - u\kappa \sin \theta \right] ds - \cos \theta du \end{aligned} \quad (\text{C.12})$$

Using Eqs. (C.12) gives

$$\mathbf{J}^{-1} = \begin{pmatrix} \frac{d\vec{R}_x}{ds} - u\kappa \cos \theta & \frac{d\vec{R}_y}{ds} - u\kappa \sin \theta \\ \sin \theta & -\cos \theta \end{pmatrix} \quad (\text{C.13})$$

It will be noted that $d\vec{R}/ds = \hat{\tau}$. This is easy to see in the special case where the vector \vec{R} rotates in a circle as a constant angular velocity. The more general case follows analogously. Using this result,

Inverting \mathbf{J}^{-1} , recalling that that $\hat{\tau}$ has unit length and using Eq. (C.10) gives,

$$\begin{pmatrix} \frac{\partial}{\partial x} \\ \frac{\partial}{\partial y} \end{pmatrix} = -\frac{1}{(1+u\kappa)} \begin{pmatrix} \cos\theta \frac{\partial}{\partial s} + \{\hat{\tau}_y - u\kappa \sin\theta\} \frac{\partial}{\partial u} \\ \sin\theta \frac{\partial}{\partial s} - \{\hat{\tau}_x - u\kappa \cos\theta\} \frac{\partial}{\partial u} \end{pmatrix} \quad (\text{C.14})$$

which, in compact notation, becomes

$$\nabla = \hat{n} \frac{\partial}{\partial u} + \frac{1}{1+u\kappa} \hat{\tau} \frac{\partial}{\partial s} \quad (\text{C.15})$$

It is useful for the analysis of section (A.9) to apply Eq. (C.15) to the case of a vector function $\vec{f} = f_{\hat{n}}(u, s)\hat{n} + f_{\hat{\tau}}(u, s)\hat{\tau}$. In that case, Eq. (C.15) can be written as

$$\begin{aligned} \nabla \cdot \vec{f} &= \partial_u (\hat{n} \cdot \vec{f}) + \frac{1}{1+u\kappa} \left\{ \partial_s (\hat{\tau} \cdot \vec{f}) - \vec{f} \cdot \partial_s \hat{\tau} \right\} \\ &= \partial_u (\hat{n} \cdot \vec{f}) + \frac{1}{1+u\kappa} \left\{ \partial_s (\hat{\tau} \cdot \vec{f}) + \kappa \hat{n} \cdot \vec{f} \right\} \end{aligned} \quad (\text{C.16})$$

where $\partial_s \hat{\tau} = \partial_s \theta \partial_\theta \hat{\tau} = -\kappa \hat{n}$ has been used in the second line of Eq. (C.16). Scaling u according to $\xi = u/W_\phi$, s by $\sigma = s/W_\phi/\epsilon$ and performing the expansion, $(1+u\kappa)^{-1} = 1 - \epsilon\xi + \dots$ (see Eqs. (A.36)) gives,

$$\nabla \cdot \vec{f} = \frac{1}{W_\phi} \left[\partial_u (\hat{n} \cdot \vec{f}) + \epsilon \left\{ \partial_\sigma (\hat{\tau} \cdot \vec{f}) + \kappa \hat{n} \cdot \vec{f} \right\} \right] + \mathcal{O}(\epsilon^2) \quad (\text{C.17})$$

This equation is useful in deriving Eqs. (A.9) and (A.10) by replacing \vec{f} by ∇ and $q\nabla$, respectively.

It is also useful to express the quantity $\nabla\phi/|\nabla\phi|$ in terms of \hat{n} . Starting with Eq. (C.15), re-scaling distances as was done above and once again expanding $(1+\epsilon\xi\bar{\kappa})$ gives

$$-\frac{\nabla\phi}{|\nabla\phi|} = \hat{n}(1 + \mathcal{O}(\epsilon^2)) + \hat{\tau}\mathcal{O}(\epsilon) \quad (\text{C.18})$$

where the minus sign is introduced so that the normal vector points from solid to liquid in the convention when $\phi_s > \phi_L$.

C.3 Newton's Method for Non-Linear Algebraic Equations: Section (6.9.5)

Let $f(x)$ be some non-linear function of x . The simplest way to solve the equation

$$f(x) = 0 \quad (\text{C.19})$$

is by Newton's iteration method. The idea is to make a first guess at the solution, called x_n . Assuming x_n is sufficiently close to the actual solution, then a first order Taylor expansion of $f(x)$ about $x = x_n$ can be used to estimate the actual solution by finding where the linear approximation to $f(x)$ is zero. Specifically, solving $f(x_{n+1}) = x_n + f'(x_n)(x_{n+1} - x_n) = 0$ yields $x_{n+1} = x_n - f(x_n)/f'(x_n) \equiv \mathcal{G}(x_n)$, where the prime denotes differentiation. Substituting x_{n+1} back on the right hand side of the previous

equation gives a refined estimate of the actual solution, i.e., $x_{n+2} = \mathcal{G}(x_{n+1})$. This procedure is repeated until the estimates stop changing, to some accuracy.

The extension of Newton's method to two non-linear equations

$$\begin{aligned} f_1(x, y) &= 0 \\ f_2(x, y) &= 0 \end{aligned} \tag{C.20}$$

is precisely analogous to the 1D case. Let the initial guess of the solution be $\vec{x}_n = (x_n, y_n)$. The functions $f_1(x, y)$ and $f_2(x, y)$ are expanded to linear order about (x_n, y_n) , yielding,

$$\begin{aligned} f_1(x_n, y_n) + \partial_x f_1(x_n, y_n)(x_{n+1} - x_n) + \partial_y f_1(x_n, y_n)(y_{n+1} - y_n) &= 0 \\ f_2(x_n, y_n) + \partial_x f_2(x_n, y_n)(x_{n+1} - x_n) + \partial_y f_2(x_n, y_n)(y_{n+1} - y_n) &= 0 \end{aligned} \tag{C.21}$$

Solving Eqs. (C.21) gives

$$\begin{pmatrix} x_{n+1} \\ y_{n+1} \end{pmatrix} = \begin{pmatrix} x_n \\ y_n \end{pmatrix} + \frac{1}{W(x_n, y_n)} \begin{pmatrix} \partial_y f_2(x_n, y_n) & -\partial_y f_1(x_n, y_n) \\ \partial_x f_2(x_n, y_n) & -\partial_x f_1(x_n, y_n) \end{pmatrix} \begin{pmatrix} f_1(x_n, y_n) \\ f_2(x_n, y_n) \end{pmatrix} \tag{C.22}$$

where $W(x_n, y_n) \equiv \partial_x f_1(x_n, y_n) \partial_y f_2(x_n, y_n) - \partial_y f_1(x_n, y_n) \partial_x f_2(x_n, y_n)$. Eq. (C.22) is of the form $\vec{x}_{n+1} = \mathcal{G}(\vec{x}_n)$, which can be iterated until iterates stop changing, to a sufficient accuracy.

Bibliography

- [1] When fluctuations are added to the SH equation it changes the order of the transition from uniform to modulated or striped phases from second order to first order. See reference [93].
- [2] D. A. and H. Levine. *Phys. Rev. A.*, **39**:3041, 1989.
- [3] A.A.Wheeler, W.J.Boettinger, and G.B.McFadden. *Phys Rev A*, **45**:7424, 1992.
- [4] C. V. Achim, M. Karttunen, K. R. Elder, E. Granato, T. Ala-Nissila, and S. C. Ying. *Phys. Rev. E*, **74**:021104, 2006.
- [5] C. V. Achim, J. A. P. Ramos, M. Karttunen, K. R. Elder, E. Granato, T. Ala-Nissila, and S. C. Ying. *Phys. Rev. E*, **79**:011606, 2009.
- [6] C. V. Achim, J.A.P. Ramos, M. Karttunen, K. R. Elder, E. Granato, T. Ala-Nissila, and S. C. Ying. Nonlinear driven response of a phase-field crystal in a periodic pinning potential. *Phys. Rev. E*, **79**:011606, 2009.
- [7] S. Akamatsu, G. Faivre, and T. Ihle. *Phys. Rev. E*, **51**:4751, 1995.
- [8] R. Almgren. *SIAM J. Appl. Math.*, 59:2086, 1999.
- [9] R. Almgren, W. S. Dai, and V. Hakim. *Phys. Rev. Lett.*, 71:3461, 1993.
- [10] Y.B. Altundas and G.Caginalp. *Jour. Stat. Phys*, **110**:1055, 2003.
- [11] A. J. Archer and M. Rauscher. *J. Phys. A*, **37**:9325, 2004.
- [12] B. P. Athreya, J. A. Dantzig, S. Liu, and R. Trivedi. On the role of confinement of solidification in pure materials and binary alloys. *Philosophical Magazine*, 86(24):3739–3756, 2006.
- [13] B. P. Athreya, N. Goldenfeld, and J. A. Dantzig. *unpublished study*, 2005.
- [14] A. A.Wheeler, W. J.Boettinger, and G. B.McFadden. *Phys Rev E*, **47**:1893, 1993.
- [15] A. A.Wheeler, B. T. Murray, and R. J. Schaefer. *Physica D*, **66**:243, 1993.
- [16] M. J. Aziz and W. J. Boettinger. *Acta Metall. Mater.*, **42** :257, 1994.
- [17] H. Garcke B. Nestler and B. Stinner. *Phys. Rev. E*, **71**:041609, 2005.

- [18] Robert W. Balluffi, Samuel M. Allen, and W. Craig Carter. *Kinetics of Materials*. Wiley- Interscience (Hoboken, New Jersey), 2005.
- [19] M. Barber, A. Barbieri, and J.S. Langer. *Phys. Rev. A*, 36:3340, 1987.
- [20] J.-L. Barrat and J.-P. Hansen. *Basic and Concepts for Simple and Complex Fluids*. Cambridge University Press, 2003.
- [21] J. Bechhoefer and A. Libchaber. *Phys. Rev. B*, **35**:1393, 1987.
- [22] E. Ben-Jacob, N. Goldenfeld, B.G. Kotliar, and J.S. Langer. *Phys. Rev. Lett.*, 53:2110, 1984.
- [23] E. Ben-Jacob, N. Goldenfeld, J.S. Langer, and G. Schön. *Phys. Rev. Lett.*, 51:1930, 1983.
- [24] J. Berry, K. R. Elder, and M. Grant. *Phys. Rev. B*, **77**:224114, 2008.
- [25] J. Berry, M. Grant, and K. R. Elder. *Phys. Rev. E*, **73**:031609, 2006.
- [26] W. J. Boettinger and J. A. Warren. *Met. Trans. A*, **27**:657, 1996.
- [27] W. J. Boettinger and J. A. Warren. *J. Crystal Growth*, 200:583, 1999.
- [28] B. Bottger, J. Eiken, and I. Steinbach. *Acta Materialia*, **54**:2697, 2006.
- [29] D. Bouchard and J. S. Kirkaldy. *Met. and Mater. Trans. B*, 28B:651, 1997.
- [30] D. Boyer and J. Vinals. Grain boundary pinning and glassy dynamics in stripe phases. *Phys. Rev. E*, 65:046119, 2002.
- [31] J. Bragard, A. Karma, Y. H. Lee, and M. Plapp. *Interface Sci.*, 10:121, 2002.
- [32] E. Brener and V. I. Melnikov. *Adv. Phys.*, 40:53, 1991.
- [33] E. Brener and D. Temkin. *Phys. Rev. E*, 51:351, 1995.
- [34] R.C. Brower, D. Kessler, J. Koplik, and H. Levine. *Phys. Rev. Lett.*, 51:1111, 1983.
- [35] G. Caginalp. *Arch. Rat. Mech. Anal.*, 92:205, 1986.
- [36] G. Caginalp. *Anal. of Phys.*, 172:136, 1986.
- [37] G. Caginalp and J. T. Lin. *IMA J. Appl. Math.*, 39:51, 1987.
- [38] G. Caginalp and E. Socolovsky. *SIAM J. Sci. Comp.*, 15:106, 1991.
- [39] J. W. Cahn and J. E. Hilliard. *J. Chem. Phys.*, 28:258, 1958.
- [40] W. Callister. *Materials Science and Engineering an Introduction*. Wiley, New York, 2nd ed edition, 2007.
- [41] C.Beckermann, H.J.Diepers, I.Steinbach, A.Karma, and X.Tong. *J Comp Phys*, **154**:468, 1999.
- [42] P. R. Cha, D. H. Yeon, and J. K. Yoon. *Acta Mater.*, **49**:3295–3307, 2001.

- [43] P.M. Chaikin and T.C Lubensky. Principles of condensed matter physics. Cambridge University Press, Cambridge, Great Britain, 1995.
- [44] Chakin and Lubensky. Principles of Condensed Matter Physics, page 629. North Holland, Amsterdam, 1987.
- [45] B. Chalmers. Principles of Solidification. Wiley, New York, 1964.
- [46] P. Y. Chan, N. Goldenfeld, and J. A. Dantzig. Molecular dynamics on diffusive time scales from the phase-field-crystal equation. Phys. Rev. E, 79:035701, 2009.
- [47] L.-Q. Chen. Script. Metall. et Mater., 32:115, 1995.
- [48] L. Q. Chen and A. G. Khachaturyan. Acta. Mater., 39:2533, 1991.
- [49] L. Q. Chen and A. G. Khachaturyan. Acta. Mater., 41(1):279, 1993.
- [50] L.-Q Chen and W. Yang. Phys. Rev. B, 50:15752, 1994.
- [51] J. B. Collins and H. Levine. Phys. Rev. B, 31:6119, 1985.
- [52] H. E. Cook. Acta Metall., 18:297, 1970.
- [53] R. D. Cook, D. D. Malkus, M. E. Plesha, and R. J. Witt. Concepts and applications of finite element analysis. John Wiley and Sons inc, 2002.
- [54] M C Cross and P C Hohenberg. Pattern formation outside of equilibrium. Rev. Mod. Phys., 65:851–1112, 1993.
- [55] M. C. Cross and D. I. Meiron. Domain coarsening in systems far from equilibrium. Phys. Rev. Lett., 75:2152, 1995.
- [56] D. Danilov and B. Nestler. Phys. Rev. Lett., 93:215501–1, 2004.
- [57] B. Echebarria, R. Folch, A. Karma, and M. Plapp. Phys. Rev. E., 70:061604–1, 2004.
- [58] B. Echebarria, A. Karma, and S. Gurevich. Phys. Rev. E, 81:021608, 2010.
- [59] J. Eiken, B. Bottger, and I. Steinbach. Phys. Rev. E, 73:2697, 2006.
- [60] K. Elder, J. Barry, and N. Provatas. TMS Letters, 3:41, 2004.
- [61] K. Elder, M. Katakowski, M. Haataja, and M. Grant. Phys. Rev. Lett., 88:245701, 2002.
- [62] K. Elder, N. Provatas, J. Berry, P. Stefanovic, and M. Grant. Phys. Rev. B., 75:064107, 2007.
- [63] K. R. Elder, F. Drolet, J. M. Kosterlitz, and M. Grant. Phys. Rev. Lett., 72:677, 1994.
- [64] K. R. Elder, M. Grant, N. Provatas, and M. Kosterlitz. Phys. Rev. E, 64:1604, 2001.
- [65] K R Elder and Martin Grant. Modeling elastic and plastic deformations in non-equilibrium processing using phase field crystals. Phys. Rev. E, 70:051605, 2004.

- [66] K. R. Elder and Martin Grant. *Modeling elastic and plastic deformations in non-equilibrium processing using phase field crystals*. Phys. Rev. E, 70(5):051605, November 2004.
- [67] K. R. Elder, Mark Katakowski, Mikko Haataja, and Martin Grant. *Modeling elasticity in crystal growth*. Physical Review Letters, 88(24):245701-1-4, 2002.
- [68] K. R. Elder, J. Vinals, and M. Grant. *Dynamic scaling and quasi-ordered states in the two dimensional swift-hohenberg equation*. Phys. Rev. A, 46:7618, 1992.
- [69] K. R. Elder, J. Vinals, and M. Grant. *Ordering dynamics in the two dimensional swift-hohenberg equation*. Phys. Rev. Lett., 68:3024, 1992.
- [70] J. D. Eshelby. *Continuum theory of defects*. Academic Press, solid state physics, vol. 3 edition, 1956.
- [71] R. Evans. *Advances in Physics*, 28, No. 2:143, 1979.
- [72] D. Fan and L.-Q. Chen. *Acta Metallurgica*, 45:3297, 2002.
- [73] D. Fan, S. P. Chen, L.-Q. Chen, and P. W. Voorhees. *Acta Materialia*, 50:1897, 2002.
- [74] R. Folch and M. Plapp. *Phys. Rev. E.*, 72:011602, 2005.
- [75] H. Garcke, B. Nestler, and B. Stoth. *SIAM J. Appl. Math.*, 60:295, 1999.
- [76] H. Garcke, B. Nestler, and B. Stoth. *SIAM J. Appl. Math.*, 64:775, 2004.
- [77] M. H. Giga and Y. Giga. *Arch. Rational Mech. Anal.*, 141:117, 1998.
- [78] N. Goldenfeld, B. P. Athreya, and J. A. Dantzig. *Phys. Rev. E.*, 72:020601(R), 2005.
- [79] N. Goldenfeld, B. P. Athreya, and J. A. Dantzig. *Renormalization-group theory for the phase-field crystal equation*. Phys. Rev. E, 75:011601, 2006.
- [80] N. Goldenfeld, B. P. Athreya, and J. A. Dantzig. *J. Stat. Phys.*, to appear, 2007.
- [81] L. Gránásy, T. Pusztai, and T. Börzsönyi. *Physical Review Letters*, 88:206105-1, 2002.
- [82] L. Gránásy, T. Pusztai, and T. Börzsönyi. *Journal of Crystal Growth*, 237-239:1813, 2002.
- [83] L. Granasy, T. Pusztai, T. Borzsonyi, J. A. Warren, B. Kvamme, and P. F. James. *Phys. Chem. Glasses*, 45:107, 2004.
- [84] L. Gránásy, T. Pusztai, J. A. Warren, J. F. Douglas, T. Börzsönyi, and V. Ferreiro. *Nature of Materials*, 2:92, 2003.
- [85] M. Greenwood. *Phase field modeling of solid state precipitates*. Ph.D Thesis, McMaster University, 2008.
- [86] M. Greenwood, M. Haataja, and N. Provatas. *Phys. Rev. Lett.*, 93:246101, 2004.
- [87] M. Greenwood, J. J. Hoyt, and N. Provatas. *Acta Materialia*, In Press, 2009.

- [88] L. Granasy, T. Pusztai, and J. A. Warren. *J. Phys.: Condens. Matter*, **16**:R1205, 2004.
- [89] T. Haxhimali, A. Karma, F. Gonzales, and M. Rappaz. *Nature Materials*, 5:660, 2006.
- [90] J. E. Hilliard. in *Phase Transformations*, pages 470–560. *American Society for Metals, Metals Park, OH*, 1970.
- [91] T. Hirouchi, T. Takaki, and Y. Tomita. *Development of numerical scheme for phase field crystal deformation simulation*. *Comp. Mat. Sci.*, 44:1192, 2009.
- [92] P. C. Hohenberg and B. I. Halperin. *Rev. Mod. Phys.*, 49:435, 1977.
- [93] P. C. Hohenberg and J. B. Swift. *Metastability in fluctuation-driven first-order transitions - nucleation of lamellar phases*. *Phy. Rev. E*, 52:1828, 1995.
- [94] Q. Hou, S. Sasa, and N. Goldenfeld. *Dynamical scaling behavior of the swift-hohenberg equation following a quench to the modulated state*. *Physica*, 239:2152, 1997.
- [95] J.J. Hoyt, M.Asta, and A.Karma. *Mat. Sci and Eng R*, R41-6:121, 2003.
- [96] Kerson Huang. *Statistical Mechanics*. *Jon Wiley and Sons*, 1987.
- [97] S.-C. Huang and M.E. Glicksman. *Acta Metall.*, 29:717, 1981.
- [98] Z-F Huang and K. R. Elder. *Phys. Rev. Lett.*, 2008.
- [99] Z. F. Huang and K. R. Elder. *Phys. Rev. B*, **81**:165421, 2010.
- [100] J. D. Hunt. *Solidification and Casting of Metals*, pages 3–9. *The Metals Society, London*, 1979.
- [101] S. .W. Husain, M. S. Ahmed, and I. Qamar. *Metall. Mater. Trans. A*, **30(A)**:1529, 1999.
- [102] T. Ihle and H. Muller-Krumbhaar. *Phys. Rev. Lett.*, **70**:3083, 1993.
- [103] G. P. Ivantsov. *Dokl. Akad. Nauk USSR*, 58:1113, 1947.
- [104] B. Nestler H. Diepers J. Taiden and I. Steinbach. *Physica D*, **115**:73, 1998.
- [105] A. Jaatinen, C. V. Achim, K. R. Elder, and T. Ala-Nissila. *Thermodynamics of bcc metals in phase field crystal models*, 2009.
- [106] A. Jaatinen and T. Ala-Nissila. *J. Phys.: Condens. Matter*, **22**:205402, 2010.
- [107] K. Janssens, G. Frans, D. Raabe, B. Nestler, E. Kozeschnik, and M. A. Miodownik. In *Computational Materials Engineering, An Introduction to Microstructure Evolution*, page 219. *Elsevier Academic Press*, 2007.
- [108] J.-H. Jeong, J. A. Dantzig, and N. Goldenfeld. *Met. Mater. Trans.*, 34A(3):459–466, 2003.
- [109] J.-H. Jeong, N. Goldenfeld, and J. A. Dantzig. *Physical Review E*, 64:041602–1 to 041602–14, 2001.
- [110] Y. M. Jin and A. G. Khachaturyan. *J. Appl. Phys.*, **100**:013519, 2006.

- [111] V. I. Kalikmanov. Statistical Physics of FLuids, Basic Concepts and Applications. *Springer*, 2001.
- [112] A. Karma. Phys. Rev. Lett, *87*:115701, 2001.
- [113] A. Karma and W.-J. Rappel. Phys. Rev. E, *53*:3017, 1996.
- [114] A. Karma and W.-J. Rappel. Phys. Rev. E, *60*:3614, 1999.
- [115] A. Kazaryan, Y. Wang, S. A. Dregia, and B. R. Patton. Phys. Rev. E, **61**(21):14 275, 2000.
- [116] A. Kazaryan, Y. Wang, S. A. Dregia, and B. R. Patton. Phys. Rev. E, **63**:184102, 2001.
- [117] A. G. Khachaturyan. Phil. Mag., page 3, 1996.
- [118] S. G. Kim. Acta Materialia, **55**:4391, 2007.
- [119] S. G. Kim, W. T. Kim, and T. Suzuki. Phys. Rev. E, **58**(3):3316, 1998.
- [120] S. G. Kim, W. T. Kim, and T. Suzuki. Phys. Rev. E, **60**:7186, 1999.
- [121] S. G. Kim, W. T. Kim, T. Suzuki, and M. Ode. J. Cryst. Growth, **261**:135, 2004.
- [122] Y.-T. Kim, N. Provatas, J. Dantzig, and N. Goldenfeld. Phys. Rev. E, *59*:2546, 1999.
- [123] J. S. Kirkaldy, L. X. Liu, and A. Kroupa. Acta Metall. Mater., **43**:2905, 1995.
- [124] J. S. Kirkaldy and D. Venugopalan. Scripta Metall., **23**:1603, 1989.
- [125] T. Kitashima, J. Wang, and H. Harada. Intermetallics, **16**:239–245, 2008.
- [126] R. Kobayashi and Y. Giga. J. Stat. Phys., **95**:1187, 1999.
- [127] R. Kobayashi, J. A. Warren, and W. C. Carter. Physica D, **119**:415, 1998.
- [128] R. Kobayashi, J. A. Warren, and W. C. Carter. Physica D., **140D**:141, 2000.
- [129] D. Kessler J. Koplík and H. Levine. Phys. Rev. A, *30*:3161, 1984.
- [130] D. Kessler J. Koplík and H. Levine. Phys. Rev. A, *31*:1712, 1985.
- [131] W. Kurz and D. J. Fisher. Acta Metall., **29**:11, 1981.
- [132] J. C. LaCombe, M. B. Koss, V. E. Fradov, and M. E. Glicksman. Phys. Rev. E, *52*:2778, 1995.
- [133] L.D Landau and E.M. Lifshitz. Statistical Physics. *Butterworth-Heinemann, Oxford, 3rd edition edition, 1980.*
- [134] L.D Landau and E.M. Lifshitz. Theory of Elasticity. *Butterworth-Heinemann, Oxford, 3rd edition edition, 1999.*
- [135] J. Langer and Muller-Krumbhaar. J. Cryst. Growth, page 11, 1977.
- [136] J. Langer and Muller-Krumbhaar. Acta Metall., page 1681;1689;1697, 1978.

- [137] J. S. Langer. Directions in Condensed Matter Physics, page 164. World Scientific, Singapore, 1986.
- [138] J.S. Langer. Rev. Mod. Phys., 52:1, 1980.
- [139] L. X. Liu and J. S. Kirkaldy. Acta Metall. Mater., **43**:2891, 1995.
- [140] W. Losert, O. N. Mesquita, J.M.A. Figueiredo, and H.Z. Cummins. Phys. Rev. Lett., **81**:409, 1998.
- [141] W. Losert, B.Q. Shi, and H.Z. Cummins. Proc. Natl. Acad. Sci. USA, **95**:431, 1998.
- [142] W. Losert, B.Q. Shi, and H.Z. Cummins. Proc. Natl. Acad. Sci. USA, **95**:439, 1998.
- [143] W. Losert, B.Q. Shi, H.Z. Cummins, and J. A. Warren. Phys. Rev. Lett., **77**:889, 1996.
- [144] H. Lowen, J Bechhoefer, and L.S.Tuckerman. Phys Rev A, **45**:2399, 1992.
- [145] Plapp M and Karma A. Phys. Rev. Let., **84**:1740–43, 2000.
- [146] Michael Mackey and Andrzej Lasota. Probabilistic Properties of Deterministic Systems. Cambridge University Press, 1985.
- [147] S. Majaniemi and M. Grant. Phys. Rev. B., **75**:054301, 2007.
- [148] M. Martin and N. Goldenfeld. Phys. Rev. A, **35**:1382, 1987.
- [149] P. C. Matthews and S. M. Cox. Nonlinearity, **13**:1293, 2000.
- [150] G. B. McFadden, A. A. Wheeler, R. J. Braun, S. R. Coriell, and R. F. Sekerka. Phys. Rev. E, **48**:2016, 1993.
- [151] M.Conti. Phys Rev E, **55**:765, 1997.
- [152] D. I. Meiron. Phys. Rev. A, **33**:2704, 1986.
- [153] J. Mellenthin, A. Karma, and M. Plapp. Phys. Rev. B, **78**:184110, 2008.
- [154] M.Haataja, J.Mahon, N.Provatas, and F. Léonard. App. Phys. Lett., **87**:251901, 2005.
- [155] R. R. Mohanty and Y. Sohn. Journal of Phase Equilibria and Diffusion, **27**:676–683, 2006.
- [156] W. W. Mullins and R. F. Sekerka. J. Appl. Phys., **34**:323, 1963.
- [157] W. W. Mullins and R. F. Sekerka. J. Appl. Phys., **35**:444, 1964.
- [158] A. H. Nayfeh. Introduction to perturbation Techniques. John Wiley and Sons, 1981.
- [159] B. Nestler and A. A. Wheeler. Physica D, **138**:114, 2000.
- [160] M. Ode, S. G. Kim, and T. Suzuki. ISIJ Inter., **41**:1076–1082, 2001.
- [161] M. Ohno and K. Matsuura. Phys. Rev. E, **79**:031603, 2009.
- [162] T. Ohta, D. Jasnow, and K. Kawasaki. Phys. Rev. Lett, **49**:1223, 1982.

- [163] Y. Oono and S. Puri. *Phys. Rev. E*, **38**:434, 1988.
- [164] S. G. Pavlik and R. F. Sekerka. *Physica A*, **268**:283, 1999.
- [165] S. G. Pavlik and R. F. Sekerka. *Physica A*, **277**:415, 2000.
- [166] Y. Pomeau and M. Ben Amar. *Solids far from equilibrium*, page 365. edited by by C. Godreche, (Cambridge Press), 1991.
- [167] D. A. Porter and K. E. Easterling. *Phase Transformations in Metals and Alloys* 2nd ed. *Stanley Thornes Ltd*, 2001.
- [168] W. H. Press, S. A. Teukolsky, W. T. Vetterling, and B. P. Flannery. *Numerical recipes*. Cambridge University Press, 1992.
- [169] N. Provatas, T. Ala-Nissila, M. Grant, K. R. Elder, and L. Piche. *J. Stat. Phys.*, **81**(3/4):737, 1995.
- [170] N. Provatas, J. Dantzig, and N. Goldenfeld. *Phys. Rev. Lett.*, **80**:3308, 1998.
- [171] N. Provatas, J. Dantzig, and N. Goldenfeld. *J. Comp. Phys.*, **148**:265, 1999.
- [172] N. Provatas, J. Dantzig, N. Goldenfeld, J. C. Lacombe, A. Lupulescu, M. B. Koss, and M. E. Glicksman. *Phys. Rev. Lett.*, **82**:4496, 1999.
- [173] N. Provatas, M. Greenwood, B. Athreya, N. Goldenfeld, and J. Dantzig. *International Journal of Modern Physics B*, **19**:4525, 2005.
- [174] N. Provatas, Q. Wang, M. Haataja, and M. Grant. *Phys. Rev. Lett.*, **91**, 2003.
- [175] *Nikolas Provatas*. *Thermodynamics notes of the derivation of the Gibb's Thomson Condition*, pages 14–15. *Nikolas Provatas*, 2007.
- [176] T V Ramakrishnan and M Yussouff. *First-principles order-parameter theory of freezing*. *Phys. Rev. B*, **19**:2775, 1979.
- [177] T. V. Ramakrishnan and M. Yussouff. *Phys. Rev. B*, **19**:2775, 1979.
- [178] J. A. P. Ramos, E. Granato, C. V. Achim, S. C. Ying, K. R. Elder, and T. Ala-Nissila. *Thermal fluctuations and phase diagrams of the phase-field crystal model with pinning*. *Phys. Rev. E*, **78**:031109, 2008.
- [179] J. A. P. Ramos, E. Granato, S. C. Yinn, C. V. Achim, K. R. Elder, and T. Ala-Nissila. *Phys. Rev. E*, **81**:011121, 2010.
- [180] W. T Read and W. Shockley. *Dislocation models of crystal grain boundaries*. *Phys. Rev.*, **78**:275, 1950.
- [181] H. Reiss. *Methods of Thermodynamics*. *Dover Publishig*, 1996.
- [182] M. Sabouri-Ghomi, N. Provatas, and M. Grant. *Phys Rev Lett*, **86**:5084, 2001.
- [183] Y. Saito. *Statistical Physics of Crystal Growth*. *World Scientific Publishing Co. PTe. Ltd.*, 1996.

- [184] K. Sakai. *J. Cryst. growth*, **237–239**:144–148, 2002.
- [185] A. Schmidt. *J. Comp. Phys.*, *125*:293, 1996.
- [186] J. P. Simmons, C. Shen, and Y. Wang. *Scr Mater.*, **43**:935, 2000.
- [187] Y. Singh. *Physics Reports*, **207**, No 6:351, 1991.
- [188] P. Stefanovic, M. Haataja, and N. Provatas. *Phys. Rev. Lett.*, **96**:225504, 2006.
- [189] I. Steinbach. *Modeling Simul. Mater. Sci. Eng.*, **17**:073001, 2009.
- [190] I. Steinbach and M. Apel. *Phys. D – Nonlinear Phenomena*, **217**:153, 2006.
- [191] I. Steinbach and F. Pezzolla. *Physica D*, **134**:385, 1999.
- [192] I. Steinbach, F. Pezzolla, B. Nestler, M. Seibelberg, R. Prieler, and G. J. Schmitz. *Physica D*, **94**:135, 1996.
- [193] J. Swift and P. C. Hohenberg. *Hydrodynamic fluctuations at the convective instability*. *Phys. Rev. A*, *15*:319–328, 1977.
- [194] C. Tong, M. Greenwood, and N. Provatas. *Phys. Rev. B*, **77**:064112, 2008.
- [195] R. Trivedi and W. Kurz. *Acta metall. mater.*, **42**:15, 1994.
- [196] R. Trivedi and K. Somboonsuk. *Mat. Sci. and Eng.*, **65**:65, 1984.
- [197] B. Utter, R. Ragnarsson, and E. Bodenschatz. *Phys. Rev. Lett.*, **86**:4604, 2001.
- [198] S. van Teeffelen, R. Backofen, A. Voigt, and H. Lwen. *Derivation of the phase field crystal model for colloidal solidification*. *Phy. Rev. E*, *79*:051404, 2009.
- [199] S-L. Wang and R. F. Sekerka. *Phys. Rev. E*, *53*:3760, 1996.
- [200] S-L. Wang, R. F. Sekerka, A. A. Wheeler, B. T. Murray, S. R. Coriell, R. J. Braun, and G. B. McFadden. *Physica D*, **69**:189, 1993.
- [201] Y. Wang and A. Khachaturyan. *Scr. Metall. Mater.*, page 1425, 1994.
- [202] Y. Wang and A. Khachaturyan. *Acta Mater.*, page 1837, 1995.
- [203] Y. Wang and A. Khachaturyan. *Acta Mater.*, page 759, 1997.
- [204] J. A. Warren and W. J. Boettinger. *Acta Metall. Mater. A*, **43**:689, 1995.
- [205] J. A. Warren, W. C. Carter, and R. Kobayashi. *Physica (Amsterdam)*, **261A**:159, 1998.
- [206] J. A. Warren, R. Kobayashi, A. E. Lobkovsky, and W. C. Carter. *Acta Materialia*, **51**:6035, 2003.
- [207] J. A. Warren and J. S. Langer. *Phys. Rev. A*, *42*(6):3518, 1990.
- [208] J. A. Warren and J. S. Langer. *Phys. Rev. E*, *74*(4):2702, 1993.
- [209] A. A. Wheeler, W. J., Boettinger, and G. B. McFadden. *Phys. Rev. A*, **45**:7424, 1992.

- [210] A. A. Wheeler, G. B. McFadden, and W.J. Boettinger. Proc. Royal Soc. London A, 452:495, 1996.
- [211] K. Wu and Y. Wang Y. A. Chang and. Scripta Mater., **50**:1145–1150, 2004.
- [212] K. A. Wu, A.Karma ad J. Hoyt, and M. Asta. Phys. Rev. B., 73:094101, 2006.
- [213] K. A. Wu and A. Karma. Phase-field crystal modeling of equilibrium bcc-liquid interfaces. Phys. Rev. B, 76:184107, 2007.
- [214] K. A. Wu and P. W. Voorhees. Phys. Rev. B, **80**:124408, 2009.
- [215] X.Tong, C.Beckermann, A.Karma, and Q.Li. Phys Rev E, **63**:1063, 2001.
- [216] D. H. Yeon, P. R. Cha, J. H. Kim, M. Grant, and J. K. Yoon. Modelling Simul. Mater. Sci. Eng., **13**:299, 2005.
- [217] D-H Yeon, Z-F Huang, K. R. Elder, and K. Thornton. Phil. Mag., **90**:237, 2010.
- [218] S Yip. The strongest size. Nature, 391:532, 1998.
- [219] Y.Lu, C.Beckermann, and A.Karma. Proceedings of IMECE2002, , 2002.
- [220] Y. S. Yoo, D. .Y. Yoon, and M. .F. Henry. Materials Mater., **1**:47, 1995.
- [221] J. Z. Zhu, T. Wang, A. J. Ardell, S. H. Zhou, Z. K. Liu, and L. Q. Chen. Acta. Materialia, 52:2837, 2004.
- [222] J. Z. Zhu, T. Wang, A. J. Ardell, S. H. Zhou, Z. K. Lui, and L. Q. Chen. Acta Materialia, **52**:2837, 2004.
- [223] J. Z. Zhu, T. Wang, S. H. Zhou, Z. K. Lui, and L. Q. Chen. Acta Materialia, **52**:833, 2004.